



OPEN

The Wiedemann-Franz law in the putative one-dimensional metallic phase of $\text{PrBa}_2\text{Cu}_4\text{O}_8$

SUBJECT AREAS:
ELECTRONIC PROPERTIES
AND MATERIALS

QUANTUM FLUIDS AND SOLIDS

A. F. Bangura^{1,2*}, Xiaofeng Xu^{1,3*}, N. Wakeham^{1,4}, N. Peng⁵, S. Horii⁶ & N. E. Hussey^{1,7}Received
17 October 2013Accepted
28 October 2013Published
20 November 2013Correspondence and
requests for materials
should be addressed to
N.E.H. (n.e.hussey@
bristol.ac.uk; n.e.
hussey@science.ru.nl)* These authors
contributed equally to
this work.

¹H. H. Wills Physics Laboratory, University of Bristol, Tyndall Avenue, Bristol BS8 1TL, United Kingdom, ²Magnetic Materials Laboratory, RIKEN, 2-1 Hirosawa, Wako, Saitama 351-0198, Japan, ³Department of Physics, Hangzhou Normal University, Hangzhou 310036, China, ⁴MPA-CMMS, Los Alamos National Laboratory, P.O. Box 1663, Los Alamos, NM 87545, USA, ⁵Surrey Ion Beam Centre, ATI, Faculty of Engineering and Physical Sciences, University of Surrey, Guildford GU2 7XH, United Kingdom, ⁶Graduate School of Energy Science, Kyoto University, Yoshida-Honmachi, Sakyo-ku, Kyoto 606-8501, Japan, ⁷High Field Magnet Laboratory, Institute for Molecules and Materials, Radboud University 6525 ED Nijmegen, The Netherlands.

The nature of the electronic state of a metal depends strongly on its dimensionality. In a system of isolated conducting chains, the Fermi-liquid (quasiparticle) description appropriate for higher dimensions is replaced by the so-called Tomonaga-Luttinger liquid picture characterized by collective excitations of spin and charge. Temperature is often regarded as a viable tuning parameter between states of different dimensionality, but what happens once thermal broadening becomes comparable to the interchain hopping energy remains an unresolved issue, one that is central to many organic and inorganic conductors. Here we use the ratio of the thermal to electrical conductivities to probe the nature of the electronic state in $\text{PrBa}_2\text{Cu}_4\text{O}_8$ as a function of temperature. We find that despite the interchain transport becoming non-metallic, the charge carriers within the CuO chains appear to retain their quasiparticle nature. This implies that temperature alone cannot induce a crossover from Fermi-liquid to Tomonaga-Luttinger-liquid behaviour in quasi-one-dimensional metals.

Understanding how the electronic state evolves in quasi-one-dimensional (q1D) metals as coupling between individual chains is strengthened or weakened, and determining the energy scale for the Fermi-liquid to Tomonaga-Luttinger liquid (FL-TLL) crossover, remain profound theoretical problems that are relevant to a host of organic and inorganic q1D conductors¹. Temperature T is often regarded as a viable tuning parameter between states of different dimensionality in q1D metals. For $k_B T < 2t_{\perp}$, the interchain hopping integral, charge hops coherently in all three dimensions, albeit with anisotropic velocities. Once thermal broadening is comparable to the warping of the Fermi sheets however, hopping between chains is predicted to become incoherent, leading to a putative 3D-1D dimensional crossover² and contrasting behaviour in the intra- and inter-chain resistivities at high T . As a result, signatures of TLL physics are expected to emerge with increasing temperature³.

In an alternative picture, it is argued that interchain coherence in a q1D FL is robust provided the intrachain scattering rate $\Gamma < \epsilon_F$, the Fermi energy⁴. Accordingly, there is no dimensional crossover with increasing T , and by inference, no FL-TLL crossover at elevated temperatures - the crossover to non-metallic behaviour in the interchain resistivity being simply due to the emergence of a second, incoherent hopping process which shorts out the small, but nonetheless metallic component⁴.

In order to address this outstanding issue experimentally, it is necessary to identify both a material whose anisotropic resistivity exhibits behaviour consistent with predictions for a thermally-induced dimensional crossover and a physical property that shows marked differences in the putative TLL and FL regimes. According to both theory and experiment, the Wiedemann-Franz (WF) law is a viable litmus test of TLL physics in the bulk. The WF law states that the ratio of the thermal κ to the electrical conductivity σ at a given T is equal to a constant called the Lorenz number, $L_0 = (\pi^2/3)(k_B/e)^2$. For FL systems, only small ($O(1)$) deviations from the WF law are expected (with an effective Lorenz ratio $L = \kappa/\sigma T \leq L_0$)⁵⁻⁸, reflecting the fact that heat and electrical currents, though relaxed differently by inelastic scattering, are carried by the same fermionic quasiparticles (Although the WF law is most applicable in the zero temperature (elastic scattering) limit, the law is found to hold equally well at finite temperatures whenever large-angle (inelastic) scattering processes dominate). For certain classes of non-FL metals, the WF law is also obeyed at low T , provided some or all of the fermionic carriers remain long-lived⁹. In a



TLL however, the Lorenz ratio is predicted to be enhanced¹⁰, by orders of magnitude under certain commensurate conditions¹¹, due to the idea that both elastic and inelastic scattering processes affect the flow of charge (carried by holons) more profoundly than the flow of entropy (carried by spinons). Recently, a marked enhancement of the Lorenz ratio was observed in the q1D purple bronze $\text{Li}_{0.9}\text{Mo}_6\text{O}_{17}$ ¹², that appeared to diverge with decreasing temperature, consistent with expectations for a TLL with repulsive interactions¹⁰.

The q1D cuprate $\text{PrBa}_2\text{Cu}_4\text{O}_8$ (Pr124) contains weakly coupled 1/4-filled zigzag chains, oriented along the crystallographic b -axis, that give rise to electronic properties that are among the most anisotropic known in existence^{13,14}. The interchain resistivities ρ_a and ρ_c , while metallic (and FL-like) at low T , become non-metallic above $T_{\text{max}} \sim 150$ K (i.e. they both decrease with increasing T)¹³. The intrachain resistivity ρ_b , on the other hand, remains metallic at all finite T , suggesting a purely 1D metallic state at elevated temperatures. Moreover, both photoemission lineshapes (in Zn-doped Pr124)¹⁵ and the optical response (in pristine Pr124)¹⁶ contain features claimed to be consistent with TLL theory.

Here, we examine the evolution of the Lorenz ratio in Pr124, through a combination of irradiation-induced and substitutional disorder, and find that $L/L_0 \leq 1$ (to within our experimental accuracy) both below T_{max} and above, following a T -dependence similar to that obeyed in elemental metals. This correspondence indicates that despite its extreme electrical anisotropy, Pr124 appears to display conventional metallic behaviour for all $T \leq 300$ K and that there is no thermally-induced FL-TLL crossover beyond $k_B T > 2t_{\perp} \sim 5$ meV^{13,14}. Comparison with $\text{Li}_{0.9}\text{Mo}_6\text{O}_{17}$ and with theory suggests that it is possibly the non-local nature of the electron correlations, rather than the degree of electrical anisotropy, that leads to the manifestation of TLL physics in the latter.

Results

The top panel in Figure 1 shows the electrical resistivity of stoichiometric Pr124 for current flow parallel ($I//b$) and perpendicular ($I//a$) to the conducting chains. Below 100 K, the electrical resistivity of Pr124 varies as $\rho \sim T^{2+\delta}$ ($0 \leq \delta < 1$) in all three crystallographic directions (data for $I//c$ not shown)¹³, consistent with expectations for a q1D FL with dominant electron-electron scattering¹⁷. The corresponding resistivity anisotropy $\rho_a : \rho_b : \rho_c \sim 300 : 1 : 1000$ at low T ¹⁸. At higher temperatures, the T -dependence of $\rho_a(T)$ (and $\rho_c(T)$) changes from metallic to non-metallic, while $\rho_b(T)$ remains metallic and monotonic. In this temperature regime, $\rho_b(T)$ becomes T -linear (see Fig. 1).

The corresponding thermal conductivity data for heat flow parallel and perpendicular to the chains is shown in the bottom panel of Figure 1. Like the electrical resistivity, it too displays a marked anisotropy, albeit reduced due to the additional phonon contribution κ_{ph} to both κ_a and κ_b . Indeed, given the extreme resistive anisotropy, it is reasonable to assume that κ_a is purely phononic in origin.

Thus, the ab -plane anisotropy in the thermal conductivity can be attributed either entirely to the electronic contribution κ_e within the chains or to a combination of κ_e and additional anisotropy in the phonon spectrum and/or phonon scattering rate. (Other contributions, e.g. due to spin fluctuations and/or magnons associated with the magnetic ordering of the copper ions in the CuO_2 plane ($T_N = 220$ K) or of the Pr ions sandwiched between the CuO_2 planes ($T_N = 17$ K)¹⁹, are expected to be isotropic within the ab -plane and therefore do not contribute to the anisotropy in κ). In isostructural $\text{YBa}_2\text{Cu}_4\text{O}_8$ (Y124), κ_{ph} scales only with sample dimensions at low T ²⁰, implying that the mean phonon velocity is also isotropic within the ab -plane. In SrCuO_2 , an insulating cuprate with an identical zigzag chain structure to Pr124, the ab -plane anisotropy in κ_{ph} is small, of order 20% and only weakly T -dependent, between 0.5 K and 300 K²¹. In Pr124, the additional (electronically inert) CuO_2

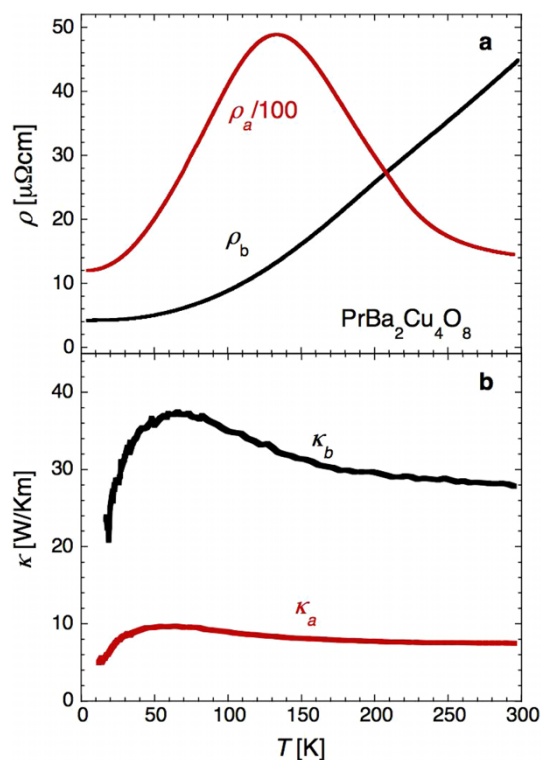


Figure 1 | Electrical and thermal conductivities of quasi-1D $\text{PrBa}_2\text{Cu}_4\text{O}_8$ (Pr124). (a). Intra- (ρ_b) and inter-chain (ρ_a) resistivity of Pr124 as a function of temperature. Note that ρ_a has been scaled by a factor of 1/100. (b). Intra- (κ_b) and inter-chain (κ_a) thermal conductivity as a function of temperature.

bilayers sandwiched between the chains will undoubtedly act to reduce the overall phonon anisotropy relative to that in SrCuO_2 . Hence it is reasonable to assume that the bulk of the difference $\kappa_b - \kappa_a$ is due solely to heat flow of the charge carriers within the CuO chains. Before we discuss the effective $L(T)$ estimated from $\kappa_b - \kappa_a$ however, we first present evidence that near room temperature at least, $L \sim L_0$ independent of any assumptions involving the anisotropy in κ_{ph} .

Figure 2 shows $\kappa_b(T)$ and $\kappa_a(T)$ data on Pr124 samples cut from the same large single crystal before and after receiving proton irradiation. The phonon peaks in the virgin crystals were both strongly suppressed, verifying that a substantial level of impurities was introduced by the radiation exposure. (At this level of irradiation, we expect the defects to be predominantly single oxygen vacancies). Significantly, κ_a at 300 K was found to be insensitive to irradiation damage. (The room temperature value of κ_a on a second non-irradiated crystal with a lower phonon peak, and therefore presumably higher disorder levels, was also coincident with those shown in Figure 2). This finding indicates that the dominant scattering mechanism for phonons at high T is phonon-phonon (Umklapp) scattering rather than phonon-impurity scattering. By contrast, κ_b was found to be suppressed by $\sim 20\%$ upon irradiation. It is evident therefore that the change in κ_b at room temperature arises solely from changes in κ_e .

With this in mind, we now proceed to examine the effect of substitutional disorder on the room temperature Lorenz ratio of Pr124. (Measuring the electrical resistivity of the irradiated crystals was not an option since post-irradiation annealing of those electrical contacts that had degraded during the irradiation process would have caused a recombination of the majority of defects). Figure 3 shows $\rho_b(T)$ (top panel) and $\kappa_b(T)$ (bottom panel) measurements on pure, 5% and 10% Zn-doped Pr124 single crystals. Note the upturns in the $\rho_b(T)$ curves

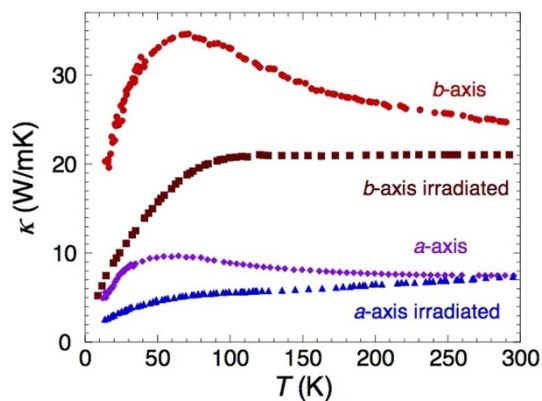


Figure 2 | Thermal conductivity data on Pr124 single crystals before and after proton-irradiation. $\kappa_b(T)$ and $\kappa_a(T)$ data on Pr124 crystals before and after receiving the same radiation dose from a 4 MeV proton beam at 300 K for 12 hours. The thickness of the two samples was small compared to the penetration depth of the protons, ensuring homogeneous damage throughout the crystals. Note that κ_p , the phonon contribution, at room temperature is insensitive to the level of disorder.

of the two Zn-doped crystals, consistent with a previous localization study of Pr124²². Note too the similarity in the $\kappa_b(T)$ curves for the irradiated and 5% Zn-doped samples (implying a similar defect density) and the fact that the small phonon peak seen in Fig. 1 is strongly suppressed upon Zn substitution. According to our simulations, the defect density of the irradiated crystals was estimated to be of order 0.1–0.2%. This is much less than the nominal Zn content in our Zn-doped crystals. It should be noted however that for low doping concentrations, Zn is believed to substitute Cu ions primarily on the CuO₂ plane, rather than on the CuO chain.

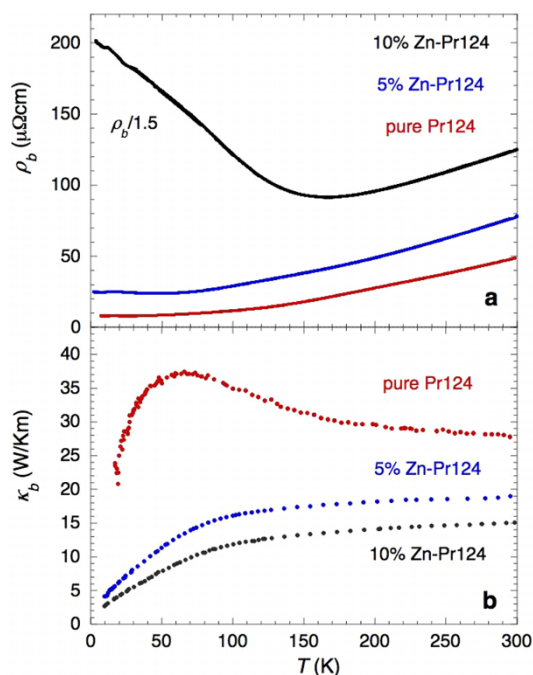


Figure 3 | Effect of Zn substitution on the in-chain charge dynamics of Pr124. (a). Temperature dependence of the in-chain electrical resistivity of Pr124 single crystals with different levels of Zn substitution (chemical formula PrBa₂(Cu_{1-x}Zn_x)₄O₈), as indicated. For clarity, ρ_b of the 10% sample has been divided by a factor of 1.5. (b). Corresponding in-chain thermal conductivity data.

Assuming, as inferred from the irradiation experiments, that at high T , $\Delta\kappa_b = \Delta\kappa_e$ (i.e. κ_{ph} is insensitive to impurities), we can calculate $\Delta\kappa_b/(\Delta\sigma_b T)$ for any combination of the three samples (where $\Delta\sigma_b$ is the corresponding change in the electrical conductivity) and obtain an average value for the WF ratio of $L/L_0 = 1.15 \pm 0.3$ at $T = 300$ K. This value of L/L_0 is entirely consistent, within our experimental uncertainty, with the value derived for Zn-free Pr124 by assuming that the difference between κ_a and κ_b is wholly due to the contribution from the charge carriers within the chains (see Fig. 4 and subsequent discussion). This implies that the magnitude of the phonon anisotropy in Pr124 is of order or smaller than our experimental error, and is comparable to that found in SrCuO₂²¹. More importantly, this analysis appears to confirm the preservation of the WF law in the putative ‘one-dimensional’ regime of Pr124, as we shall now discuss.

Discussion

Figure 4 shows the resultant effective Lorenz ratio $L (= (\kappa_b - \kappa_a)/\sigma_b T)$, where $\sigma_b = 1/\rho_b$, for the data shown in Fig. 1 normalized to the Lorenz number $L_0 (= 2.45 \times 10^{-8} \text{ V}^2\text{K}^{-2})$. For comparison, we also show in Fig. 4 the corresponding plot of L/L_0 for Ni²³. Similar behaviour is also seen in other elemental metals such as Cu²⁴ and Co²³. With decreasing temperature, L/L_0 for Pr124 remains within 20% of its room temperature value and follows an almost identical T -dependence to that found in elemental Ni, dropping below unity at intermediate temperatures (presumably due to the different weighting of small- and large-angle scattering on the heat and charge currents) and recovering as T approaches the elastic scattering limit at $T = 0$. This pattern contrasts markedly with what is observed in the q1D purple bronze Li_{0.9}Mo₆O₁₇¹², reproduced in the inset to Fig. 4, for which the effective Lorenz ratio is found to be several times larger than L_0 and to diverge with decreasing temperature¹². It should be stressed here that according to theory¹¹, the Lorenz ratio in a TLL is highly sensitive to both d , the deviation from commensurate filling and to D , the ratio of the elastic to el-el Umklapp scattering rates. However, as noted in Fig. 1 of Ref. 11, for values of D relevant to our crystals ($0.1 < D < 1$) and the temperature range of our experiments ($10 \text{ K} < T < 300 \text{ K}$), L/L_0 in a TLL is always enhanced by a factor of 2 or higher, for *all* values of d considered.

Fig. 4 encapsulates the key result of this study, namely the equivalence of the T -dependence of L/L_0 in Pr124 to that found in

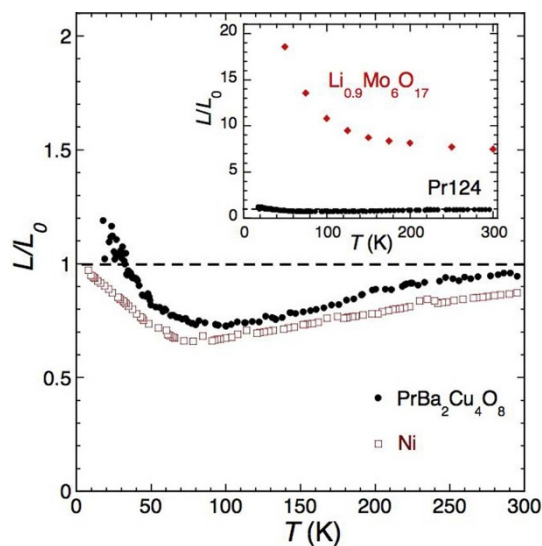


Figure 4 | Verification of the Wiedemann-Franz law in Pr124. Solid circles: normalized WF ratio in Pr124. Open circles: corresponding L/L_0 for Ni²³. Inset: Comparison of L/L_0 for Pr124 (solid circles) and Li_{0.9}Mo₆O₁₇ (solid diamonds).



ordinary, elemental metals. (The observed excess of L over L_0 below 30 K is attributed to experimental uncertainties, e.g. in our estimate of the distance between thermocouple contacts, or to any residual low- T anisotropy in κ_{ph} that has been hitherto ignored). Given the striking violation in the WF law found in $\text{Li}_{0.9}\text{Mo}_6\text{O}_{17}$ ¹², the observation of WF law verification in Pr124 can be viewed as primary experimental evidence that the metallic state in Pr124 retains its quasiparticle (FL) nature for all $T \leq 300$ K. This finding contrasts with the reported emergence of TLL behaviour at finite frequencies¹⁶ or energies¹⁵ in Pr124 and challenges the widely-held viewpoint³ that temperature alone can induce a radical change in the nature of the electronic state in q1D metals once $k_B T > 2t_{\perp}$. It also highlights a fundamental difference between probing physical processes at or near the Fermi level with increasing temperature and probing physical processes at finite frequencies or equivalently, at energies away from ϵ_F .

It is not yet clear whether these findings support Gutman and Maslov's original argument that interchain transport remains coherent above T_{max} ⁴, since the loss of interchain coherence (i.e. once the scattering rate $1/\tau < 2t_{\perp}$) may not necessarily induce a crossover to TLL physics²⁵. Intriguingly, the strictly T -linear $\rho_b(T)$ observed in Pr124 above T_{max} is consistent both with expectations for a 1/4-filled TLL with repulsive interactions² and, from simple phase-space arguments, for a q1D FL whose Fermi surface warping has been smeared out¹⁷.

Which factor or factors ultimately determine the contrasting electronic states in Pr124 and $\text{Li}_{0.9}\text{Mo}_6\text{O}_{17}$ is an important open question. One obvious measure of the degree of three-dimensionality in a q1D FL is the interchain hopping integral t_{\perp} (For simplicity, we assume here that $2t_{\perp}$ is the same in both directions orthogonal to the conducting chains). As stated above, in Pr124, a consistent value of $2t_{\perp} \sim 5$ meV has been obtained from a variety of studies^{13,14,18,22,26}. For $\text{Li}_{0.9}\text{Mo}_6\text{O}_{17}$, band structure calculations suggest that $2t_{\perp} \sim 36$ meV²⁷, while the resistive anisotropy ($\rho_a/\rho_b \sim 0.5(t_{\parallel}/t_{\perp})^2$), combined with an estimate of the intrachain bandwidth t_{\parallel} from angle-resolved photoemission²⁸, gives $2t_{\perp} \sim 15$ meV. Thus it would appear that the magnitude of t_{\perp} does not, by itself, determine the nature of the electronic state in q1D metals. According to Castellani and co-workers, for short-range interactions, the FL ground state is believed to be stable to any finite interchain coupling²⁹. For sufficiently small t_{\perp} and sufficiently long-range interactions however, Kopietz *et al.* argue that the response of a system to experimental probes can be indistinguishable from that of a TLL, even in the dc limit, and characterized by the same TLL exponents that would exist if $t_{\perp} = 0$ ³⁰. This contrasting behaviour implies that it is the nature of the effective correlations, rather than the strength of the interchain coupling, that ultimately determines whether a metallic system near the 1D boundary displays FL or TLL phenomenology. In this regard, it is perhaps worth noting that repulsive interchain interactions are known to enhance pairing in the spin-triplet channel of q1D superconductors^{31–33}, a scenario consistent with the recent observation of a strong violation of the Pauli paramagnetic limit in $\text{Li}_{0.9}\text{Mo}_6\text{O}_{17}$ ^{34,35}.

In summary, we have demonstrated that for $10 \text{ K} \leq T \leq 300 \text{ K}$, the effective Lorenz ratio in Pr124 has a magnitude and T -dependence that is identical (to within our experimental uncertainty) with that found in elemental metals. Thus, despite its interchain resistivity having characteristics associated with a loss of dimensionality at elevated temperatures (i.e. above $T_{\text{max}} \sim 150$ K), the electronic state of Pr124 does not appear to undergo any transition or crossover to TLL physics once $k_B T > 2t_{\perp}$, in contrast to certain prevailing theoretical arguments. There is now a significant body of experimental evidence suggesting that the effective dimensionality of the conduction electrons in Pr124 can be modified through changes in temperature¹³, intrachain scattering²² and magnetic fields^{14,26} (i.e. once the energy scale of the relevant perturbation exceeds $2t_{\perp}$). However, it would appear that signatures of TLL physics are only manifest in

spectroscopic measurements carried out at high frequencies^{15,16}. This dichotomy is also seen in non-metallic magnetic systems on the 1D boundary³⁶. It will be highly informative to see whether the electronic state of other q1D conductors, in particular $\text{Li}_{0.9}\text{Mo}_6\text{O}_{17}$ and the organic Bechgaard salts $(\text{TMTSF})_2\text{X}$ ($\text{X} = \text{ClO}_4, \text{PF}_6$) show a similar response to the different perturbations.

Methods

Pr124 crystals were grown using a self-flux method in MgO crucibles in a high-pressure furnace (11 atm of oxygen)³⁷. Bar-shaped samples (approximate dimensions $500 \times 100 \times 30 \mu\text{m}^3$) were cut from a large rectangular as-grown sample with edges parallel to the crystallographic a - and b -axes. For the thermal conductivity measurements, we employed a modified steady-state method in which a temperature gradient, measured using a differential thermocouple, is set up across the sample through a pair of calibrated heat-links attached to each end³⁸. The heat links determine the power entering and leaving the crystal, thus ensuring that any power loss due to radiative losses and heat conduction through the thermocouple wires to the heat-bath is known. Provided the difference between the power entering and leaving the sample is less than 20%, the power through the sample can be taken as the average of the input and output power. This condition was satisfied for all $T \leq 300$ K and the total power loss typically fell to below 2% at $T \sim 200$ K.

In order to test the validity of the WF law, accurate measurements of the electrical resistivity are paramount. In a q1D conductor, extreme care is required to short out the sample electrically in the two directions orthogonal to the chain and thus ensure that current flow between the voltage contacts is uniaxial. This was achieved here by coating conductive paint across the entire sample in both directions perpendicular to the current flow. The zero-field measurements were carried out for $4.2 \text{ K} < T < 300 \text{ K}$ in a He dipping cryostat.

1. Voit, J. One-dimensional Fermi-liquids. *Rep. Prog. Phys.* **58**, 977–1116 (1995).
2. Giamarchi, T. Theoretical framework for quasi-one dimensional systems. *Chem. Rev.* **104**, 5037–5055 (2004).
3. Biermann, S., Georges, A., Lichtenstein, A. & Giamarchi, T. Deconfinement transition and Luttinger to Fermi liquid crossover in quasi-one-dimensional systems. *Phys. Rev. Lett.* **87**, 276405 (2001).
4. Gutman, D. B. & Maslov, D. L. Anomalous c -axis transport in layered metals. *Phys. Rev. Lett.* **99**, 196602 (2007).
5. Chester, G. V. & Thellung, A. Law of Wiedemann and Franz. *Proc. Phys. Soc. London* **77**, 1005–1013 (1961).
6. Strinati, G. & Castellani, C. Energy diffusion in disordered electronic systems near the Anderson transition. *Phys. Rev. B* **38**, 2270–2276 (1987).
7. Castellani, C., DiCastro, C., Kotliar, G., Lee, P. A. & Strinati, G. Thermal conductivity in disordered interacting-electron systems. *Phys. Rev. Lett.* **59**, 477–480 (1987).
8. Kearney, M. J. & Butcher, P. N. Thermal transport in disordered systems. *J. Phys. C: Solid State Phys.* **21**, L265–L270 (1988).
9. Mahajan, R., Barkeshli, M. & Hartnoll, S. A. Non-Fermi liquids and the Wiedemann-Franz law. *Phys. Rev. B* **88**, 125107 (2013).
10. Kane, C. L. & Fisher, M. P. A. Thermal transport in a Luttinger liquid. *Phys. Rev. Lett.* **76**, 3192–3195 (1996).
11. Garg, A., Rasch, D., Shimshoni, E. & Rosch, A. Large violation of the Wiedemann-Franz law in Luttinger liquids. *Phys. Rev. Lett.* **103**, 096402 (2009).
12. Wakeham, N. *et al.* Gross violation of the Wiedemann-Franz law in a quasi-one-dimensional conductor. *Nat. Commun.* **2**, 396 (2011).
13. McBrien, M. N. *et al.* Metallic c -axis transport across insulating planes in $\text{PrBa}_2\text{Cu}_4\text{O}_8$. *J. Phys. Soc. Japan* **71**, 701–704 (2002).
14. Hussey, N. E. *et al.* Three-dimensional Fermi-liquid ground state in the quasi-one-dimensional cuprate $\text{PrBa}_2\text{Cu}_4\text{O}_8$. *Phys. Rev. Lett.* **89**, 086601 (2002).
15. Mizokawa, T. *et al.* Angle-resolved photoemission study of Zn-doped $\text{PrBa}_2\text{Cu}_4\text{O}_8$: possible observation of single-particle spectral function for a Tomonaga-Luttinger liquid. *Phys. Rev. B* **65**, 193101 (2002).
16. Takenaka, K. *et al.* Anisotropic optical spectra of $\text{PrBa}_2\text{Cu}_4\text{O}_8$: possible Tomonaga-Luttinger liquid response of the quasi-one-dimensional metallic CuO double chains. *Phys. Rev. Lett.* **85**, 5428–5431 (2000).
17. Oshiyama, A., Naka, K. & Kamimura, H. Electrical resistivity due to electron-electron scattering in quasi-one-dimensional metals. *J. Phys. Soc. Jpn.* **45**, 1136–1146 (1978).
18. Narduzzo, A. *et al.* Fragile three-dimensionality in the quasi-one-dimensional cuprate $\text{PrBa}_2\text{Cu}_4\text{O}_8$. *New J. Phys.* **8**, 172 (2006).
19. Li, W.-H. *et al.* Magnetic ordering in double-chain $\text{PrBa}_2\text{Cu}_4\text{O}_8$. *Phys. Rev. B* **60**, 4212–4219 (1999).
20. Hussey, N. E. *et al.* Absence of residual quasiparticle conductivity in the underdoped cuprate $\text{YBa}_2\text{Cu}_3\text{O}_7$. *Phys. Rev. Lett.* **85**, 4140–4143 (2000).
21. Sologubenko, A. V. *et al.* Heat transport by lattice and spin excitations in the spin-chain compounds SrCu_2O_7 and Sr_2CuO_3 . *Phys. Rev. B* **64**, 054412 (2001).
22. Enayati-Rad, A. *et al.* Irradiation-induced confinement in a quasi-one-dimensional metal. *Phys. Rev. Lett.* **99**, 136402 (2007).
23. Shiomi, Y., Onose, Y. & Tokura, Y. Effect of scattering on intrinsic anomalous Hall effect investigated by Lorenz ratio. *Phys. Rev. B* **81**, 054414 (2010).



24. Zhang, Y. *et al.* Determining the Wiedemann-Franz ratio from the thermal Hall conductivity: application to Cu and $\text{YBa}_2\text{Cu}_3\text{O}_{6.95}$. *Phys. Rev. Lett.* **84**, 2219–2222 (2000).
25. McKenzie, R. H. & Moses, P. Incoherent interlayer transport and angular-dependent magneto-resistance oscillations in layered metals. *Phys. Rev. Lett.* **81**, 4492–4495 (1998).
26. Xu, X. *et al.* Dimensionality-driven spin-flop transition in quasi-one-dimensional $\text{PrBa}_2\text{Cu}_4\text{O}_8$. *Phys. Rev. B* **81**, 224435 (2010).
27. Merino, J. & McKenzie, R. H. Effective Hamiltonian for the electronic properties of the quasi-one-dimensional material $\text{Li}_{0.9}\text{Mo}_6\text{O}_{17}$. *Phys. Rev. B* **85**, 235128 (2012).
28. Xue, J. *et al.* Electronic structure near the Fermi surface in the quasi-one-dimensional conductor $\text{Li}_{0.9}\text{Mo}_6\text{O}_{17}$. *Phys. Rev. Lett.* **83**, 1235–1238 (1999).
29. Castellani, C., Di Castro, C. & Metzner, W. Dimensional crossover from Fermi to Luttinger liquid. *Phys. Rev. Lett.* **72**, 316–319 (1994).
30. Kopietz, P., Meden, V. & Schönhammer, K. Anomalous scaling and spin-charge separation in coupled chains. *Phys. Rev. Lett.* **74**, 2997–3000 (1995).
31. Kuroki, K., Arita, R. & Aoki, H. Spin-triplet *f*-wave-like pairing proposed for an organic superconductor $(\text{TMTSF})_2\text{PF}_6$. *Phys. Rev. B* **63**, 094509 (2001).
32. Fuseya, Y. & Suzumura, Y. Superconductivity and density wave in the quasi-one-dimensional systems: renormalization group study. *J. Phys. Soc. Japan* **74**, 1263–1269 (2005).
33. Nickel, J. C., Duprat, R., Bourbonnais, C. & Dupuis, N. Triplet superconducting pairing and density-wave instabilities in organic conductors. *Phys. Rev. Lett.* **95**, 247001 (2005).
34. Mercure, J.-F. *et al.* Upper critical magnetic field far above the paramagnetic pair-breaking limit of superconducting one-dimensional $\text{Li}_{0.9}\text{Mo}_6\text{O}_{17}$ single crystals. *Phys. Rev. Lett.* **108**, 187003 (2012).
35. Lebed, A. G. & Sepper, O. Possible triplet superconductivity in the quasi-one-dimensional conductor $\text{Li}_{0.9}\text{Mo}_6\text{O}_{17}$. *Phys. Rev. B* **87**, 100511(R) (2013).
36. Lake, B., Tennant, D. A., Frost, C. D. & Nagler, S. E. Quantum criticality and universal scaling of a quantum antiferromagnet. *Nat. Mater.* **4**, 329–334 (2005).
37. Horii, S. *et al.* Growth and anisotropic resistivity of $\text{PrBa}_2\text{Cu}_4\text{O}_8$ and $\text{Pr}_2\text{Ba}_4\text{Cu}_7\text{O}_{15-y}$ single crystals: a direct probe of metallic Cu-O double chains. *Phys. Rev. B* **61**, 6327–6333 (2000).
38. Xu, X. PhD thesis, 'Thermal and electrical transport in quasi-one-dimensional oxides' (University of Bristol, 2009).

Acknowledgments

We thank T. Giamarchi, R. H. McKenzie and N. Shannon for stimulating discussions and N. A. Fox for technical assistance. This work was supported by the EPSRC (UK) (GR/). NEH acknowledges a Royal Society Wolfson Research Merit Award. XX would like to acknowledge the valuable discussion with Jianhui Dai and the financial support from NSFC (Grant No. 11104051).

Author contributions

S.H. grew the single crystals and commented on the manuscript. N. P. performed the proton irradiation experiments. A.F.B., X.X., N.W. and N.E.H. designed and performed the transport experiments and co-wrote the paper.

Additional information

Competing financial interests: The authors declare no competing financial interests.

How to cite this article: Bangura, A.F. *et al.* The Wiedemann-Franz law in the putative one-dimensional metallic phase of $\text{PrBa}_2\text{Cu}_4\text{O}_8$. *Sci. Rep.* **3**, 3261; DOI:10.1038/srep03261 (2013).



This work is licensed under a Creative Commons Attribution 3.0 Unported license. To view a copy of this license, visit <http://creativecommons.org/licenses/by/3.0>