

SCIENTIFIC REPORTS



OPEN

Thermodynamic Calculation among Cerium, Oxygen, and Sulfur in Liquid Iron

Fei Pan^{1,2,3,*}, Jian Zhang^{1,4,*}, Hao-Long Chen⁵, Yen-Hsun Su¹, Yen-Hao Su⁶ & Weng-Sing Hwang¹

Received: 25 May 2016

Accepted: 06 October 2016

Published: 21 October 2016

Thermodynamic calculation has been applied to predict the inclusion formation in molten SS400 steel. When the Cerium addition in liquid iron is 70 ppm and the initial Oxygen and Sulphur are both 110 ppm, the formation of oxides containing Cerium would experience the transformation from Ce_2O_3 to CeO_2 and also the formation of sulfides containing Cerium would experience the transformation from CeS to Ce_2S_3 and then to Ce_3S_4 . Below 2000 K the most thermodynamic stable matter is CeO_2 and the less thermodynamic stable inclusion is CeS . Only when the amount of [O] is extremely low and the amount of [S] and [Ce] is relatively high, Ce_2S_3 has the possibility to form.

Rare earth (RE) metals have many applications^{1–5} and their addition to molten iron has attracted increasing research attention⁶. Such addition affects inclusion structures⁷ and can be used to purify steel⁸. The conjugation between oxygen and RE metals⁹ and between sulfur and RE metals¹⁰ is very strong. A lot of research^{11–13} has been done on the equilibrium relation between O, S, and RE metals. It has been found that extremely low oxygen and sulfur concentrations in steel can be achieved via the addition of an RE metal¹⁴. A lot of research^{15–18} has also been done on steel deoxidization and desulfurization via titanium and magnesium. RE metals can be used to deoxidize and desulfurize steel to control inclusion size and chemical composition. Few studies have performed thermodynamic calculations on the use of cerium to modify inclusions.

This paper focuses on the thermodynamic calculations of the cerium-oxygen-sulfur system in molten SS400 steel. The formation conditions of CeS , Ce_2S_3 , Ce_3S_4 , CeO_2 , and Ce_2O_3 in molten steel are examined using Wagner's relation and Lupis's relation based on the Gibbs free energy change. The transformation mechanism is analyzed by determining the thermodynamic conditions of Ce-desulfurized and Ce-deoxidized steel. The segregation of Ce_2O_3 in molten iron is also analyzed. In addition, a model for predicting the formation of various inclusions is established for SS400 steel with cerium addition.

Calculations

The thermodynamic calculations of the Ce-O-S system are based on Wagner's relation¹⁹ and Lupis' relation²⁰. These calculations were implemented in C++. The segregation of Ce_2O_3 in molten SS400 steel, whose chemical composition is shown in Table 1, was calculated in Matlab 2015a.

The Ce-O-S system is the thermodynamic relation between the dissolved Oxygen, Sulphur and Cerium in liquid iron to explore the formations of inclusions containing Cerium. The first stage for thermodynamic calculation is to derive the thermodynamic equations for the inclusion formations by Wagner's relation¹⁹ and Lupis' relation²⁰. Then the second stage is to use C++ programming software to derive the unknown chemical composition values for every equation.

Results and Discussion


For the addition of cerium into molten SS400 steel, the reactions of [O], [S], and [Ce] are of interest because Ce has strong affinity with S and O. As reported previously²¹, when $w(CE)/(w[O] + w[S]) = 3.9$, the function of

¹Department of Materials Science and Engineering, National Cheng Kung University, Tainan 70101, Taiwan. ²Physics Department, Technische Universität München, Munich 85748, Germany. ³Physics Department, Ludwig-Maximilians-Universität München, Munich 80799, Germany. ⁴Chengdu Base, Panzhihua Iron & Steel Research Institute Co., LTD, Chengdu 610399, China. ⁵Department of Electronic Engineering, Kao Yuan University, Kaohsiung 82151, Taiwan. ⁶Steelmaking Process Development Section, China Steel Corporation, Kaohsiung 81233, Taiwan. *These authors contributed equally to this work. Correspondence and requests for materials should be addressed to F.P. (email: phoenix.pan@tum.de) or W.-S.H. (email: wshwang@mail.ncku.edu.tw)

C	Si	Mn	P	S	O
0.14	0.26	0.90	0.02	0.03	0.018

Table 1. Chemical composition of SS400 steel (wt. %).

Reaction	Standard Gibbs Free energy, J/mol	No.
[Ce] + 2[O] = CeO ₂ (s)	$\Delta G^\theta = -854270 + 250T$	(3)
[Ce] + 3/2[O] = 1/2Ce ₂ O ₃ (s)	$\Delta G^\theta = -715560 + 180T$	(4)
[Ce] + [S] = CeS(s)	$\Delta G^\theta = -211390 + 60.5T$	(5)
[Ce] + 3/2[S] = 1/2Ce ₂ S ₃ (s)	$\Delta G^\theta = -537290 + 164T$	(6)
[Ce] + 4/3[S] = 1/3Ce ₃ S ₄ (s)	$\Delta G^\theta = -498480 + 146.3T$	(7)
[Ce] + [O] + 1/2[S] = 1/2Ce ₂ O ₂ S(s)	$\Delta G^\theta = -676795 + 166T^{18}$	(8)

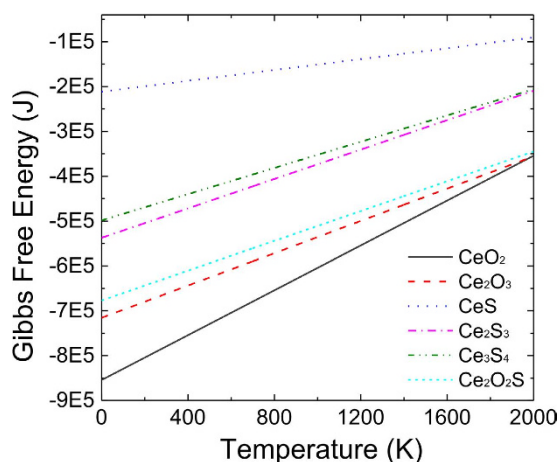Table 2. Formation equations and Gibbs free energy of oxides, sulfides and oxysulfides of cerium^{14,21–26}.**Figure 1. Gibbs free energy of formation for various oxides and sulfides containing cerium at various temperatures.**

cerium is optimal. To determine the separation sequence for various oxides and sulfides of cerium, the amount of cerium in the calculations was set as 1 mol to compare the Gibbs free energy of formation for various inclusions, which can be derived as:

$$\Delta G = \Delta G^\theta + RT \ln J \quad (1)$$

$$\Delta G^\theta = -RT \ln K \quad (2)$$

where J denotes the reaction quotient (unitless), ΔG is the Gibbs free energy change of reaction (J/mol), ΔG^θ denotes the Gibbs free energy change of reaction for unmixed reactants and products at standard conditions (J/mol), R is the gas constant ($\text{J}\cdot\text{mol}^{-1}\cdot\text{K}^{-1}$), T is temperature (K), and K is the equilibrium constant (unitless).

The Gibbs free energy of oxides, sulfides and oxysulfides of cerium are shown in Table 2^{14,21–26}.

Below 2000 K, the most thermodynamically stable inclusion was CeO₂, as shown in Fig. 1. Therefore, CeO₂ likely formed in the molten iron when the temperature reached the simulated steelmaking temperature of 1873 K. In Fig. 1, it could be read that the least thermodynamic stable inclusion is CeS and the thermodynamic stable sequence of the possible inclusion formed in liquid steel is CeO₂ > Ce₂O₃ > Ce₂O₂S > Ce₂S₃ > Ce₃S₄ > CeS. However, the most thermodynamically stable matter does not guarantee the formation of CeO₂, because the formation of oxides containing cerium are controlled not only by the equilibrium constant but also by the concentrations of cerium and oxygen in the molten iron. That is to say, the formation of CeO₂ at 1873 K is also determined by the solubility product of CeO₂ and the concentration of cerium and oxygen, even though the Gibbs Free Energy of CeO₂ is the lowest at 1873 K.

The activities and activity coefficient of Ce, O and S can be written as Eqs (9) and (10) from Wagner's relation⁷ and Lupis' relation²⁰ as follow,

$$\alpha_i = f_i \cdot w[i] \quad (9)$$

e_i^j	e_{Ce}^{Ce}	e_S^{Ce}	e_{Ce}^S	e_S^S	e_O^{Ce}	e_{Ce}^O	e_O^O
T = 1873 K	0.0039	-9.1	-40	-0.046	-64	-560	-0.17

Table 3. First-order interaction parameter e_i^j of cerium, oxygen, and sulfur at 1873 K³⁰.

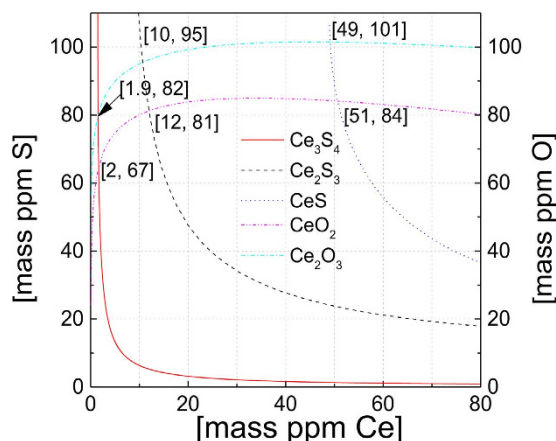


Figure 2. Deoxidation and Desulfurization with Cerium in liquid iron at 1873 K.

$$\lg f_i = \sum_j^n e_i^j w[j] \quad (10)$$

where f_i is the Henrian activity coefficient of component i relative to the dilute solution and e_i^j is the first-order interaction parameter of i on j in molten iron; $w[i]$ and $w[j]$ are the mass percentages of elements i and j , respectively (Table 3); α_i 's the activity of element i .

By using data^{22,23} from Tables 2 and 3, the following curves for Ce-S and Ce-O in Fig. 2 can be calculated. The key to derive every line in Fig. 2 is the relation of equilibrium constant, Gibbs free energy and the amount of the chemical compositions for every possible inclusion according to Wagner's relation¹⁹ and Lupis' relation²⁰. When the equilibrium constant is linked to the amount of the chemical compositions for every possible inclusion, equations for Fig. 2 can be obtained. When the weight percentage of cerium, oxygen and sulphur are known in the molten iron at 1873 K, the main inclusion formed would be found in Fig. 2. As shown in Fig. 2, if the cerium addition in liquid iron is 70 ppm and the initial oxygen and sulphur are both 110 ppm, the formation of oxides containing cerium would experience the transformation from Ce_2O_3 to CeO_2 and also the formation of sulfides containing cerium would experience the transformation from CeS to Ce_2S_3 and then to Ce_3S_4 . From Fig. 2, when the temperature of molten iron reached 1873 K, Ce_3S_4 is the main product, as the amount of cerium in molten iron is high and the amount of sulphur is relatively lower compared to the formation of CeS and Ce_2S_3 .

In order to investigate the formation conditions of Ce_2O_3 , Ce_2S_3 and Ce_2O_2S , the doubly saturated curve with Ce_2O_3/Ce_2O_2S and Ce_2S_3/Ce_2O_2S are calculated, using the thermodynamic data derived in Tables 2 and Equation 1–2.

In molten iron, it is assumed that $K_{Ce_2O_3,1873K} = [\%Ce]^2 \cdot [\%O]^3 = 10^{-11}$ and $K_{Ce_2S_3,1873K} = [\%Ce]^2 \cdot [\%S]^3 = 10^{-6}$. Based on the reaction $Ce_2O_2S + [O] = Ce_2O_3 + [S]$, it is found that $[\%S] = 10[\%O]$ when Ce_2O_2S and Ce_2O_3 coexist. When Ce_2O_2S and Ce_2S_3 coexist in molten iron, it is derived that $[\%S] = 100[\%O]$, based on the thermodynamic calculation of the reaction $Ce_2S_3 + 2[O] = Ce_2O_2S + 2[S]$. Figure 3 was derived from the above calculations. In Fig. 3, it can be concluded that Ce_2O_3 and Ce_2O_2S can exist in molten iron in a wide amount range of $[Ce]$, $[O]$ and $[S]$. More importantly, only when the amount of $[O]$ is extremely low and the amount of $[S]$ and $[Ce]$ is relatively high, Ce_2S_3 has the possibility to form.

Cerium is a perfect deoxidizer and desulfurizer for steel purification. Compared with other elements, for example Aluminum, Titanium, Magnesium and Calcium^{27,28}, which can also deoxidize and desulfurize, cerium can form a complex compound Ce_2O_2S which contains Oxygen and Sulphur together. The formation possibility of Ce_2O_2S has been verified by Hu's research²⁹ when they studied the effect of Ce addition on the C-Mn steel microstructure. It is reported by Wang²⁶ that Ce_2O_3 is easier to form in molten iron when the iron molten temperature is 1873 K. However, the thermodynamic conditions were changed when the temperature decreases from 1873 K to solidus temperature. On the other hand, when the temperature of molten iron decreases to that at which solid steel starts to form, the cerium and oxygen in the molten iron begin to segregate. Their amounts are respectively:

$$W_{(Ce)} = W_{(Ce)_0} (1 - f_s)^{k_{Ce}-1}$$

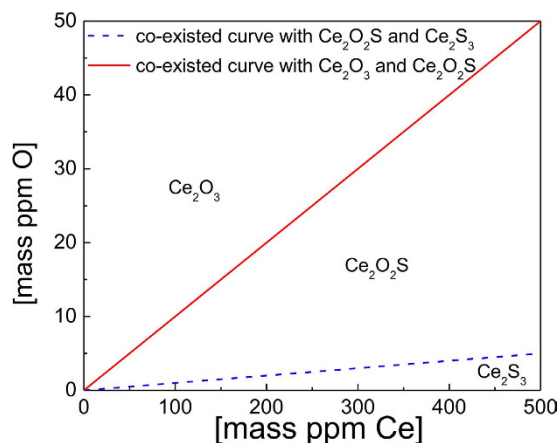


Figure 3. Relationship of [O] and [S] when Ce_2O_2S , Ce_2O_3 , and Ce_2S_3 can form as stable compounds in molten iron at 1873 K.

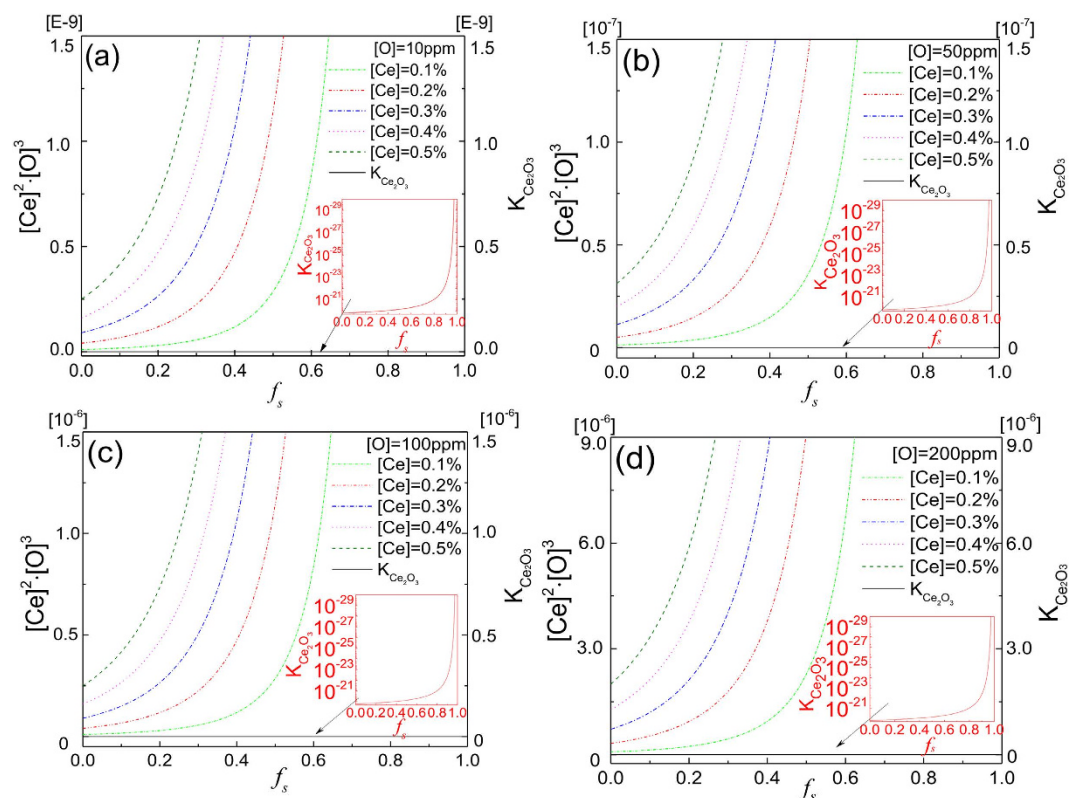


Figure 4. Segregation of Ce_2O_3 in solid and liquid phases when $\alpha_{[O]}$ is (a) 10, (b) 50, (c) 100, and (d) 200 ppm.

$$W_{(O)} = \frac{W_{(O)_0}}{f_s(k_0 - 1) + 1} \tag{12}$$

where $W_{(Ce)}$ and $W_{(O)}$ are the percentage amounts of cerium and oxygen of molten iron during the molten iron solidification, respectively; $W_{(Ce)_0}$ and $W_{(O)_0}$ are the initial percentage amounts of cerium and oxygen in the liquid phase, respectively; k_{Ce} ($=0.005$) and k_O ($=0.022$) are the solvent partition coefficients at equilibrium for cerium and oxygen, respectively; f_s is the solid fraction.

The solidus temperature of SS400 is 1777 K. The solubility product of the Ce_2O_3 formed in molten iron can be expressed as:

$$Q_{\text{Ce}_2\text{O}_3} = W_{\text{Ce}}^2 \cdot W_{\text{O}}^3 \quad (13)$$

The solubility product of the Ce_2O_3 formed in molten iron at equilibrium can be expressed as:

$$K_{\text{Ce}_2\text{O}_3} = \alpha_{\text{Ce}}^2 \cdot \alpha_{\text{O}}^3 = 10^{(-\frac{74695}{T} + 18.75)} \quad (14)$$

From Eqs (11) to (14), the solubility products versus solidification ratio (f_s) are plotted in Fig. 4. In Fig. 4(a), where the simulated oxygen concentration in liquid steel is 10 ppm and the cerium concentration varies from 0.1% to 0.5%, the solubility products versus solidification ratio (f_s) are plotted with the varying cerium concentration (shown in the colorful lines of Fig. 4(a)) and the equilibrium constant of Ce_2O_3 ($K_{\text{Ce}_2\text{O}_3}$) versus solidification ratio f_s is curved as the black solid line in Fig. 4(a). It is read in Fig. 4(a) that the colorful lines are all in the above of the black solid line, which means Ce_2O_3 prefers to segregate in liquid phase with the 10 ppm Oxygen concentration in liquid iron. Moreover, the same conclusion can be drawn from the similar Fig. 4(b–d) with 50 ppm, 100 ppm, 200 ppm oxygen concentration in liquid iron. The inset red diagrams in Fig. 4(a–d) are the detailed solid black curves appeared in Fig. 4(a–d). Figure 4 shows that when the oxygen concentration in molten iron was increased from 10 to 200 ppm and the cerium concentration was in the range of 0.1% to 0.5%, Ce_2O_3 preferred to segregate in the liquid phase.

Conclusion

By the addition of cerium in molten SS400 steel, when the temperature of molten iron reached 1873 K, at the same time that the Cerium addition in liquid iron is 70 ppm and the initial Oxygen and Sulphur are both 110 ppm, the formation of oxides containing Cerium would experience the transformation from Ce_2O_3 to CeO_2 and also the formation of sulfides containing Cerium would experience the transformation from CeS to Ce_2S_3 and then to Ce_3S_4 . Below 2000 K the most thermodynamic stable matter CeO_2 and the least thermodynamic stable inclusion is CeS . And the thermodynamic stable sequence of the possible inclusions formed in liquid steel is $\text{CeO}_2 > \text{Ce}_2\text{O}_3 > \text{Ce}_2\text{O}_2\text{S} > \text{Ce}_2\text{S}_3 > \text{Ce}_3\text{S}_4 > \text{CeS}$. Only when the amount of [O] is extremely low and the amount of [S] and [Ce] is relatively high, Ce_2S_3 has the possibility to form. With the amount of oxygen in molten iron increasing from 10 ppm to 200 ppm and the amount range of cerium increasing from 0.1% to 0.5%, Ce_2O_3 prefers to segregate in liquid phase all the time.

References

- Su, Y. & Lai, Y. Performance enhancement of natural pigments on a high light transmission ZrO_2 nanoparticle layer in a water-based dye-sensitized solar cell. *Int. J. Energ. Res.* **38**, 436–443 (2014).
- Kung, P. *et al.* Down-conversion photoluminescence sensitizing plasmonic silver nanoparticles on ZnO nanorods to generate hydrogen by water splitting photochemistry. *Appl. Phys. Lett.* **106**, 023114 (2015).
- Lin, K. & Su, Y. Photoluminescence of Cu: ZnS, Ag: ZnS, and Au: ZnS nanoparticles applied in Bio-LED. *Appl. Phys. B: Lasers Opt.* **113**, 351–359 (2013).
- Lai, Y., Su, Y. & Lin, M. Photochemical water splitting performance of Fluorescein, Rhodamine B, and Chlorophyll-Cu supported on ZrO_2 nanoparticles layer anode. *Dyes Pigm.* **103**, 76–81 (2014).
- Su, Y. *et al.* Ellipsometric advances for local surface plasmon resonance to determine chitosan adsorption on layer-by-layer gold nanoparticles. *Appl. Spectrosc.* **61**, 1007–1014 (2007).
- Fruehan, R. J. The effect of zirconium, cerium, and lanthanum on the solubility of oxygen in liquid iron. *Metall. Mater. Trans. B* **5**, 345–347 (1974).
- Wilson, W. G., Kay, D. & Vahed, A. The use of thermodynamics and phase equilibria to predict the behavior of the rare earth elements in steel. *J. O. M.* **26**, 14–23 (1975).
- Fischer, W. A. & Bertram, H. The deoxidation, desulphurization and nitrogen removal of iron melts containing oxygen, sulfur or nitrogen using the rare earth metals cerium and lanthanum. *Arch. Eisenhüttenwes.* **44**, 87–95 (1973).
- Han, Q. *et al.* Equilibria between cerium or neodymium and oxygen in molten iron. *Metall. Mater. Trans. B* **21**, 295–302 (1990).
- Langenberg, F. C. & Chipman, J. Equilibrium between cerium and sulfur in liquid iron. *Trans. Met. Soc. AIME* **212**, 290–293 (1958).
- Pan, F. *et al.* Effects of rare earth metals on steel microstructures. *Materials* **9**, 417 (2016).
- Arunachalam, V. & Ramachandran, S. Rare earths in steel technology. *Sci. Technol. Rare Earth Mater.* 415–434 (1980).
- Wu, Y., Wang, L. & Du, T. Thermodynamics of rare earth elements in liquid iron. *J. Less Common Metals* **110**, 187–193 (1985).
- Li, W. C. Thermodynamics of the formation of rare earth inclusions in steel. *Iron and Steel* **21**, 7–12 (1986).
- Byun, J., Shim, J., Cho, Y. & Lee, D. Non-metallic inclusion and intragranular nucleation of ferrite in Ti-killed C–Mn steel. *Acta Metall.* **51**, 1593–1606 (2003).
- Yang, J., Yamasaki, T. & Kuwabara, M. Behavior of inclusions in deoxidation process of molten steel with *in situ* produced Mg vapor. *ISIJ Int.* **47**, 699–708 (2007).
- Seo, C. *et al.* Modification and minimization of spinel ($\text{Al}_2\text{O}_3\text{-xMgO}$) inclusions formed in Ti-added steel melts. *Metall. Mater. Trans. B* **41**, 790–797 (2010).
- Su, Y. *et al.* Photoelectric characteristics of natural pigments self-assembly fabricated on TiO_2/FTO substrate. *J. Nanosci. Nanotechnol.* **9**, 960–964 (2009).
- Wagner, C. *Thermodynamics of alloys* (Massachusetts: Addison-Wesley Press). p. 22 (1952).
- Lupis, C. H. *Chemical thermodynamics of materials* (Amsterdam: North-Holland). p. 31 (1983).
- Liu, Y. H., Lin, Q. & Ye, W. Behavior of rare earths in ultralow-sulfur microalloyed steel. *J. Rare Earths* **17**, 207–212 (1999).
- Wang, L. M. *et al.* Thermodynamics and application of rare earth elements in steel. *J. Chin. RE Soc.* **21**, 251–254 (2003).
- Chen, J. X. *Handbook of common datas and graph in steelmaking* (Beijing: Metallurgical Industry Press). p. 757–761 (2010).
- Katsumata, A. & Todoroki, H. Effect of rare earth metal on inclusion composition in molten stainless steel. *Iron Steelmaker* **29**, 51–57 (2002).
- Vahed, A. & Kayd, A. R. Thermodynamics of rare earths in steelmaking. *Metall. Mater. Trans. B* **7**, 375–383 (1976).
- Wang, G. C. *et al.* Experimental and thermodynamic study on formation of inclusions containing cerium in HP295 steel. *J. Chin. RE Soc.* **31**, 161–168 (2013).
- Ono, H. *et al.* Formation conditions of Mg_2TiO_4 and MgAl_2O_4 in Ti-Mg-Al complex deoxidation of molten iron. *ISIJ Int.* **49**, 957–964 (2009).

28. Tomita, Y. Effect of desulphurization and calcium treatments on the inclusion morphology of 0.4 C-Cr-Mo-Ni steel. *J. Mater. Sci.* **29**, 2873–2878 (1994).
29. Hu, Z. Y. *et al.* Effect of Ce addition on inclusion and microstructure in C-Mn steel. *Metal. Int.* **17**, 11–17 (2012).
30. Wang, L. M., Du, T. & Wu, Y. M. Thermodynamic study on formation RES and RE₂S₃ between rare earth elements and sulphur in iron-based solution. *J. Chin. RE Soc.* **6**, 11 (1987).

Acknowledgements

Our work is sponsored by China Steel Company, National Science Council (MOST104-2622-8-006-001) and Research Center for Energy Technology and Strategy (D105-23008) National Cheng Kung University in Taiwan. Thanks Dr. Ho-Lin Tsai, James Augusto, Shuo-Yen Fang and Guan-Ping Qi for their kind help.

Author Contributions

This paper was proposed by W.-S.H., F.P. and J.Z. contributed to this article equally. This manuscript was written by F.P. The thermodynamic calculations were carried out by F.P. and J.Z. H.-L.C. and Y.-H.S. contributed to data analysis. Y.-H.S. gave us a lot of suggestions to promote our research. All authors reviewed the manuscript.

Additional Information

Competing financial interests: The authors declare no competing financial interests.

How to cite this article: Pan, F. *et al.* Thermodynamic Calculation among Cerium, Oxygen, and Sulfur in Liquid Iron. *Sci. Rep.* **6**, 35843; doi: 10.1038/srep35843 (2016).



This work is licensed under a Creative Commons Attribution 4.0 International License. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in the credit line; if the material is not included under the Creative Commons license, users will need to obtain permission from the license holder to reproduce the material. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>

© The Author(s) 2016