

SCIENTIFIC REPORTS

OPEN

Enhanced cycling stability of NiCo₂S₄@NiO core-shell nanowire arrays for all-solid-state asymmetric supercapacitors

Received: 18 August 2016
Accepted: 11 November 2016
Published: 07 December 2016

Yuan Yuan Huang¹, Tielin Shi^{1,2}, Shulan Jiang³, Siyi Cheng¹, Xiangxu Tao¹, Yan Zhong¹, Guanglan Liao^{1,2} & Zirong Tang^{1,2}

As a new class of pseudocapacitive material, metal sulfides possess high electrochemical performance. However, their cycling performance as conventional electrodes is rather poor for practical applications. In this article, we report an original composite electrode based on NiCo₂S₄@NiO core-shell nanowire arrays (NWAs) with enhanced cycling stability. This three-dimensional electrode also has a high specific capacitance of 12.2 F cm⁻² at the current density of 1 mA cm⁻² and excellent cycling stability (about 89% retention after 10,000 cycles). Moreover, an all-solid-state asymmetric supercapacitor (ASC) device has been assembled with NiCo₂S₄@NiO NWAs as the positive electrode and active carbon (AC) as the negative electrode, delivering a high energy density of 30.38 Wh kg⁻¹ at 0.288 kW kg⁻¹ and good cycling stability (about 109% retention after 5000 cycles). The results show that NiCo₂S₄@NiO NWAs are promising for high-performance supercapacitors with stable cycling based on the unique core-shell structure and well-designed combinations.

With the increasing demand in energy and environmental protection, the development of high performance energy storage devices has become urgent. Supercapacitors have attracted vast attentions due to the advantages like fast charge-recharge ability, high specific capacity and long cycle life compared with other traditional energy storage devices such as rechargeable fuel cells and batteries^{1–8}. Supercapacitors are commonly divided into electric double layer capacitors (EDLCs) which store energy using ion adsorption and pseudocapacitors using frequently reversible redox reactions in electrode surface. Pseudocapacitive materials such as metal oxides and electronically conducting polymers have been extensively studied owing to their high theoretical specific capacitance, high energy densities, low cost, and low toxicity compared with most commercial supercapacitor materials^{9,10}.

Recently, metal sulfides such as Ni₃S₂^{11,12}, CoS¹³ and MoS₂¹⁴ have been applied to pseudocapacitors as promising electrode materials owing to their great electrochemical performance like high reversible capacity and good electrical conductivity synergistically. Among them, NiCo₂S₄ is outstanding owing to its higher reversible capacity, richer redox reactions and more sensitive electrical conductivity than the other metal sulfides^{15,16}. NiCo₂S₄ has been widely studied for supercapacitor applications in the past few years. For example, NiCo₂S₄ nanosheets grown on reduced graphene oxide (RGO) present a high specific capacitance of 1161 F g⁻¹ at the current density of 5 A g⁻¹ (4.5% loss after 2,000 cycles)¹⁵. NiCo₂S₄ nanosheets grown on Nitrogen-doped carbon foams show a great specific capacitance of 8.77 F g⁻¹ at the current density of 20 A g⁻¹ (9.6% loss after 2,000 cycles)¹⁷. NiCo₂S₄ nanotubes grown on Ni foam exhibit a specific capacitance of 738 F g⁻¹ at the current density of 4 A g⁻¹ (6.6% loss after 4,000 cycles)¹⁸. NiCo₂S₄ porous nanotubes through a sacrificial template method show a specific capacitance of 1093 F g⁻¹ at a current density of 0.2 A g⁻¹ (15.5% loss after 5,000 cycles)¹⁹. However, bare NiCo₂S₄ electrode often results in poor cycleability and low energy density because of the occurrence of redox reactions, the insufficient contact between the active material and electrolyte, and the instable structure during the electrochemical reaction. In this regard, well-designed NiCo₂S₄-based hybrid nano-architectures with other well-known metal oxides/hydroxide

¹State Key Laboratory of Digital Manufacturing Equipment and Technology, Huazhong University of Science and Technology, Wuhan 430074, China. ²Wuhan National Laboratory for Optoelectronics, Huazhong University of Science and Technology, Wuhan 430074, China. ³Tribology Research Institute, Southwest Jiaotong University, Chengdu 610031, China. Correspondence and requests for materials should be addressed to Z.T. (email: zirong@hust.edu.cn)

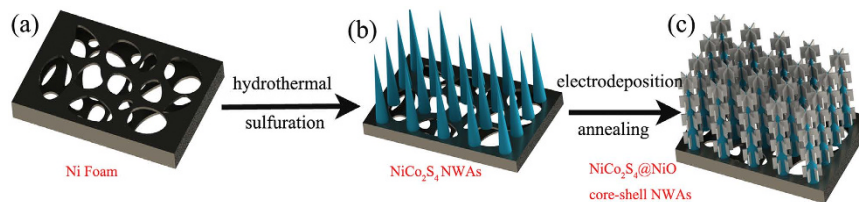


Figure 1. Schematic illustrating the formation process of the NiCo₂S₄@NiO NWAs on Ni foam. (a) Ni foam, (b) NiCo₂S₄ NWAs, (c) NiCo₂S₄@NiO NWAs.

capacitive materials may be a good way to meet the requirement of high-performance supercapacitors^{20–24}. In the meantime, NiO is widely studied for supercapacitors as the positive electrode material due to its high theoretical specific capacitance of 2573 F g⁻¹ within 0.5 V²⁵, good electrochemical stability²⁶, practical availability, environmentally benign nature and low cost.

Herein, we developed a facile and low-cost process to fabricate an original three-dimensional core-shell structure on Ni foam with NiCo₂S₄ nanowires and NiO nanosheets as core and shell, respectively. NiCo₂S₄ nanowires synthesized through two-step hydrothermal reactions acted as skeleton supporting for the NiO shell. NiO nanosheets were coated on the surface of NiCo₂S₄ nanowires by electrochemical deposition and post-annealing subsequently. The core-shell structure can provide abundant redox reaction sites, facilitate the sufficient contact of electrode and electrolyte, and enhance the cycleability. The new electrode demonstrates a remarkable specific capacitance (12.2 F cm⁻² at the current density of 1 mA cm⁻²) and enhanced cycling performance (the capacity retention of 89% over 10,000 cycles). To further evaluate the NiCo₂S₄@NiO NWAs electrode for practical applications, an all-solid state ASC was fabricated. The assembled device receives a superior energy density of 30.38 W h kg⁻¹ at 0.288 KW kg⁻¹, outstanding power density of 0.72 KW kg⁻¹ at 10.36 W h kg⁻¹ and good cycling stability (109% retention after 5,000 cycles). The results demonstrate that NiCo₂S₄@NiO NWAs are the kind of promising electrode with enhanced cycling stability for high performance supercapacitor applications. The methodology through well-designed combinations and fabrication method presented in this work are applicable for the development of the energy storage devices with a wide variety of excellent capacitive materials.

Results and Discussion

The electrode fabrication procedure of NiCo₂S₄@NiO NWAs is schematically shown in Fig. 1. Firstly, NiCo₂S₄ nanowires were densely grown on Ni foam through a hydrothermal and sulfuration process. Later, the NiCo₂S₄ nanowires were acted as a scaffold for the growth of NiO nanosheets through electrochemical deposition and post-annealing process. The NiO nanosheets can act as an armor to protect the integrity of NiCo₂S₄ nanowires surviving from reversible redox reactions.

A series of characterizations were carried out to study the morphologies of the NiCo₂S₄@NiO NWAs. Figure 2 presents typical SEM images of the NiCo₂S₄ nanowires and NiCo₂S₄@NiO NWAs supported on the 3D porous Ni Foam substrate. From Fig. 2(a), Ni foam is completely covered by orderly NiCo₂S₄ nanowires. Enlarged SEM images of Fig. 2(b), 2(c) reveal that the surface of NiCo₂S₄ nanowires is relatively smooth. After electrodeposited for 10 minutes and annealed, the NiCo₂S₄ nanowires are covered by thin NiO nanosheets, as shown in Fig. 2(d), forming a core-shell hierarchical nanostructure. From the enlarged images of Fig. 2(e) and (f), the thin NiO nanosheets are connected with each other, forming the unique core-shell structure. The obtained core-shell structure greatly enlarges the surface area, offering abundant redox reactions sites.

The Fig. 3 shows the corresponding X-ray diffraction (XRD) patterns of the as-synthesized sample. The three typical peaks at 44.7°, 52.1° and 76.5° are respectively identified as (111), (200) and (220) planes of the Ni foam. The four major peaks at 31.5°, 38.3°, 50.4° and 55.3° can be respectively identified as (311), (400), (511) and (440) planes of the NiCo₂S₄ phase (JCPDS card No. 20-0782)^{27–30}. Moreover, the diffraction peaks at 37.2°, 43.3°, 62.9° coincide with (111) (200) (220) plane respectively in the standard NiO spectrum (JCPDS card No. 47-1049). And no additional diffraction peak is detected, which confirms that the hybrid structure consists of NiCo₂S₄ and NiO only.

The detailed morphology and core-shell structure of NiCo₂S₄@NiO were confirmed by TEM, high-resolution TEM (HRTEM), as shown in Fig. 4 and EDX mapping in Figure S1. The core-shell structure of NiCo₂S₄@NiO is clearly shown in Fig. 4(a), where the core and the shell can be distinguished by the illustrated red lines. The HRTEM image further verifies the core-shell nanostructure, as exhibited in Fig. 4(b). The heterointerface between the NiCo₂S₄ core and the NiO shell can be obviously distinguished by the red line. Top part shown in Fig. 4(b) reveals the inner NiO nanocrystallite, which has a lattice fringe of 0.209 nm, assigning to the (200) crystal plane of NiO. Bottom part in Fig. 4(b) reveals the lattice fringe of 0.28 nm which is close to the (311) crystal plane of NiCo₂S₄. These results well agreed with XRD patterns. The EDX mapping of the NiCo₂S₄@NiO NWAs is also displayed in Figure S1, which further confirm the multiple core-shell structure of the composite.

Electrochemical performance of the NiCo₂S₄@NiO NWAs

Electrochemical measurements were carried out in a three-electrode electrochemical cell with 3 M KOH as the electrolyte. Figure 5(a) shows respective CV curves over a potential range from -0.2 to 0.6 V for the NiCo₂S₄@NiO, NiCo₂S₄ and NiO electrode at 5 mV s⁻¹. Obviously, at the same scan rate, the integrated area of the NiCo₂S₄@NiO NWAs is much larger than that of the NiCo₂S₄ or NiO nanostructure electrodes, which indicates that the NiCo₂S₄@NiO NWAs electrode has the highest capacity. As shown in Fig. 5b, with the increment of scan rate, the voltammetric current of the NiCo₂S₄@NiO NWAs electrode increases. The redox peaks in each CV curve

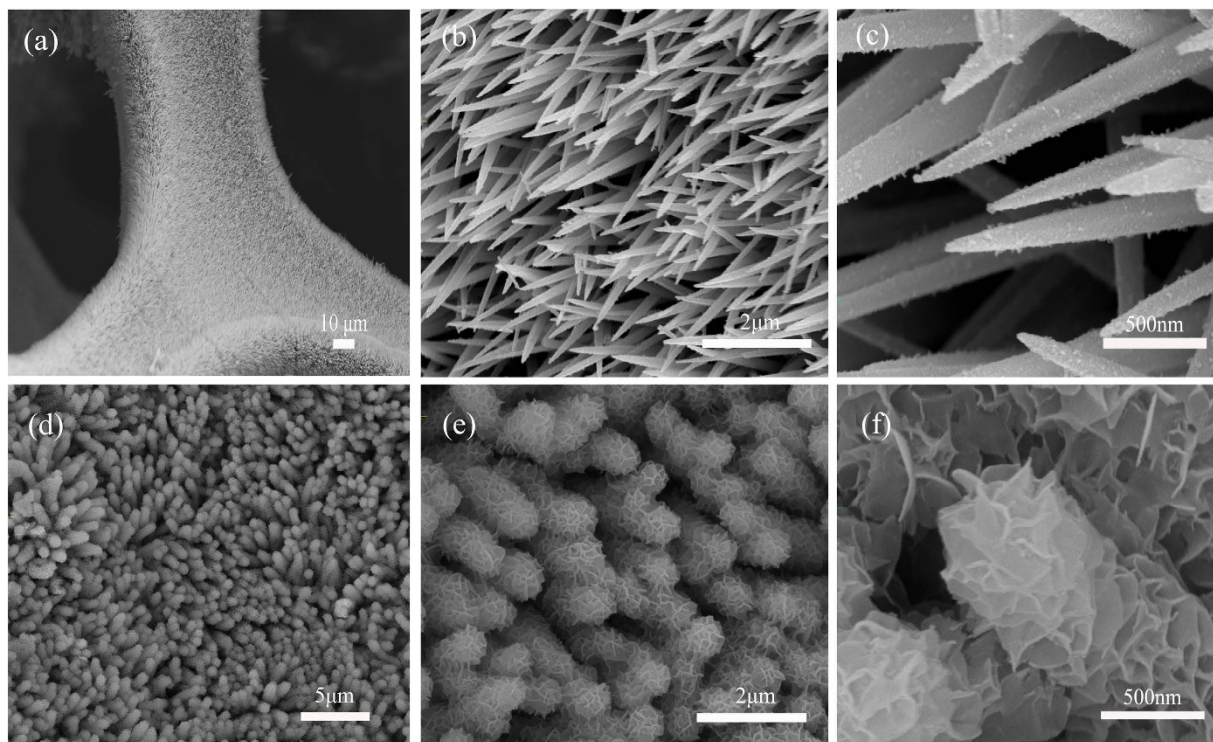


Figure 2. SEM images of NiCo_2S_4 NWAs (**a**, **b** and **c**) at different magnifications; SEM images of $\text{NiCo}_2\text{S}_4@$ NiO NWAs (**d**, **e**, and **f**) at different magnifications.


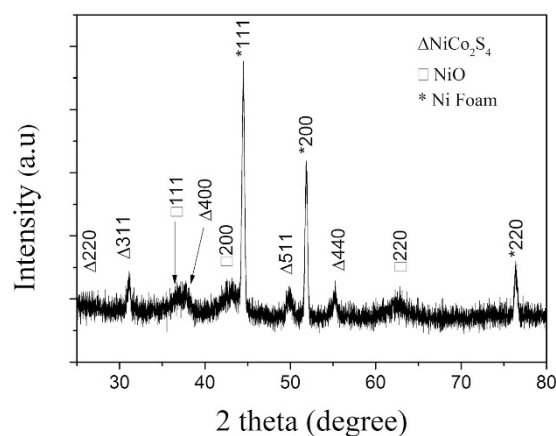


Figure 3. XRD pattern of the hierarchical $\text{NiCo}_2\text{S}_4@$ NiO core-shell nanowires scratched from NiO foam.

demonstrate the pseudocapacitive properties of the NiCo_2S_4 and NiO, which may owe to $\text{Ni}^{2+}/\text{Ni}^{3+}$, $\text{Co}^{2+}/\text{Co}^{3+}$ and $\text{Co}^{3+}/\text{Co}^{4+}$ transitions as shown in the following equations^{17,26}.



Galvanostatic charge-discharge (GCD) tests were also carried out to estimate the electrochemical performance of the $\text{NiCo}_2\text{S}_4@$ NiO NWAs electrode. Figure 5(c) shows the comparison of the charge and discharge curves of the $\text{NiCo}_2\text{S}_4@$ NiO NWAs, NiCo_2S_4 NWAs and NiO nanosheets, respectively. The $\text{NiCo}_2\text{S}_4@$ NiO NWAs

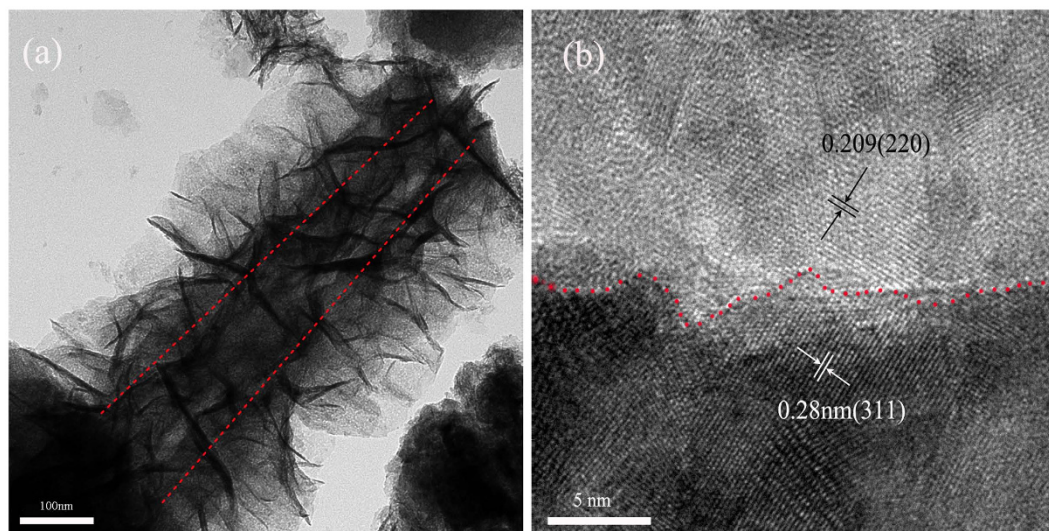


Figure 4. (a) TEM image of the NiCo₂S₄@NiO core-shell nanowire. (b) HRTEM image of the NiCo₂S₄@NiO core-shell nanowire.

electrode reveals vastly longer charge-discharge time than both NiCo₂S₄ nanowires and NiO nanosheets at the same current density. And Fig. 5(d) shows the GCD curves of NiCo₂S₄@NiO NWAs electrode at various current densities varying from 1 to 20 mA cm⁻². According to the equation (7) and (8), the specific capacitance was calculated with the discharge time and the corresponding results were plotted in Fig. 5(e). Evidently, the NiCo₂S₄@NiO delivers a high specific capacitance 12.2 F cm⁻² at the current density of 1 mA cm⁻². And the calculated results of the specific capacitance based on the active mass was also provided in Figure S2. Obviously, the NiCo₂S₄@NiO NWAs electrode delivers much higher areal specific capacitance than the NiCo₂S₄ nanowire arrays or NiO nanosheets, and also higher than many previously reported electrodes based on NiCo₂S₄, such as NiCo₂S₄@Ni_(1-x)Co_x(OH)₂ core-shell nanoarrays (3.54 F cm⁻² at 1 mA cm⁻²)³¹, NiCo₂S₄ nanotube@Ni-Mn Layered Double Hydroxide arrays/graphene sponge (1.74 F cm⁻² at 1 mA cm⁻²)²⁸, NiCo₂S₄ nanotube@NiCo₂S₄ nanosheet arrays on Ni foam (4.38 F cm⁻² at 5 mA cm⁻²)³² and NiCo₂S₄@MnO₂ heterostructures (2.6 F cm⁻² at 3 mA cm⁻²)³³. The high specific capacitance of the electrode can be attributed to the specific core-shell arrays structure and the well-designed combination of NiCo₂S₄ with NiO. The 3D core-shell structure also enables easy access of electrolyte, and promotes the transport of electrolyte and the contact between the electrode and electrolyte. And the NiCo₂S₄ nanowire arrays electrode possesses not only good pseudocapacitive behavior itself, but also provides vast electron passageways. The thin NiO nanosheets can enhance the surface area and protect the NiCo₂S₄ nanowire surviving from redox reactions.

The measurement of cycling performance for the NiCo₂S₄@NiO NWAs and NiCo₂S₄ NWAs electrodes were shown in Fig. 5(f). The overall loss of NiCo₂S₄@NiO NWAs after 10,000 cycles was less than 11.15%, much better than the NiCo₂S₄ electrode's 29.42%. Obviously, the cycling stability has tremendously improved after the compositing. Comparing with NiCo₂S₄ nanowire arrays, the enhanced stability of NiCo₂S₄@NiO core-shell arrays can be attributed to the coaxial structure and the well-designed combination, in which the NiCo₂S₄ core offers a solid skeleton to interlink the NiO nanosheets, and the NiO layer protects the NiCo₂S₄ structural from destroyed in electrolyte. As a result, the mutual cooperation ensures the structural integrity of NiCo₂S₄@NiO nanocomposites and thus the enhanced cycling stability. And to the best of our knowledge, the cycling stability of NiCo₂S₄@NiO NWAs is also much higher than previously reported NiCo₂S₄ based electrodes, such as NiCo₂S₄ nanosheets grown on Nitrogen-doped carbon foam (9.6% capacity loss after 2,000 cycles)¹⁷, NiCo₂S₄ nanotube@Ni-Mn (11.7% capacity loss after 1,000 cycles)²⁸, CoxNi_{1-x}(OH)₂/NiCo₂S₄ nanotube (4% capacity loss after 2,000 cycles)³⁴.

Electrochemical impedance spectroscopy (EIS) tests had been further conducted to observe the intrinsic mechanism on the dramatic performance improvement of the NiCo₂S₄@NiO nanocomposites. Figure 6 depicts the Nyquist plots of the EIS spectra for the NiCo₂S₄@NiO and NiCo₂S₄ electrode, respectively. The charge transfer resistance R_{ct} of the hybrid NiCo₂S₄@NiO NWAs electrode (0.03 Ω) is lower than that of the pristine NiCo₂S₄ NWAs electrode (0.09 Ω), which was deduced by the diameter of the semicircle³⁵. NiCo₂S₄@NiO shows lower internal resistance R_e (0.237 Ω) than NiCo₂S₄ (0.275 Ω). This result clearly reveals that the NiCo₂S₄@NiO demonstrates better charge-transfer kinetics and quick ion transport than NiCo₂S₄.

Comparing with NiCo₂S₄ nanowire arrays, the smart design of NiCo₂S₄@NiO NWAs shows outstanding electrochemical performance, which can be included the following advantages. (i) Both NiCo₂S₄ and NiO have high specific capacitance, and exhibit excellent capacitive behavior in the same KOH alkaline electrolyte, thereby contributing to the increase of overall capacitance significantly. (ii) The NiCo₂S₄ core has an intimate electrical connection to the NiO nanosheets, which builds a reliable conductive network for quick ion transport. The thin NiO nanosheets can enlarge the effective contact surface area, which enables the full exposure of the active materials to the electrolyte. The core-shell structure could provide short pathways for the ion diffusion and rapid charge collection/transfer, and the enlarged surface area make more sufficient contact between the electrolyte and the

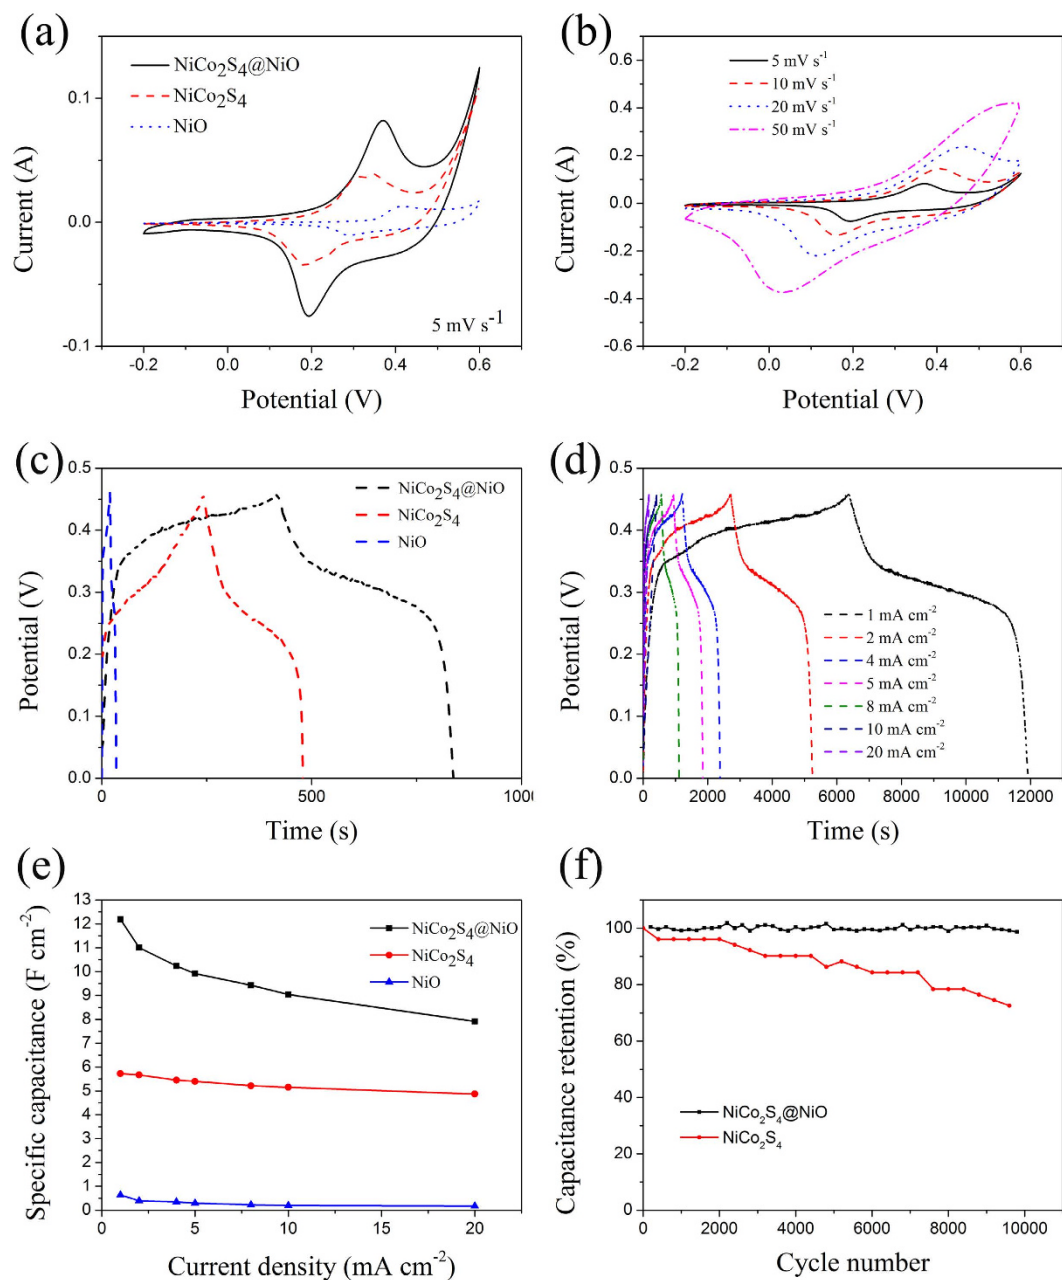


Figure 5. (a) Comparison of CV curves of NiCo₂S₄@NiO core-shell NWAs, NiCo₂S₄ NWAs and NiO nanosheets at the scan rate of 5 mV s⁻¹. (b) The CV curves of NiCo₂S₄@NiO core-shell NWAs electrode at different scan rates. (c) Comparison of GCD curves of NiCo₂S₄@NiO core-shell NWAs, NiCo₂S₄ NWAs and NiO nanosheets at the current density of 10 mV cm⁻². (d) The GCD curves of NiCo₂S₄@NiO core-shell NWAs electrode at different current densities. (e) Geometric specific capacitances of NiCo₂S₄@NiO core-shell NWAs, NiCo₂S₄ NWAs and NiO nanosheets electrodes at different current densities. (f) Cycling properties of NiCo₂S₄@NiO core-shell NWAs electrode and NiCo₂S₄ NWAs electrode at the current density of 20 mA cm⁻² for 10,000 cycles.

electrode^{17,29,30}. Therefore, the maximum harvest of pseudocapacitance can be achieved from the NiCo₂S₄@NiO core-shell nanostructure^{36–39}. (iii) The combination of NiCo₂S₄ and NiO with different redox reaction potential results in more electro active sites for the Faradaic redox reactions^{40–42}. (iv) Comparing with the bare NiCo₂S₄ NWAs, the three-dimensional core-shell structure of the NiCo₂S₄@NiO NWAs can retard the inside strain which caused by the volume changes during the cycling. The NiCo₂S₄ NWAs are served as rigid back-bones to support NiO by interlinking the polymeric chains, the NiO nanosheets coated on the NiCo₂S₄ NWs may relieve the stress exerted on inner nanowires caused by severe volume change, and thus suppress the degradation of the NiCo₂S₄ core^{43–45}. Thus, the *in-situ* combination of NiCo₂S₄ and NiO would give rise to a strong synergetic effect and good mechanical integrity for improving the electrochemical performance and cycling stability. In summary, the composed electrode of NiCo₂S₄@NiO NWAs can achieve vastly enhanced performance than bare NiCo₂S₄.

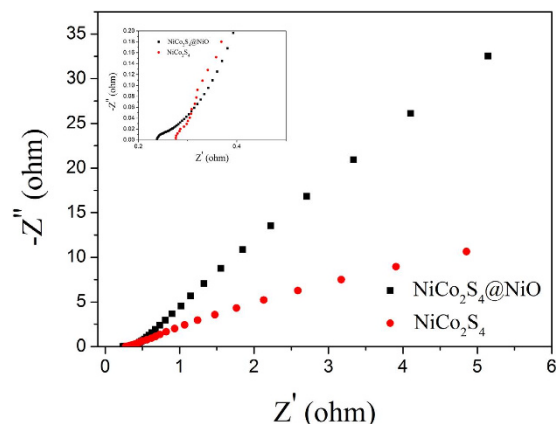


Figure 6. Nyquist plots of $\text{NiCo}_2\text{S}_4@\text{NiO}$ and NiCo_2S_4 .

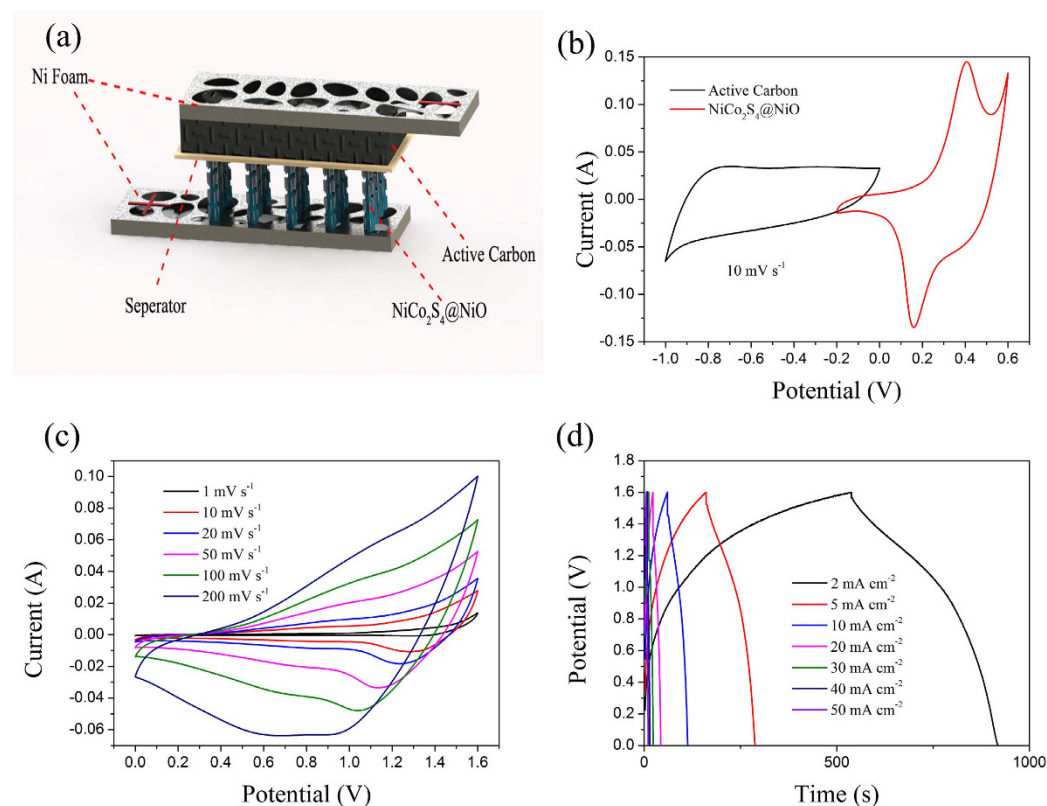


Figure 7. (a) Schematic illustration of an ASC that composed of the positive electrode of $\text{NiCo}_2\text{S}_4@\text{NiO}$ NWAs, separator, and the negative electrode of AC; (b) CV curves of $\text{NiCo}_2\text{S}_4@\text{NiO}$ NWAs and AC half cells in 3 M KOH solution at the scan rate of 10 mV s^{-1} ; (c) CV curves of the ASC tested at different scan rates ranging from 1 to 200 mV s^{-1} ; (d) Galvanostatic charge-discharge curves at different current densities from 2 to 50 mA cm^{-2}

Electrochemical performance of the $\text{NiCo}_2\text{S}_4@\text{NiO}/\text{AC}$ all-solid-state ASCs

To further evaluate the $\text{NiCo}_2\text{S}_4@\text{NiO}$ NWAs electrode for practical applications, the ASC was fabricated using the $\text{NiCo}_2\text{S}_4@\text{NiO}$ NWAs as the positive material and the AC film as the negative material, as shown in Fig. 7(a). To investigate the potential range of the device, the CV curves collected in a three-electrode system from the AC film electrode and $\text{NiCo}_2\text{S}_4@\text{NiO}$ NWAs hybrid electrode in 3 M KOH electrolyte were demonstrated in Fig. 7(b). The CV curve of the AC is a nearly rectangular shape without redox peaks, which shows classic EDLCs behavior. And the CV curves of $\text{NiCo}_2\text{S}_4@\text{NiO}$ electrode shows two pairs of redox peaks in the potential window from -0.2 to 0.6 V , attributing to the typical pseudocapacitance character^{46,47}. In order to obtain the optimal performance of the ASC device, the charge between the positive and the negative electrodes should be balanced following the relationship $q^+ = q^-$. The charge stored by each electrode depends on the specific capacitance (C), the potential range for the charge/discharge process (ΔE) and the mass of the electrode (m) following the equation (5)⁴⁸:

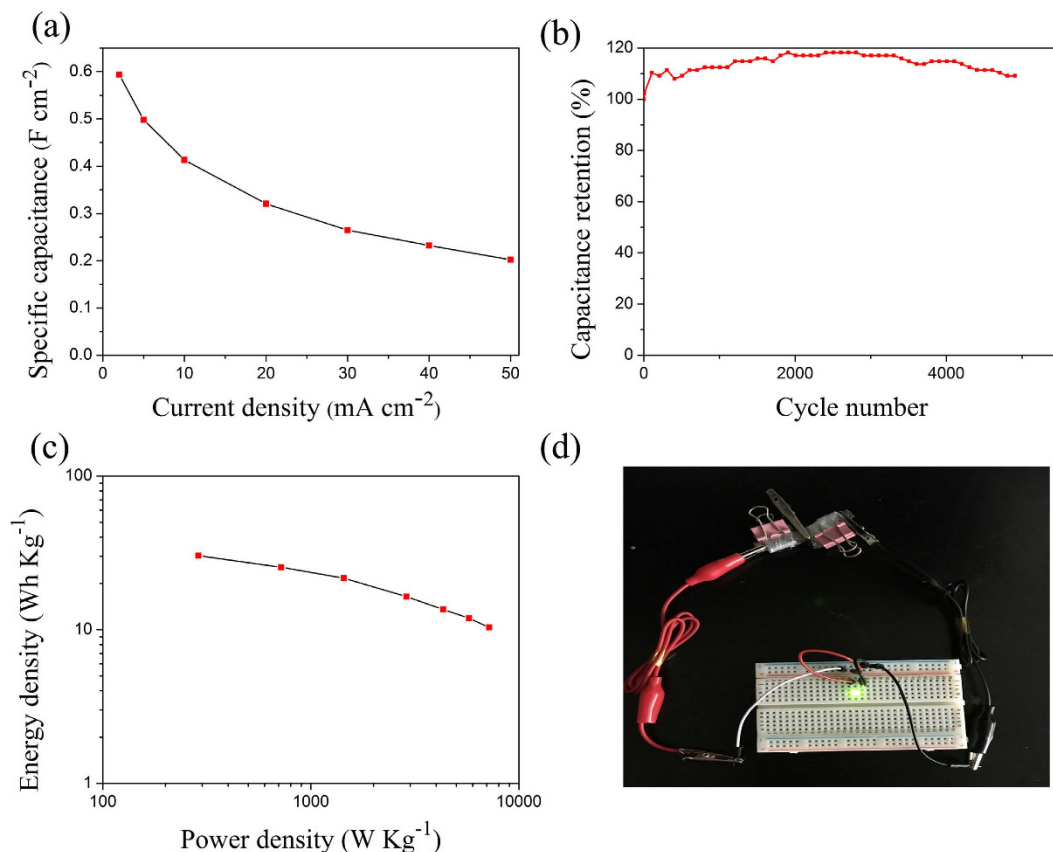


Figure 8. (a) Specific capacitance of the ASC at different current densities; (b) Cycling performance of ASC devices collected at the scan rate of 20 mA cm⁻²; (c) Ragone plots of energy density and power density of NiCo₂S₄@NiO//AC; (d) Optical images showing that two NiCo₂S₄@NiO//AC all-solid-state ASCs in series lighting up a green LED indicator.

$$Q = C \times \Delta E \times m \quad (5)$$

And the mass ratio will follow the equation (6):

$$\frac{m^+}{m^-} = \frac{C^- \times \Delta E^-}{C^+ \times \Delta E^+} \quad (6)$$

According to the equation, the mass ratio between the NiCo₂S₄@NiO electrode and AC electrode was calculated to be around 1:1.8. To investigate the influence of scan rate on the electrochemical performance, the rate-dependent CV curves of the NiCo₂S₄@NiO//AC ASC device with scan rates from 10 to 200 mV s⁻¹ were measured in Fig. 7(c). Notably, at the high scan rate of 200 mV s⁻¹ and the maximum working voltage of 1.6 V, the shape of the CV curve is still well retained, denoting a good rate capability.

Galvanostatic charge-discharge measurements were conducted between 0 to 1.6 V to calculate the specific capacitance of NiCo₂S₄@NiO//AC. Figure 7(d) shows the galvanostatic charge-discharge curves for the different current densities from 2 mA cm⁻² to 50 mA cm⁻² in the potential window of 0–1.6 V. During the charge-discharge, the charge curves of the NiCo₂S₄@NiO//AC ASCs are almost symmetric to its corresponding discharge counterpart, even at the high current density of 200 mA cm⁻². The capacitance of NiCo₂S₄@NiO//AC device with different current densities was calculated according to equation (7) and (8), which was plotted in Fig. 8(a). The capacitance of NiCo₂S₄@NiO//AC changed from 0.59 to 0.21 F cm⁻² with the augment of the current density from 2 to 50 mA cm⁻². As shown in Fig. 8(b), the capacitance was slowly increased during the first cycle because only a fraction of material was active. And after more cycles of the charge and discharge, the NiCo₂S₄@NiO core-shell nanowires became fully activated and contributed to the large increase of the capacitance. The specific capacitance of the hybrid electrode still retained about 109% of its initial value after 5,000 cycles. According to equation (9) and (10), the energy density and power density were calculated and shown in Fig. 8(c). The maximum energy density of the ASC was further calculated to be 30.385 W h Kg⁻¹ at the power density of 0.288 KW Kg⁻¹. At the high discharge current of 20 mA cm⁻², the energy density still remained 10.36 W h Kg⁻¹ at the power density of 0.72 KW Kg⁻¹. The highest energy density obtained here is superior than that of many reported ASC devices based on NiCo₂S₄, such as the NiCo₂S₄ nanosheet//AC with the energy density of 25.5 W h Kg⁻¹⁴⁹, the NiCo₂S₄//AC with the energy density of 22.8 W h Kg⁻¹ at 0.16 W Kg⁻¹⁵⁰, the NiCo₂S₄ (nanosheets)//AC with

the energy density of 22.4 W h kg^{-1} at 0.335 kW kg^{-1} ⁴⁹ and mesoporous NiCo_2S_4 (nanoparticles)//AC with the energy density of 28.3 W h kg^{-1} at 0.245 kW kg^{-1} ⁵¹. Compared with a sequence of other ASC devices based the core-shell structure, like CNT@NiO//PCPs (25.4 W h kg^{-1} at 0.4 kW kg^{-1})⁵², Ni(OH)₂@3DNI//AC (21.8 W h kg^{-1} at 0.66 kW kg^{-1})⁴⁶ and NiCo_2O_4 @NiMoO₄//AC (21.7 W h kg^{-1} at 0.157 kW kg^{-1})⁴¹, the result of NiCo_2S_4 @NiO//AC device developed here also possesses a competitive superiority. In order to further demonstrate the potential application of the ASC, a green light-emitting diode (LED) indicator was powered after charging to 3.2 V for 20 s, as shown in Fig. 8(d). These results show outstanding performance of the ASCs and prove that the as-obtained NiCo_2S_4 @NiO NWAs are promising for practical applications.

In general, we have exhibited a low-cost hydrothermal synthesis with a subsequent electrochemical deposition process for the fabrication of the three-dimensional NiCo_2S_4 @NiO NWAs on Ni foam. The NiCo_2S_4 @NiO NWAs electrode exhibited superior performance with high specific capacitance of 12.2 F cm^{-2} at the current density of 1 mA cm^{-2} , a remarkable cycling stability (about 89% retention after 10,000 cycles). The fabricated all-solid-state ASC device based on the NiCo_2S_4 @NiO core-shell electrode also demonstrated excellent electrochemical performance in terms of energy density ($30.385 \text{ W h Kg}^{-1}$ at $0.288 \text{ k W Kg}^{-1}$), cycling lifespan (109% retention after 5000 cycles). The ASC was further assembled in series to verify their practical application, for LED indicator as the example. We anticipate that this work will advance the development of supercapacitors with metal sulfide materials, and the methodology through unique structural and well-designed combinations are also applicable to improve the electrochemical performance for energy-storage devices.

Methods

Synthesis of NiCo_2S_4 nanowire arrays. All the chemicals used in this study were purchased without further purification. In a typical procedure, the Ni foam was cleaned by 5% HCl, ethanol and deionized (DI) water to remove impurities and oxides. Then, 1.903 g of $\text{CoCl}_2 \cdot 6\text{H}_2\text{O}$, 0.95076 g of NiCl_2 , and 0.72072 g of urea were dissolved in 60 mL DI water. Later, transferring the solution into a 100 ml Teflon-lined autoclave and putting a piece of clean Ni foam in the autoclave. Then the autoclave was put in the oven and the oven was kept at $120 \text{ }^\circ\text{C}$ for 6 h. After cooling down to room temperature, the precursors were received after washing with DI water and ethanol for several times. Next, 4.8 g sodium sulfide was dissolved in 60 ml DI water. Then the solution was transferred into the 100 ml Teflon-lined autoclave together with the as-obtained precursors, and the autoclave was kept in the oven under $160 \text{ }^\circ\text{C}$ for 6 h. Finally, the NiCo_2S_4 nanowire arrays were obtained through washing the sample with DI water and ethanol for several times, and then dried at $60 \text{ }^\circ\text{C}$ for 12 h. The mass loading of NiCo_2S_4 was around 9.1 mg cm^{-2} .

Synthesis of NiCo_2S_4 @NiO core-shell nanowire arrays

Ni(OH)_2 nanosheets were synthesized through an electrochemical deposition process. The as-fabricated NiCo_2S_4 nanowires on Ni foam acted as the working electrode, a saturated SCE acted as the reference electrode and a Pt sheet acted as the counter electrode. The electrochemical deposition process was conducted in the solution of 0.1 M NiNO_3 at the potential of -1 V . Different electrochemical deposition duration of 1, 5, 10, 15, and 20 minutes was respectively selected to find the optimal loading of NiO for the composite electrode. Then, the obtained samples were washed by DI water, dried at $60 \text{ }^\circ\text{C}$ for 12 h. Finally, the NiCo_2S_4 @NiO NWAs supported on Ni foam were synthesized by annealing the as-obtained NiCo_2S_4 @NiO NWAs on Ni foam in air atmosphere at $300 \text{ }^\circ\text{C}$ for 2 h. The CV curves of the electrodes were showed in Figure S3 and more discussions were provided in the support information. Based on the CV curve analysis, we chose 10 minutes of electrochemical deposition as the optimal deposition duration. In the manuscript, all of the NiCo_2S_4 @NiO NWAs related tests were based on it. The mass loading of NiCo_2S_4 @NiO NWAs with electrochemical deposition of 10 minutes was around 13.48 mg cm^{-2} .

Synthesis of NiO nanosheets arrays

First of all, the Ni foam was cleaned by 5% HCl, ethanol and deionized (DI) water to remove impurities and oxides. Using the same method mentioned previously, Ni(OH)_2 nanosheets were synthesized via the electrochemical depositing process. Ni foam acted as the working electrode, a saturated SCE acted as the reference electrode and a Pt sheet acted as the counter electrode. The electrochemical deposition was conducted in the solution of 0.1 M NiNO_3 at the potential of -1 V for 10 minutes. Then, the obtained sample was washed by DI water, dried at $60 \text{ }^\circ\text{C}$ for 12 h. Finally, the NiO nanosheets supported on Ni foam were synthesized by annealing the as-obtained NiOH nanosheets on Ni foam in air atmosphere at $300 \text{ }^\circ\text{C}$ for 2 h. The mass loading of NiO was around 1 mg cm^{-2} .

Characterization. The morphologies of the samples were characterized by scanning electron microscopy (SEM, FEI Nova NanoSEM 450) and transmission electron microscopy (TEM, FEI Tecnai G2 S-TWIN). The crystallographic phases of the NiCo_2S_4 @NiO NWAs were characterized by X-ray diffraction (XRD) with radiation from a Cu target ($K\alpha$, $\lambda = 0.154 \text{ nm}$).

Electrochemical measurements. The electrochemical performance of as-prepared NiCo_2S_4 NWAs, NiCo_2S_4 @NiO NWAs and NiO nanosheets samples were all evaluated using an electrochemical Autolab workstation (PGSTAT-302N, Eco Chemie B.V. Company). The cyclic voltammetry (CV) and electrochemical impedance spectroscopy (EIS) measurements were taken by the three-electrode cell in 3 M KOH aqueous electrolytes. Galvanostatic charging/discharging (GCD) and cycling tests of the electrodes were conducted using a battery measurement system (LAND CT2001A). The EIS measurements were conducted with a frequency range from 10^{-2} Hz to 10^5 Hz and voltage amplitude of 10 mV at open-circuit potential. The areal specific capacitance (C_a) and mass specific capacitance (C_m), energy density (E), and power density (P) were calculated by following equations⁴⁷:

$$C_m = I \times t / (m \times \Delta V) \quad (7)$$

$$C_a = I \times t / (A \times \Delta V) \quad (8)$$

$$E = C_m \times (\Delta V)^2 / 2 \quad (9)$$

$$P = E / \Delta V \quad (10)$$

where I , t , m , ΔV , and A respectively represents the discharge current (mA), the discharge time (s), the total mass of active materials (g), the potential window of the electrode (V), and the surface area of the electrode (cm²).

Fabrication of all-solid-state asymmetric supercapacitor devices

The ASCs were assembled using NiCo₂S₄@NiO NWAs as the positive electrode and activated carbon slurry by mixing 80 wt% AC, 10 wt% carbon black with 10 wt% polytetrafluorene-ethylene (PTFE) as the negative electrode and a piece of filter paper as the separator. The PVA-KOH gel electrolyte was obtained by mixing 3 g polyvinyl alcohol (PVA), 1.63 g KOH with 30 ml of DI water.

References

- Conway, B. *Electrochemical Supercapacitors-Scientific Fundamentals and Technological Applications* Plenum Press. *New York* (1999).
- Simon, P. & Gogotsi, Y. Materials for electrochemical capacitors. *Nature materials* **7**, 845–854 (2008).
- Hall, P. J. & Bain, E. J. Energy-storage technologies and electricity generation. *Energy policy* **36**, 4352–4355 (2008).
- Miller, J. R. & Simon, P. Electrochemical capacitors for energy management. *Science Magazine* **321**, 651–652 (2008).
- Shukla, A., Sampath, S. & Vijayamohan, K. Electrochemical supercapacitors: Energy storage beyond batteries. *Current science* **79**, 1656–1661 (2000).
- Hall, P. J. *et al.* Energy storage in electrochemical capacitors: designing functional materials to improve performance. *Energy & Environmental Science* **3**, 1238–1251 (2010).
- Jiang, S. *et al.* High-performance binder-free supercapacitor electrode by direct growth of cobalt-manganese composite oxide nanostructures on nickel foam. *Nanoscale research letters* **9**, 1–8 (2014).
- Jiang, S., Shi, T., Zhan, X., Huang, Y. & Tang, Z. Superior electrochemical performance of carbon cloth electrode-based supercapacitors through surface activation and nitrogen doping. *Ionics* **1–10** (2016).
- Ben-Ishai, M. & Patolsky, F. A Route to High-Quality Crystalline Coaxial Core/Multishell Ge@ Si (GeSi) n and Si@(GeSi) n Nanowire Heterostructures. *Advanced Materials* **22**, 902–906 (2010).
- Chen, W. *et al.* High-performance nanostructured supercapacitors on a sponge. *Nano letters* **11**, 5165–5172 (2011).
- Zhou, W. *et al.* Ni₃S₂ nanorods/Ni foam composite electrode with low overpotential for electrocatalytic oxygen evolution. *Energy & Environmental Science* **6**, 2921–2924 (2013).
- Li, R., Wang, S., Wang, J. & Huang, Z. Ni₃S₂@ CoS core-shell nano-triangular pyramid arrays on Ni foam for high-performance supercapacitors. *Physical Chemistry Chemical Physics* **17**, 16434–16442 (2015).
- Ray, R. S., Sarma, B., Jurovitzki, A. L. & Misra, M. Fabrication and characterization of titania nanotube/cobalt sulfide supercapacitor electrode in various electrolytes. *Chemical Engineering Journal* **260**, 671–683 (2015).
- Wang, J. *et al.* Ni₃S₂@ MoS₂ core/shell nanorod arrays on Ni foam for high-performance electrochemical energy storage. *Nano Energy* **7**, 151–160 (2014).
- Peng, S. *et al.* *In situ* growth of NiCo₂S₄ nanosheets on graphene for high-performance supercapacitors. *Chemical Communications* **49**, 10178–10180 (2013).
- Xiao, Y. *et al.* Rapid microwave-assisted fabrication of 3D cauliflower-like NiCo₂S₄ architectures for asymmetric supercapacitors. *RSC Advances* **5**, 21604–21613 (2015).
- Shen, L. *et al.* NiCo₂S₄ Nanosheets Grown on Nitrogen-Doped Carbon Foams as an Advanced Electrode for Supercapacitors. *Advanced Energy Materials* **5** (2015).
- Pu, J. *et al.* Direct Growth of NiCo₂S₄ Nanotube Arrays on Nickel Foam as High-Performance Binder-Free Electrodes for Supercapacitors. *ChemPlusChem* **79**, 577–583 (2014).
- Wan, H. *et al.* NiCo₂S₄ porous nanotubes synthesis via sacrificial templates: high-performance electrode materials of supercapacitors. *CrystEngComm* **15**, 7649–7651 (2013).
- Mai, L.-Q. *et al.* Hierarchical MnMoO₄/CoMoO₄ heterostructured nanowires with enhanced supercapacitor performance. *Nature communications* **2**, 381 (2011).
- Xia, X. *et al.* High-quality metal oxide core/shell nanowire arrays on conductive substrates for electrochemical energy storage. *ACS nano* **6**, 5531–5538 (2012).
- Zhao, Y., Hu, L., Zhao, S. & Wu, L. Preparation of MnCo₂O₄@ Ni (OH)₂ Core-Shell Flowers for Asymmetric Supercapacitor Materials with Ultrahigh Specific Capacitance. *Advanced Functional Materials* (2016).
- Niu, M. *et al.* Hydrothermal synthesis, structural characteristics, and enhanced photocatalysis of SnO₂/α-Fe₂O₃ semiconductor nanoheterostructures. *ACS Nano* **4**, 681–688 (2010).
- Wang, H., Ma, D., Huang, X., Huang, Y. & Zhang, X. General and controllable synthesis strategy of metal oxide/TiO₂ hierarchical heterostructures with improved lithium-ion battery performance. *Scientific reports* **2** (2012).
- Liu, K. C. & Anderson, M. A. Porous nickel oxide/nickel films for electrochemical capacitors. *Journal of the Electrochemical Society* **143**, 124–130 (1996).
- Yuan, C., Zhang, X., Su, L., Gao, B. & Shen, L. Facile synthesis and self-assembly of hierarchical porous NiO nano/micro spherical superstructures for high performance supercapacitors. *Journal of Materials Chemistry* **19**, 5772–5777 (2009).
- Fu, W. *et al.* Cobalt sulfide nanosheets coated on NiCo₂S₄ nanotube arrays as electrode materials for high-performance supercapacitors. *Journal of Materials Chemistry A* **3**, 10492–10497 (2015).
- Wan, H. *et al.* Hierarchical Configuration of NiCo₂S₄ Nanotube@ Ni–Mn Layered Double Hydroxide Arrays/Three-Dimensional Graphene Sponge as Electrode Materials for High-Capacitance Supercapacitors. *ACS applied materials & interfaces* **7**, 15840–15847 (2015).
- Chen, H. *et al.* *In situ* growth of NiCo₂S₄ nanotube arrays on Ni foam for supercapacitors: maximizing utilization efficiency at high mass loading to achieve ultrahigh areal pseudocapacitance. *Journal of Power Sources* **254**, 249–257 (2014).
- Cai, D. *et al.* Construction of desirable NiCo₂S₄ nanotube arrays on nickel foam substrate for pseudocapacitors with enhanced performance. *Electrochimica Acta* **151**, 35–41 (2015).
- Zhou, W. *et al.* Hierarchically constructed NiCo₂S₄@ Ni (1–x) Co x (OH)₂ core/shell nanoarrays and their application in energy storage. *Nanotechnology* **27**, 235402 (2016).

32. Chen, H. *et al.* Hierarchical NiCo₂S₄ Nanotube@NiCo₂S₄ Nanosheet Arrays on Ni Foam for High-Performance Supercapacitors. *Chemistry—An Asian Journal* **11**, 248–255 (2016).
33. Xu, K. *et al.* Design and synthesis of 3D hierarchical NiCo₂S₄@MnO₂ core-shell nanosheet arrays for high-performance pseudocapacitors. *RSC Advances* **5**, 44642–44647 (2015).
34. Xiao, J., Wan, L., Yang, S., Xiao, F. & Wang, S. Design hierarchical electrodes with highly conductive NiCo₂S₄ nanotube arrays grown on carbon fiber paper for high-performance pseudocapacitors. *Nano letters* **14**, 831–838 (2014).
35. Kong, D., Ren, W., Luo, Y., Yang, Y. & Cheng, C. Scalable synthesis of graphene-wrapped Li₄Ti₅O₁₂ dandelion-like microspheres for lithium-ion batteries with excellent rate capability and long-cycle life. *Journal of Materials Chemistry A* **2**, 20221–20230 (2014).
36. Sreekumar, T. V. *et al.* Polyacrylonitrile single-walled carbon nanotube composite fibers. *Advanced Materials* **16**, 58–61 (2004).
37. Chang, J.-K., Wu, C.-M. & Sun, I.-W. Nano-architected Co(OH)₂ electrodes constructed using an easily-manipulated electrochemical protocol for high-performance energy storage applications. *Journal of Materials Chemistry* **20**, 3729–3735 (2010).
38. Bao, L., Zang, J. & Li, X. Flexible Zn₂SnO₄/MnO₂ core/shell nanocable-carbon microfiber hybrid composites for high-performance supercapacitor electrodes. *Nano letters* **11**, 1215–1220 (2011).
39. Guan, C. *et al.* Hybrid structure of cobalt monoxide nanowire@nickel hydroxide nanoflake aligned on nickel foam for high-rate supercapacitor. *Energy & Environmental Science* **4**, 4496–4499 (2011).
40. Liu, X., Liu, J. & Sun, X. NiCo₂O₄@NiO hybrid arrays with improved electrochemical performance for pseudocapacitors. *Journal of Materials Chemistry A* **3**, 13900–13905 (2015).
41. Cheng, D. *et al.* Hierarchical NiCo₂O₄@NiMoO₄ core-shell hybrid nanowire/nanosheet arrays for high-performance pseudocapacitors. *Journal of Materials Chemistry A* **3**, 14348–14357 (2015).
42. Kong, D. *et al.* Three-dimensional Co₃O₄@C@Ni₃S₂ sandwich-structured nanoneedle arrays: towards high-performance flexible all-solid-state asymmetric supercapacitors. *Journal of Materials Chemistry A* **3**, 16150–16161 (2015).
43. Wang, Y., Zeng, H. C. & Lee, J. Y. Highly reversible lithium storage in porous SnO₂ nanotubes with coaxially grown carbon nanotube overlayers. *Advanced Materials* **18**, 645–649 (2006).
44. Wang, Y., Xia, H., Lu, L. & Lin, J. Excellent performance in lithium-ion battery anodes: rational synthesis of Co(CO₃)_{0.5}(OH)_{0.11}H₂O nanobelt array and its conversion into mesoporous and single-crystal Co₃O₄. *ACS Nano* **4**, 1425–1432 (2010).
45. Wang, Y. & Cao, G. Developments in Nanostructured Cathode Materials for High-Performance Lithium-Ion Batteries. *Advanced Materials* **20**, 2251–2269 (2008).
46. Su, Y.-Z., Xiao, K., Li, N., Liu, Z.-Q. & Qiao, S.-Z. Amorphous Ni(OH)₂@three-dimensional Ni core-shell nanostructures for high capacitance pseudocapacitors and asymmetric supercapacitors. *Journal of Materials Chemistry A* **2**, 13845–13853 (2014).
47. Li, R., Wang, S., Huang, Z., Lu, F. & He, T. NiCo₂S₄@Co(OH)₂ core-shell nanotube arrays *in situ* grown on Ni foam for high performance asymmetric supercapacitors. *Journal of Power Sources* **312**, 156–164 (2016).
48. Lu, X. *et al.* High energy density asymmetric quasi-solid-state supercapacitor based on porous vanadium nitride nanowire anode. *Nano letters* **13**, 2628–2633 (2013).
49. Wu, Z. *et al.* High energy density asymmetric supercapacitors from mesoporous NiCo₂S₄ nanosheets. *Electrochimica Acta* **174**, 238–245 (2015).
50. Kong, W., Lu, C., Zhang, W., Pu, J. & Wang, Z. Homogeneous core-shell NiCo₂S₄ nanostructures supported on nickel foam for supercapacitors. *Journal of Materials Chemistry A* **3**, 12452–12460 (2015).
51. Zhu, Y. *et al.* Mesoporous NiCo₂S₄ nanoparticles as high-performance electrode materials for supercapacitors. *Journal of Power Sources* **273**, 584–590 (2015).
52. Yi, H., Wang, H., Jing, Y., Peng, T. & Wang, X. Asymmetric supercapacitors based on carbon nanotubes@NiO ultrathin nanosheets core-shell composites and MOF-derived porous carbon polyhedrons with super-long cycle life. *Journal of Power Sources* **285**, 281–290 (2015).

Acknowledgements

This work is supported by the National Science Foundation of China (Nos. 51275195 and 51605400), the National Basic Research Program of China (No. 2015CB057205), the Program for Changjiang Scholars and the Innovative Research Team in University (grant no. IRT13017). We would like to thank the Analytical and Testing Center of Huazhong University of Science and Technology.

Author Contributions

Y.Y.H, Z.R.T and S.L.J designed and performed the experiments. Y.Y.H, S.Y.C, Z.Y, and X.X.T prepares the samples and analyzed the data. Y.Y.H and Z.R.T wrote the manuscript. G.L.L and T.L.S participated in interpreting and analyzing the data.

Additional Information

Supplementary information accompanies this paper at <http://www.nature.com/srep>

Competing financial interests: The authors declare no competing financial interests.

How to cite this article: Huang, Y. *et al.* Enhanced cycling stability of NiCo₂S₄@NiO core-shell nanowire arrays for all-solid-state asymmetric supercapacitors. *Sci. Rep.* **6**, 38620; doi: 10.1038/srep38620 (2016).

Publisher's note: Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.



This work is licensed under a Creative Commons Attribution 4.0 International License. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in the credit line; if the material is not included under the Creative Commons license, users will need to obtain permission from the license holder to reproduce the material. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>

© The Author(s) 2016