

SCIENTIFIC REPORTS



OPEN

Relationship between structural order and water-like anomalies in metastable liquid silicon: *Ab initio* molecular dynamics

Received: 21 July 2016
Accepted: 30 November 2016
Published: 05 January 2017

G. Zhao, J. L. Yan, Y. J. Yu, M. C. Ding, X. G. Zhao & H. Y. Wang

The relationship between structural order and water-like anomalies in tetrahedral liquids is still open. Here, first-principle molecular dynamics are performed to study it in metastable liquid Si. It is found that in T - P phase diagram, there indeed exists a structural anomaly region, which encloses density anomaly but not diffusivity anomaly. This is consistent with that of SW Si and BKS SiO₂ but different from that of SPC/E water. Two-body excess entropy anomaly can neither capture the diffusivity, structural, and density anomalies, as it can in a two-scale potential fluid. In structural anomaly region, tetrahedrality order q_{tetra} (measuring the extent to which an atom and its four nearest neighbours adopt tetrahedral arrangement) and translational order t_{trans} (measuring the tendency of two atoms to adopt preferential separation) are not perfectly correlated, which is different from that in SW Si and renders it impossible to use the isotaxis line to quantify the degree of structural order needed for water-like anomalies to occur. Along the isotherm of critical temperature T_{ci} t_{trans}/q_{tetra} is approximately linear with pressure. With decreasing pressure along the isotherm below T_{ci} t_{trans}/q_{tetra} departs downward from the line, while it is the opposite case above T_{ci} .

Tetrahedral liquids, in which the anisotropic bonding gives rise to a three-dimensional, liquid-state network with an energetic bias towards local tetrahedral order, are ubiquitous in everyday life, such as water, SiO₂, BeF₂, GeO₂, C, Si, Ge, Sn. Although the interactions between atoms or molecules are different, including ionic, metallic, covalent and hydrogen bonding, they share a preference for forming tetrahedrally coordinated configurations at the micro level and displaying water-like anomalous behaviour at the macro level, such as the well-known density maximum (density anomaly)¹, the anomalous increase of diffusivity upon pressurizing (diffusivity anomaly)^{2–6}, and the first-order liquid-liquid phase transition (LLPT)^{7–18}. Tetrahedral liquids form a large fraction of our world and have fundamental biological and technological relevance. Therefore, a general interpretation of these anomalous behaviours is of wide interest.

In recent years, much effort has been expended to understand the relationship between the atomic level structure and the water-like anomalies. In 2001, Errington and Debenedetti⁶ firstly introduced two measures of order, the translational order parameter (t_{trans})¹⁹ and the tetrahedrality order parameter (q_{tetra})²⁰, to analyse the local structural order in the SPC/E model of water and further to study the relationship between structural order and these anomalies. It was found that, in the region bounded by loci of maximum q_{tetra} at low densities and minimum t_{trans} at high densities along the isotherm, q_{tetra} and t_{trans} decrease on compression, in contrast to what is observed for simple fluids. Therefore, this region was identified by the authors as a structurally anomalous region, which in turn encloses the regions of diffusivity anomaly and density anomaly in the T - ρ phase diagram. Moreover, the two orders were found to be strictly coupled in this region, i.e., a particular value of q_{tetra} is associated with a unique value of t_{trans} , and so the isotaxis lines (from the Greek word taxis, meaning order, or arrangement) can be used to quantify the degree of structural order needed for these anomalies to occur. Soon after that, using the Beest-Kramer-van Santen (BKS) model potential, a similar analysis in liquid silica was carried out by Shell *et al.*²¹. However, they found that even though there also exists a structurally anomalous region similar to that in water and it encloses the density anomaly, it does not encompass the region of diffusivity anomaly and the structural order parameters q_{tetra} and t_{trans} are not strictly coupled in this region. Therefore, they concluded that q_{tetra} and t_{trans}

School of Physics and Optoelectronic Engineering, Ludong University, Yantai 264025, P. R. China. Correspondence and requests for materials should be addressed to G.Z. (email: gzhao19800209@126.com)

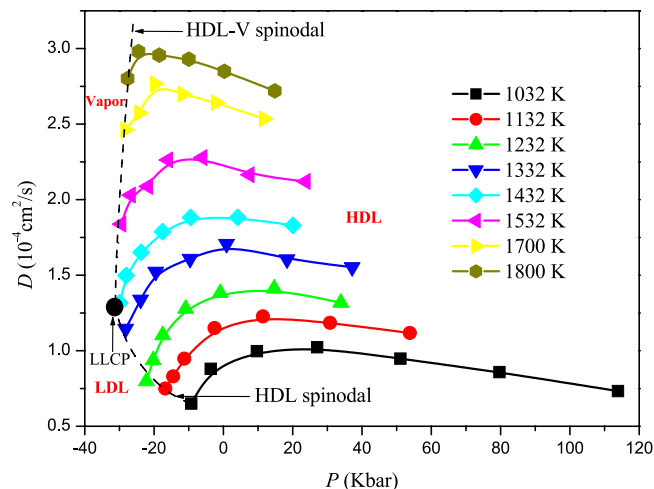


Figure 1. Diffusivity as a function of pressure for different temperatures from 1032 to 1800 K obtained from *ab initio* molecular dynamics simulations of liquid Si. The maximum in diffusivity demarcates the regions of normal and anomalous behaviour in T - P phase diagram.

can not anticipate the occurrence of the diffusivity anomaly and hence can not provide a satisfactory microscopic picture of the anomalous behaviour in liquid silica. The later results of liquid BeF_2 with the transferable rigid ion model (TRIM) by Agarwal *et al.*²² shows the similar result with BKS SiO_2 , but that of the Oeffner-Elliot (OE) model of GeO_2 by Jabes *et al.*²³ is similar to SPC/E water. The systematic comparison for different model potentials of water (mTIP3P, TIP4P, TIP4P/2005, TIP5P, SPC/E), ionic liquids (SiO_2 and BeF_2), and liquids characterised by the Stillinger-Weber (SW) potential (including Si)^{24–27} suggests that a strong correlation between q_{tetra} and t_{trans} exists only in rigid-body model potentials for water and SW liquids (in a limited range of tetrahedrality strength), but not in ionic melts. In addition, to obtain a more general picture of the origins of these anomalies, the excess entropy has also been attempted to understand these anomalies and has been tested to be able to predict the regions of anomalies in the phase diagram^{22–29}.

It should be noted that the water-like cascading of anomalous regions in the phase diagram has been observed not only in systems having directional interactions but also in the simulation studies of spherically symmetric potentials^{29–33}. Especially, the study of Jagla model by Yan *et al.*³⁰ suggests the water-like relationship between structural order and anomalies is related to the presence of two different length scales in the potential. Moreover, the study of a core-softened model by Fomin *et al.*³³ shows that the order of the cascading regions of anomaly can be changed by increasing the depth of the attractive part of the potential.

Although so many computer simulation studies of tetrahedral liquids have focused on the relationship between structural order and water-like anomalies, they all depended on different model potentials or empirical potentials. To our knowledge, first-principle computer simulations have not been performed to study this question so far. It is well-known that the first-principle force neither makes assumptions such as empirical model nor includes fitting parameter to experimental data, so it is expected to give more realistic results. In the past few decades, first-principle simulations had achieved great success in investigating structural and dynamic properties of liquids. Based on first-principle calculations, we have studied the inherent structures of high-density liquid (HDL) and low-density liquid (LDL) Si and found that the first-order LLPT in metastable liquid Si is a transition between a sp^3 -hybridization LDL and a white-tin-like HDL³⁴. Further, we found that the liquid-liquid critical point (LLCP) is hidden, blended in with the continuous reentrant spinodal of HDL, suggesting that the phase behaviour of metastable liquid Si tends to be a critical-point-free scenario rather than a second-critical-point one based on SW potential³⁵. In this work, based on the prior research, we turn our attention to the relationship between structural order and water-like anomalies (including the well-known first-order LLPT) in metastable liquid silicon.

Results

The density anomaly and the first-order LLPT have been shown in our previous work³⁵. In the studied pressure range from -27.25 to 6.50 kbar, an obvious maximum can be observed along each ρ - T isobar line³⁵ and in T - P phase diagram, the line of density maxima tends to pass through the LLCP, located at $T_c \sim 1420 \pm 10$ K and $P_c \sim -30.5 \pm 1.0$ kbar³⁵, which is different from the result in ref. 17 ($T_c \sim 1120$ K and $P_c \sim 0.60$ GPa). We speculate that such a difference maybe origins from the different potentials adopted. Although the LLPT is proved to exist for SW liquid Si, it has been reported that it strongly depends on the parameters of the potential and an arbitrary variation, albeit small, of the parameters may even lead to its disappearance³⁶. Here, we begin by presenting our results related to the diffusivity anomaly.

Diffusivity anomaly. In Fig. 1, we show our calculated diffusion coefficient D as a function of pressure along eight different isotherms ranging from 1032 to 1800 K. Along each isotherm, the pressure is gradually decreased to the stability limit of HDL and an obvious maximum can be found in the whole temperature range studied here, which marks the upper bound of diffusivity anomaly region. Along each isotherm below T_c , the

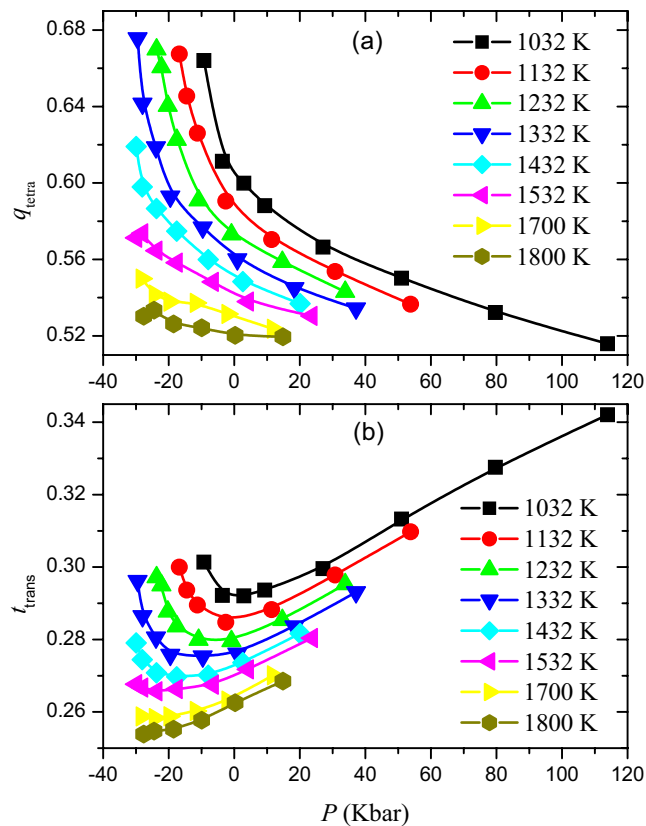


Figure 2. The average tetrahedrality order q_{tetra} (a) and translational order t_{trans} (b) as a function of pressure for different temperatures from 1032 to 1800 K obtained from *ab initio* molecular dynamics simulations of liquid Si. q_{tetra} increases with decreasing pressure. From 1032 to 1700 K, t_{trans} decreases with decreasing pressure and goes through a minimum, which marks an onset of structural anomaly.

locus of diffusivity minimum, which marks the lower bound of diffusivity anomaly region, can not be found and is expected to be located in LDL, where system's dynamics is slow and there is considerable error in computing D and locating the diffusivity minima. So we have not attempted to find this locus in our study. Above T_c , the diffusivity minimum is expected to be located at the HDL-V spinodal because of the larger D in vapor than that in liquid.

Structural anomaly. Figure 2 presents the evolution of structural order (t_{trans} and q_{tetra}) with decreasing pressure along the isotherm. From Fig. 2(a), it can be found that q_{tetra} increases with the decrease of pressure in the simulated temperature range from 1032 to 1800 K, which is in contrast to what is observed for simple fluids and so is termed as structural anomaly. Below T_c , we do not find a maximum of q_{tetra} in our simulated pressure range, which marks the lower bound of structural anomaly region and is expected to be found in LDL. At temperatures above T_c , the maximum of q_{tetra} is expected to be located at the HDL-V spinodal, such as for $T = 1532$ and 1800 K. In Fig. 2(b), in the temperature range from 1032 to 1700 K, t_{trans} decreases with decreasing pressure and goes through a minimum, which marks the upper bound of structural anomaly region as suggested by Errington and Debenedetti⁶. For temperature $T = 1800$ K, the minimum cannot be found until the HDL-V spinodal is encountered.

Excess entropy anomaly. The excess entropy S_{ex} is defined as the entropy of the liquid relative to that of the ideal gas at the same temperature and pressure and can be expressed in terms of an expansion of n -body correlation functions. The first term, namely the two-body contribution S_2 , accounts for a large proportion, such as 80–90% in Lennard-Jones fluids³⁷. Because S_{ex} characterizes the reduction in the number of states (relative to an ideal gas) accessible to a system due to translational interparticle correlations, it can also be thought of as a metric for translational order. Errington and co-workers²⁹ argued that the region in the phase diagram where the excess entropy anomalously increases with decrease in density is also the region where translational order anomaly is observed. Indeed, many studies mentioned above have showed that there also exists a S_{ex} or S_2 anomaly region in the T - ρ phase diagram, where S_{ex} or S_2 anomalously increases with increasing pressure. In this work, we calculated S_2 as a function of pressure along eight different isotherms, shown in Fig. 3. In the temperature range from 1032 to 1432 K, along each isotherm a maximum occurs but the minimum can not be found until the HDL spinodal is encountered, which is expected to be found in LDL. From 1532 to 1800 K, the maximum can not be found until the HDL-V spinodal is encountered.

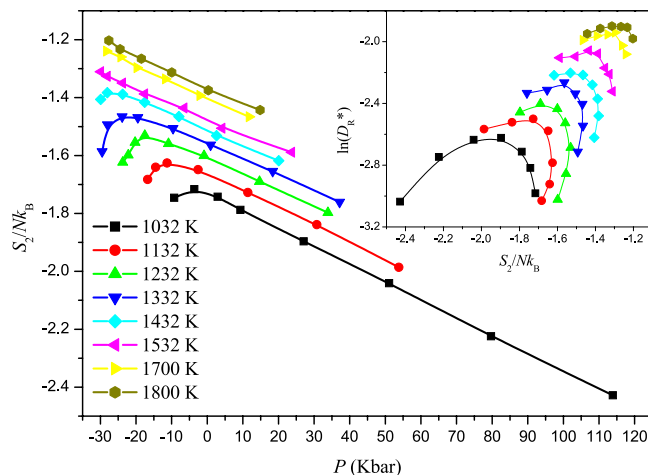


Figure 3. Two-body excess entropy S_2 of liquid Si as function of pressure for different temperatures from 1032 to 1800 K obtained from the pair correlation function. S_2 decreases anomalously with decreasing pressure after going through a maximum, for temperature ranging from 1032 to 1432 K. Inset: The Rosenfeld reduced diffusion coefficient D^* against S_2 for different isotherms. The relation between $\ln(D_R^*)$ and S_2 is not linear, showing a different behaviour from that of Rosenfeld and Dzугutov.

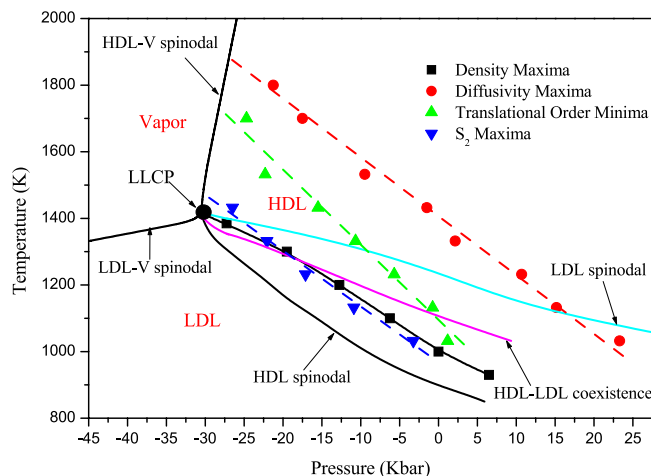


Figure 4. T - P phase diagram of liquid silicon showing the loci of density maxima, diffusivity maxima, translational order minima and two-body excess entropy maxima along other features of the phase diagram.

It is known that there is a strong connection between transport properties of fluids and excess entropy, such as the Rosenfeld scaling relation $D_R^* = a_D \exp(b_D S_E)$ ^{38,39} and the Dzугutov scaling relation $D_z^* = a_0 \exp(S_2)$ ⁴⁰. In the former, the reduced diffusion coefficient $D_R^* = D \rho^{1/3} / (k_B T / m)^{1/2}$, m is the mass of the particle, and ρ is the number density. In the later, $D_z^* = D \Gamma^{-1} \sigma^{-2}$, Γ is the collision frequency and equals $4\sigma^2 g(\sigma) \rho (\pi k_B T / m)^{1/2}$, σ is the hard-sphere diameter, and $g(\sigma)$ is the value of radial distribution function at the constant distance. In Fig. 3 (inset), we also test the scaling relation between D_R^* and S_2 . The relation between D_z^* and S_2 is similar to that presented in Fig. 3 (inset) and not shown here. However, it can be seen that the relation between $\ln(D_R^*)$ and S_2 is not linear, showing a different behaviour from that of Rosenfeld and Dzугutov. Based on the results in Figs 1 and 3, it is due to the fact that along an isotherm, the change of diffusivity with pressure is out of step with that of S_2 versus pressure, which is different from the results in ref. 41 based on a core-softened potential (i.e., a Lennard-Jones potential plus a Gaussian repulsion). Thus we can comment that, based on first-principle calculations, the Rosenfeld and Dzугutov scaling relations are invalid along an isotherm in the anomalous region. This is consistent with that observed in supercooled liquid Si based on SW potential²⁷ and the systems based on some two-scale potentials^{42,43}.

Discussion

Based on the above results, now we turn to discuss the relationship of these anomalies in T - P phase diagram, shown in Fig. 4. The spinodals, LLCP, HDL-LDL coexistence line, and density maxima are obtained from our

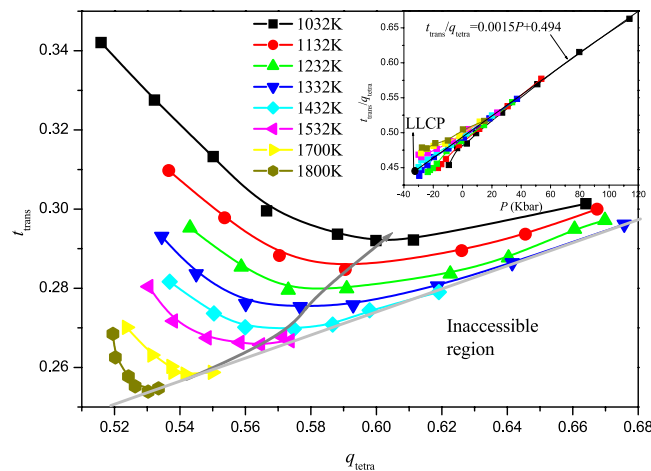


Figure 5. Parametric plot of translational order t_{trans} against tetrahedrality order q_{tetra} for different temperatures from 1032 to 1800 K obtained from *ab initio* molecular dynamics simulations of liquid Si.

q_{tetra} and t_{trans} are not perfectly correlated in the structural anomaly region and with decreasing temperature, the correlation becomes weaker and weaker. Inset: The value of t_{trans}/q_{tetra} against pressure for different isotherms. Along the isotherm of T_c , t_{trans}/q_{tetra} is approximately linear with pressure, $t_{trans}/q_{tetra} = 0.0015P + 0.494$. With decreasing pressure along the isotherm below T_c , t_{trans}/q_{tetra} departs downward from the line until the LLPT occurs, while it is the opposite case above T_c .

previous work³⁵. The LDL-V and the HDL-V spinodals form a continuous liquid-vapor spinodal, which meets the liquid-vapor critical point at higher temperature and higher pressure (not shown here), and the LLCPP seems to just be hidden, blended in with the liquid-vapour spinodal. This is consistent with the critical-point-free scenario suggested by Angell in refs 44 and 45, but is different with the two-critical-point scenario, in which the LLCPP occurs above the liquid-vapor spinodal, similar to that presented in Fig. 2 in ref. 46. From Fig. 4, it can be seen that the region of diffusivity anomaly encloses the region of structural anomaly, which in turn encloses the region of density anomaly. This result is consistent with that of SW Si²⁷ and is similar to that of BKS SiO₂²¹ but different from that of SPC/E model of water⁶. In addition, it should be noticed that the two-body excess entropy anomaly region does not enclose the diffusivity anomaly as it does in a fluid interacting through a two-scale potential²⁹. On the contrary, it is also included in the structural anomaly region determined by the translational order minima, with the S_2 maxima line going across the density maxima line. So S_2 anomaly can not be used as a criteria of structural anomaly to capture the region of diffusivity and density anomalies. This may originate in the fact that the relation between $\ln(D_R^*)$ and S_2 shows an anomalous behaviour, presented in Fig. 3 (inset).

Recently, it has been shown for the two-scale potential that different criteria of structural anomaly can lead to completely different results⁴⁷. It was found that the structural anomaly region determined by the S_{ex} anomaly lies much deeper than that obtained from the approximate S_2 anomaly. This means that the structural anomaly calculated from the S_{ex} criterion may be inside the density anomaly shown in Fig. 4, which is in contradiction with the thermodynamically consistent relation that the region of anomalous density is always inside the region of anomalous S_{ex} ⁴⁷. We think that there are two main reasons accountable for this. The first is that there is a larger error in determining the temperature of density maximum, the higher the pressure, the greater the error (see Fig. 3 in ref. 35). The second is that, although the structural anomaly region determined by S_{ex} lies much deeper than that obtained from S_2 for the two-scale potential⁴⁷, it is not necessarily the case for other systems. For example, in SW Si the onset pressure of S_{ex} anomaly is the same with that of S_2 anomaly and at lower temperatures the former is even slightly larger than the latter (see Fig. 12(a) in ref. 27).

As mentioned above, in the structural anomaly region, a strong correlation between q_{tetra} and t_{trans} exists in rigid-body model potentials for water and SW liquids (in a limited range of tetrahedrality strength), but not in ionic melts. Here, we also present the correlation between q_{tetra} and t_{trans} , shown in Fig. 5. Similar to water, our Si order parameter map also suggests an inaccessible region in the high- q_{tetra} , low- t_{trans} quadrant. In other words, for any given value of t_{trans} , there is a maximum value of q_{tetra} that the system can attain. Likewise, for any given value of q_{tetra} , there is a minimum attainable t_{trans} . However, in the structural anomaly region, q_{tetra} and t_{trans} do not collapse onto a single line, as is the case for water, suggesting that q_{tetra} and t_{trans} are not perfectly correlated. With the decrease of temperature, the correlation becomes weaker and weaker. These results are different from those observed in SW Si²⁵⁻²⁷, in which q_{tetra} and t_{trans} are perfectly correlated in the structural anomaly region. This degree of independence renders it impossible to use the isotaxis line to quantify the degree of structural order needed for the water-like anomalies to occur.

To obtain the relationship between structural order and the LLPT, in Fig. 5 (inset), we also present the value of t_{trans}/q_{tetra} as a function of pressure. It can be found that at higher pressure above 20 kbar, t_{trans}/q_{tetra} is independent of temperature and is linear with pressure. Along the isotherm of T_c , t_{trans}/q_{tetra} can be approximately expressed as a linear relationship with pressure, $t_{trans}/q_{tetra} = 0.0015P + 0.494$. With decreasing pressure along the isotherm below T_c , t_{trans}/q_{tetra} departs downward from the straight line until the LLPT is encountered, while it is the opposite case above T_c until the liquid-vapor transition occurs.

In summary, first-principle molecular dynamics are performed for the first time to study the relationship between structural order and water-like anomalies in metastable liquid Si. Our results show that in T - P phase diagram, there indeed exists a structural anomaly region, which encloses the density anomaly but not the diffusivity anomaly. This is consistent with that of SW Si and BKS SiO₂ but different from that of SPC/E model of water. Two-body excess entropy anomaly can neither capture the diffusivity, structural, and density anomalies, as it can in a fluid interacting through a two-scale potential. Moreover, in the structural anomaly region, q_{tetra} and t_{trans} are not perfectly correlated, which is different from that in SW Si and renders it impossible to use the isotaxis line to quantify the degree of structural order needed for water-like anomalies to occur. Along the isotherm of critical temperature T_c , t_{trans}/q_{tetra} is approximately linear with pressure, $t_{trans}/q_{tetra} = 0.0015P + 0.494$. With decreasing pressure along the isotherm below T_c , t_{trans}/q_{tetra} departs downward from the line until the liquid-liquid phase transition occurs, while it is the opposite case above T_c .

Methods

Ab initio molecular dynamics. The simulations are performed by the Vienna *ab initio* simulation package (VASP)^{48,49} together with projector augmented wave (PAW) potential^{50,51} in the Perdew-Burke-Ernzerhof generalized gradient approximation (PBE-GGA)⁵². A system of 216 Si atoms in a cubic supercell with periodical boundary conditions is used. The electronic wave functions are expanded in the plane wave basis set with an energy cutoff of 245 eV and a Pulay stress⁵³ of 1.65 kbar is added to offset the incompleteness of the plane wave basis set. Only Γ -point is used to sample the supercell Brillouin zone. The canonical (NVT) ensemble simulations are performed with a Nosé thermostat for temperature control⁵⁴. Newton's equations of motion are integrated using Verlet's algorithm in the velocity form with a time step of 2 fs.

The initial configuration, a diamond cubic crystal structure with the volume of 17.2 Å³/atom, is heated up to 2000 K. After a run of 20 ps with constant temperature 2000 K, the system arrives at an equilibrium liquid state. The temperature is then gradually reduced to the desired temperature with a cooling rate of 0.5×10^{15} K/s and a subsequent run of 15–20 ps is performed at this temperature. Then, the simulations are performed with a series of successively larger volumes along the isotherm up to the stability limit of HDL. At each simulation point, we performed a simulation about 15–30 ps. It is found that for HDL 5 ps is enough to equilibrate and the statistical averages are collected for the rest of the simulation. Along each isotherm, the end point of the previous simulation is scaled to obtain the initial conditions for the next.

Calculation of self-diffusion coefficient D . The self-diffusion coefficient D in liquids was obtained by fitting the long time mean square displacement (MSD). MSD is defined as

$$\Delta \vec{r}^2 = \frac{1}{N} \sum_{i=1}^N [\vec{r}_i(t) - \vec{r}_i(t_0)]^2 \quad (1)$$

where \vec{r}_i is the coordinates of atom i , t_0 is an arbitrary origin of time. The diffusion coefficient D can be calculated by

$$D = \frac{1}{6} \lim_{t \rightarrow \infty} \frac{\Delta \vec{r}^2}{t} \quad (2)$$

Structural order parameters. The translational order parameter t_{trans} is defined as

$$t_{trans} = \frac{\int_0^{\xi_c} |g(\xi) - 1| d\xi}{\xi_c} \quad (3)$$

where $\xi = r\rho^{1/3}$ is the distance r between two Si atoms divided by the mean separation between a pair of atoms at the given number density ρ ; $g(\xi)$ is the pair correlation function, and ξ_c is a cutoff distance beyond which the system's pair correlation function cannot be distinguished from its asymptotic value of 1. In this work, ξ_c is chosen to be $9.0 \times \rho^{1/3}$. Scaled coordinates are used so that the above integral sums over an equivalent number of coordinate shells at each density. For an ideal gas, since $g(r) = 1.0$, t_{trans} is zero and for a crystal, it has a finite value depending on the cutoff distance. In the liquid phase, t_{trans} will have a value in between that of the ideal gas and a crystal. The tetrahedrality order parameter q_{tetra} is defined as

$$q_{tetra} = 1 - \frac{3}{8} \sum_{j=1}^3 \sum_{k=j+1}^4 \left(\cos \psi_{jk} + \frac{1}{3} \right)^2 \quad (4)$$

where ψ_{jk} is the angle formed by the lines joining a reference atom i and its nearest neighbours j and k . The average q_{tetra} varies between 0 (in the case of an ideal gas) and 1 (in the case of a cubic diamond crystal).

Excess entropy. Excess entropy S_E is defined as $S_E = S - S_{id}$, where S is the total entropy of the system and S_{id} is the entropy of an ideal gas system. In present work, we calculate the two body approximation (S_2) to S_E from the pair correlation function, and is given by

$$S_2/Nk_B = -2\pi\rho \int_0^\infty \{g(r)\ln(g(r)) - [g(r) - 1]\} r^2 dr \quad (5)$$

where $g(r)$ is the pair correlation function, and ρ is the number density.

References

- Angell, C. A., Bressel, R. D., Hemmati, M., Sare, E. J. & Tucker, J. C. Water and its anomalies in perspective: tetrahedral liquids with and without liquid-liquid phase transitions. *Phys. Chem. Chem. Phys.* **2**, 1559–1566 (2000).
- Prielmeier, F. X., Lang, E. W., Speedy, R. J. & Lüdemann, H.-D. Diffusion in supercooled water to 300 MPa. *Phys. Rev. Lett.* **59**, 1128–1131 (1987).
- Angell, C. A., Finch, E. D., Woolf, L. A. & Bach, P. Spin-echo diffusion coefficients of water to 2380 bar and -20°C . *J. Chem. Phys.* **65**, 3063–3066 (1976).
- Poole, P. H., Hemmati, M. & Angell, C. A. Comparison of thermodynamic properties of simulated liquid silica and water. *Phys. Rev. Lett.* **79**, 2281–2284 (1997).
- Scala, A., Starr, F. W., La Nave, E., Sciortino, F. & Stanley, H. E. Configurational entropy and diffusivity of supercooled water. *Nature* **406**, 166–169 (2000).
- Errington, J. R. & Debenedetti, P. G. Relationship between structural order and the anomalies of liquid water. *Nature* **409**, 318–321 (2001).
- Poole, P. H., Sciortino, F., Essmann, U. & Stanley, H. E. Phase behaviour of metastable water. *Nature* **360**, 324–328 (1992).
- Poole, P. H., Grande, T., Angell, C. A. & McMillan, P. F. Polymorphic phase transitions in liquids and glasses. *Science* **275**, 322–323 (1997).
- Azouzi, M. E. M., Ramboz, C., Lenain, J.-F. & Caupin, F. A coherent picture of water at extreme negative pressure. *Nature Phys.* **9**, 38–41 (2013).
- Pallares, G. *et al.* Anomalies in bulk supercooled water at negative pressure. *Proc. Natl. Acad. Sci. USA* **111**, 7936–7941 (2014).
- Palmer, J. C. *et al.* Metastable liquid-liquid transition in a molecular model of water. *Nature* **510**, 385–388 (2014).
- Sastry, S. & Angell, C. A. Liquid-liquid phase transition in supercooled silicon. *Nature Mater.* **2**, 739–743 (2003).
- Jakse, N. & Pasturel, A. Liquid-Liquid phase transformation in silicon: Evidence from first-principles molecular dynamics simulations. *Phys. Rev. Lett.* **99**, 205702 (2007).
- Ganesh, P. & Widom, M. Liquid-liquid transition in supercooled silicon determined by first-principles simulation. *Phys. Rev. Lett.* **102**, 075701 (2009).
- Beye, M., Sorgenfrei, F., Schlotter, W. F., Wurth, W. & Föhlisch, A. The liquid-liquid phase transition in silicon revealed by snapshots of valence electrons. *Proc. Natl. Acad. Sci. USA* **107**, 16772–16776 (2010).
- Sastry, S. Illuminating liquid polymorphism in silicon. *Proc. Natl. Acad. Sci. USA* **107**, 17063–17064 (2010).
- Vasishth, V. V., Saw, S. & Sastry, S. Liquid-liquid critical point in supercooled silicon. *Nature Phys.* **7**, 549–553 (2011).
- Sciortino, F. Liquid-liquid transitions silicon in silico. *Nature Phys.* **7**, 523–524 (2011).
- Truskett, T. M., Torquato, S. & Debenedetti, P. G. Towards a quantification of disorder in materials: Distinguishing equilibrium and glassy sphere packings. *Phys. Rev. E* **62**, 993–1001 (2000).
- Chau, P.-L. & Hardwick, A. J. A new order parameter for tetrahedral configurations. *Mol. Phys.* **93**, 511–518 (1998).
- Shell, M. S., Debenedetti, P. G. & Panagiotopoulos, A. Z. Molecular structural order and anomalies in liquid silica. *Phys. Rev. E* **66**, 011202 (2002).
- Agarwal, M. & Chakravarty, C. Water-like structural and excess entropy anomalies in liquid beryllium fluoride. *J. Phys. Chem. B* **111**, 13294–13300 (2007).
- Jabes, B. S., Agarwal, M. & Chakravarty, C. Tetrahedral order, pair correlation entropy, and waterlike liquid state anomalies: Comparison of GeO_2 with BeF_2 , SiO_2 , and H_2O . *J. Chem. Phys.* **132**, 234507 (2010).
- Agarwal, M., Mohammad, P. A. & Chakravarty, C. Thermodynamic, diffusional, and structural anomalies in rigid-body water models. *J. Phys. Chem. B* **115**, 6935–6945 (2011).
- Jabes, B. S., Nayar, D., Dhabal, D., Molinero, V. & Chakravarty, C. Water and other tetrahedral liquids: order, anomalies and solvation. *J. Phys.: Condens. Matter* **24**, 284116 (2012).
- Nayar, D. & Chakravarty, C. Water and water-like liquids: relationships between structure, entropy and mobility. *Phys. Chem. Chem. Phys.* **15**, 14162–14177 (2013).
- Vasishth, V. V., Mathew, J., Sengupta, S. & Sastry, S. Nesting of thermodynamic, structural, and dynamic anomalies in liquid silicon. *J. Chem. Phys.* **141**, 124501 (2014).
- Sharma, R., Chakraborty, S. N. & Chakravarty, C. Entropy, diffusivity, and structural order in liquids with waterlike anomalies. *J. Chem. Phys.* **125**, 204501 (2006).
- Errington, J. R., Truskett, T. M. & Mittal, J. Excess-entropy-based anomalies for a waterlike fluid. *J. Chem. Phys.* **125**, 244502 (2006).
- Yan, Z., Buldyrev, S. V., Giovambattista, N. & Stanley, H. E. Structural order for one-scale and two-scale potentials. *Phys. Rev. Lett.* **95**, 130604 (2005).
- Krekelberg, W. P., Mittal, J., Ganesan, V. & Truskett, T. M. How short-range attractions impact the structural order, self-diffusivity, and viscosity of a fluid. *J. Chem. Phys.* **127**, 044502 (2007).
- Oliveira, A. B. de, Franzese, G., Netz, P. A. & Barbosa, M. C. Waterlike hierarchy of anomalies in a continuous spherical shouldered potential. *J. Chem. Phys.* **128**, 064901 (2008).
- Fomin, Y. D., Tsiok, E. N. & Ryzhov, V. N. Silicalike sequence of anomalies in core-softened systems. *Phys. Rev. E* **87**, 042122 (2013).
- Zhao, G., Yu, Y. J. & Tan, X. M. Nature of the first-order liquid-liquid phase transition in supercooled silicon. *J. Chem. Phys.* **143**, 054508 (2015).
- Zhao, G. *et al.* Phase behavior of metastable liquid silicon at negative pressure: Ab initio molecular dynamics. *Phys. Rev. B* **93**, 140203(R) (2016).
- Beaucage, P. & Mousseau, N. Liquid-liquid phase transition in Stillinger-Weber silicon. *J. Phys. Condens. Matter* **17**, 2269–2279 (2005).
- Borzsk, I. & Baranyai, A. On the convergence of Green's entropy expansion. *Chem. Phys.* **165**, 227–230 (1992).
- Rosenfeld, Y. Relation between the transport coefficients and the internal entropy of simple systems. *Phys. Rev. A* **15**, 2545–2549 (1977).
- Rosenfeld, Y. A quasi-universal scaling law for atomic transport in simple fluids. *J. Phys. Condens. Matter* **11**, 5415–5427 (1999).
- Dzugutov, M. A universal scaling law for atomic diffusion in condensed matter. *Nature* **381**, 137–139 (1996).
- Mittal, J., Errington, J. R. & Truskett, T. M. Relationship between thermodynamics and dynamics of supercooled liquids. *J. Chem. Phys.* **125**, 076102 (2006).
- Fomin, Y. D. & Ryzhov, V. N. Breakdown of excess entropy scaling for systems with thermodynamic anomalies. *Phys. Rev. E* **81**, 061201 (2010).
- Fomin, Y. D., Tsiok, E. N. & Ryzhov, V. N. Core-softened system with attraction: Trajectory dependence of anomalous behavior. *J. Chem. Phys.* **135**, 124512 (2011).
- Angell, C. A. Insights into phase of liquid water from study of its unusual glass-forming properties. *Science* **319**, 582–587 (2008).
- Angell, C. A. Supercooled water two phases. *Nat. Mater.* **13**, 673–675 (2014).
- Truskett, T. M., Debenedetti, P. G., Sastry, S. & Torquato, S. A single-bond approach to orientation-dependent interactions and its implications for liquid water. *J. Chem. Phys.* **111**, 2647–2656 (1999).
- Fomin, Y. D., Ryzhov, V. N., Klumov, B. A. & Tsiok, E. N. How to quantify structural anomalies in fluids? *J. Chem. Phys.* **141**, 034508 (2014).
- Kresse, G. & Hafner, J. Ab initio molecular dynamics for liquid metals. *Phys. Rev. B* **47**, R558–R561 (1993).

49. Kresse, G. & Furthmüller, J. Efficient iterative schemes for *ab initio* total-energy calculations using a plane-wave basis set. *Phys. Rev. B* **54**, 11169–11186 (1996).
50. Blöchl, P. E. Projector augmented-wave method. *Phys. Rev. B* **50**, 17953–17979 (1994).
51. Kresse, G. & Joubert, D. From ultrasoft pseudopotentials to the projector augmented-wave method. *Phys. Rev. B* **59**, 1758–1775 (1999).
52. Perdew, J. P. Burke, K. & Ernzerhof, M. Generalized gradient approximation made simple. *Phys. Rev. Lett.* **77**, 3865–3868 (1996).
53. Francis, G. P. & Payne, M. C. Finite basis set corrections to total energy pseudopotential calculations. *J. Phys.: Condens. Matter* **2**, 4395–4404 (1990).
54. Nose, S. A unified formulation of the constant temperature molecular dynamics methods. *J. Chem. Phys.* **81**, 511–519 (1984).

Acknowledgements

This work is supported by Natural Science Foundation of Shandong Province of China (Grant Nos ZR2012AQ014 and ZR2014AP014) and National Natural Science Foundation of China (Grant No. 11504154).

Author Contributions

G.Z., Y.J.Y., M.C.D. and X.G.Z. conducted MD simulations at School of Physics and Optoelectronic Engineering in Ludong University; G.Z., J.L.Y. and H.Y.W. analysed the data; G.Z. wrote the paper and J.L.Y. revised it.

Additional Information

Competing financial interests: The authors declare no competing financial interests.

How to cite this article: Zhao, G. *et al.* Relationship between structural order and water-like anomalies in metastable liquid silicon: *Ab initio* molecular dynamics. *Sci. Rep.* **7**, 39952; doi: 10.1038/srep39952 (2017).

Publisher's note: Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.



This work is licensed under a Creative Commons Attribution 4.0 International License. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in the credit line; if the material is not included under the Creative Commons license, users will need to obtain permission from the license holder to reproduce the material. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>

© The Author(s) 2017