Since the double bond line of the 1.3.cyclohexadiene is more displaced towards smaller frequencies than the known line at 1584 cm.-1 in benzene, and since it is near the latter in spite of the enormous differences in the saturation characteristics of the two compounds, the interpretation of the line 1584 cm.-1 of benzene as being due to a double ethylenic bond in the ordinary meaning of organic chemistry would appear to be very doubtful.

G. B. BONINO.

R. MANZONI ANSIDEI.

Laboratorio di Chimica-Fisica della R. Università, Bologna.

¹ Mem. Acc. Sci. Ist. Bologna Sess., May 27, 1934. ⁹ J. Chem. Soc., 85, 1403; 1904. ⁹ Ber., 45, 809; 1912. ⁴ Ber., 45, 1464; 1912.

Crystal Structure of some Alkali Tungsten Chlorides

ABOUT twenty years ago, O. Olsson-Collenberg¹ synthesised a series of alkali tungsten chlorides with trivalent tungsten of the general formula M₃W₂Cl₉. Later, Collenberg and Sandved² found that water solutions of these compounds contain the complex ion W₂Cl₉. An X-ray analysis of these chlorides has now shown that this ion is present also in their crystals.

The ammonium, potassium, rubidium, cæsium and thallium compounds are all isomorphous and crystallise in the space-group C_{ch}^2 . The unit cell of K₃W₂Cl₉ has the dimensions $a = 7 \cdot 16 \text{ A.};$ $c = 16 \cdot 16$ A. and contains two molecules. Using Wyckoff's notation, the atomic positions are :

2 K at 2(a), 6 Cl at 6(h), $(u_3 = 0.45, v_3 = 0.44)$. 4 K at 4(f), $(u_1 = 0.31)$. 12 Cl at 12(i), (x = 0.12), y = 0.35, z = 0.16). 4 W at 4(f), $(u_2 = 0.076)$.

In this structure the W2Cl, groups have the con-

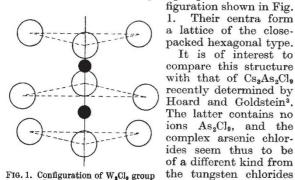


FIG. 1. Configuration of W_1Cl_9 group in $M_3W_2Cl_9$. \bigcirc , Cl; \bullet , W.

position. A complete report of the structure determination will be given in the immediate future, and the investigation will be extended to embrace also the tungsten chlorides with metal-ammonia and partly organic cations.

of

CYRILL BROSSET.

analogous

Their centra form

It is of interest to

Institute of General and Inorganic Chemistry, University, Stockholm. March 1.

¹ Thesis, Uppsala, 1914. ⁸ Z. anorg. allg. Chemie, **130**, 1; 1923. ⁹ J. Chem. Phys., **3**, 117; 1935.

The Spinels and the Cubic Sodium-Tungsten Bronzes as New Examples of Structures with Vacant Lattice Points

X-RAY studies, carried out in this Institute, have shown that when the spinel, MgO.Al₂O₃, dissolves Al₂O₃, the oxygen excess is caused by the occurrence of vacant points in the metal lattices. In accordance with this, γ -Al₂O₃, the unstable limit of these solid solutions, represents a spinel lattice where 1/9 of the metal positions are vacant.

In the same way it has been shown that when Fe_3O_4 is oxidised to γ - Fe_2O_3 , this process is accompanied by the occurrence of vacant points in the Fe lattice so that only 8/9 of them are occupied in γ -Fe₂O₃. At the same time the lattice dimensions decrease. The presence of vacant points has been definitely shown by measurements of both the intensities of the interferences and the densities of the preparations.

The general formula of the sodium-tungsten bronzes has been shown to be Na_xWO_3 . In the gold yellow bronze, x is 1 and the cube edge = 3.850 A. This bronze contains W^{+5} ions and crystallises in a complete perowskite lattice. The deepening of the colour from yellow through red to blue is accompanied by a continual decrease in sodium content and dimensions. With decreasing values of x, vacant points occur in the original Na lattice and in the blue bronze (x = 0.3-0.4, a = 3.813 A.), about two thirds of the original Na positions are empty. At the same time, W^{+6} ions occur and the increasing amount of these ions is probably the cause of the deepening of the colour.

The above 'subtraction phases' represent, quite as much as the 'addition' or 'interstitial' phases, solid solutions with a variable number of atoms per unit cell. It is a mere matter of convenience if such a phase is termed a 'subtraction' or an 'addition' phase. In all cases where a variable number of atoms has been found, the structure is built up by large atoms or ions (in most cases anions, and especially oxygen ions). The atoms, which vary in number, are always comparatively small and placed in the interstices of the skeleton formed by the large atoms. A variation of their number is possible if the structure is of a non-polar type (hydrides, carbides, nitrides of many transition elements), if ions are substituted by other ions with another charge (MgO.Al₂O₃ $\rightarrow \gamma$ -Al₂O₃, tremolite \rightarrow hornblende, β -cristobalite $\rightarrow \alpha$ -carnegieite, $AgI \rightarrow Ag_2HgI_4$), or if the lattice contains ions which are able to change their charge (especially in lattices containing transition elements, for example, $Fe_3O_4 \rightarrow \gamma - Fe_2O_3$, the cubic Na-W-bronzes).

More detailed reports of these investigations will be published elsewhere.

GUNNAR HÄGG.

Institute of General and Inorganic Chemistry, University, Stockholm. Feb. 28.

Bio-Electric Transients during Fertilisation

IN 1909 R. S. Lillie¹ suggested that the activation of the unfertilised egg by a spermatozoon or by a parthenogenetic agent might involve the temporary depolarisation of the cell surface, the process being similar to that observed in stimulated nerve or muscle. This so-called 'physical' theory of fertilisation and parthenogenesis has been elaborated by Gray²,

com-