

ARTICLE

Received 16 Feb 2016 | Accepted 12 Jul 2016 | Published 9 Sep 2016

DOI: 10.1038/ncomms12543

OPEN

Mass production of two-dimensional oxides by rapid heating of hydrous chlorides

Chunsong Zhao¹, Haitian Zhang¹, Wenjie Si¹ & Hui Wu¹

Two-dimensional (2D) nanoscale oxides have attracted research interest owing to their electronic, magnetic optical and catalytic properties. If they could be manufactured on a large scale, 2D oxides would be attractive for applications ranging from electronics to energy conversion and storage. Herein, we report facile fabrication of oxide nanosheets by rapid thermal annealing of corresponding hydrous-chloride compounds. By heating $\text{CrCl}_3 \cdot 6\text{H}_2\text{O}$, $\text{ZrOCl}_2 \cdot 8\text{H}_2\text{O}$, $\text{AlCl}_3 \cdot 6\text{H}_2\text{O}$ and $\text{YCl}_3 \cdot 6\text{H}_2\text{O}$ crystals as precursors, we immediately collect large quantities of ultrathin Cr_2O_3 , ZrO_2 , Al_2O_3 and Y_2O_3 nanosheets, respectively. The formation of layered nanosheets relies on exfoliation driven by rapid evaporation of water and/or other gas molecules generated under annealing. Our route allows simple, efficient and inexpensive production of 2D oxides. As a demonstration, we evaluate Cr_2O_3 nanosheets prepared by our method as anodes in lithium-ion batteries and find superior performance in comparison with their microcrystalline counterparts.

¹State Key Laboratory of New Ceramics and Fine Processing, School of Materials Science and Engineering, Tsinghua University, Beijing 100084, China. Correspondence and requests for materials should be addressed to H.W. (email: huiwu@tsinghua.edu.cn).

Materials of small geometrical dimensions have been successfully used in many technological applications because of their size-dependent physical and chemical properties^{1–4}. In particular, the remarkable properties of graphene have renewed interest in inorganic two-dimensional (2D) materials with unique electronic, mechanical and optical attributes^{5–10}. Beyond graphene, other 2D materials, such as transition metal dichalcogenides (for example, MoS₂ and WS₂), graphene analogues (for example, boron nitride), black phosphorus and some transition metal oxides (TMOs) (for example, MnO₂ and TiO₂) have attracted great attention because of their important applications in sensors, electrochemical catalysts and battery electrodes^{11–18}.

Scientists have reported multiple methods of preparing 2D nanosheets. One of the most common strategies used to prepare 2D nanolayers is mechanical or chemical exfoliation; some layered materials, such as BN, MoS₂, MoSe₂, MoTe₂ and TaSe, which have strong in-plane chemical bonds and weak out-of-plane van der Waals interactions, are easily exfoliated normal to the in-plane direction under extreme conditions^{17,19,20}. A family of 2D nanosheets, labelled MXene, was produced through selective etching of the A-group atoms from MAX-phase solids such as Ti₃AlC₂ (refs 21–24). Numerous 2D metal oxide nanosheets of materials such as TiO₂, ZnO and MnO₂ can be fabricated by self-assembly or other wet chemistry methods^{16,25}. Some nanosheets without layered crystal structures can also be synthesized from starting materials such as metals. For example, researchers have prepared ultrathin metal nanosheets from materials such as rhodium and gold via solvothermal and wet chemistry methods, respectively^{26,27}. Although researchers have studied many methods to synthesize 2D materials, these methods are usually complex, expensive and inefficient. The lack of chemical or physical approaches to synthesizing ultrathin nanosheets in large quantities has limited further development and applications of these 2D materials. Therefore, a simple, fast and economical method for the mass production of 2D nanomaterials remains an interesting challenge²⁸.

In the liquid exfoliation method, ions or molecules are usually intercalated between layers to weaken the out-of-plane van der Waals interactions before the layer-structured materials are exfoliated^{29–32}. Some layer-structured minerals with molecules between the layers also exist in nature, such as vermiculite. Vermiculite comprises a group of 2:1 phyllosilicate clay minerals that consist of hydrated sheet silicates that contain layers of water molecules within their internal structure^{33,34}. When subjected to heat, vermiculite has the unusual property of expanding (commercial varieties can expand 8–20 times or more) because of the interlamellar generation of steam^{33,34}. Accordingly, exfoliation of thin vermiculite layers occurs when the mineral is heated sufficiently (Supplementary Fig. 1).

Herein, inspired by the expansion and exfoliation that occur on heating of vermiculite, we apply rapid annealing to hydrous chlorides and oxychlorides and observe similar, large volume expansions. Using this approach, we successfully obtain sheets of layered oxides, including Cr₂O₃, ZrO₂, Al₂O₃ and Y₂O₃. The thinnest of the exfoliated oxide layers was ~1.2 nm thick (Supplementary Fig. 2) and spans several micrometres. Importantly, oxide nanosheets can be generated in large quantities by this rapid process. As a demonstration, Cr₂O₃ synthesized by our technique was evaluated as an anode material in the Li-ion batteries. The 2D structure provides a larger and more stable surface area than do microparticles, enhancing capacities accessible at useful rates. Moreover, Cr₂O₃ nanosheets show strong adhesion to the copper foil, even without binder, which enhances mechanical stability of electrodes during cycling.




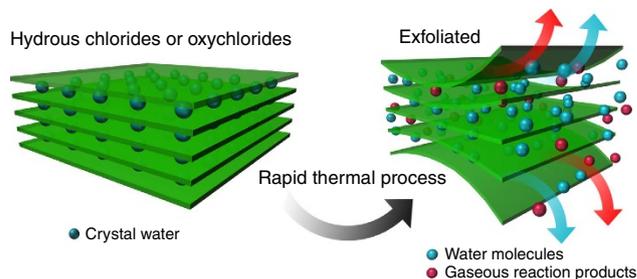


Figure 1 | Material synthesis. Schematic of the exfoliation of hydrous chlorides. During heating, large quantities of gas (water or other gaseous reaction products) are released. The force generated by gas generation and expansion leads to the exfoliation of the hydrates.

Results

Materials design and synthesis. Some metal oxide solids cannot be synthesized by direct exfoliation methods because they do not have layered crystal structures. However, some chlorides or oxychlorides of the corresponding metal oxides possess layered structures. In addition, the chlorides and oxychlorides usually have water in the crystal lattice, such as CrCl₃·6H₂O, ZrOCl₂·8H₂O, AlCl₃·6H₂O and YCl₃·6H₂O. When the hydrous chlorides or oxychlorides are heated under dry conditions or/and at high temperatures, the following four chemical reactions occur:



During the dehydration and hydrolysis reactions in the rapid thermal process, a large quantity of gaseous reaction products, such as H₂O and HCl, are produced within a short time, generating large pressures. The forces caused by gas evolution can drive exfoliation of layered solid products such as MCl_x. The produced layers can further react spontaneously to form M₂O_x nanosheets (Fig. 1a). Accordingly, we are able to obtain 2D metal oxide nanosheets from hydrated precursors via a rapid thermal process.

Microwave heating is a common method used to heat or dry materials. The energy of the microwaves can be absorbed by water in a process called dielectric heating³⁵, which is rapid and uniform. Accordingly, we used microwave heating to treat the CrCl₃·6H₂O precursor. The morphology of the CrCl₃·6H₂O particles is shown in a scanning electron microscopy (SEM) image (Supplementary Fig. 3); the particles were not layered nanosheets. The CrCl₃·6H₂O was placed in a glass bottle and then heated in a domestic microwave oven for 5 min. After heating, water was observed inside the bottle cap. The CrCl₃·6H₂O in the glass bottle underwent a very large volume expansion (Fig. 2a and Supplementary Movie 1). These observed phenomena were consistent with our expectations. The material obtained from CrCl₃·6H₂O through microwave heating is deliquescent and must be stored under dry conditions. We used SEM and transmission electron microscopy (TEM) to examine the sample (Fig. 2b,c). Typical 2D nanosheets with relatively large areas were observed. The diffraction pattern (Fig. 2c) indicated that the sample was amorphous. We used energy-dispersive spectroscopy (EDS) to detect the chemical elements in the sample. The resulting atomic ratio for Cr, O and Cl of 1:1:1 suggested that the sample was CrOCl (Supplementary Fig. 4a). The reason that we did not obtain Cr₂O₃ was likely insufficient

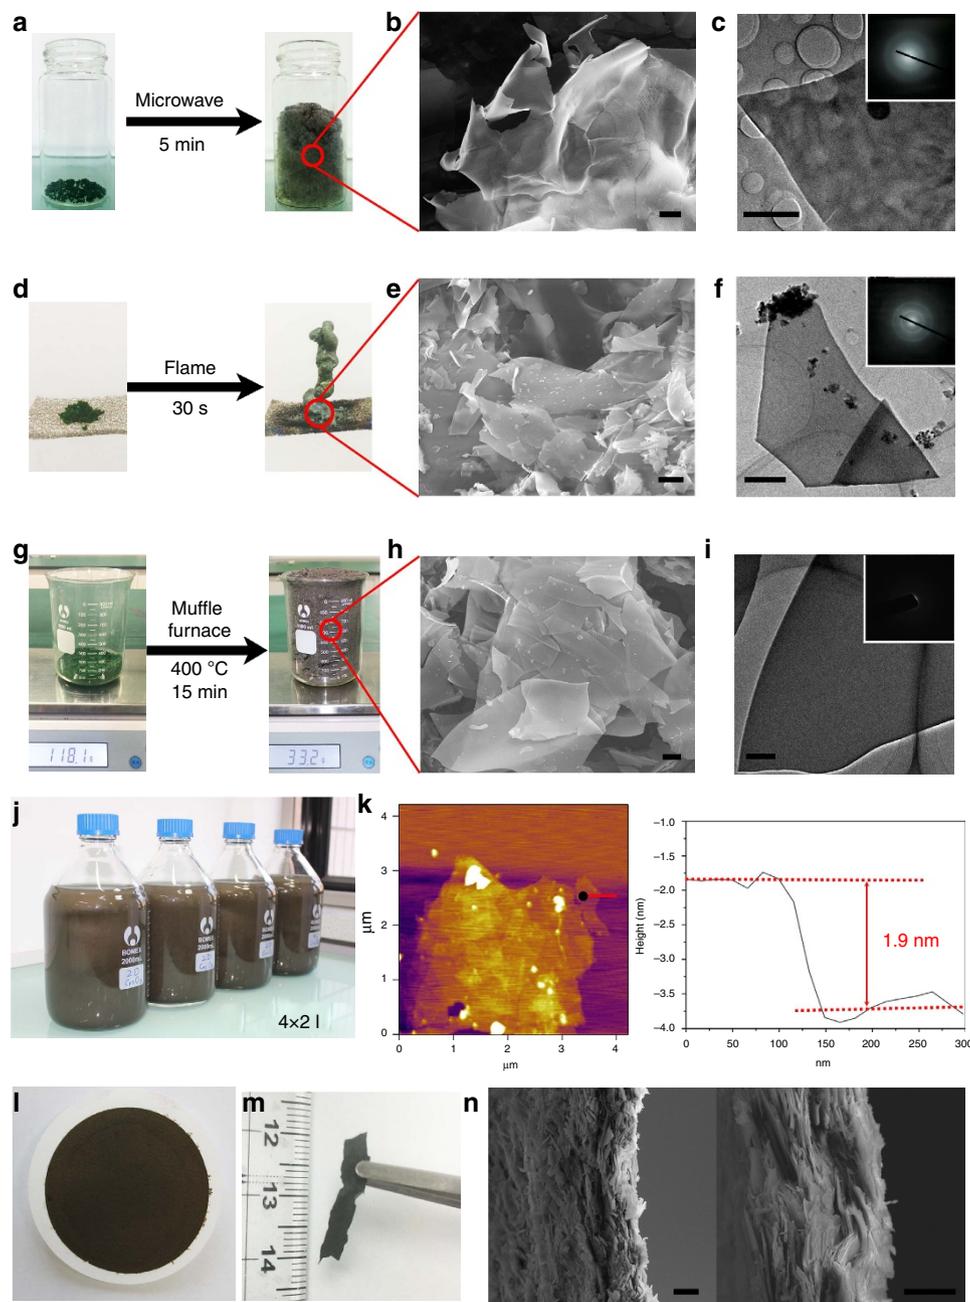


Figure 2 | Nanosheets produced from chromium trichloride hexahydrate. (a) A $\text{CrCl}_3 \cdot 6\text{H}_2\text{O}$ sample before (left of panel) and after (right of panel) microwave heating. (b) SEM and (c) TEM images (inset, corresponding electron diffraction pattern) correspond to the sample in a. (d) A $\text{CrCl}_3 \cdot 6\text{H}_2\text{O}$ sample before (left of panel) and after (right of panel) flame heating. (e) SEM and (f) TEM images (inset, corresponding electron diffraction pattern) correspond to the sample in d. (g) A $\text{CrCl}_3 \cdot 6\text{H}_2\text{O}$ sample before (left of panel) and after (right of panel) being heated in the muffle furnace. (h) SEM and (i) TEM images (inset, corresponding electron diffraction pattern) correspond to the $\text{CrCl}_3 \cdot 6\text{H}_2\text{O}$ sample in g. (j) A large quantity (8 l) of the 2D Cr_2O_3 dispersion solution. (k) AFM characterization of the Cr_2O_3 obtained by alcohol lamp heating. (l) The 2D Cr_2O_3 film produced by vacuum filtration. (m) The free-standing 2D Cr_2O_3 film. (n) Cross-sectional SEM images of the free-standing 2D Cr_2O_3 film. Scale bars, 2 μm (b,c), 5 μm (e), 500 nm (f,i) and 10 μm (h,n).

heating power of the household microwave oven, leading to partial Cl removal. Although we collected CrOCl nanosheets using microwave heating, we investigated other rapid heating methods that could be used to obtain the oxides from $\text{CrCl}_3 \cdot 6\text{H}_2\text{O}$.


The most immediate heating method is using a flame. The flame of an alcohol lamp is a dry environment and a high temperature ($\sim 500^\circ\text{C}$). We placed $\text{CrCl}_3 \cdot 6\text{H}_2\text{O}$ crystals on nickel foam and heated the crystals in the flame of an alcohol

lamp for 30 s. We again observed marked volume expansion (Fig. 2d). Most of the obtained sample was insoluble in water. Typical 2D nanosheets with large area were observed by SEM (Fig. 2e) and TEM characterization (Fig. 2f). The nanosheets were amorphous according to the diffraction pattern (Fig. 2f) and the high-resolution TEM (HRTEM) image (Supplementary Fig. 5a). EDS analysis (Supplementary Fig. 5b) indicated that the nanosheets were mainly composed of Cr and O, but Cl was also present. On the basis of the EDS and X-ray photoelectron

spectroscopy (XPS) results (Supplementary Fig. 5c), we posited that the obtained nanosheets were amorphous chromium oxide. However, it is difficult to distinguish between Cr_2O_3 and CrO_2 using XPS results. Although we believe that a portion of the Cr in the nonstoichiometric amorphous product is high-valence Cr, for convenience, we refer to the materials as amorphous Cr_2O_3 . The thickness of the Cr_2O_3 nanosheets was measured by atomic force microscopy (AFM). The thickness of the amorphous Cr_2O_3 obtained by alcohol lamp heating reached 1.9 nm (Fig. 2k). However, we also observed some sheets that were composed of small crystalline particles (Supplementary Fig. 5d,e). In addition, the X-ray diffraction pattern also suggested that the sample contained crystallographic Cr_2O_3 (Supplementary Fig. 5f). This result may be a consequence of the temperature distribution of the alcohol lamp flame being inhomogeneous, resulting in uneven heating of the $\text{CrCl}_3 \cdot 6\text{H}_2\text{O}$ crystals, which caused the sample to be non-uniform. We therefore changed the heating method from flame heating to a more homogeneous heating method to obtain uniform amorphous Cr_2O_3 nanosheets.

A muffle furnace can control temperature and maintain it at a constant level. This heating method is more homogeneous and capable of treating more samples. We set the temperature of the muffle furnace at 400 °C. The $\text{CrCl}_3 \cdot 6\text{H}_2\text{O}$ crystals were placed in a quartz crucible, directly placed into the furnace at 400 °C and treated for 15 min. After the heating process, the raw $\text{CrCl}_3 \cdot 6\text{H}_2\text{O}$ material exhibited large volume expansion (Fig. 2g and Supplementary Movie 2). Most of the obtained sample was insoluble in water, and large-area layered materials were observed by optical microscopy (Supplementary Fig. 6a). We observed a large quantity of 2D sheets by SEM (Fig. 2h). In addition, according to the diffraction pattern (Fig. 2i) and HRTEM results (Supplementary Fig. 6b), the nanosheets were amorphous. The EDS (Supplementary Fig. 6c) and XPS analysis results (Supplementary Fig. 6d) showed the samples mainly consisted of Cr and O with a small amount of Cl; the results also indicated that the obtained material was amorphous Cr_2O_3 nanosheets. Compared with the density of normal Cr_2O_3 ($\sim 5.21 \text{ g ml}^{-1}$), the tap density of the expanded Cr_2O_3 was very low, $\sim 0.0332 \text{ g ml}^{-1}$. Using this method, we could mass-produce Cr_2O_3 nanosheets as shown in Supplementary Fig. 7a. For instance, we could fabricate 1,000 ml of Cr_2O_3 nanosheets in ~ 2 h in the lab using only a small muffle furnace (the interior dimensions of the furnace are $\sim 10 \times 10 \times 10 \text{ cm}^3$, as shown in Supplementary Fig. 7b). After removing the soluble impurities, the production yield of the Cr_2O_3 nanosheets is around 88%. We could also prepare 8 l of an aqueous Cr_2O_3 nanosheet solution at a concentration of 3 g l^{-1} (Fig. 2j). The Cr_2O_3 solution could be used to prepare free-standing films of Cr_2O_3 by vacuum filtration (Fig. 2l,m). Figure 2n shows a cross-section of the free-standing Cr_2O_3 films. Such solution-based methods are favourable for practical applications such as preparing and processing electrode slurries. In addition to the rapid heating treatment, we also annealed $\text{CrCl}_3 \cdot 6\text{H}_2\text{O}$ crystals under a gradually increasing temperature profile; samples were heated from room temperature to 400 °C at 5 °C min^{-1} in a muffle furnace and maintained at 400 °C for 15 min. We observed the expected volume expansion, but we did not observe predominant quantities of smooth, large-area nanosheets. Most of the resulting sample was in the form of thick sheets formed by small particles (Supplementary Fig. 8). This result suggests that the hydrous chloride crystals could be exfoliated and further reacted to form oxides by heat treatment. However, layer thickness may be influenced by the rate of temperature increase; the exfoliated oxide sheets gradually crystallize to form small Cr_2O_3 crystal particles during the slow heat-treatment process. Accordingly, the rate of temperature increase during the heating treatment is key to obtaining ultrathin 2D metal oxide nanosheets.

Electrochemical performance of the Cr_2O_3 nanosheets. To explore the application of our exfoliated 2D Cr_2O_3 nanosheets, we incorporated the amorphous Cr_2O_3 nanosheets into Li-ion batteries. Lithium can be stored reversibly in TMOs through the following reaction:



Among TMOs, Cr_2O_3 is suitable as an anode material for Li-ion batteries because of its high theoretical capacity ($1,058 \text{ mAh g}^{-1}$), low average charging voltage ($\sim 1.2 \text{ V}$) and low electromotive force value (1.085 V versus Li/Li^+)^{36,37}. However, the cycling performance of Cr_2O_3 electrodes is poor because of a loss of electronic contact of active materials and poor electron and ion transport properties within the active material³⁶. We investigated whether use of our 2D Cr_2O_3 nanosheets as active materials could address these limitations. We fabricated graphene/2D Cr_2O_3 composite electrodes. The graphene and Cr_2O_3 were assembled layer by layer because of their similar 2D layered structure. The stacked 2D structure can provide good electrical contact between the graphene and Cr_2O_3 nanosheets, improving electron transport. The ultrathin, 2D layered structure can help access to the active material by the electrolyte and aid ion transport.

We fabricated graphene/ Cr_2O_3 (2D) electrodes and graphene/ Cr_2O_3 (particle)/polyvinylidene difluoride (PVDF) electrodes, as mentioned in the Methods section. The cells were tested over a voltage range from 0 to 3 V versus Li^+/Li . During the test, the initial lithiation and delithiation capacity of the graphene/ Cr_2O_3 (particle)/PVDF electrodes was only ~ 738 and 316 mAh g^{-1} , respectively, and the delithiation capacity decreased to only 168 mAh g^{-1} after ~ 10 cycles at the current density of 0.2 A g^{-1} (Fig. 3a). By contrast, the graphene/ Cr_2O_3 (2D) electrodes exhibited a high capacity and stable cycling performance. The graphene/ Cr_2O_3 (2D) electrodes achieved an initial delithiation capacity of 974 mAh g^{-1} at a rate of 0.2 A g^{-1} . After 297 cycles, the capacity was $\sim 986 \text{ mAh g}^{-1}$, and the cell continued to function well (Fig. 3a). This electrochemical performance of the graphene/ Cr_2O_3 (2D) electrodes is excellent compared with the reported performance of other Cr_2O_3 electrodes^{38–42}. The galvanostatic lithiation/delithiation profiles and rate performance of our 2D Cr_2O_3 electrodes are included in Fig. 3b,c. We measured the impedance of the electrodes by electrochemical impedance spectroscopy in terms of Nyquist plots (Supplementary Fig. 9). The semicircle in high-frequency region is related to the solid electrolyte interphase (SEI) film and the medium-frequency semicircle due to the charge transfer resistance, and the inclined line in the low-frequency region represents the diffusion of lithium ions^{43,44}. The surface film resistance, which originates from the SEI, and the charge transfer resistance of the graphene/ Cr_2O_3 (particle)/PVDF electrode were 12.3 and 56.9Ω , respectively. However, the graphene/ Cr_2O_3 (2D) composites showed lower SEI and charge transfer resistances, which were 6.6 and 21.4Ω . The electrochemical impedance spectroscopy results indicated the interface of graphene/ Cr_2O_3 (2D) electrodes is more stable and confirmed the 2D structure is attributed to the charge transfer and charge diffusion, which could support the good electrochemical and rate performances of graphene/ Cr_2O_3 (2D) electrodes. Importantly, the graphene/ Cr_2O_3 (2D) composites exhibited strong adhesion to the current collector (copper foil) and between the layers. The graphene/ Cr_2O_3 (2D) electrodes and graphene/ Cr_2O_3 (particle)/PVDF electrodes were immersed in the electrolyte solution; we then sonicated the electrodes in the electrolyte solution with ultrasonic cleaning (80 W, 40 kHz) for 5 min. For the graphene/ Cr_2O_3 (particle)/PVDF electrodes, the PVDF binder did not prevent the spalling of the electrode

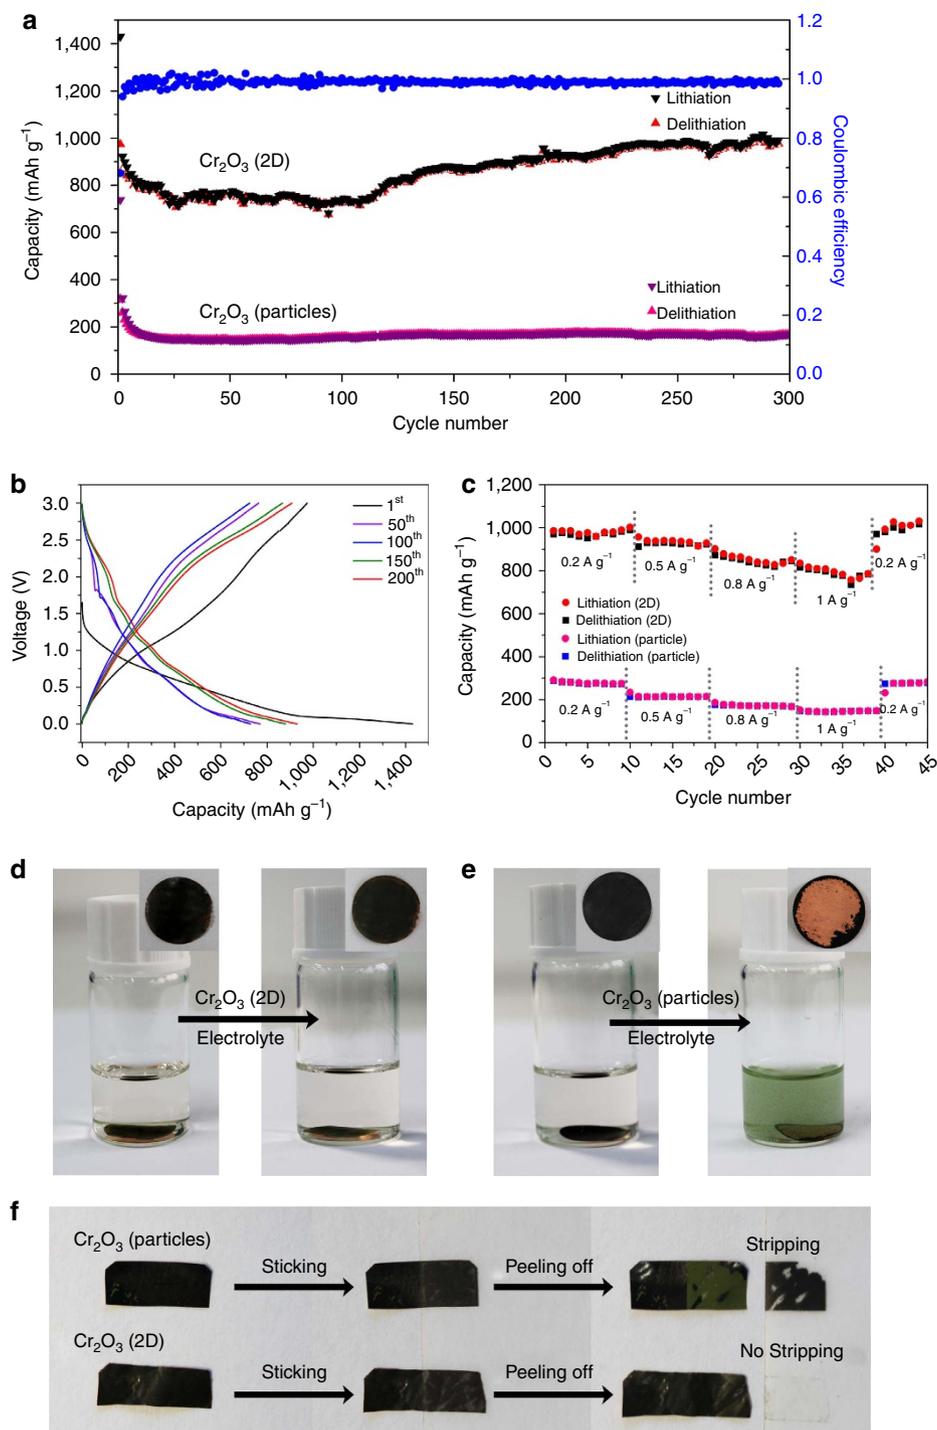


Figure 3 | Electrochemical and adhesion performance of chromic oxides. (a) The cycling performance of the Cr_2O_3 electrodes. (b) The galvanostatic lithiation/delithiation profiles of the 2D Cr_2O_3 electrodes. (c) The rate performance of the Cr_2O_3 electrodes. (d) The Cr_2O_3 (2D) electrode and (e) Cr_2O_3 (particles) electrode before (left of panel) and after (right of panel) being ultrasonically cleaned in an electrolyte solution. (f) The Cr_2O_3 electrodes before and after mechanical exfoliation.

material from the current collector during the ultrasonic cleaning process (Fig. 3e). However, the graphene/ Cr_2O_3 (2D) composite materials remained on the current collector (Fig. 3d). We also tested the adhesion of the two electrode types by cleaning them ultrasonically in water and ethyl alcohol. The graphene/ Cr_2O_3 (2D) electrodes maintained structural stability in all three solutions, whereas the graphene/ Cr_2O_3 (particle)/PVDF electrodes exhibited different degrees of spalling (Supplementary

Fig. 10). We used the scotch tape method to mechanically remove material from the electrodes. While the graphene/ Cr_2O_3 (particle)/PVDF electrode was easily peeled off, the graphene/ Cr_2O_3 (2D) electrodes remained intact and no stripping happened (Fig. 3f and Supplementary Movie 3). The observed strong adhesion and the structural stability of our graphene/2D Cr_2O_3 composite materials could explain the stable electrochemical performance of the graphene/ Cr_2O_3 (2D) electrodes.

We suggest the strong adhesion has three potential causes. First, the 2D structure of Cr_2O_3 provides a high contact area with graphene and copper foil, and the calendaring process ensures good contact between Cr_2O_3 (2D), graphene and copper foil. Second, according to zeta potential measurements under neutral conditions, graphene was negatively charged (-9.26 mV) and the 2D Cr_2O_3 was positively charged (32.5 mV), suggesting that electrostatic attraction contributes to the adhesion between 2D Cr_2O_3 and graphene. Third, and finally, we speculate that some chemical bonding may occur at the interface between the electrode material and current collector, between amorphous Cr_2O_3 nanosheets and the copper foil due to the high-valence Cr and low-coordinated surface atoms, leading to robust adhesion to the copper foil^{45,46}. Such adhesion properties are interesting for applications in many fields, such as flexible energy storage devices or chemical coatings.

Extended material systems. Beyond the chromium oxides from the $\text{CrCl}_3 \cdot 6\text{H}_2\text{O}$, we applied the rapid heating method to other hydrous chlorides to obtain metal oxides such as ZrO_2 , Al_2O_3 and Y_2O_3 . The $\text{ZrOCl}_2 \cdot 8\text{H}_2\text{O}$, $\text{AlCl}_3 \cdot 6\text{H}_2\text{O}$ and $\text{YCl}_3 \cdot 6\text{H}_2\text{O}$ crystals were not layered nanosheets before the rapid heating treatment (Supplementary Fig. 11). The $\text{ZrOCl}_2 \cdot 8\text{H}_2\text{O}$ starting material was heated in the microwave oven for 10 min. A portion of the obtained sample dissolved in water, and we collected the insoluble portion. Typical nanosheets were obtained, as shown by optical microscopy (Supplementary Fig. 12a), SEM (Fig. 4a) and TEM

images (Fig. 4b). On the basis of the EDS (Supplementary Fig. 12c) and XPS (Supplementary Fig. 12d) results, we deduced the nanosheets to be ZrO_2 . The diffraction pattern (Fig. 4b) and HRTEM results (Supplementary Fig. 12b) indicated that the 2D ZrO_2 sheets were amorphous.

In the case of the $\text{AlCl}_3 \cdot 6\text{H}_2\text{O}$ crystals, we placed the crystals in a glass bottle and heated them for ~ 5 min using the alcohol lamp. After the heat treatment, the exfoliated sample was observed by SEM (Supplementary Fig. 13), although individual sheets were difficult to distinguish. We therefore chose an alternative method to produce Al_2O_3 sheets. We used a heating gun to generate hot air with a maximum temperature of ~ 500 °C. We prepared an AlCl_3 solution (1 g ml^{-1}) in water and painted the solution onto copper foil. The copper foil was then dried in an oven at 60 °C for ~ 30 min to obtain a hydrous AlCl_3 thin film. We heated the hydrous AlCl_3 on the copper foil using the heating gun (~ 500 °C) until the light-yellow solid appeared. We observed that the solid formed on the copper foil was exfoliated Al_2O_3 (Fig. 4d); ultrathin nanosheets were observed using TEM (Fig. 4e). These sheets were amorphous Al_2O_3 according to the diffraction pattern (Fig. 4e), HRTEM, EDS and XPS results (Supplementary Fig. 14).

We also produced Y_2O_3 nanosheets using the rapid heat-treatment furnace, which could heat to hundreds of degrees within a few seconds. The heating principle of the rapid heat treatment furnace is light radiation, and the process generates strong air flow. The light radiation heats the hydrous chlorides and causes water and hydrogen chloride molecules to escape from

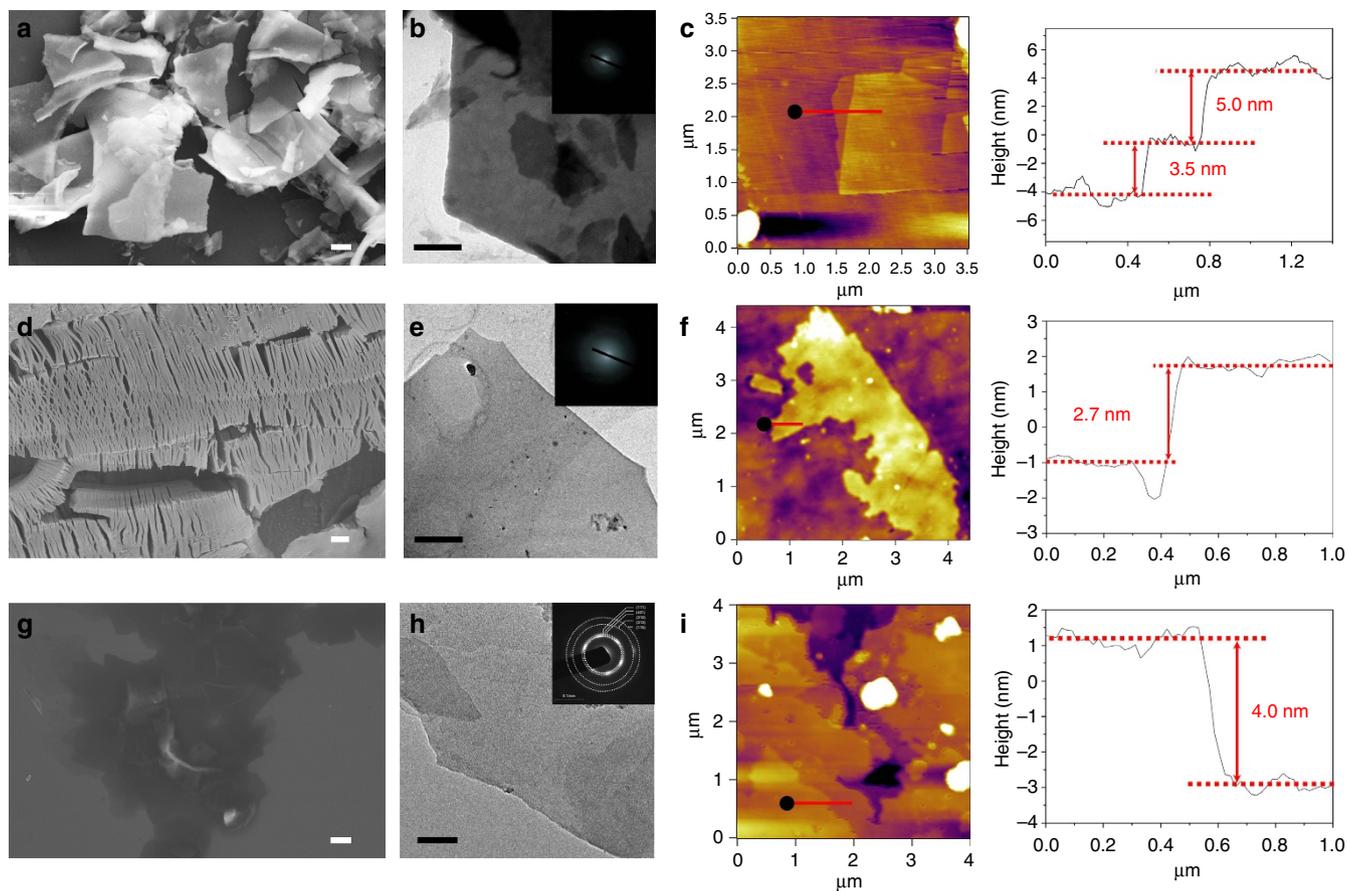


Figure 4 | Characterizations of the oxide nanosheets. (a) SEM, (b) TEM (inset, corresponding electron diffraction pattern) and (c) AFM characterizations of the ZrO_2 nanosheets. (d) SEM, (e) TEM (inset, corresponding electron diffraction pattern) and (f) AFM characterizations of the Al_2O_3 nanosheets. (g) SEM, (h) TEM (inset, corresponding electron diffraction pattern) and (i) AFM characterizations of the Y_2O_3 nanosheets. Scale bars, $2 \mu\text{m}$ (a,d,g), 500 nm (b,e) and 50 nm (h).

the crystals. The air flow removes the water and hydrogen chloride molecules from the environment, which favours the escape of more gas molecules. We treated $\text{YCl}_3 \cdot 6\text{H}_2\text{O}$ samples in this furnace. The $\text{YCl}_3 \cdot 6\text{H}_2\text{O}$ was placed in a crucible, heated to 600 °C, and maintained at this temperature for 2 min in the rapid heat-treatment furnace. Although the samples were not uniform and contained numerous particles, we still obtained Y_2O_3 nanosheets, as indicated by SEM, TEM (Fig. 4g,h) and EDS results (Supplementary Fig. 15b). The diffraction pattern (Fig. 4h) and HRTEM (Supplementary Fig. 15a) results indicated that part of the Y_2O_3 nanosheets was crystallized (PDF#44-0399), but the crystallinity was poor. We measured the thickness of the metal oxide nanosheets using AFM. The thinnest layers of the ZrO_2 , Al_2O_3 and Y_2O_3 obtained by rapid heating methods exhibited layer thicknesses of 3.5, 2.7 and 4.0 nm, respectively (Fig. 4c,f,i).

Discussion

We could collect the 2D nanosheets using different combinations of the aforementioned materials and heating methods. For example, we obtained amorphous Cr_2O_3 nanosheets by heating the $\text{CrCl}_3 \cdot 6\text{H}_2\text{O}$ in the rapid heat treatment furnace (Supplementary Fig. 16). Some precursors without crystal water (such as anhydrous AlCl_3) or without layered crystal structure (such as $\text{AlNO}_3 \cdot 9\text{H}_2\text{O}$) were also treated by the rapid heating process, however the 2D oxides were not obtained in these cases (Supplementary Figs 17 and 18), which strengthens our point about the formation mechanism of oxide nanosheets. Although we obtained metal oxides using the various methods previously mentioned, the idea of treating the hydrous chloride with a rapid thermal process is consistent. The differences are the heating principles and specific procedures. However, the influential factors and manufacturing techniques require further improvement and study because the products obtained were not uniform and because we could not produce other TMOs to the same degree as we could produce the Cr_2O_3 nanosheets.

We produced the 2D Cr_2O_3 nanosheets on a large scale within a short time (that is, several minutes) by rapidly heating hydrous chlorides; the 2D Cr_2O_3 showed excellent electrochemical performance in Li-ion battery and surprisingly strong adhesion to the copper foil substrate. We also demonstrated that this method of producing ultrathin nanosheets could be generalized to allow rapid production of other oxides such as ZrO_2 , Al_2O_3 and Y_2O_3 . We believe that this concept provides a practically promising avenue for simple, efficient, fast and inexpensive production of large quantities of large-area, ultrathin 2D nanosheets.

Methods

Synthesis of 2D CrOCl by microwave heating. The $\text{CrCl}_3 \cdot 6\text{H}_2\text{O}$ crystals were placed in a glass bottle and heated using a microwave oven for ~5 min. Then, the obtained CrOCl materials were transferred and stored in an Ar-filled glove box. The CrOCl nanosheets were dispersed in benzene to prepare TEM samples.

Synthesis of the 2D oxides. The $\text{CrCl}_3 \cdot 6\text{H}_2\text{O}$ crystals were placed on nickel foam and heated using an alcohol lamp for ~2 min; or placed in a quartz crucible and heated in a muffle furnace at 400 °C for ~15 min. The $\text{ZrOCl}_2 \cdot 8\text{H}_2\text{O}$ crystals were placed in a glass bottle and heated using a microwave oven for ~10 min. The $\text{AlCl}_3 \cdot 6\text{H}_2\text{O}$ crystals were dissolved in deionized water at a concentration of 1 g ml⁻¹, and the solution was painted onto copper foil. The copper foil was dried in an oven at 60 °C for 30 min to obtain the hydrous AlCl_3 thin film. We heated the hydrous AlCl_3 on the copper foil using a heating gun until a white or light-yellow solid appeared. The white or light-yellow solid was Al_2O_3 nanosheets. The $\text{YCl}_3 \cdot 6\text{H}_2\text{O}$ crystals were placed in an alumina crucible and heated in the rapid heat treatment furnace at 600 °C for ~2 min. The obtained metal oxide products contain incompletely reacted intermediate products. We dispersed the obtained products in deionized water to remove the soluble impurities. The dispersion of products was centrifuged for 5 min at 12,000 r.p.m. to obtain the sediment. We repeated the centrifuging process three times to clean the products (the first two times using deionized water and the third time using ethyl alcohol). The obtained sediment was dried in an oven at 80 °C.

Battery electrodes based on nanosheets or on microparticles. We dispersed graphene (10 wt%) and Cr_2O_3 nanosheets (90 wt%) in water at a concentration of 10 mg ml⁻¹ (total mass). We also dispersed graphene (10 wt%), Cr_2O_3 particles (~300 nm, 80 wt%) and PVDF (10 wt%) in N-methyl-2-pyrrolidone (NMP) at a concentration of 10 mg ml⁻¹ (total mass). The composite slurry was dropped onto a flat copper foil and dried in an oven at ~80 °C. The dried electrodes were pressed using a calendaring process (~20 MPa). The mass loading of the electrodes was ~0.5 mg cm⁻². The electrodes were assembled into half-cells with Li metal foil (MTI) as a counter electrode in an Ar-filled glove box. We used a 25 μm-thick microporous polypropylene membrane as the separator (Asahi Kasei) and 1 M LiPF₆ in ethylene carbonate/diethyl carbonate/fluoroethylene carbonate (1:1:0.04 vol/vol/vol, Ferro Corporation) as the electrolyte.

Characterization. The X-ray diffraction patterns of the rare materials and products were evaluated using a D/max-2500 diffractometer (Rigaku, Japan) equipped with a CuK_α radiation source. The chemical states of the products were determined by XPS (Thermo Fisher ESCALAB 250Xi). The morphology of the samples was observed with a SEM (MERLIN VP Compact, ZEISS, Germany). The chemical composition of the samples was analysed using EDS (X-Max^N, Oxford Instruments). HRTEM observation was carried out using JEOL-2100 TEM operated at 200 kV. The thickness of the nanosheets was determined by AFM (MFP-3D, Asylum Research, Oxford Instruments). The electrochemical performances of the batteries were measured by a BS-9300R/10V2A MTI 8 channels battery analyser.

Data availability. The data that support the findings of this study are available from the corresponding author on request.

References

- Novoselov, K. S. *et al.* Two-dimensional atomic crystals. *Proc. Natl Acad. Sci. USA* **102**, 10451–10453 (2005).
- Novoselov, K. S. *et al.* A roadmap for graphene. *Nature* **490**, 192–200 (2012).
- Wang, Q. H., Kalantar-Zadeh, K., Kis, A., Coleman, J. N. & Strano, M. S. Electronics and optoelectronics of two-dimensional transition metal dichalcogenides. *Nat. Nanotechnol.* **7**, 699–712 (2012).
- Geim, A. K. Graphene: status and prospects. *Science* **324**, 1530–1534 (2009).
- Geim, A. K. & Novoselov, K. S. The rise of graphene. *Nat. Mater.* **6**, 183–191 (2007).
- Berger, C. *et al.* Electronic confinement and coherence in patterned epitaxial graphene. *Science* **312**, 1191–1196 (2006).
- Kim, K. S. *et al.* Large-scale pattern growth of graphene films for stretchable transparent electrodes. *Nature* **457**, 706–710 (2009).
- Eda, G., Fanchini, G. & Chhowalla, M. Large-area ultrathin films of reduced graphene oxide as a transparent and flexible electronic material. *Nat. Nanotechnol.* **3**, 270–274 (2008).
- Novoselov, K. S. *et al.* Electric field effect in atomically thin carbon films. *Science* **306**, 666–669 (2004).
- Huang, X., Qi, X., Boey, F. & Zhang, H. Graphene-based composites. *Chem. Soc. Rev.* **41**, 666–686 (2012).
- Sun, Y. *et al.* Fabrication of flexible and freestanding zinc chalcogenide single layers. *Nat. Commun.* **3**, 1057 (2012).
- Koski, K. J. & Cui, Y. The new skinny in two-dimensional nanomaterials. *ACS Nano* **7**, 3739–3743 (2013).
- Radisavljevic, B., Radenovic, A., Brivio, J., Giacometti, V. & Kis, A. Single-layer MoS₂ transistors. *Nat. Nanotechnol.* **6**, 147–150 (2011).
- Zhi, C., Bando, Y., Tang, C., Kuwahara, H. & Golberg, D. Large-scale fabrication of boron nitride nanosheets and their utilization in polymeric composites with improved thermal and mechanical properties. *Adv. Mater.* **21**, 2889–2893 (2009).
- Li, L. *et al.* Black phosphorus field-effect transistors. *Nat. Nanotechnol.* **9**, 372–377 (2014).
- Osada, M. & Sasaki, T. Exfoliated oxide nanosheets: new solution to nanoelectronics. *J. Mater. Chem.* **19**, 2503–2511 (2009).
- Chhowalla, M. *et al.* The chemistry of two-dimensional layered transition metal dichalcogenide nanosheets. *Nat. Chem.* **5**, 263–275 (2013).
- Zhang, X. & Xie, Y. Recent advances in free-standing two-dimensional crystals with atomic thickness: design, assembly and transfer strategies. *Chem. Soc. Rev.* **42**, 8187–8199 (2013).
- Coleman, J. N. *et al.* Two-dimensional nanosheets produced by liquid exfoliation of layered materials. *Science* **331**, 568–571 (2011).
- Paton, K. R. *et al.* Scalable production of large quantities of defect-free few-layer graphene by shear exfoliation in liquids. *Nat. Mater.* **13**, 624–630 (2014).
- Naguib, M. *et al.* Two-dimensional nanocrystals produced by exfoliation of Ti_3AlC_2 . *Adv. Mater.* **23**, 4248–4253 (2011).
- Naguib, M., Mochalin, V. N., Barsoum, M. W. & Gogotsi, Y. 25th anniversary article: MXenes: a new family of two-dimensional materials. *Adv. Mater.* **26**, 992–1005 (2014).

23. Naguib, M. *et al.* Two-dimensional transition metal carbides. *ACS Nano* **6**, 1322–1331 (2012).
24. Lukatskaya, M. R. *et al.* Cation intercalation and high volumetric capacitance of two-dimensional titanium carbide. *Science* **341**, 1502–1505 (2013).
25. Sun, Z. *et al.* Generalized self-assembly of scalable two-dimensional transition metal oxide nanosheets. *Nat. Commun.* **5**, 3813 (2014).
26. Duan, H. *et al.* Ultrathin rhodium nanosheets. *Nat. Commun.* **5**, 3093 (2014).
27. Wang, L. *et al.* Two-dimensional gold nanostructures with high activity for selective oxidation of carbon-hydrogen bonds. *Nat. Commun.* **6**, 6957 (2015).
28. Niu, L. *et al.* Production of two-dimensional nanomaterials via liquid-based direct exfoliation. *Small* **12**, 272–293 (2015).
29. Nicolosi, V., Chhowalla, M., Kanatzidis, M. G., Strano, M. S. & Coleman, J. N. Liquid exfoliation of layered materials. *Science* **340**, 1226419 (2013).
30. Shih, C. J. *et al.* Bi-and trilayer graphene solutions. *Nat. Nanotechnol.* **6**, 439–445 (2011).
31. Eda, G. *et al.* Photoluminescence from chemically exfoliated MoS₂. *Nano Lett.* **11**, 5111–5116 (2011).
32. Ida, S., Shiga, D., Koinuma, M. & Matsumoto, Y. Synthesis of hexagonal nickel hydroxide nanosheets by exfoliation of layered nickel hydroxide intercalated with dodecyl sulfate ions. *J. Am. Chem. Soc.* **130**, 14038–14039 (2008).
33. Folorunso, O., Dodds, C., Dimitrakis, G. & Kingman, S. Continuous energy efficient exfoliation of vermiculite through microwave heating. *Int. J. Miner. Process.* **114**, 69–79 (2012).
34. Marcos, C. & Rodriguez, I. Exfoliation of vermiculites with chemical treatment using hydrogen peroxide and thermal treatment using microwaves. *Appl. Clay Sci.* **87**, 219–227 (2014).
35. Mingos, D. M. P. & Whittaker, A. G. *Microwave Dielectric Heating Effects in Chemical Synthesis* (Wiley and Spectrum, 1997).
36. Li, H., Wang, Z., Chen, L. & Huang, X. Research on advanced materials for Li-ion batteries. *Adv. Mater.* **21**, 4593–4607 (2009).
37. Li, H., Balaya, P. & Maier, J. Li-storage via heterogeneous reaction in selected binary metal fluorides and oxides. *J. Electrochem. Soc.* **151**, A1878–A1885 (2004).
38. Yue, W., Tao, S., Fu, J., Gao, Z. & Ren, Y. Carbon-coated grapheme-Cr₂O₃ composites with enhanced electrochemical performances for Li-ion batteries. *Carbon* **65**, 97–104 (2013).
39. Xu, H., Zeng, M. & Li, J. Graphene-wrapped Cr₂O₃ hollow nanospheres with enhanced electrochemical performances for lithium-ion batteries. *Int. J. Electrochem. Sci.* **10**, 7361–7370 (2015).
40. Liu, H., Du, X., Xing, X., Wang, G. & Qiao, S. Z. Highly ordered mesoporous Cr₂O₃ materials with enhanced performance for gas sensors and lithium ion batteries. *Chem. Commun.* **48**, 865–867 (2012).
41. Guo, B., Chi, M., Sun, X. G. & Dai, S. Mesoporous carbon-Cr₂O₃ composite as an anode material for lithium ion batteries. *J. Power Sources* **205**, 495–499 (2012).
42. Jiang, L. Y. *et al.* Non-sacrificial template synthesis of Cr₂O₃-C hierarchical core/shell nanospheres and their application as anode materials in lithium-ion batteries. *J. Mater. Chem.* **20**, 7565–7569 (2010).
43. Chang, J. *et al.* Multilayered Si nanoparticle/reduced graphene oxide hybrid as a high-performance lithium-ion battery anode. *Adv. Mater.* **26**, 758–764 (2014).
44. Rahman, M. A. & Wen, C. Nanogel structured NiO/Ni foam as electrode for high-performance lithium-ion batteries. *Ionics* **21**, 2709–2723 (2015).
45. Yumoto, H. *et al.* Effect of oxides on the adhesion of Cu films deposited onto stainless steel by electron shower and thermal evaporation methods. *J. Adhes. Sci. Technol.* **11**, 665–677 (1997).
46. Xiao, M., Zhao, M., Lang, X., Zhu, Y. & Jiang, Q. Improvement of electromigration reliability and diffusion of Cu films using coherent Cu (111)/Cr₂O₃ (0001) interfaces. *Chem. Phys. Lett.* **542**, 85–88 (2012).

Acknowledgements

This study was supported by the National Basic Research of China (Grant Nos. 2015CB932500 and 2013CB632702) and the NSF of China (Grant No. 51302141). We thank Dr M. Z. from Tsinghua University for the TEM characterizations and helpful discussions. We thank Dr Y. X. from Tsinghua University for the EIS analysis.

Author contributions

H.W. and C.Z. conceived and designed the study; C.Z. and H.Z. performed the synthesis and analysis; W.S. provided helpful suggestions for analysis and manuscript revision; all authors discussed the results; C.Z. and H.W. wrote the manuscript, with contributions and feedback from all the authors.

Additional information

Supplementary Information accompanies this paper at <http://www.nature.com/naturecommunications>

Competing financial interests: The authors declare no competing financial interests.

Reprints and permission information is available online at <http://npg.nature.com/reprintsandpermissions/>

How to cite this article: Zhao, C. *et al.* Mass production of two-dimensional oxides by rapid heating of hydrous chlorides. *Nat. Commun.* **7**:12543 doi: 10.1038/ncomms12543 (2016).



This work is licensed under a Creative Commons Attribution 4.0 International License. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in the credit line; if the material is not included under the Creative Commons license, users will need to obtain permission from the license holder to reproduce the material. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>

© The Author(s) 2016