

ARTICLE

Received 15 Dec 2014 | Accepted 14 Apr 2015 | Published 18 May 2015

DOI: 10.1038/ncomms8179

OPEN

Strain induced fragility transition in metallic glass

Hai-Bin Yu^{1,†}, Ranko Richert², Robert Maaß³ & Konrad Samwer¹

Relaxation dynamics are the central topic in glassy physics. Recently, there is an emerging view that mechanical strain plays a similar role as temperature in altering the relaxation dynamics. Here, we report that mechanical strain in a model metallic glass modulates the relaxation dynamics in unexpected ways. We find that a large strain amplitude makes a fragile liquid become stronger, reduces dynamical heterogeneity at the glass transition and broadens the loss spectra asymmetrically, in addition to speeding up the relaxation dynamics. These findings demonstrate the distinctive roles of strain compared with temperature on the relaxation dynamics and indicate that dynamical heterogeneity inherently relates to the fragility of glass-forming materials.

¹Physikalisches Institut, Universität Göttingen, D-37077 Göttingen, Germany. ²Department of Chemistry and Biochemistry, Arizona State University, Tempe, Arizona 85287, USA. ³Institute for Materials Physics, University of Göttingen, D-37077 Göttingen, Germany. † Present address: Department of Chemistry and Biochemistry, Arizona State University, Tempe, Arizona 85287, USA. Correspondence and requests for materials should be addressed to H.-B.Y. (email: haibinyu@asu.edu) or to K.S. (email: ksamwer@gwdg.de).

Glasses and supercooled liquids feature diverse and complex relaxation dynamics^{1–8}. The most prominent relaxation mode is the so-called primary (α -) relaxation, which signals a nonequilibrium transition from a solid-like state to a viscous liquid-like state, characterized solely by the change of dynamics^{1–4}. Recently, it has been recognized that mechanical stress (or strain) plays a similar role as temperature in the dynamics of the α relaxation in many kinds of glass-forming materials⁹, including colloidal glasses^{9–11}, granular materials¹² and metallic glasses (MGs)^{13–16}. Initially, Liu and Nagel⁹ introduced the concept of a jamming diagram to unify the roles of stress, temperature and density in colloidal glasses. The pursuits of this view have also led to some scaling laws in different types of glasses to rationalize the roles of temperature, strain/stress and other variables^{13,17}. Quantitatively, such jamming diagrams and scaling laws, however, depend on the intrinsic properties of glass-forming materials such as the interaction potentials^{9,18}, and thus cannot be generalized across different types of glasses.

In the field of MGs, such a view and its equivalent idea that ‘stress/strain-driven glass transitions’ have particular significance as they have been taken as an essential ingredient to understand a number of crucial issues, such as the mechanical properties (strength and ductility)^{19–21}, mechanisms of plastic deformation^{22,23}, as well as the origins of shear-banding and serrated flow^{24–26}. Despite its importance, we note that there is still no direct characterization of the dynamics of the α relaxation under stress/strain for MGs. Previous results were based on either apparent viscosity or structural perspectives^{13,14}. Partly, the difficulty stems from the fact that conventional mechanical spectroscopy that probes relaxation dynamics of MGs is not applicable to nonlinear deformation regime where large stress and strain are required^{7,8}. Therefore, the basic question whether temperature and stress indeed have similar or different role in relaxation dynamics of MGs is still not clear.

In this work, we address this issue by studying the relaxation spectra of a model MG in the parameter space of temperature, frequency and strain amplitude, via a recently proposed molecular dynamics simulation of dynamical mechanical spectroscopy (MD-DMS)²⁷ together with structural analysis. We find that mechanical strain not only accelerates the relaxation dynamics as previously assumed but also alters it in unexpected ways: a fragile MG gradually becomes a strong one under increasing strain, together with a phenomenon of broadening the peak of α relaxation on the loss spectra only for the low-temperature side (while the high-temperature side remains almost unchanged). Structurally, these processes are accompanied by a suppression of dynamical heterogeneity at the glass transition, demonstrating the key role of dynamical heterogeneity in controlling the fragility of glass-forming materials.

Results

Relaxation spectra. The details of our model system and the protocol of MD-DMS are given in Methods. Briefly, at a temperature T , we apply a sinusoidal strain $\varepsilon(t) = \varepsilon_A \sin(2\pi t/t_\omega)$, with a period t_ω (related to frequency $f = 1/t_\omega$) and a strain amplitude ε_A , along the x direction of a model $\text{Cu}_{65}\text{Zr}_{35}$ MG and the resulting stress $\sigma(t)$ is measured. To study the strain effects on glassy dynamics, we intentionally vary ε_A from linear (elastic) to nonlinear (plastic) deformation regimes. For simplicity, this work focuses on the first Fourier component of the response stress. High-order effects due to nonlinear response will be discussed in a later work. The storage (E') and loss (E'') moduli are calculated as functions of T , t_ω and ε_A .

Figure 1a shows an example of E' and E'' as a function of T for a selected combination of $\varepsilon_A = 1.25\%$ and $t_\omega = 1,000$ ps (or $f = 1$ GHz). They exhibit the typical features of an α relaxation that is consistent with experimental DMS^{7,8}, that is, a sudden drop of E' as well as an asymmetrical peak of E'' around $T_\alpha = 1,000$ K (the temperature corresponding to the α relaxation time $\tau_\alpha = t_\omega$), that signal the transition from a glassy state to a supercooled liquid state. Figure 1b shows E' and E'' for a fixed temperature of $T = 800$ K as a function of ε_A . One can see that for $\varepsilon_A < 2\%$, the values of E' are high, while E'' are low, and both are nearly independent of ε_A , indicating that the model MG is in a glassy state and responds linearly to the external mechanical oscillations. However, with further increase in ε_A , E' decreases rapidly in a sigmoidal manner, while E'' first increases and then decreases, with a peak around $\varepsilon_A = 5\%$. These features, phenomenally similar to Fig. 1a, indicate that the model MG enters into a liquid-like state driven by mechanical strain, that is, the α relaxation takes place at $T = 800$ K under $\varepsilon_A = 5\%$, which is 200 K lower than for the case of $\varepsilon_A = 1.25\%$, as shown in Fig. 1a.

Figure 2a,b shows the T -dependent curves for E' and E'' , respectively, for various values of ε_A at $t_\omega = 1,000$ ps. For a better view, Fig. 2c,d recasts the same data in terms of contour plots as two-dimensional (2D) functions of T and ε_A . The values of ε_A range from 0.625 to 10%, covering both elastic and plastic deformation regimes of the model MG. First, Fig. 2a,b shows a pronounced nonlinear effect on the magnitudes of E' and E'' , which agrees with Fig. 1b. Second, Fig. 2c,d indicates that the α relaxation can be activated either by T or ε_A or a combination of both, and the α relaxation can take place at any temperature depending on ε_A . For instance, although $T_\alpha = 1,000$ K in the linear response regime, it is reduced to a temperature as low as 500 K when ε_A approaches 6.25%. For $\varepsilon_A \geq 10\%$, we even find that

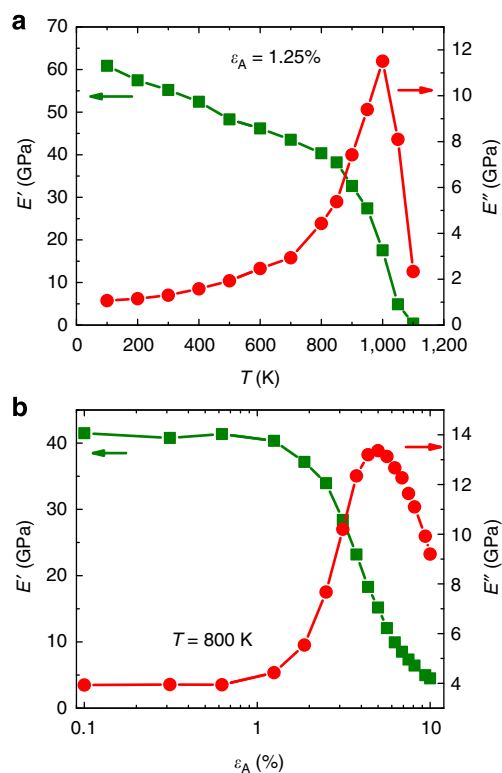


Figure 1 | Storage (E') and loss (E'') moduli from MD-DMS. (a) E' and E'' as a function of temperature T with a strain amplitude $\varepsilon_A = 1.25\%$ (b) as a function of ε_A with $T = 800$ K. The period is $t_\omega = 1,000$ ps.

the model MG always behaves like in a liquid-like state at any T in our MD-DMS, which means T_α is practically 0 K in that case. Overall, these results provide convincing evidence that strain can accelerate the relaxation dynamics and support the notion of a

mechanically driven liquid-glass transition¹³. Third, we note that Fig. 2b reveals one intriguing feature of nonlinear effects on the first-order mechanical spectra: the E'' peak of the α relaxation broadens substantially in the left (low T) side, while the right

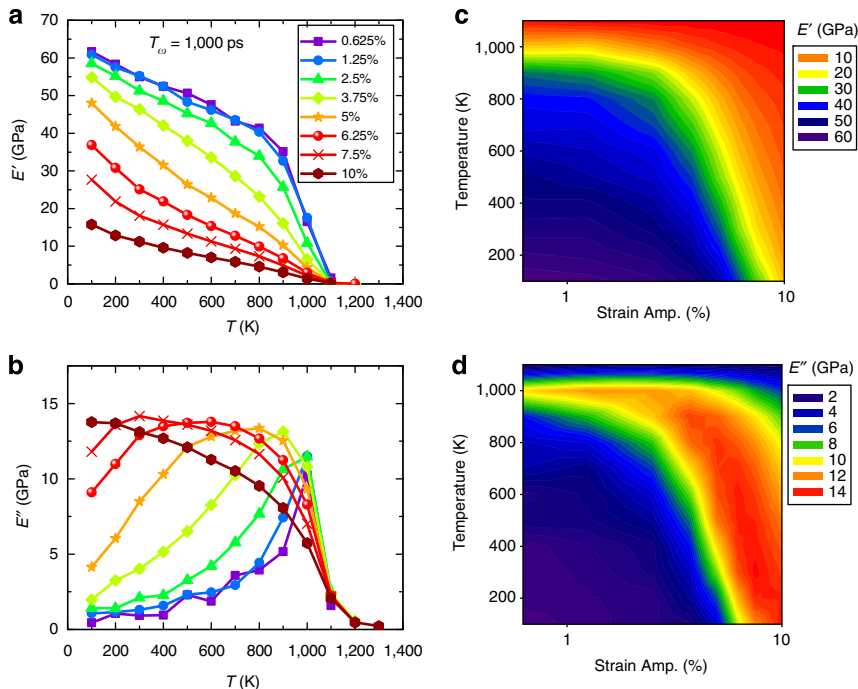


Figure 2 | Temperature and strain amplitude dependent modulus. (a) E' and (b) E'' as a function of T for different strain amplitude levels, ϵ_A . (c) E' and (d) E'' contour plots as 2D function of T and ϵ_A . The period is $t_\omega = 1,000$ ps.

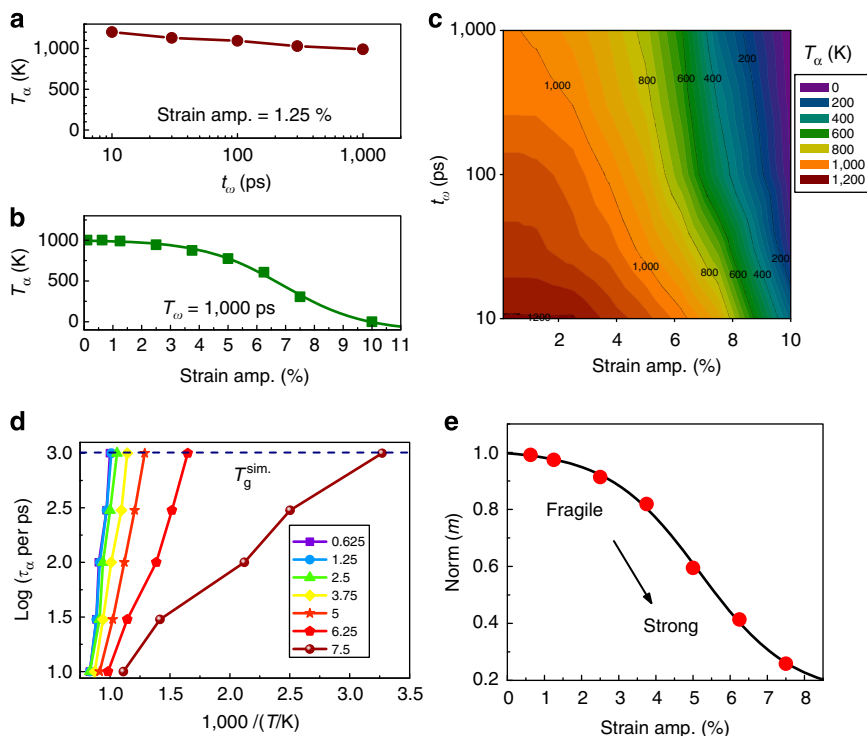


Figure 3 | Temperature and strain amplitude dependent α relaxations. (a) The primary relaxation temperature T_α as a function of period t_ω for $\epsilon_A = 1.25\%$. (b) T_α as a function of ϵ_A for $t_\omega = 1,000$ ps. (c) T_α as a 2D function of t_ω and ϵ_A . (d) The α relaxation dynamics as a function of $1,000/T$ for different ϵ_A as indicated in percentage. (e) The normalized fragility index m as a function of ϵ_A .

(high T) side of it is almost unchanged. This feature implies that strain in the nonlinear regime alters the relaxation dynamics in a distinctive way compared with temperature: if mechanical strain behaves similarly as enhanced effective temperature, then the spectra of E'' will just shift to low T side as a whole, keeping the shape almost unchanged, and the left-side broadening of E'' peak could not be observed. We note that a signature of similar (but much smaller) nonlinear effects is observed in experimental dielectric spectra of organic glasses, which reveal that large amplitudes of electric fields modify only the high-frequency side of the dielectric spectra of the α relaxation during a constant T measurement^{28,29}.

Relaxation dynamics and fragility. Next, we focus on T_α , determined from the peak temperature of E'' as a direct indicator of relaxation dynamics. Figure 3a,b shows the values of T_α as a function of t_ω and ε_A , respectively. One can see that T_α decreases from 1,200 to 1,000 K as t_ω increases from 10 to 1,000 ps for $\varepsilon_A = 1.25\%$ (Fig. 3a, frequency effects), while it decreases from

1,000 K to almost below 50 K in the nonlinear response regime from $\varepsilon_A = 3$ to 10% at a fixed $t_\omega = 1,000$ ps (Fig. 3b, strain effects). This suggests that mechanical strain is more effective in modifying the relaxation dynamics than temperature within the capacity of MD simulations, since MD is usually limited by timescale; however, the mechanical strain can be changed readily. Figure 3c summarizes how T_α changes as a 2D function of ε_A and t_ω . A general trend is that T_α decreases with ε_A for any t_ω in the nonlinear response regime. However, the magnitude of the decrease in T_α is larger for higher t_ω . For example, for $t_\omega = 1,000$ ps, T_α decreases from 1,000 K at $\varepsilon_A < 2.5\%$ to 350 K at $\varepsilon_A = 7.5\%$, while for $t_\omega = 10$ ps T_α decreases only from 1,200 to 1,000 K with the same ε_A .

To quantify the effects of strain on relaxation dynamics, Fig. 3d plots the relaxation time as a function of inverse temperature. One can observe that strain modifies the relaxation dynamics in a nontrivial way. Specifically, the effects of stress are more pronounced at low temperatures than at high temperatures. Thus, the relaxation time is strongly reduced at low temperatures

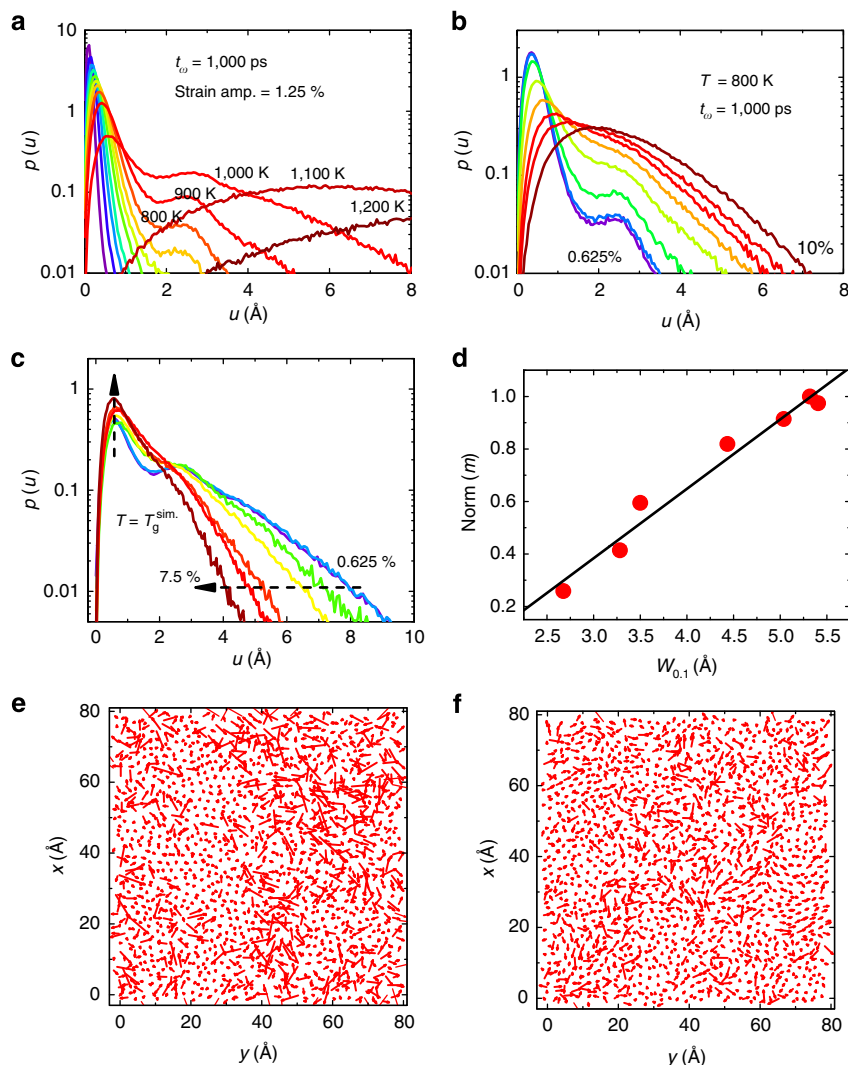


Figure 4 | Structural analysis on the basis of the mean square atomic jump distance u . (a) Probability density $p(u)$ for different T at $t_\omega = 1,000$ ps and $\varepsilon_A = 1.25\%$, temperature ranges from 100 K to 1,200 K for every 100 K from left to right. (b) $p(u)$ for different ε_A at $T = 800$ K and $t_\omega = 1,000$ ps, the strain amplitudes are 0.625%, 1.25%, 2.5%, 3.75%, 5.0%, 6.25%, 7.5% and 10% from left to right. (c) $p(u)$ at the simulation glass transition temperature $T_g^{\text{sim}} = T_\alpha$ ($t_\omega = 1,000$ ps) for different ε_A of 0.626%, 1.25%, 2.5%, 3.75%, 5.0%, 6.25% and 7.5% from right to left. (d) Relation between normalized fragility m and the width of $p(u)$ at 1/10 maximum $W_{0.1}$. (e, f) 2D xy slices ($20 \text{ \AA} < z \leq 24 \text{ \AA}$) of the vector field of u at T_g^{sim} for $\varepsilon_A = 1.25\%$ and 7.5%, respectively.

but less at high temperatures. In this connection, it would be useful to consider the concept of fragility^{30–32}, quantified by $m = \text{dlog}(\tau_\alpha)/\text{d}(T_g/T)$, that characterizes how rapidly the dynamics of a material slow down as it is cooled towards the glass transition. Liquids with large m are called fragile, while those with small m are considered strong. In our simulations, the glass transition temperature is defined as $T_g^{\text{sim}} \equiv T_\alpha$ ($t_\omega = 1,000$ ps) as shown in Fig. 3d, which for those in the linear response regime agree with the temperature at which the slope of a volume– T curve would change. The resulting m values are shown in Fig. 3e and are normalized to low-strain-limit fragility, approximated by m at $\varepsilon_A = 0.625\%$. We find that m is nearly independent of ε_A in the linear response regime as expected, while, intriguingly, it shows pronounced dependence on ε_A in the nonlinear response regime and decreases to $\sim 1/4$ of its linear response value when ε_A reaches 7.5%. Such a large reduction of m is nontrivial, as m is known to be insensitive to many external variables and is often considered an intrinsic property of glass-forming materials³³. For example, m is only weakly dependent on hydrostatic pressures³⁴. In addition, we note that the reduction of m underpins the broadening of the spectra of E'' in Fig. 2b, as it is known that materials with a higher fragility have a relatively narrow glass transition temperature range, while the stronger materials (those with lower fragility) have a wide glass transition temperature range³².

Discussion

To further study the nonlinear strain effects on the relaxation dynamics and to understand why m is dramatically reduced in the nonlinear regime, we conducted a structural analysis and calculated the mean square atomic jump distance u for each atom during a time interval of $\Delta t = t_\omega$ for all the combinations of T , t_ω and ε_A . This choice of Δt is meant to avoid atomic displacements due to the overall deformations applied by the MD-DMS. Figure 4a,b shows the resulting probability density function $p(u)$ for different T (where $\varepsilon_A = 1.25\%$ and $t_\omega = 1,000$ ps remain fixed) and different ε_A ($T = 800$ K, $t_\omega = 1,000$ ps), respectively. The peak position u_p and the width of $p(u)$ represents the most probable atomic jump distance of all the atoms and the jump distance dispersion, respectively. The latter quantity is associated with dynamical heterogeneity. From Fig. 4a,b, one can see that both mechanical strain and temperature can increase u_p and broaden the distribution of $p(u)$, which provides structural evidence for the strain-accelerated dynamics as outlined in Figs 1 and 2. Figure 4c plots $p(u)$ at $T = T_g^{\text{sim}} = T_\alpha$ ($t_\omega = 1,000$ ps) for different ε_A . Interestingly, we find at T_g^{sim} that mechanical strain can reduce substantially the distribution of $p(u)$, a signature of suppressing the dynamical heterogeneity substantially. Such a behaviour is consistent with some recent simulations and experiments, which reveal that in the presence of mechanical deformation, the dynamics of supercooled liquids are more homogenous, as the deformation reduces the correlation length and the lifetime of dynamical heterogeneity^{35,36}. Figure 4d plots m as a function of $W_{0,1}$, where $W_{0,1}$ is defined as the width of $p(u)$ at 1/10 of the maximum as an indicator of dynamical heterogeneity. Remarkably, we observe a strong correlation between m and $W_{0,1}$, even where the MD-DMS covers both the linear and nonlinear response regimes. Such a correlation clearly suggests that dynamical heterogeneity is a key feature that relates to fragility of glass-forming materials. Figure 4e,f presents two typical slices of 2D vector fields of u at $T = T_g^{\text{sim}}$ for $\varepsilon_A = 1.25\%$ and 7.5%, respectively. One can see that the u -field with $\varepsilon_A = 1.25\%$ (Fig. 4e) is more heterogeneous than the one with $\varepsilon_A = 7.5\%$, corroborating that deformation reduces dynamical heterogeneity in terms of its correlation lengths at the glass transition T_g^{sim} .

The results discussed above not only demonstrate that high strain amplitudes can accelerate dynamics, as does an increase in temperature, but also that the value of τ_α alone does not specify the entire dynamics of the MG system. In other words, two states with identical α relaxation time (one reached by low T and high ε_A , another reached by high T and low ε_A) will not coincide regarding other aspects of the dynamics, such as fragility and dynamic heterogeneity. Our explanation is as follows: nonlinear response is reached by strain amplitudes for which the mechanical energy involved per period, $\propto \sigma_A \varepsilon_A$, becomes comparable to or even large than $k_B T$. In a potential energy landscape (PEL) picture^{37,38}, higher temperature assists activation and modifies the population within a given landscape, whereas high values of ε_A are equivalent to tilting the PEL, which affects low and high barriers in different ways.

In summary, we show that mechanical strain not only accelerates the relaxation dynamics of a model MG, but also modifies it in unique ways. In particular, a fragile glass former becomes stronger under mechanical strain, and the peak of the α relaxation broadens asymmetrically. Structurally, dynamical heterogeneity at the glass transition is gradually suppressed with increasing strain amplitude. These findings emphasize the distinctive roles of strain compared with temperature on the relaxation dynamics, and provide microscopic insights to the concept of fragility as well.

Methods

Simulation details and samples. An open source LAMMPS package³⁹ was used for the MD simulations. The model system contains $N = 32,000$ atoms with the composition $\text{Cu}_{65}\text{Zr}_{35}$, and the constituting atoms are interacting via an embedded atom method potential⁴⁰. For the sample preparations, the system was melted and equilibrated at $T = 3,000$ K, and then cooled down to $T = 100$ K with a cooling rate of 10^{12} K s⁻¹, during which the cell sizes were adjusted to give zero pressure within the constant number, pressure and temperature (NPT) ensemble. Periodic boundary conditions were applied for all the calculations.

Simulation of dynamical mechanical spectroscopy. As in the case of experimental DMS, we apply a sinusoidal strain $\varepsilon(t) = \varepsilon_A \sin(2\pi t/t_\omega)$ along the x direction of the model MG, where t_ω is the period and is selected as 10, 30, 100, 300 and 1,000 ps, while ε_A is selected as 0.625, 1.25, 2.5, 3.75, 5.0, 7.5 and 10% in this work. For each MD-DMS, 10 full cycles were used, that is, t in the range $(0, 10t_\omega)$. We fitted the resulting stress as: $\sigma(t) = \sigma_0 + \sigma_A \sin(2\pi t/t_\omega + \delta)$ where σ_0 is a constant term and usually small ($\sigma_0 < 0.1\sigma_A$ in the glassy state), δ the phase difference between stress and strain. Storage (E') and loss (E'') moduli are calculated as $E' = \sigma_A/\varepsilon_A \cos(\delta)$ and $E'' = \sigma_A/\varepsilon_A \sin(\delta)$, respectively. The MD-DMS was carried out during the cooling processes of the sample preparations, and constant number, volume and temperature (NVT) ensemble was applied during the cyclic deformations. No shear-band formation was observed during the MD-DMS simulations across the entire strain and temperature ranges.

Jump distance probability density functions $p(u)$. The probability density function $p(u)$ is defined as $p(u) = \frac{P(u+\Delta u) - P(u)}{\Delta u}$, where $P(u)$ is the distribution that quantifies the probability of finding $X \leq u$. Here we employ $\Delta u = 0.01$ Å for all the calculations. Note that the probability density is normalized according to $\int_0^\infty p(u) \text{d}(u) = 1$.

References

- Lunkenheimer, P., Schneider, U., Brand, R. & Loid, A. Glassy dynamics. *Contemp. Phys.* **41**, 15–36 (2000).
- Ngai, K. L. *Relaxation and Diffusion in Complex Systems* (Springer, 2011).
- Berthier, L. & Biroli, G. Theoretical perspective on the glass transition and amorphous materials. *Rev. Mod. Phys.* **83**, 587–645 (2011).
- Ediger, M. D. & Harrowell, P. Perspective: supercooled liquids and glasses. *J. Chem. Phys.* **137**, 080901–080915 (2012).
- Angell, C. A., Ngai, K. L., McKenna, G. B., McMillan, P. F. & Martin, S. W. Relaxation in glassforming liquids and amorphous solids. *J. Appl. Phys.* **88**, 3113–3157 (2000).
- Debenedetti, P. G. & Stillinger, F. H. Supercooled liquids and the glass transition. *Nature* **410**, 259–267 (2001).
- Yu, H. B., Wang, W. H. & Samwer, K. The beta relaxation in metallic glasses: an overview. *Mater. Today* **16**, 183–191 (2013).

8. Yu, H. B., Wang, W. H., Bai, H. Y. & Samwer, K. The beta -relaxation in metallic glasses. *Natl Sci. Rev.* **1**, 429–461 (2014).
9. Liu, A. J. & Nagel, S. R. Nonlinear dynamics - Jamming is not just cool any more. *Nature* **396**, 21–22 (1998).
10. Zhang, Z. X. *et al.* Thermal vestige of the zero-temperature jamming transition. *Nature* **459**, 230–233 (2009).
11. Agarwal, P. & Archer, L. A. Strain-accelerated dynamics of soft colloidal glasses. *Phys. Rev. E* **83**, 041402 (2011).
12. Forterre, Y. & Pouliquen, O. Flows of dense granular media. *Annu. Rev. Fluid Mech.* **40**, 1–24 (2008).
13. Guan, P. F., Chen, M. W. & Egami, T. Stress-temperature scaling for steady-state flow in metallic glasses. *Phys. Rev. Lett.* **104**, 205701 (2010).
14. Peng, H. L., Li, M. Z. & Wang, W. H. Stress-versus temperature-induced structural evolution in metallic glasses. *Appl. Phys. Lett.* **102**, 131908 (2013).
15. Zink, M., Samwer, K., Johnson, W. L. & Mayr, S. G. Validity of temperature and time equivalence in metallic glasses during shear deformation. *Phys. Rev. B* **74**, 012201 (2006).
16. Liu, S. T., Jiao, W., Sun, B. A. & Wang, W. H. A quasi-phase perspective on flow units of glass transition and plastic flow in metallic glasses. *J. Non-Cryst. Solids* **376**, 76–80 (2013).
17. Olsson, P. & Teitel, S. Critical scaling of shear viscosity at the jamming transition. *Phys. Rev. Lett.* **99**, 178001 (2007).
18. Trappe, V., Prasad, V., Cipelletti, L., Segre, P. N. & Weitz, D. A. Jamming phase diagram for attractive particles. *Nature* **411**, 772–775 (2001).
19. Wang, L. *et al.* Effect of temperature on the yield strength of a binary CuZr metallic glass: stress-induced glass transition. *Intermetallics* **26**, 162–165 (2012).
20. Yang, B., Liu, C. T. & Nieh, T. G. Unified equation for the strength of bulk metallic glasses. *Appl. Phys. Lett.* **88**, 221911 (2006).
21. Yu, H. B., Wang, W. H., Bai, H. Y., Wu, Y. & Chen, M. W. Relating activation of shear transformation zones to beta relaxations in metallic glasses. *Phys. Rev. B* **81**, 220201 (2010).
22. Johnson, W. L. & Samwer, K. A universal criterion for plastic yielding of metallic glasses with a $(T/T_g)^{2/3}$ temperature dependence. *Phys. Rev. Lett.* **95**, 195501 (2005).
23. Chen, M. W. Mechanical behavior of metallic glasses: microscopic understanding of strength and ductility. *Ann. Rev. Mater. Res.* **38**, 445–469 (2008).
24. Klaumünzer, D. *et al.* Probing shear-band initiation in metallic glasses. *Phys. Rev. Lett.* **107**, 185502 (2011).
25. Schuh, C. A., Hufnagel, T. C. & Ramamurty, U. Overview No.144 - mechanical behavior of amorphous alloys. *Acta Mater.* **55**, 4067–4109 (2007).
26. Greer, A. L., Cheng, Y. Q. & Ma, E. Shear bands in metallic glasses. *Mater. Sci. Eng. R* **74**, 71–132 (2013).
27. Yu, H. B. & Samwer, K. Atomic signature of internal friction in a model metallic glass. *Phys. Rev. B* **90**, 144201 (2014).
28. Richert, R. & Weinstein, S. Nonlinear dielectric response and thermodynamic heterogeneity in liquids. *Phys. Rev. Lett.* **97**, 095703 (2006).
29. Bauer, T., Lunkenheimer, P., Kastner, S. & Loidl, A. Nonlinear dielectric response at the excess wing of glass-forming liquids. *Phys. Rev. Lett.* **110**, 107603 (2013).
30. Angell, C. A. Formation of glasses from liquids and biopolymers. *Science* **267**, 1924–1935 (1995).
31. Böhmer, R., Ngai, K. L., Angell, C. A. & Plazek, D. J. Nonexponential relaxations in strong and fragile glass formers. *J. Chem. Phys.* **99**, 4201–4209 (1993).
32. Ito, K., Moynihan, C. T. & Angell, C. A. Thermodynamic determination of fragility in liquids and a fragile-to-strong liquid transition in water. *Nature* **398**, 492–495 (1999).
33. Bendert, J. C., Gangopadhyay, A. K., Mauro, N. A. & Kelton, K. F. Volume expansion measurements in metallic liquids and their relation to fragility and glass forming ability: an energy landscape interpretation. *Phys. Rev. Lett.* **109**, 185901 (2012).
34. Roland, C. M., Hensel-Bielowka, S., Paluch, M. & Casalini, R. Supercooled dynamics of glass-forming liquids and polymers under hydrostatic pressure. *Rep. Prog. Phys.* **68**, 1405 (2005).
35. Lee, H. N., Paeng, K., Swallen, S. F. & Ediger, M. D. Direct measurement of molecular mobility in actively deformed polymer glasses. *Science* **323**, 231–234 (2009).
36. Mizuno, H. & Yamamoto, R. Dynamical heterogeneity in a highly supercooled liquid under a sheared situation. *J. Chem. Phys.* **136**, 084505 (2012).
37. Stillinger, F. H. A topographic view of supercooled liquids and glass-formation. *Science* **267**, 1935–1939 (1995).
38. Sastry, S., Debenedetti, P. G. & Stillinger, F. H. Signatures of distinct dynamical regimes in the energy landscape of a glass-forming liquid. *Nature* **393**, 554–557 (1998).
39. Plimpton, S. Fast parallel algorithms for short-range molecular dynamics. *J. Comput. Phys.* **117**, 1–19 (1995).
40. Mendelev, M. I. *et al.* Development of suitable interatomic potentials for simulation of liquid and amorphous Cu–Zr alloys. *Philos. Mag.* **89**, 967–987 (2009).

Acknowledgements

We thank Professor C.A. Angell for discussions regarding the definition of fragility and glass transition, as well as Dr W. Huang for discussing nonlinear dielectric effects. We are gratefully acknowledge the support from the Deutsche Forschungsgemeinschaft (DFG) within the FOR 1394 and computational service from Gesellschaft für wissenschaftliche Datenverarbeitung, Göttingen (GWDG).

Author contributions

H.-B.Y. conducted simulations and analysed the results. R.R., R.M. and K.S. initiated the research. All the authors wrote the manuscript together.

Additional information

Competing financial interests: The authors declare no competing financial interests.

Reprints and permission information is available online at <http://npg.nature.com/reprintsandpermissions/>

How to cite this article: Yu, H.-B. *et al.* Strain induced fragility transition in metallic glass. *Nat. Commun.* 6:7179 doi: 10.1038/ncomms8179 (2015).



This work is licensed under a Creative Commons Attribution 4.0 International License. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in the credit line; if the material is not included under the Creative Commons license, users will need to obtain permission from the license holder to reproduce the material. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>