

SCIENTIFIC REPORTS

OPEN

Highly Active 2D Layered MoS₂-rGO Hybrids for Energy Conversion and Storage Applications

Swagatika Kamila^{1,2}, Bishnupad Mohanty^{1,6}, Aneeya K. Samantara^{1,2}, Puspendu Guha^{3,4}, Arnab Ghosh^{3,5}, Bijayalaxmi Jena⁶, Parlapalli V. Satyam^{3,4}, B. K. Mishra^{1,2} & Bikash Kumar Jena^{1,2}

The development of efficient materials for the generation and storage of renewable energy is now an urgent task for future energy demand. In this report, molybdenum disulphide hollow sphere (MoS₂-HS) and its reduced graphene oxide hybrid (rGO/MoS₂-S) have been synthesized and explored for energy generation and storage applications. The surface morphology, crystallinity and elemental composition of the as-synthesized materials have been thoroughly analysed. Inspired by the fascinating morphology of the MoS₂-HS and rGO/MoS₂-S materials, the electrochemical performance towards hydrogen evolution and supercapacitor has been demonstrated. The rGO/MoS₂-S shows enhanced gravimetric capacitance values ($318 \pm 14 \text{ Fg}^{-1}$) with higher specific energy/power outputs ($44.1 \pm 2.1 \text{ Whkg}^{-1}$ and $159.16 \pm 7.0 \text{ Wkg}^{-1}$) and better cyclic performances ($82 \pm 0.95\%$ even after 5000 cycles). Further, a prototype of the supercapacitor in a coin cell configuration has been fabricated and demonstrated towards powering a LED. The unique balance of exposed edge site and electrical conductivity of rGO/MoS₂-S shows remarkably superior HER performances with lower onset over potential ($0.16 \pm 0.05 \text{ V}$), lower Tafel slope ($75 \pm 4 \text{ mVdec}^{-1}$), higher exchange current density ($0.072 \pm 0.023 \text{ mAcm}^{-2}$) and higher TOF ($1.47 \pm 0.085 \text{ s}^{-1}$) values. The dual performance of the rGO/MoS₂-S substantiates the promising application for hydrogen generation and supercapacitor application of interest.

The continuous and widespread use of fossil fuels has led to increased pollution and ecological problems¹. Today these problems have resulted in unrepairable damage and the crisis is such that almost all countries have started switching to alternate energy resources^{2,3}. In this regard, substantial research efforts have been directed to the development of efficient and eco-friendly technologies for the production of energy conversion and storage devices⁴. Out of others, the energy from H₂ has been pursued as a clean and alternative source of fossil fuel. The generation of H₂ from water is the most important method which stands as a potential alternative to our energy demands⁵. The photochemical, photoelectrochemical and electrochemical methods have been broadly used for splitting of water^{6,7}. The electrochemical method is widely adopted due to its higher efficiency, cost effectiveness, and easy instrumental setups. However, the efficient conversion of H₂O to H₂ strongly depends on the activity of the electrode materials. The Pt-based materials are observed to be the most active and benchmark electrocatalyst which catalyses the conversion process nearly at zero overpotential⁸. However, the high cost and scarcity of the material limit its use for rapid commercialisation. Therefore, it demands to develop an alternative, low cost, electrocatalytic active material from abundantly available precursors by an efficient process.

On the other hand, the supercapacitors (SCs) arouse substantial attention due to its ease of fabrication, low cost, negligible environmental concerns, higher power output and excellent cyclic performances over the traditional secondary batteries⁹. These important properties keep the supercapacitor in demand for use as portable storage systems in electronic devices^{10,11}. Among other components of a supercapacitor, the electrode material plays an important role to evaluate the charge storage performance. Therefore, the effort has been devoted to developing different electrode materials like pseudo-capacitive or electrical double layered capacitive (EDLC)

¹CSIR-Institute of Minerals and Materials Technology, Bhubaneswar, 751013, India. ²Academy of Scientific & Innovative Research, New Delhi, 110001, India. ³Institute of Physics, Bhubaneswar-751005, Bhubaneswar, India. ⁴Homi Bhabha National Institute, Training School Complex, Anushakti Nagar, Mumbai, 400085, India. ⁵Department of Physics, Indian Institute of Technology Kharagpur, Kharagpur, 721302, India. ⁶Department of Chemistry, Utkal University, Bhubaneswar, 751004, Odisha, India. Swagatika Kamila and Bishnupad Mohanty contributed equally to this work. Correspondence and requests for materials should be addressed to B.K.J. (email: bikash@immt.res.in)

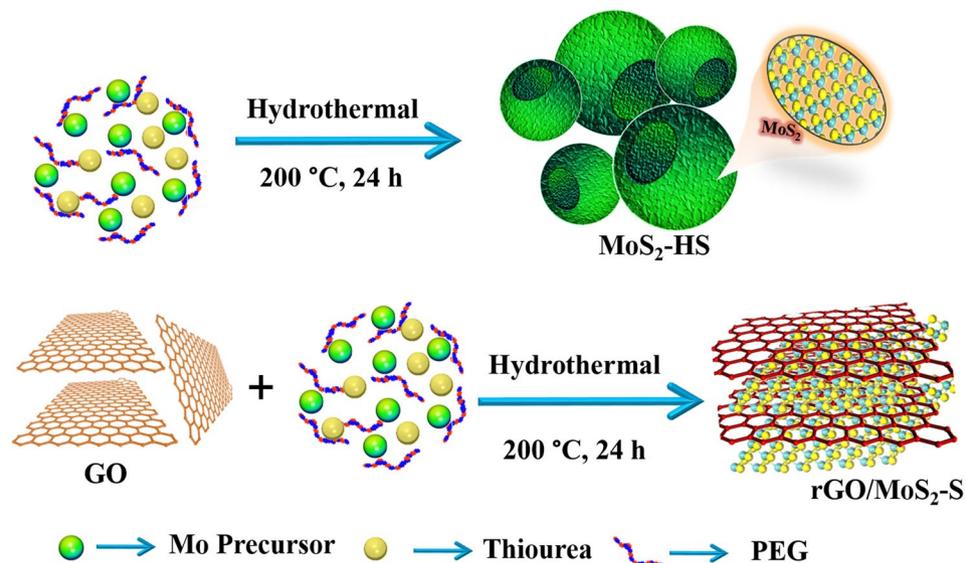


Figure 1. The schematic presentation for the synthesis of MoS₂-HS and rGO/MoS₂-S hybrids.

materials¹². Whereas the prominent redox properties of the pseudo-capacitive materials make them show higher capacitance values compared to the EDLCs¹³. Thus, substantial scientific interest focuses on the development of different pseudocapacitive based materials like metal oxides, sulphides, nitrides and so forth¹⁴. However, the amorphous RuO₂ has found to be an efficient electrode material for supercapacitor performance study, but the high cost and limited existence in the earth crust restrict its commercial application^{15,16}. Therefore, substantial research efforts must be paid to find promising materials with high capacitance behaviour.

Though many of the pseudocapacitive materials have been developed, molybdenum disulphide nanostructures of various surface morphologies show excellent performances¹⁷. Not only the interesting 2D layered structure of MoS₂ avails higher surface area for charge accumulation but also the ion diffusion at the layer interfaces provides the redox properties^{18,19}. The combined effect of both these EDLCs and pseudocapacitive behaviour make the MoS₂ as a suitable material for SC study. However, the lower conductivity and possible aggregation hinder the charge storage performance of the MoS₂ demanding some alternative way of preparation²⁰. The recent studies focus on the substrate mediated synthesis of MoS₂ and their hybrids with the polymers, carbon nanotubes and their mixtures and explored their activities towards the SC and HER^{21–23}. But the multi-step process and cost of the precursor materials demands to prepare MoS₂ based materials in an alternative way using low-cost starting materials. Further, MoS₂ is a nonprecious HER electrocatalyst with higher activity and excellent stability in acid medium. The computational and experimental studies established that the atomic basal plane of MoS₂ has less activity towards HER but the sulphur edge sites of MoS₂ possess excellent catalytic activity towards HER^{24,25}. Therefore, different strategies have been employed to increase the HER activity of MoS₂ by increasing the active sites, the electrical contact of the sites^{26,27}, and exfoliation of layers to increase the surface area²⁸. Also, the effort has been made to increase the activity of basal plane of MoS₂²⁹. The improvement of the electrical conductivity and exposure of more active sites plays an important role to improve the electrocatalytic performance of MoS₂. However, the low intrinsic conductivity and restacking of the layered interfaces limit the performance of MoS₂ for energy conversion and storage applications³⁰.

In this work, MoS₂ nanostructure and its hybrid with reduced graphene oxide have been successfully synthesized. The dual functional activity of the materials has been measured to ascertain the energy storage (supercapacitor) and energy conversion (HER) capacities. The hybridizations boosted the properties of individual components and thereby exhibited higher performance as a whole due to the synergistic contribution.

Result and Discussion

In this work, MoS₂ nanostructure and its reduced graphene oxide hybrid have been synthesized by a facile hydrothermal synthesis method (Fig. 1). Here, ammonium heptamolybdate and thiourea were taken as the Mo and S source. The morphology of MoS₂ was examined with the SEM measurements (Fig. 2). It can be seen that the MoS₂ are in the form of hollow spheres (Fig. 2C). The high resolution of SEM image further reveals that the MoS₂ hollow spheres (MoS₂-HS) are constructed with layers of nanosheets (Fig. 2D). The elemental color mapping and EDS spectrum of as-synthesized MoS₂-HS has been presented in Figure S1. Further, the morphology of the MoS₂-HS was examined by transmission electron microscope (TEM) and the high-resolution TEM (HRTEM). It was observed that each of the hollow spheres constitutes well-arranged nanosheets throughout the surface (Fig. 3). The hi-resolution TEM image shows lattice fringes ≈ 0.63 nm indexed to the (002) plane of hexagonal phase of MoS₂. The presence of diffraction ring patterns in the selected area electron diffraction (SAED) data supports the polycrystalline nature of the MoS₂-HS. The MoS₂ and its graphene hybrids were synthesized and examined with the SEM and TEM measurements (Fig. 4). As it can be seen from SEM images, the rGO/MoS₂-S shows layers of MoS₂ and rGO nanosheets embedded with each other. The distinct structures of MoS₂-HS completely disappeared during the formation of rGO/MoS₂-S. That may be due to the interaction between the functional

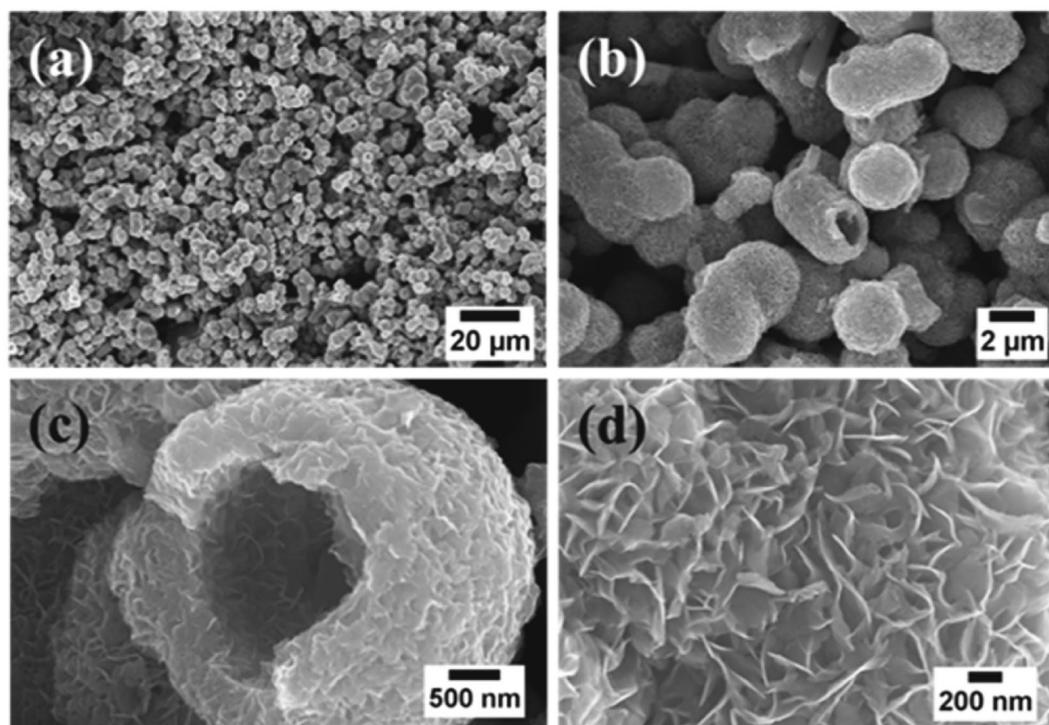


Figure 2. SEM image of MoS₂-HS.

groups of graphene oxide (GO) with Mo precursor which limits the growth of MoS₂ layers to a unique hollow spherical structure as observed in the absence of GO. Interestingly, in the absence of GO, the MoS₂ nanosheets were coalesced to form hollow sphere like morphology (vide infra). The elemental color mapping confirmed the presence of constituent elements (Mo, S, C and O) and clarified the compositional profile of the hybrids (Figure S2). Further, the EDS spectrum shows characteristic X-ray emission peaks for Mo, S, C and O (Figure S3). The TEM measurement reveals that the MoS₂ and graphene sheets are well dispersed and embedded each other in rGO/MoS₂-S (Fig. 4). It clearly demonstrates that the layer structure of MoS₂ is uniformly distributed in the rGO sheet. The HRTEM image reveals the crystal lattice structure of MoS₂ and rGO in rGO/MoS₂-S. The interlayer spacing of MoS₂ and rGO in the hybrid were estimated to be 0.63 nm and 0.33 nm respectively, which can be indexed to their (002) lattice planes (Fig. 4e and g). The SAED measurement supports the presence of distinct ring patterns indexed to the (002), (100) and (110) planes of MoS₂ and (002) plane of rGO in the rGO/MoS₂-S (Fig. 4f).

The XRD characterization was carried out to analyze the structural information for as-synthesized MoS₂-HS and rGO/MoS₂-S (Figure S4). In the case of MoS₂-HS, the diffraction peaks were observed at 2θ of 14°, 32.4°, 35.4°, 43.3° and 57.4° corresponding to the (002), (100), (102), (006), (110) planes respectively (JCPDS 37-1492)³¹. The presence of (002) diffraction peak of MoS₂-HS indicates that the stacking of monolayer MoS₂ takes place along the c axis^{32,33}. In the case of rGO/MoS₂-S, the (002) plane of MoS₂ shifts towards 16.8° which can be estimated a decrease in the interlayer spacing value of 0.63 nm (002 of MoS₂-HS) to 0.52 nm (002 of rGO/MoS₂-S). That signifies the incorporation of graphene within the MoS₂ crystal during the formation of rGO/MoS₂-S³⁴. However, the characteristic signal of rGO in rGO/MoS₂-S was not observed in the XRD patterns. That can be attributed to the low content of rGO in the hybrid³⁵.

The growth of rGO/MoS₂-S was further investigated by the Raman spectroscopy. The MoS₂-HS shows the characteristic bands at 377 cm⁻¹ and 403 cm⁻¹ that are assigned to the in-plane E_{2g}¹ and out of plane A_{1g}¹ vibration modes of hexagonal MoS₂²⁷. The presence of the peaks at 448 cm⁻¹ and 750 cm⁻¹ were assigned to the 2LA(M) and 2E_{2g} vibrational modes of MoS₂, respectively^{36,37}. The additional peaks at 814 cm⁻¹ and 993 cm⁻¹ are assigned to the terminal stretching vibration of Mo = O of MoO₃³⁶. This may be due to the presence of partially oxidised MoS₂ which was formed after getting exposed to air. In the case of rGO/MoS₂-S, the characteristic bands for MoS₂ and rGO were observed and confirmed their presence in the hybrids. Here, the D and G bands of rGO in rGO/MoS₂-S appears at 1351 cm⁻¹ and 1592 cm⁻¹, and the I_D/I_G ratio of the composite was calculated to be 1.05. Whereas, the Raman spectrum of pristine rGO exhibits the characteristic D and G bands at 1345 cm⁻¹ and 1587 cm⁻¹, respectively (Fig. 5, inset) having an I_D/I_G ratio of 1.00³⁸.

The XPS analysis was carried out to deduce the exact elemental composition of the rGO/MoS₂-S (Figure S5). The full scan of the rGO/MoS₂-S gives the characteristic peaks for Mo3d, S2p, C1s and O1s with their corresponding binding energies. The hi-resolution spectrum of Mo3d has been deconvoluted into four characteristic peaks. The strongest signal at 229.8 and 233 eV represents the characteristic bands of Mo3d_{5/2} and Mo3d_{3/2}. Whereas, the signals appeared at 232.8 and 235.6 eV corresponds to the oxidic states of Mo3d_{5/2} and Mo3d_{3/2}. That is due to the presence of MoO₃ or MoO₄²⁻, which usually resulted in slight oxidation of the MoS₂ in exposure

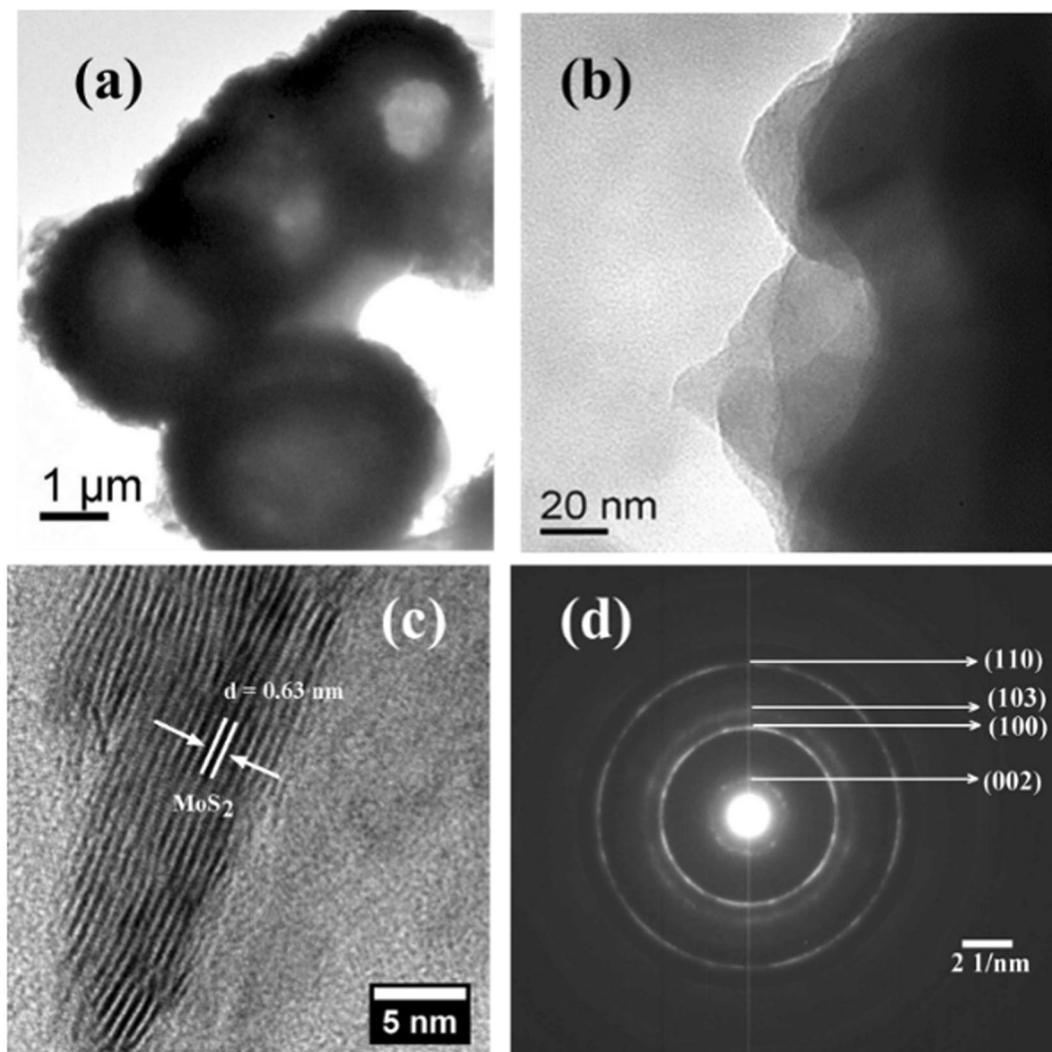


Figure 3. HRTEM image of MoS₂-HS.

to atmosphere^{39–41}. The analysis of S2p regions shows the characteristic peaks at 163 and 164.9 eV for S2p_{3/2} and S2p_{1/2} of MoS₂ phase⁴⁰. The deconvoluted peaks of C1s give signals at 284.7 and 286 eV that are assigned to sp² hybridized graphite-like carbon atom and carbon atom bound to one oxygen atom⁴². The weak peaks observed at 287.2 eV is due to the oxygen functional groups of C=O⁴³. Similarly the XPS spectra of MoS₂-HS was carried out to know the presence of elements at their corresponding binding energies (Figure S6). The high-resolution Mo peak of Mo3d gives the characteristic bands of Mo3d_{5/2} and Mo3d_{3/2} at binding energy of 229.8 and 233 eV, respectively. Also, the S2p regions give similar observation like in rGO/MoS₂-S composite. Further, the specific surface area of as-synthesized materials were estimated by measuring the N₂ adsorption desorption isotherms at 77 K using the Brunauer-Emmett-Teller method (Figure S7). The rGO/MoS₂-S hybrid shows higher specific surface area of 104 m²/g compared to the pristine MoS₂-HS (4 m²/g) and rGO (19 m²/g).

The interesting structure of MoS₂-HS and its graphene hybrids inspired to study their activity towards energy storage (supercapacitor) and energy conversion (HER) applications. The cyclic voltammetry (CV) and galvanostatic charge-discharge (GCD) techniques were employed in a two compartment three electrodes electrochemical cell to evaluate the electrochemical supercapacitor performance of the as-synthesized materials. Here, the sample modified glassy carbon was taken as the working electrode, Ag/AgCl as the reference and bare platinum wire as the counter electrode in 1 M Na₂SO₄ aqueous electrolyte. The overlapped CV and GCD profiles of MoS₂-HS, rGO and rGO/MoS₂-S are shown in Figure S8. From CV, the rGO/MoS₂-S gives humps like a peak at a higher potential and is attributed the pseudocapacitance effect of MoS₂ to the total capacitance behaviour of the hybrid material. Also, the cycle life of the as-synthesized materials was studied in three electrode system. Interestingly, the rGO/MoS₂-S shows a retention of 84.4 ± 0.55% of initial capacitance value as compared to the rGO (79.4 ± 0.6%) and MoS₂-HS (75.8 ± 1%) even after 5000 repeated cycles. That can be ascribed to the synergetic role of both the rGO and MoS₂ in enhancing the capacitance retention performance of the rGO/MoS₂-S.

For the practical application of the as-synthesized material, the electrochemical energy storage performance in a symmetrical two electrode system has been demonstrated. The two electrode design reflects the physical

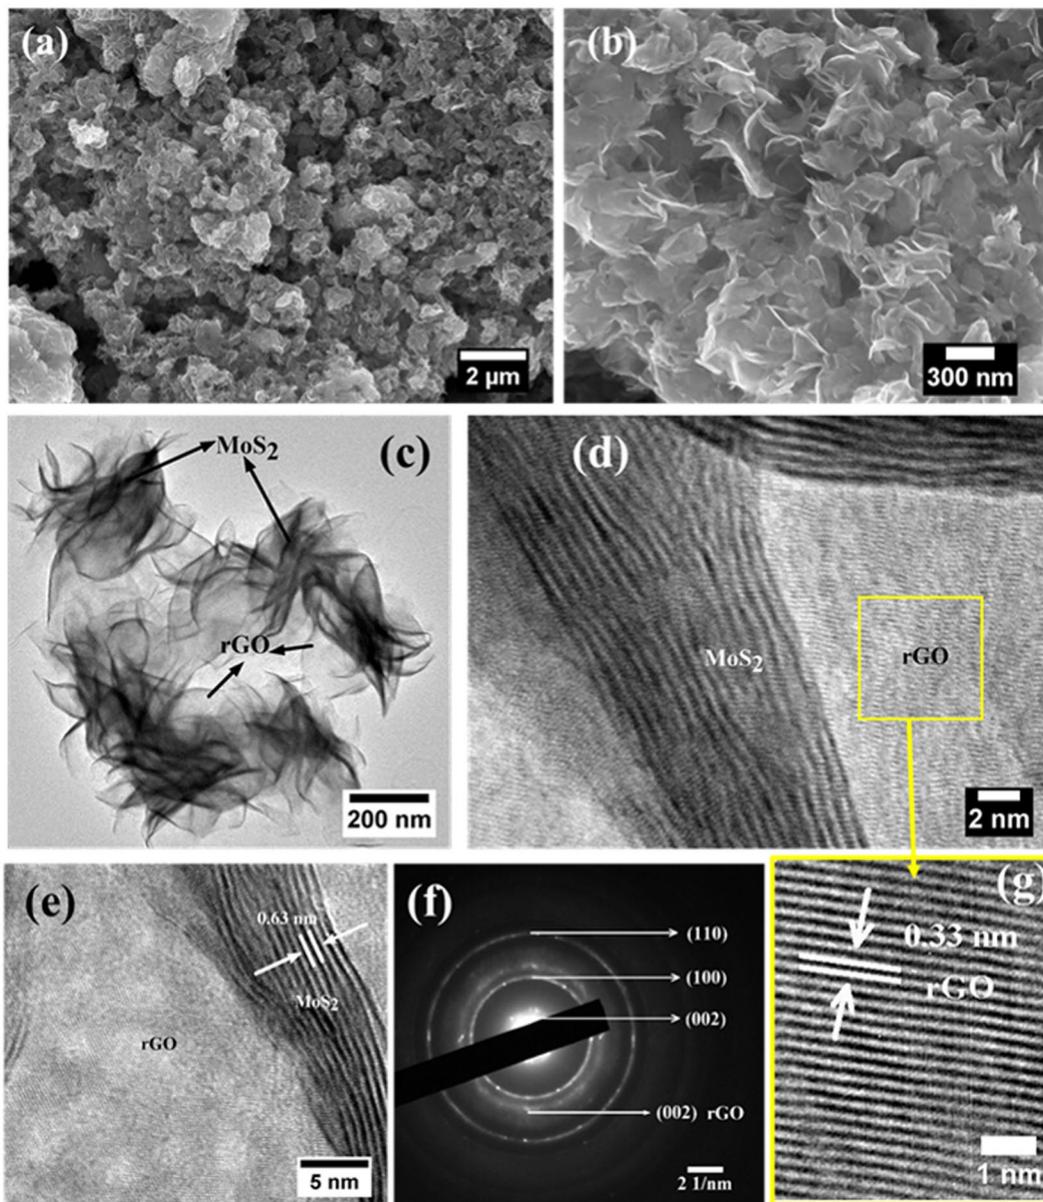


Figure 4. SEM (a,b) and HRTEM (c-g) image of the rGO/MoS₂-S.

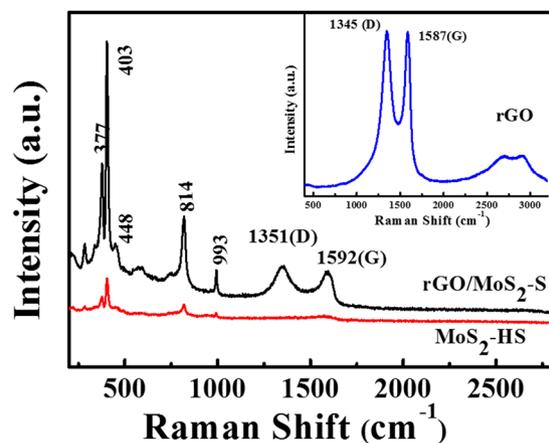


Figure 5. The Raman Spectra of MoS₂-HS and rGO/MoS₂-S hybrid.

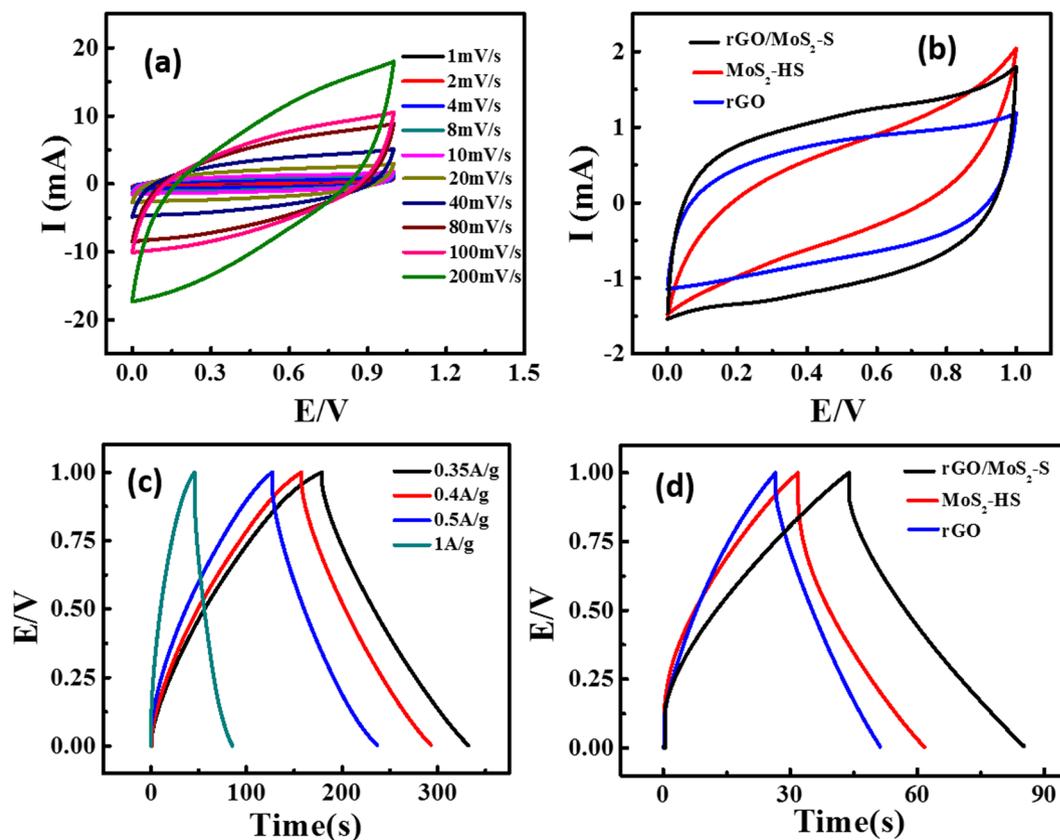


Figure 6. (a) CV of rGO/MoS₂-S hybrid at different scan rate (1 to 200 mV/s), (b) CV of MoS₂-HS, rGO and rGO/MoS₂-S hybrid at 10 mV/s, (c) GCD data of rGO/MoS₂-S hybrid at different current density and (d) GCD of MoS₂-HS, rGO and rGO/MoS₂-S hybrid at a current density of 1 A/g.

configuration, internal voltages, and capacitance of a packaged supercapacitor⁴⁴. The CV performance of rGO/MoS₂-S materials at different scan rates are presented in (Fig. 6a). The area under the CV curve shows rectangular and symmetric pattern revealing the better choice for energy storage application. Similarly, the CV performance of MoS₂-HS and rGO were recorded under the same conditions (Figure S9). The overlapped CV curves of MoS₂-HS, rGO and rGO/MoS₂-S are presented in (Fig. 6b). The area under the CV curve of rGO/MoS₂-S was found to be larger than the rGO and MoS₂-HS electrode. This observation indicates that the hybrid material shows good capacitive behaviour due to a synergistic contribution of both MoS₂ and rGO. The specific capacitance of the symmetrical supercapacitor was calculated from CV profile following equation 1.

$$C_{sp} = 2 \times \frac{\int I(V)dV}{\nu m \Delta V} \quad (1)$$

Where $\int I(V)dV$ is the area under the CV curve, m is the mass of the electrode materials, ν is the scan rate, and ΔV is the potential window taken. The rGO/MoS₂-S give highest specific capacitance of $318 \pm 14 \text{ F g}^{-1}$ compared to rGO ($186 \pm 12.6 \text{ F g}^{-1}$) and MoS₂-HS ($204 \pm 17.6 \text{ F g}^{-1}$) at a scan rate of 1 mV s^{-1} . Here, the hybrids show the capacitance behaviour approximately 1.7 and 1.5 times greater than rGO and MoS₂-HS electrode material, respectively. Similarly, the galvanostatic charge-discharge (GCD) technique was carried to know the capacitance behaviour of as-synthesized materials at different current densities (Fig. 6c). The GCD curve of rGO/MoS₂-S shows the symmetric charging and discharging curve. That reveals the good capacitive behaviour of hybrids. The GCD performance of the pristine rGO and MoS₂ electrodes were carried out for comparison (Fig. 6d). The specific capacitance of the hybrid material was derived from GCD curve following equation 2⁴⁵.

$$C_{sp} = 4 \frac{I}{m(dV/dt)} \quad (2)$$

Where m is the mass of material taken and dV/dt is the slope of the discharge plot at constant current 'I'. The specific capacitance of rGO/MoS₂-S was found to be $190 \pm 9.5 \text{ F g}^{-1}$ which is higher compared to MoS₂-HS ($97.5 \pm 3.5 \text{ F g}^{-1}$) and rGO ($69.5 \pm 2 \text{ F g}^{-1}$) at 1 A g^{-1} current density. Here, the unique structure of the rGO/MoS₂-S material shows better electrochemical behaviour over the rGO and MoS₂-HS electrode which is validated by both the CV and GCD data. That signifies the synergetic role of rGO and MoS₂ towards enhancement in capacitor performance of the rGO/MoS₂-S material. This enhancement could be due to easy intercalation of

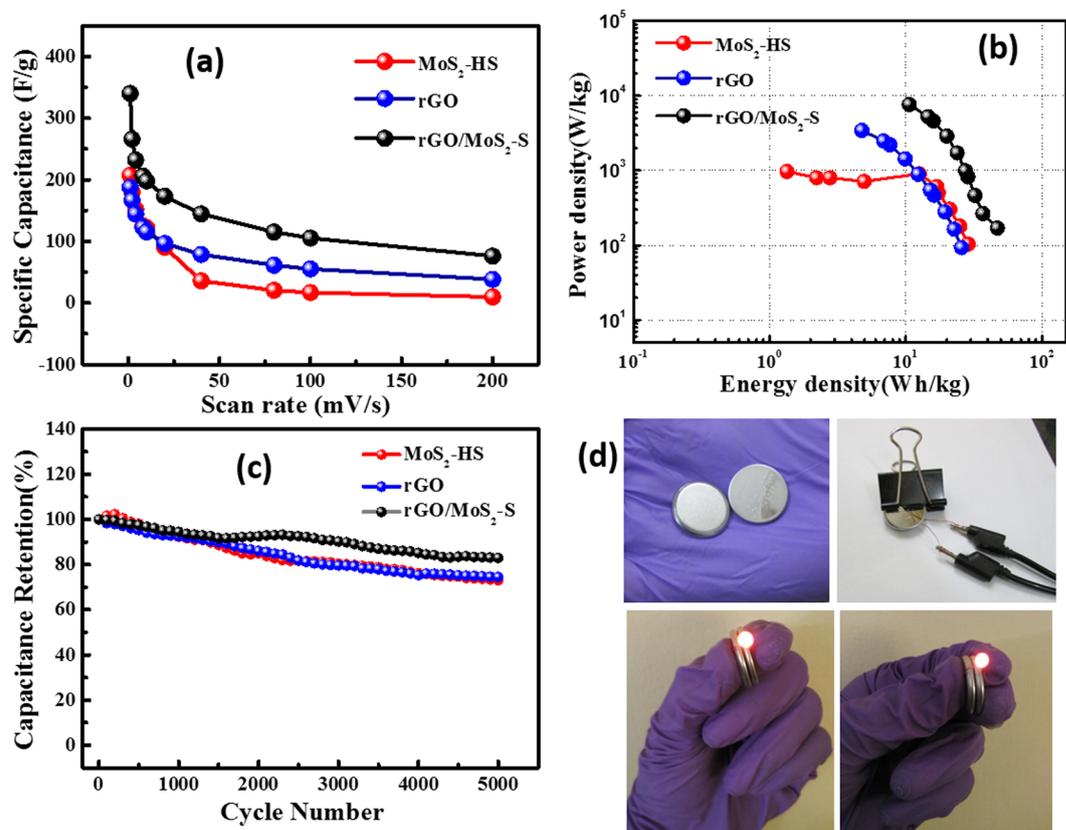


Figure 7. (a) Plot of specific capacitance vs. scan rates, (b) Ragone plot (energy density vs power density) (c) Plot of capacitance retention at different cycles of MoS₂-HS, rGO and rGO/MoS₂-S hybrid and (d) Photograph demonstrating the powering of a red LED with a stack of two coin cell type supercapacitor device fabricated from rGO/MoS₂-S hybrid.

ions through the Van der Waals gap of MoS₂ and rGO layers. The presence of rGO in the hybrid material may prevent the agglomeration of the MoS₂ nanosheets. Therefore, the hybrid possesses more active sites towards the accessibility of electrolyte ion and thereby enhances the capacitance behaviour of the hybrid material. For comparison with available data, the performance of the as-synthesized electrode materials based on MoS₂ particularly concerning capacitance is summarized in Table S1^{18,46–49}. It has been observed that the rGO/MoS₂-S material has unique characteristics and holds potential for supercapacitor application. The hybrid materials were synthesized at different concentration of GO to explore the effect of rGO content towards the capacitance behaviour. Here, the materials synthesized in the presence of 5 mg, 10 mg and 20 mg of the GO in 30 ml of the reaction solution are referred as rGO/MoS₂-S(5), rGO/MoS₂-S and rGO/MoS₂-S(20), respectively. The CV and GCD measurements of the materials were carried with the similar two electrode system and presented in Figure S10. From CV measurement, It has been observed that the capacitance value increases on increasing the rGO content from rGO/MoS₂-S(5) to rGO/MoS₂-S. However, the performance decreased at higher rGO content rGO/MoS₂-S(20). The GCD measurement reveals the similar performance patterns. So, the rGO content plays the significant role during the growth of rGO/MoS₂-S and decides the performance towards supercapacitor application.

The specific capacitance value of the rGO/MoS₂-S was estimated at different scan rates (Fig. 7a). It has been observed that on increasing the scan rate, the capacitive value decreases. Usually, at higher scan rate, sufficient ion diffusion cannot take place within a constant time, and therefore, reflects a reduction of capacitance values^{50,51}. The energy density (ED) and power density (PD) were calculated from cyclic voltammograms by following the equations 3 and 4⁵²,

$$E. D. = \frac{1}{2} C_{sp} (\Delta V)^2 \quad (3)$$

$$P. D. = \frac{1}{2} C_{sp} (\Delta V) \nu \quad (4)$$

The Ragone plots (a plot of ED vs. PD) for MoS₂-HS, rGO and rGO/MoS₂-S are presented in Fig. 7b. From this plot, the ED and PD values of rGO/MoS₂-S found to be $44.1 \pm 2.1 \text{ Wh kg}^{-1}$ and $159.16 \pm 7.0 \text{ W kg}^{-1}$, respectively. It possesses greater specific energy and power density compared to rGO ($25.8 \pm 1.7 \text{ Wh kg}^{-1}$ and $93.4 \pm 6.3 \text{ W kg}^{-1}$) and MoS₂-HS ($29.17 \pm 1.6 \text{ Wh kg}^{-1}$ and $105.33 \pm 5.7 \text{ W kg}^{-1}$) electrodes, respectively. The

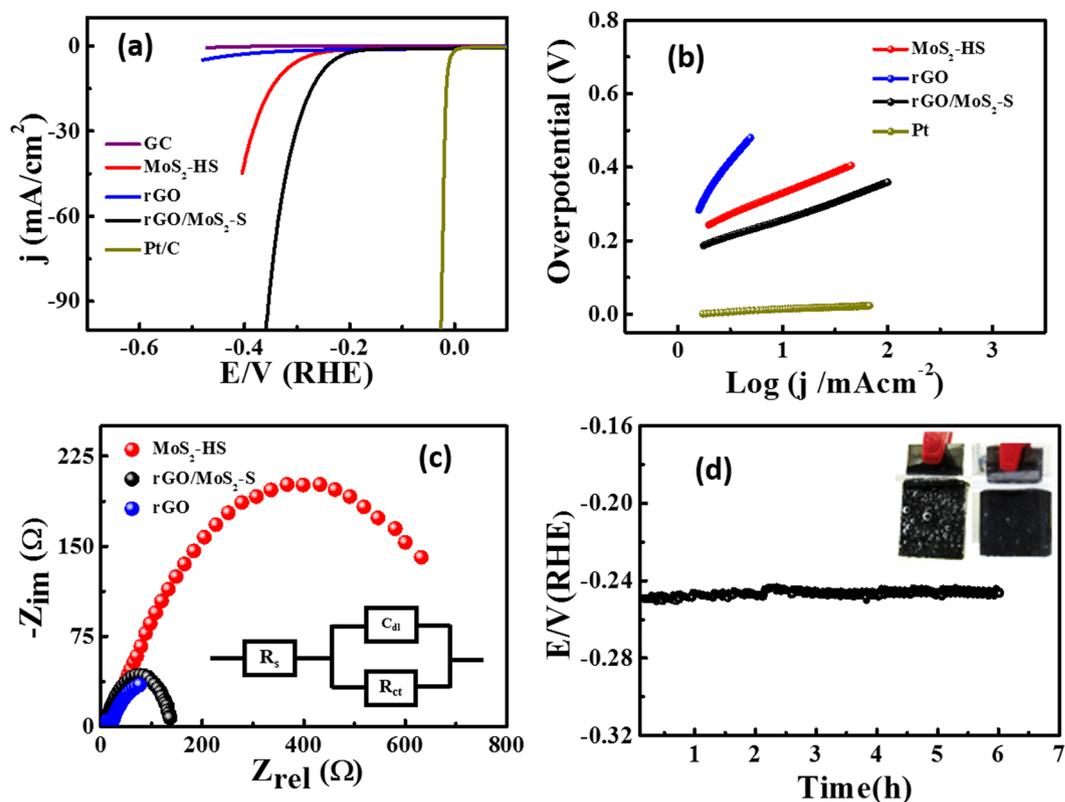


Figure 8. (a) Linear sweep voltammograms (LSV) of bare GC, Pt/C, MoS₂-HS, rGO and rGO/MoS₂-S hybrid modified electrodes towards HER in 1 M H₂SO₄ at a sweep rate of 5 mV/s, (b) Corresponding Tafel plots, (c) Nyquist plots of MoS₂-HS, rGO and rGO/MoS₂-S hybrid modified electrodes. (d) The long-term stability of rGO/MoS₂-S hybrid at 10 mA/cm² and the inset in (d) shows the photograph of the rGO/MoS₂-S hybrid modified electrode before and during the time of the stability test.

long-term cycling stability is one of the most important factors for practical application of a supercapacitor material. Therefore, the cycling stability of the materials has been evaluated using CV technique. Very interestingly, it has been observed that the rGO/MoS₂-S shows $82 \pm 0.95\%$ retention of initial capacitance values compared to MoS₂-HS ($72 \pm 1.3\%$) and rGO ($74.1 \pm 0.5\%$) even after 5000 repeated cycles (Fig. 7c). The cycle life of rGO/MoS₂-S is compared with existing literature and presented in Table S1.

Indeed it is worth to verify the morphology and elemental composition change of the rGO/MoS₂-S after the capacitance retention test. The post capacitance stability characterisations of rGO/MoS₂-S was carried by TEM, FESEM, XRD and Raman measurements. The TEM and FESEM images before and after the capacitance retention test are presented in the Figure S11. Interestingly, no such significant change in the morphology of the rGO/MoS₂-S was observed. That signify the robust nature of the rGO/MoS₂-S. The post XRD showed the similar diffraction peaks for MoS₂, but some shift in the 002 plane was observed (Figure S12a). In addition some characteristic peaks appeared for the Na₂SO₄ used as the electrolyte. Whereas, the post Raman characterization supports the retention of the characteristic bands for the MoS₂ and rGO in the hybrids (Figure S12b). But, the peaks at around 814 and 993 cm⁻¹ corresponding to the MoO₃ got decreased. Thus, the characterisations data after capacitance stability test revealed the real phenomena of the as-synthesized materials and guided to improve the performance.

A simple application to power a red light emitting diode (LED) has been demonstrated to validate the potential usefulness of the rGO/MoS₂-S material based SCs (Fig. 7d). For this purpose, two coin cell supercapacitors (CR2025) were connected in series to extend the potential window for the tandem device. It is clear that the coin cell supercapacitor can power one red LED. The observation and demonstration make a strong case for rGO/MoS₂-S as a potential supercapacitor material for wider application of interest.

The interesting structure of MoS₂ and its graphene hybrid material motivated us to investigate the performance for hydrogen evolution. Figure 8a shows the linear sweep voltammetry of the MoS₂-HS and rGO/MoS₂-S modified GC electrodes in 0.5 M H₂SO₄. The iR compensation has been carried out for all the LSV measurements. The LSV data before and after iR compensation has been presented in Figure S13. The control experiments on bare GC and rGO modified GC were also performed for verification and benchmarked against Pt/C catalyst. It is apparent that the blank GC does not show any HER activity before -0.4 V (vs. RHE) and the rGO too shows no such significant HER activity compared to MoS₂-HS and rGO/MoS₂-S. Interestingly, the rapid cathodic current rises beyond -0.145 V in the case of rGO/MoS₂-S was observed which is indicative of the higher electrocatalytic activity towards the HER. It is surprising that rGO/MoS₂-S shows higher cathodic current density with a lower onset overpotential of 0.16 ± 0.05 V than the MoS₂-HS. The rGO/MoS₂-S yields the state-of-art current

density of 10 mA cm^{-2} at an overpotential of $0.25 \pm 0.04 \text{ V}$. It shows lower activity compared to the state-of-the-art catalyst, namely Pt/C. However, against the cost and scarcity of Pt, rGO/MoS₂-S stands out for the lower cost, abundance, and ease of production. The kinetics of the as-synthesized material for HER was investigated by measuring the Tafel slope (Fig. 8b)⁵³. The Tafel slope analysis reveals the possible mechanism involved in the HER process. In theory, the mechanism for conversion of H⁺ to H₂ follows three main paths in acidic medium. In the first step, the electrochemical hydrogen adsorption reaction takes place ($\text{H}_3\text{O}^+ + \text{e}^- \rightarrow \text{H}_{\text{ads}} + \text{H}_2\text{O}$) and refers as Volmer reaction. The second step follows the electrochemical desorption path ($\text{H}_{\text{ads}} + \text{H}_3\text{O}^+ + \text{e}^- \rightarrow \text{H}_2 + \text{H}_2\text{O}$) and refers as the Heyrovsky reaction. The final step involves the recombination path $\text{H}_{\text{ads}} + \text{H}_{\text{ads}} \rightarrow \text{H}_2$ and refers as the Tafel reaction. The evolution of hydrogen follows either the Volmer-Heyrovsky or Volmer-Tafel reaction mechanism⁵⁴. Concerning to the previous reports, the Tafel slope value of $\approx 30 \text{ mV dec}^{-1}$, $\approx 40 \text{ mV dec}^{-1}$ and $\approx 120 \text{ mV dec}^{-1}$ represents the Tafel, Heyrovsky and Volmer reactions, respectively as the rate determining step of HER²⁶. The Tafel slope of $75 \pm 4 \text{ mV dec}^{-1}$ for rGO/MoS₂-S indicate that the reaction proceeds through the Volmer-Heyrovsky mechanism⁵⁵. The rGO/MoS₂-S exhibits lower Tafel slope compared to the MoS₂-HS. The enhanced electrocatalytic properties of rGO/MoS₂-S may be attributed to a strong chemical and electronic interaction between rGO and MoS₂ which provides the efficient electrical commutation between the catalytic edge sites and the core material. Though the Tafel slope of rGO/MoS₂-S is higher than that obtained for the benchmarked Pt/C catalyst (30 mV dec^{-1}), it showed lower value compared to the previous reports⁵⁶. Further, a comparison was made on the performance of some state-of-the-art catalysts and summarized in Table S2. No doubt rGO/MoS₂-S finds a place as one of the efficient catalytic materials for HER. Further, the exchange current density (j_0) of rGO/MoS₂-S, MoS₂-HS and Pt/C were calculated from Tafel plot using the extrapolation methods and presented in Figure S14. The rGO/MoS₂-S exhibits the higher exchange current density (j_0) of $0.072 \pm 0.023 \text{ mA cm}^{-2}$ compared to the pristine MoS₂-HS ($0.030 \pm 0.025 \text{ mA cm}^{-2}$). That signifies the higher activity of the rGO/MoS₂-S towards HER. It is worth to compare the j_0 value of the rGO-MoS₂-S with the MoS₂ based materials of the previous report. For example, the rGO-MoS₂-S shows higher j_0 compared to defect-rich MoS₂ ($8.91 \times 10^{-3} \text{ mA cm}^{-2}$)⁵⁷, double-gyroid MoS₂/FTO ($6.9 \times 10^{-4} \text{ mA cm}^{-2}$)⁵⁸, Core-shell MoO₃-MoS₂/FTO ($8.2 \times 10^{-5} \text{ mA cm}^{-2}$)⁵⁹, MoS₃ particle ($6.3 \times 10^{-7} \text{ mA cm}^{-2}$)⁶⁰, MoS₃/FTO ($1.3 \times 10^{-7} \text{ mA cm}^{-2}$)⁶¹, CoS₂@MoS₂/RGO ($0.0246 \text{ mA cm}^{-2}$)⁶², and Cu-MoS₂/rGO ($77.6 \times 10^{-3} \text{ mA cm}^{-2}$)⁶³.

Electrochemical impedance spectroscopy (EIS) measurement was carried out to understand the role of electrode kinetics and interface reaction of MoS₂ and its graphene hybrid on HER. The Nyquist plots of the samples are presented in Fig. 8c. The observed semi-circle is due to the charge transfer resistance (R_{ct}) at the electrode and electrolyte interface. From the impedance fitting, it has been observed that the rGO/MoS₂-S presents lower charge transfers resistance (R_{ct}) of 80Ω in comparison to MoS₂-HS (372Ω). Lower the R_{ct} value of the rGO/MoS₂-S better is the enhancement in the electron transfer process which goes to enhance HER.

The stability of rGO/MoS₂-S catalyst for HER was further analysed by Chronopotentiometric electrolysis at a current density of 10 mA cm^{-2} (Fig. 8d). After 6 h of continuous electrolysis, $\sim 6 \text{ mV}$ decrease in over potential was observed that indicates a standard level of stability for long term operation. A movie recorded during the hydrogen evolution from the rGO/MoS₂-S glassy carbon plate electrode is presented in the supporting information (Movie S1). Also, the stability of rGO/MoS₂-S was carried out with continuous potential cycling the samples over 2000 cycles. The LSV data before and after the potential cycles was recorded (Figure S15a). Interestingly, only a 5 mV difference in the overpotential at the benchmark current density of 10 mA cm^{-2} was observed. That signifies that the rGO/MoS₂-S is a robust electrocatalyst for HER application to endure from accelerated degradation. Further, the stability of the catalysts before and after the potential cycle was correlated with their before and after cycle EIS measurements (Figure S15b). The R_{ct} values were evaluated from the impedance fitting. The R_{ct} values of rGO/MoS₂-S before and after stability cycles were estimated to be 80Ω and 78Ω , respectively.

Like the capacitance retention test, it is essential to verify the morphology and elemental composition change of the rGO/MoS₂-S after the HER stability. The post HER characterisations of rGO/MoS₂-S was carried by TEM, FESEM, XRD, Raman and XPS measurements. The TEM and FESEM images before and after the HER stability test is presented in the Figure S16. Interestingly, no such significant change in the morphology of the rGO/MoS₂-S was observed. The elemental color mapping spectrum clearly signifies the presence of constituent elements of rGO/MoS₂-S (Figure S17). That signifies the robust nature of the rGO/MoS₂-S towards HER. The post-XRD showed the similar diffraction peaks for MoS₂ but shifting in the (002) plane was observed (Figure S18a). The post-Raman characterization supports the retention of the characteristic bands for the MoS₂ and rGO in the hybrids (Figure S18b). But, the peaks at around 814 and 993 cm^{-1} corresponding to the MoO₃ substantially vanished. Further, the XPS data before and after HER stability test is also presented in Figure S19. The full scan of the rGO/MoS₂-S after HER gives the characteristic peaks for Mo3d, S2p, C1s and O1s with their corresponding binding energies. No such significant change in the peak position was observed. However, an intense peak at 688 eV was appeared and identified as the characteristic peak for F1s. That has been contributed from the Nafion used as a binder for casting the rGO/MoS₂-S on the electrode surface (experimental section). The deconvolution of high resolution spectra of Mo3d, S2p and O1s was carried out to reveal any changes of the material after HER stability test (Figure S20). No such substantial change in the peak pattern was observed. However, the ratio in the area under the curve for Mo3d and its oxidic peaks was increased. That signifies the reduction of the oxidic states after prolong HER test.

To understand the intrinsic electrocatalytic activity of MoS₂-HS and rGO/MoS₂-S, the turnover frequency (TOF) of the catalyst has been evaluated⁶⁴. First, the number of active sites (n) was calculated from the cyclic voltammetry data measured in the potential range of -0.2 to $+0.6 \text{ V}$ (vs. RHE) in 1 M phosphate buffer ($\text{pH} = 7$) electrolyte at a sweep rate of 50 mVs^{-1} (Figure S21). Here n is directly proportional to the integrated charge (Q_{cv}) obtained from the CV measurement and was derived using the equation ^{56,64}.

$$n = \frac{Q_{cv}}{2F} \quad (5)$$

Where F is the Faraday constant (96485 C mol^{-1}). The value of n for MoS_2 -HS and rGO/MoS_2 -S was estimated to be 1.55×10^{-8} and 6.8×10^{-9} , respectively. Thus, the TOF value can be calculated using the equation ⁶⁴.

$$\text{TOF} = \frac{I}{2 \times F \times n} \quad (6)$$

Where I , F and n are referred as current (A), Faraday constant (96485 C mol^{-1}) and number of active sites, respectively. The TOF was calculated to be 0.623 s^{-1} and 1.47 s^{-1} for MoS_2 -HS and rGO/MoS_2 -S respectively at an overpotential of 250 mV that produces the benchmark current density of 10 mA cm^{-2} . At the overpotential of 200 mV s^{-1} , the TOF of MoS_2 -HS and rGO/MoS_2 -S was estimated to be 0.107 s^{-1} and 0.340 s^{-1} , respectively. It is pertinent to compare the TOF values of rGO/MoS_2 -S with the MoS_x based catalyst of previous reports following the above methodology^{61, 65, 66}. For example, rGO/MoS_2 -S shows higher TOF compared to amorphous molybdenum plasma pre-treatment (PP) and electrochemical pre-treatment (EP) amorphous molybdenum sulphide on carbon fiber catalysts (0.32 , 0.23 and 0.15 s^{-1} for $\text{MoS}_x/\text{PP-CFP}$, $\text{MoS}_x/\text{EP-CFP}$ and $\text{MoS}_x/\text{N-CFP}$, respectively at 200 mV)⁶⁶, amorphous molybdenum sulphide film (MoS_3 -CV) catalyst (0.3 s^{-1} at 340 mV). The above observations reveal that the rGO/MoS_2 -S holds certain position concerning higher activity that enhances HER.

In summary, a single-step hydrothermal process has been followed for the synthesis of rGO/MoS_2 -S materials. The electrochemical performance of the hybrid material has been analysed for both the energy conversion and storage applications especially in respect to HER and supercapacitor of interest, respectively. The rGO/MoS_2 -S gives a specific capacitance of $318 \pm 14 \text{ F g}^{-1}$ with enhanced energy and power density ($44.1 \pm 2.1 \text{ Wh kg}^{-1}$ and $159.16 \pm 7.0 \text{ W kg}^{-1}$) having capacitance retention of $82 \pm 0.95\%$ even after 5000 repeated cycles. Along with the storage efficiency, the rGO/MoS_2 -S shows enhanced performance as a cathode electrocatalyst for HER. It requires only $0.25 \pm 0.04 \text{ V}$ overpotential to deliver a current density of 10 mA cm^{-2} with a lower Tafel slope of $75 \pm 4 \text{ mV dec}^{-1}$. That has been supported by a higher TOF value ($1.47 \pm 0.085 \text{ s}^{-1}$) and long term operational stability. The synergistic effect of MoS_2 and rGO enhances intercalation and transfer process of ions and prevents layered stacking with exposure of additional active edges that are responsible for better energy storage and HER performance. This report provides an interesting method for production of MoS_2 and its graphene hybrids for potential applications as the electrode material for future energy conversion and storage of general interest.

Methods

Materials. Ammonium heptamolybdate, tetrahydrate $[(\text{NH}_4)_6\text{Mo}_7\text{O}_{24} \cdot 4\text{H}_2\text{O}]$, 99.0%, thiourea (NH_2CSNH_2 , 99%), polyethylene glycol [(PEG)-4000, 99%] were purchased from Himedia, India. The Nafion was procured from Sigma-Aldrich. The deionised (DI) water was obtained by Millipore milli-Q water purification system ($18.2 \text{ M } \Omega$). All the reagents were directly used without further purification

Preparation of GO and rGO. The synthesis of graphene oxide was carried out by modified Hummer's method⁶⁷. Briefly, 1 g of graphite powder was dispersed in 25 ml of concentrated sulphuric acid. Then, 6 g of KMnO_4 was added slowly to it under ice-cooled condition. Then, it was allowed for continuous stirring up to 2 h at room temperature. Afterward, 50 ml of H_2O was added under ice-cooled condition followed by slow addition of H_2O_2 (30%) till the effervescence of gas seized. The colour of the suspension was changed from brown to yellow. Then, the suspension was filtered and washed with copious amount of 0.1 M HCl and followed by DI H_2O to remove the SO_4^{2-} ion. The resulting solid was dried under vacuum and stored for prior use. For the synthesis of reduced graphene oxide (rGO), an aqueous dispersion of GO was made by taking 10 mg of GO in 30 ml of deionised H_2O followed by 30 minutes of sonication. Then, the aqueous GO dispersion was taken in a 50 ml Teflon-lined stainless steel autoclave. The autoclave was kept at 200°C for 24 h in an oven for the hydrothermal reduction of GO to rGO. The rGO was collected and dried in a hot air oven and kept it prior to use.

Synthesis of MoS_2 hollow spheres (MoS_2 -HS). MoS_2 -HS was synthesized by a facile one-step hydrothermal process. In this experiment 0.6 g of ammonium heptamolybdate, 0.75 g of thiourea, and 0.7 g of PEG were mixed in 30 ml DI water and sonicated for 45 minutes. Then, the solution was taken in a Teflon-lined 50 ml stainless-steel autoclave and treated at 200°C for 24 h . The precipitate was collected after cooling down to room temperature and washed with DI water followed by ethanol for several times. The sample was dried in an oven for 12 h at 80°C and stored in a desiccator for future use.

Synthesis of rGO and MoS_2 hybrids (rGO/MoS_2 -S). The rGO/MoS_2 -S was synthesized in the presence of GO by the same method followed by MoS_2 hollow sphere synthesis. In brief, 0.01 g of GO dispersion in 30 ml DI H_2O , 0.6 g of ammonium heptamolybdate, 0.75 g of thiourea and 0.7 g of PEG were mixed with constant stirring for 30 minutes. The solution was transferred to a Teflon-lined 50 ml stainless-steel autoclave and treated at 200°C for 24 h . After natural cooling to room temperature, the precipitate was collected by centrifugation and washed with DI water followed by ethanol for several times. The sample was dried in an oven for 12 h at 80°C and stored in a desiccator for future use.

Electrode preparation. Electrode preparation for supercapacitor testing was carried out with Swagelok type two electrode cell (Figure S22). For this setup, two symmetrical stainless steel electrodes were taken. The homogenous dispersion of well-ground materials sample in ethanol was coated on both the electrodes by drop cast and then dried under vacuum. The cellulose nitrate membrane (of 13 mm diameter) was soaked in a $1 \text{ M Na}_2\text{SO}_4$ electrolyte solution and used as a separator between the two electrodes. The membrane and materials

modified electrode was fitted by Swagelok type setup. The measurements for supercapacitor testing were carried out with Bio-logic Science instrument (VSP-300). The electrochemical performance was also studied by the three-electrode system. For this setup, glassy carbon electrode was used as the working electrode, a platinum wire as the counter, an Ag/AgCl as the reference and 1 M Na₂SO₄ used as the electrolyte. In this process for sample loading, 1 mg of as-synthesized samples are separately dispersed in a mixture of 90 µl of ethanol and 10 µl of Nafion (as a binder) sonicated properly to get a homogenous solution. From the above mixture, 10 µl of the solution drop casted on glassy carbon electrode and vacuum dried. Then the electrode was taken for electrochemical study in Bio-logic Science instrument (VSP-300).

The hydrogen evolution reaction was performed with a two-compartment three-electrode cell system containing Platinum wire as the counter electrode, Ag/AgCl as the reference electrode and a glassy carbon (GC, geometrical surface area: 0.07 cm²) as the working electrode. In a typical experiment, mixtures of 5% Nafion and as-synthesized samples were prepared and drop casted on GC electrode (of loading 2 mg cm⁻²) followed by vacuum drying. The linear sweep voltammetry was recorded using a computer-controlled Bio-logic science instrument (VSP-300). The electrochemical impedance spectroscopy (EIS) were measured on the same instrument at 1 Hz to 100 kHz, and the data are presented with the Nyquist plot. The potential reported in this report was calculated against the reversible hydrogen electrode (RHE). The potential conversion from Ag/AgCl to RHE was carried out according to equation (7) reported elsewhere²⁷.

$$E_{RHE} = E_{Ag/AgCl} + 0.059pH + E_{Ag/AgCl}^0 \quad (7)$$

References

- Chow, J., Kopp, R. J. & Portney, P. R. Energy Resources and Global Development. *Science* **302**, 1528–1531 (2003).
- Dresselhaus, M. S. & Thomas, I. L. Alternative energy technologies. *Nature* **414**, 332–337 (2001).
- Chu, S. & Majumdar, A. Opportunities and challenges for a sustainable energy future. *Nature* **488**, 294–303 (2012).
- Turner, J. A. A Realizable Renewable Energy Future. *Science* **285**, 687–689 (1999).
- Turner, J. A. Sustainable Hydrogen Production. *Science* **305**, 972–974 (2004).
- Laursen, A. B., Kegnaes, S., Dahl, S. & Chorkendorff, I. Molybdenum sulfides-efficient and viable materials for electro- and photoelectrocatalytic hydrogen evolution. *Energy Environ. Sci.* **5**, 5577–5591 (2012).
- Khan, S. U. M., Al-Shahry, M. & Ingler, W. B. Efficient Photochemical Water Splitting by a Chemically Modified n-TiO₂. *Science* **297**, 2243–2245 (2002).
- Anantharaj, S., Karthik, P. E., Subramanian, B. & Kundu, S. Pt Nanoparticle Anchored Molecular Self-Assemblies of DNA: An Extremely Stable and Efficient HER Electrocatalyst with Ultralow Pt Content. *ACS Catal.* **6**, 4660–4672 (2016).
- Qi, D., Liu, Y., Liu, Z., Zhang, L. & Chen, X. Design of Architectures and Materials in In-Plane Micro-supercapacitors: Current Status and Future Challenges. *Adv. Mater.* **29**, 1602801 (2017).
- Li, L., Wu, Z., Yuan, S. & Zhang, X.-B. Advances and challenges for flexible energy storage and conversion devices and systems. *Energy Environ. Sci.* **7**, 2101–2122 (2014).
- González, A., Goikolea, E., Barrena, J. A. & Mysyk, R. Review on supercapacitors: Technologies and materials. *Renew. Sustain. Energy Rev.* **58**, 1189–1206 (2016).
- Wang, G., Zhang, L. & Zhang, J. A review of electrode materials for electrochemical supercapacitors. *Chem. Soc. Rev.* **41**, 797–828 (2012).
- Wang, Y., Song, Y. & Xia, Y. Electrochemical capacitors: mechanism, materials, systems, characterization and applications. *Chem. Soc. Rev.* **45**, 5925–5950 (2016).
- Yu, Z., Tetard, L., Zhai, L. & Thomas, J. Supercapacitor electrode materials: nanostructures from 0 to 3 dimensions. *Energy Environ. Sci.* **8**, 702–730 (2015).
- Ferris, A., Garbarino, S., Guay, D. & Pech, D. 3D RuO₂ Microsupercapacitors with Remarkable Areal Energy. *Adv. Mater.* **27**, 6625–6629 (2015).
- Wu, Z.-S. *et al.* Anchoring Hydrous RuO₂ on Graphene Sheets for High-Performance Electrochemical Capacitors. *Adv. Funct. Mater.* **20**, 3595–3602 (2010).
- Wang, X. *et al.* High supercapacitor and adsorption behaviors of flower-like MoS₂ nanostructures. *J. Mater. Chem. A* **2**, 15958–15963 (2014).
- da Silveira Firmiano, E. G. *et al.* Supercapacitor Electrodes Obtained by Directly Bonding 2D MoS₂ on Reduced Graphene Oxide. *Adv. Energy Mater.* **4**, 1301380 (2014).
- Yang, Y., Fei, H., Ruan, G., Xiang, C. & Tour, J. M. Edge-Oriented MoS₂ Nanoporous Films as Flexible Electrodes for Hydrogen Evolution Reactions and Supercapacitor Devices. *Adv. Mater.* **26**, 8163–8168 (2014).
- Zhu, J. *et al.* Multifunctional Architectures Constructing of PANI Nanoneedle Arrays on MoS₂ Thin Nanosheets for High-Energy Supercapacitors. *Small* **11**, 4123–4129 (2015).
- Huang, K.-J., Wang, L., Zhang, J.-Z., Wang, L.-L. & Mo, Y.-P. One-step preparation of layered molybdenum disulfide/multi-walled carbon nanotube composites for enhanced performance supercapacitor. *Energy* **67**, 234–240 (2014).
- Lv, Z. *et al.* Fabrication of zero to three dimensional nanostructured molybdenum sulfides and their electrochemical and photocatalytic applications. *Nanoscale* **8**, 18250–18269 (2016).
- Li, X. *et al.* Facile Synthesis of MoS₂/Reduced Graphene Oxide@Polyaniline for High-Performance Supercapacitors. *ACS Appl. Mater. Interfaces* **8**, 21373–21380 (2016).
- Benck, J. D., Hellstern, T. R., Kibsgaard, J., Chakthranont, P. & Jaramillo, T. F. Catalyzing the Hydrogen Evolution Reaction (HER) with Molybdenum Sulfide Nanomaterials. *ACS Catal.* **4**, 3957–3971 (2014).
- Hinnemann, B. *et al.* Biomimetic Hydrogen Evolution: MoS₂ Nanoparticles as Catalyst for Hydrogen Evolution. *J. Am. Chem. Soc.* **127**, 5308–5309 (2005).
- Li, Y. *et al.* MoS₂ Nanoparticles Grown on Graphene: An Advanced Catalyst for the Hydrogen Evolution Reaction. *J. Am. Chem. Soc.* **133**, 7296–7299 (2011).
- Zheng, X. *et al.* Space-Confined Growth of MoS₂ Nanosheets within Graphite: The Layered Hybrid of MoS₂ and Graphene as an Active Catalyst for Hydrogen Evolution Reaction. *Chem. Mater.* **26**, 2344–2353 (2014).
- Lukowski, M. A. *et al.* Enhanced Hydrogen Evolution Catalysis from Chemically Exfoliated Metallic MoS₂ Nanosheets. *J. Am. Chem. Soc.* **135**, 10274–10277 (2013).
- Li, H. *et al.* Activating and optimizing MoS₂ basal planes for hydrogen evolution through the formation of strained sulphur vacancies. *Nat Mater* **15**, 48–53 (2016).
- Kumar, N. A., Dar, M. A., Gul, R. & Baek, J.-B. Graphene and molybdenum disulfide hybrids: synthesis and applications. *Mater. Today* **18**, 286–298 (2015).

31. Sun, P., Zhang, W., Hu, X., Yuan, L. & Huang, Y. Synthesis of hierarchical MoS₂ and its electrochemical performance as an anode material for lithium-ion batteries. *J. Mater. Chem. A* **2**, 3498–3504 (2014).
32. Zhang, S., Chowdari, B. V. R., Wen, Z., Jin, J. & Yang, J. Constructing Highly Oriented Configuration by Few-Layer MoS₂: Toward High-Performance Lithium-Ion Batteries and Hydrogen Evolution Reactions. *ACS Nano* **9**, 12464–12472 (2015).
33. Yang, L. *et al.* Lattice strain effects on the optical properties of MoS₂ nanosheets. *Sci. Rep.* **4**, 5649 (2014).
34. Huang, G. *et al.* Graphene-Like MoS₂/Graphene Composites: Cationic Surfactant-Assisted Hydrothermal Synthesis and Electrochemical Reversible Storage of Lithium. *Small* **9**, 3693–3703 (2013).
35. Xiao, W. *et al.* Simple Synthesis of Molybdenum Disulfide/Reduced Graphene Oxide Composite Hollow Microspheres as Supercapacitor Electrode Material. *Materials (Basel)* **9** (2016).
36. Qin, P. *et al.* *In situ* growth of double-layer MoO₃/MoS₂ film from MoS₂ for hole-transport layers in organic solar cell. *J. Mater. Chem. A* **2**, 2742–2756 (2014).
37. Lee, J.-U., Park, J., Son, Y.-W. & Cheong, H. Anomalous excitonic resonance Raman effects in few-layered MoS₂. *Nanoscale* **7**, 3229–3236 (2015).
38. Hu, T. *et al.* Rapid synthesis of nitrogen-doped graphene for a lithium ion battery anode with excellent rate performance and super-long cyclic stability. *Phys. Chem. Chem. Phys.* **16**, 1060–1066 (2014).
39. Koroteev, V. O. *et al.* Charge Transfer in the MoS₂/Carbon Nanotube Composite. *J. Phys. Chem. C* **115**, 21199–21204 (2011).
40. Guo, X. *et al.* A bulky and flexible electrocatalyst for efficient hydrogen evolution based on the growth of MoS₂ nanoparticles on carbon nanofiber foam. *J. Mater. Chem. A* **3**, 5041–5046 (2015).
41. Khan, M. *et al.* Molybdenum sulfide/graphene-carbon nanotube nanocomposite material for electrocatalytic applications in hydrogen evolution reactions. *Nano Res.* **9**, 837–848 (2016).
42. Chang, K. *et al.* Ultrathin MoS₂/Nitrogen-Doped Graphene Nanosheets with Highly Reversible Lithium Storage. *Adv. Energy Mater.* **3**, 839–844 (2013).
43. Xu, Y., Sheng, K., Li, C. & Shi, G. Self-Assembled Graphene Hydrogel via a One-Step Hydrothermal Process. *ACS Nano* **4**, 4324–4330 (2010).
44. Stoller, M. D. & Ruoff, R. S. Best practice methods for determining an electrode material's performance for ultracapacitors. *Energy Environ. Sci.* **3**, 1294–1301 (2010).
45. Anothumakkool, B., Soni, R., Bhang, S. N. & Kurungot, S. Novel scalable synthesis of highly conducting and robust PEDOT paper for a high performance flexible solid supercapacitor. *Energy Environ. Sci.* **8**, 1339–1347 (2015).
46. Weng, Q. *et al.* Supercapacitive energy storage performance of molybdenum disulfide nanosheets wrapped with microporous carbons. *J. Mater. Chem. A* **3**, 3097–3102 (2015).
47. Fan, L.-Q., Liu, G.-J., Zhang, C.-Y., Wu, J.-H. & Wei, Y.-L. Facile one-step hydrothermal preparation of molybdenum disulfide/carbon composite for use in supercapacitor. *Int. J. Hydrogen Energy* **40**, 10150–10157 (2015).
48. Khawula, T. N. Y., Raju, K., Franklyn, P. J., Sigalas, I. & Ozoemena, K. I. Symmetric pseudocapacitors based on molybdenum disulfide (MoS₂)-modified carbon nanospheres: correlating physicochemistry and synergistic interaction on energy storage. *J. Mater. Chem. A* **4**, 6411–6425 (2016).
49. Bissett, M. A., Kinloch, I. A. & Dryfe, R. A. W. Characterization of MoS₂-Graphene Composites for High-Performance Coin Cell Supercapacitors. *ACS Appl. Mater. Interfaces* **7**, 17388–17398 (2015).
50. Krishnamoorthy, K. & Kim, S.-J. Growth, characterization and electrochemical properties of hierarchical CuO nanostructures for supercapacitor applications. *Mater. Res. Bull.* **48**, 3136–3139 (2013).
51. Ratha, S. & Rout, C. S. Supercapacitor Electrodes Based on Layered Tungsten Disulfide-Reduced Graphene Oxide Hybrids Synthesized by a Facile Hydrothermal Method. *ACS Appl. Mater. Interfaces* **5**, 11427–11433 (2013).
52. Samantara, A. K., Chandra Sahu, S., Ghosh, A. & Jena, B. K. Sandwiched graphene with nitrogen{,} sulphur co-doped CQDs: an efficient metal-free material for energy storage and conversion applications. *J. Mater. Chem. A* **3**, 16961–16970 (2015).
53. Yu, Y. *et al.* Layer-Dependent Electrocatalysis of MoS₂ for Hydrogen Evolution. *Nano Lett.* **14**, 553–558 (2014).
54. Benson, J., Li, M., Wang, S., Wang, P. & Papakonstantinou, P. Electrocatalytic Hydrogen Evolution Reaction on Edges of a Few Layer Molybdenum Disulfide Nanodots. *ACS Appl. Mater. Interfaces* **7**, 14113–14122 (2015).
55. Zhang, J., Liu, S., Liang, H., Dong, R. & Feng, X. Hierarchical Transition-Metal Dichalcogenide Nanosheets for Enhanced Electrocatalytic Hydrogen Evolution. *Adv. Mater.* **27**, 7426–7431 (2015).
56. Ma, C.-B. *et al.* MoS₂ nanoflower-decorated reduced graphene oxide paper for high-performance hydrogen evolution reaction. *Nanoscale* **6**, 5624–5629 (2014).
57. Xie, J. *et al.* Defect-Rich MoS₂ Ultrathin Nanosheets with Additional Active Edge Sites for Enhanced Electrocatalytic Hydrogen Evolution. *Adv. Mater.* **25**, 5807–5813 (2013).
58. Kibsgaard, J., Chen, Z., Reinecke, B. N. & Jaramillo, T. F. Engineering the surface structure of MoS₂ to preferentially expose active edge sites for electrocatalysis. *Nat Mater* **11**, 963–969 (2012).
59. Chen, Z. *et al.* Core-shell MoO₃-MoS₂ Nanowires for Hydrogen Evolution: A Functional Design for Electrocatalytic Materials. *Nano Lett.* **11**, 4168–4175 (2011).
60. Vrabel, H., Merki, D. & Hu, X. Hydrogen evolution catalyzed by MoS₃ and MoS₂ particles. *Energy Environ. Sci.* **5**, 6136–6144 (2012).
61. Merki, D., Fierro, S., Vrabel, H. & Hu, X. Amorphous molybdenum sulfide films as catalysts for electrochemical hydrogen production in water. *Chem. Sci.* **2**, 1262–1267 (2011).
62. Guo, Y., Gan, L., Shang, C., Wang, E. & Wang, J. A Cake-Style CoS₂@MoS₂/RGO Hybrid Catalyst for Efficient Hydrogen Evolution. *Adv. Funct. Mater.* **27**, 1602699 (2017).
63. Li, F. *et al.* Synthesis of Cu-MoS₂/rGO hybrid as non-noble metal electrocatalysts for the hydrogen evolution reaction. *J. Power Sources* **292**, 15–22 (2015).
64. An, L. *et al.* A Self-Standing High-Performance Hydrogen Evolution Electrode with Nanostructured NiCo₂O₄/CuS Heterostructures. *Adv. Funct. Mater.* **25**, 6814–6822 (2015).
65. Pham, K.-C. *et al.* Amorphous Molybdenum Sulfide on Graphene-Carbon Nanotube Hybrids as Highly Active Hydrogen Evolution Reaction Catalysts. *ACS Appl. Mater. Interfaces* **8**, 5961–5971 (2016).
66. Bose, R. *et al.* Importance of Hydrophilic Pretreatment in the Hydrothermal Growth of Amorphous Molybdenum Sulfide for Hydrogen Evolution Catalysis. *Langmuir* **31**, 5220–5227 (2015).
67. Jr., W. S. H. & Offeman, R. E. Preparation of Graphitic Oxide. *J. Am. Chem. Soc.* **80**, 1339 (1958).

Acknowledgements

The authors are grateful to the Director CSIR-IMMT for his kind permission and encouragement for doing this work. Dr. B. K. Jena acknowledges BRNS, Mumbai, India (No-2013/37 P/67/BRNS), MNRE, New Delhi, India (No-102/87/2011-NT) and CSIR, New Delhi, India {(OLP-65 (translational), YSP-02 (P-81–113), MULTIFUN (CSC-0101)} for the financial support. SK acknowledges DST, New Delhi and BPM acknowledge UGC, New Delhi for the fellowship. The authors are thankful to Mr A. Dash and central characterization cell facility for TEM measurements and other characterizations. The authors thank to Dr. D.P. Das for BET measurement. The authors thank Dr. S. S. Rath and Mr. B. K. Parida for helping in preparation of scheme.

Author Contributions

B.K.J. initiated the project. S.K. and B.P.M. carried out experiments and analysed the data. A.K.S. supported during experiments and analysis of data. P.G., A.G. supported the characterizations of the materials and analysis. B.J. supported in the analysis of H.E.R. data and added suggestions/corrections in writing the paper. P.V.S. supported in characterization of materials and added suggestions/corrections in writing the manuscript. B.K.M. supported in the analysis of supercapacitor data and added comments/suggestions on the manuscript.

Additional Information

Supplementary information accompanies this paper at doi:[10.1038/s41598-017-08677-5](https://doi.org/10.1038/s41598-017-08677-5)

Competing Interests: The authors declare that they have no competing interests.

Publisher's note: Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.



Open Access This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons license, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons license and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>.

© The Author(s) 2017