



OPEN

SUBJECT AREAS:

MAGNETIC PROPERTIES  
AND MATERIALSSURFACES, INTERFACES AND  
THIN FILMS

# Positive exchange-bias and giant vertical hysteretic shift in $\text{La}_{0.3}\text{Sr}_{0.7}\text{FeO}_3/\text{SrRuO}_3$ bilayers

Rakesh Rana, Parul Pandey, R. P. Singh &amp; D. S. Rana

Department of Physics, Indian Institute of Science Education and Research Bhopal, Govindpura, Bhopal-462023, India.


Received  
15 August 2013Accepted  
28 January 2014Published  
26 February 2014Correspondence and  
requests for materials  
should be addressed to  
D.S.R. (dsrana@iiserb.  
ac.in)

The exchange-bias effects in the mosaic epitaxial bilayers of the itinerant ferromagnet (FM)  $\text{SrRuO}_3$  and the antiferromagnetic (AFM) charge-ordered  $\text{La}_{0.3}\text{Sr}_{0.7}\text{FeO}_3$  were investigated. An uncharacteristic low-field positive exchange bias, a cooling-field driven reversal of positive to negative exchange-bias and a layer thickness optimised unusual vertical magnetization shift were all novel facets of exchange bias realized for the first time in magnetic oxides. The successive magnetic training induces a transition from positive to negative exchange bias regime with changes in domain configurations. These observations are well corroborated by the hysteretic loop asymmetries which display the modifications in the AFM spin correlations. These exotic features emphasize the key role of i) mosaic disorder induced subtle interplay of competing AFM-superexchange and FM double exchange at the exchange biased interface and, ii) training induced irrecoverable alterations in the AFM spin structure.

The discovery of exchange bias (EB) effect by Meiklejohn and Bean<sup>1</sup> has garnered enormous interest from the scientific community for its intriguing fundamental and technological aspects. Recent impetus on EB have resulted in diverse tantalizing avenues as the modern day electronic devices include its usage in spin valves, magnetic recording read heads, giant magnetoresistive sensors, etc<sup>2,3</sup>. The EB is usually characterized by an asymmetric shift in the magnetic hysteresis loop along the field axis when a ferromagnetic (FM)-antiferromagnetic (AFM) layered or a composite system is cooled in a static magnetic field through the Néel temperature ( $T_N$ ) of the AFM phase<sup>4</sup>. The magnitude of the loop shift ( $H_{EB}$ ) depends on various factors such as the interfacial roughness, characteristics of the FM-AFM layers involved, the complex spin structure at the interface, the uncompensated moments at the interface, etc<sup>4-6</sup>. Usually for FM-AFM systems, the shift of the hysteresis loop is opposite to the cooling field ( $H_{CF}$ ) direction and is termed as negative exchange bias (NEB). On the other hand, the shift of hysteresis loop along the same sign of  $H_{CF}$  is termed as positive exchange bias (PEB)<sup>5,6</sup>. The PEB, a rarely observed phenomenon, was first reported for  $\text{FeF}_2/\text{Fe}$  bilayer thin-films<sup>5,6</sup>. It is attributed to the AFM exchange coupling with its sign and magnitude strongly dependent on the  $H_{CF}$ <sup>5,6</sup>. The AFM exchange coupling at the interface was also reported for two FM perovskite oxides, namely,  $\text{La}_{2/3}\text{Sr}_{1/3}\text{MnO}_3$  and  $\text{SrRuO}_3$ <sup>7</sup>. The  $\text{Cu}_{1-x}\text{Mn}_x/\text{Co}$  bilayers exhibited PEB in the vicinity of blocking temperature which subsequently vanishes at lower temperatures resulting in NEB due to the coexistence of FM and AFM interface coupling<sup>8</sup>. More recently, the PEB for  $\text{Ni}_{81}\text{Fe}_{19}/\text{Ir}_{20}\text{Mn}_{80}$  bilayers was observed and explained in the framework of meta-stable magnetic disorder at the FM-AFM interface induced by the magnetic training effect (TE)<sup>9</sup>.

Initially, most of the scientific quest to unravel the EB phenomenon was seen on metallic systems<sup>1,3,4-11</sup>. Recently, however, this phenomenon is also being explored and tuned in the magnetic perovskite oxides<sup>7,12-16</sup>. Understanding the evolution of EB in perovskite oxide bilayers and multilayers is essential as these systems present a greater degree of freedom for tunability of EB at the interface via strain, orbital reconstruction, charge-transfer, etc. Their suitable combinations with structural compatibility at the FM-AFM interface might unveil many potent facets of EB. Observation of EB in the disordered-ordered magnetic interfaces, *i.e.*, in paramagnetic (PM)  $\text{LaNiO}_3$  and FM  $\text{LaMnO}_3$  superlattice and the PM  $\text{CaRuO}_3$  and AFM  $\text{CaMnO}_3$  superlattices are clearly the recent important discoveries in this area<sup>12,13</sup>. More recently, strain engineered unexpected EB with the emergence of a self assembled spin glass like phase of  $\text{LaSrMnO}_4$  at the film/substrate interface was reported for  $(\text{La,Sr})\text{MnO}_3$  single thin-films<sup>17</sup>. All endeavours are focussed on controlling and manipulation of EB by the interfacial interactions, thickness and number of layers of the FM and AFM phases, and the type of AFM order in the superlattice structures<sup>14,15</sup>. Overall the progress in EB has been two-fold. First, the EB has been addressed in unconventional heterostructures/bilayers with FM-PM, AFM-PM and collinear-noncollinear magnetic heterostructures<sup>7,12,13,16</sup>.



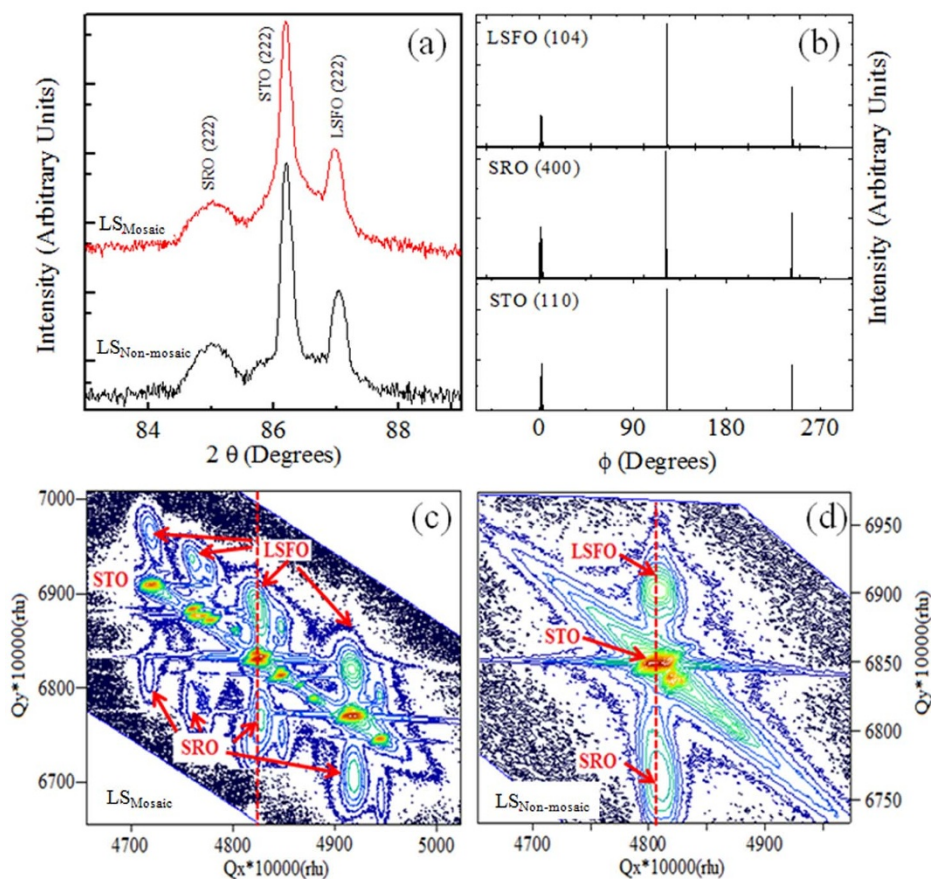


**Figure 2** | (a) shows  $\theta - 2\theta$  scan for  $LS_{Mosaic}$  and  $LS_{Non-mosaic}$  sample, (b)  $\phi$ -scans along the peaks (104) for LSFO, (400) for SRO and (110) for STO substrate, (c–d) shows the reciprocal space maps for  $LS_{Mosaic}$  and  $LS_{Non-mosaic}$  along the asymmetric (330) orientation of the mosaic and non-mosaic STO (111) substrate, respectively.


exists a reflection of the coherently strained LSFO and SRO epitaxial layers for the  $LS_{Mosaic}$ . Such exhibition of multiple epitaxial peaks is absent in the  $LS_{Non-mosaic}$  sample which is formed on non-mosaic STO substrate [figure 2(d)]. The bulk pseudo-cubic lattice parameter of the LSFO is 3.87 Å, SRO is 3.93 Å and the STO is 3.905 Å. The out-of-plane lattice constant for the LSFO is 3.85 Å and the SRO is 3.945 Å. This suggests that the LSFO is under tensile strain, whereas, the SRO is under compressive strain. Overall, we can recognize qualitatively different crystal structures of the same substrate on

which the LSFO/SRO bilayers namely,  $LS_{Mosaic}$  and  $LS_{Non-mosaic}$  were fabricated and their respective implications on the EB properties studied.

Magnetization ( $M$ ) versus temperature ( $T$ ) at a magnetic field ( $H$ ) of 500 Oe in the field cooled cooling (FCC) protocol shows a  $T_C \sim 150$  K for  $LS_{Mosaic}$  and  $LS_{Non-mosaic}$  [inset figure 3(a)]. This is slightly lower than the bulk  $T_C \sim 160$  K of the SRO, presumably, due to strain in the thin film<sup>14,15</sup>. The  $M$  versus  $H$  loops at 2 K for zero-field cooling (ZFC) and in different  $H_{CF}$  for  $LS_{Mosaic}$  are shown in

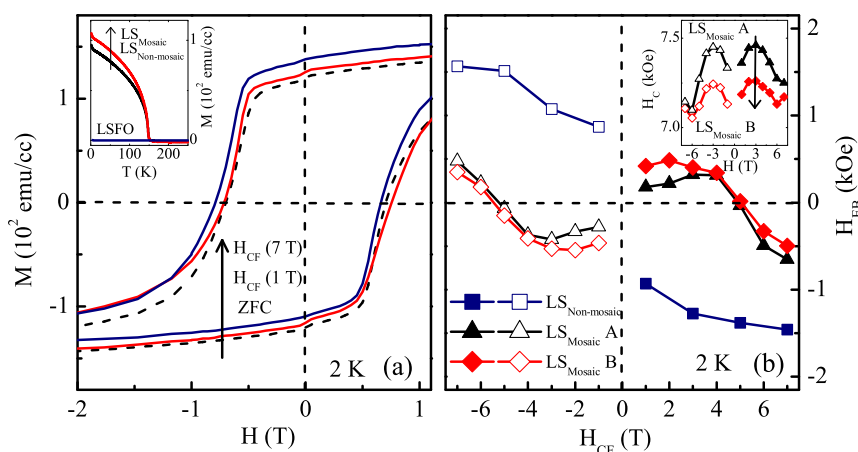

**Figure 3** | (a) Magnetization ( $M$ ) versus magnetic field ( $H$ ) loops of  $LS_{Mosaic}$  in zero field cooling (ZFC) and at various cooling fields ( $H_{CF}$ ), inset shows  $M$  versus temperature ( $T$ ) plot in field cool warming protocol ( $H = 500$  Oe) for  $LS_{Mosaic}$ ,  $LS_{Non-mosaic}$  and LSFO and (b) shows  $H_{CF}$  dependence of exchange bias ( $H_{EB}$ ) for  $LS_{Mosaic}$  and  $LS_{Non-mosaic}$  sample, inset depicts the training induced decrease in coercivity ( $H_C$ ) of  $LS_{Mosaic}$ .

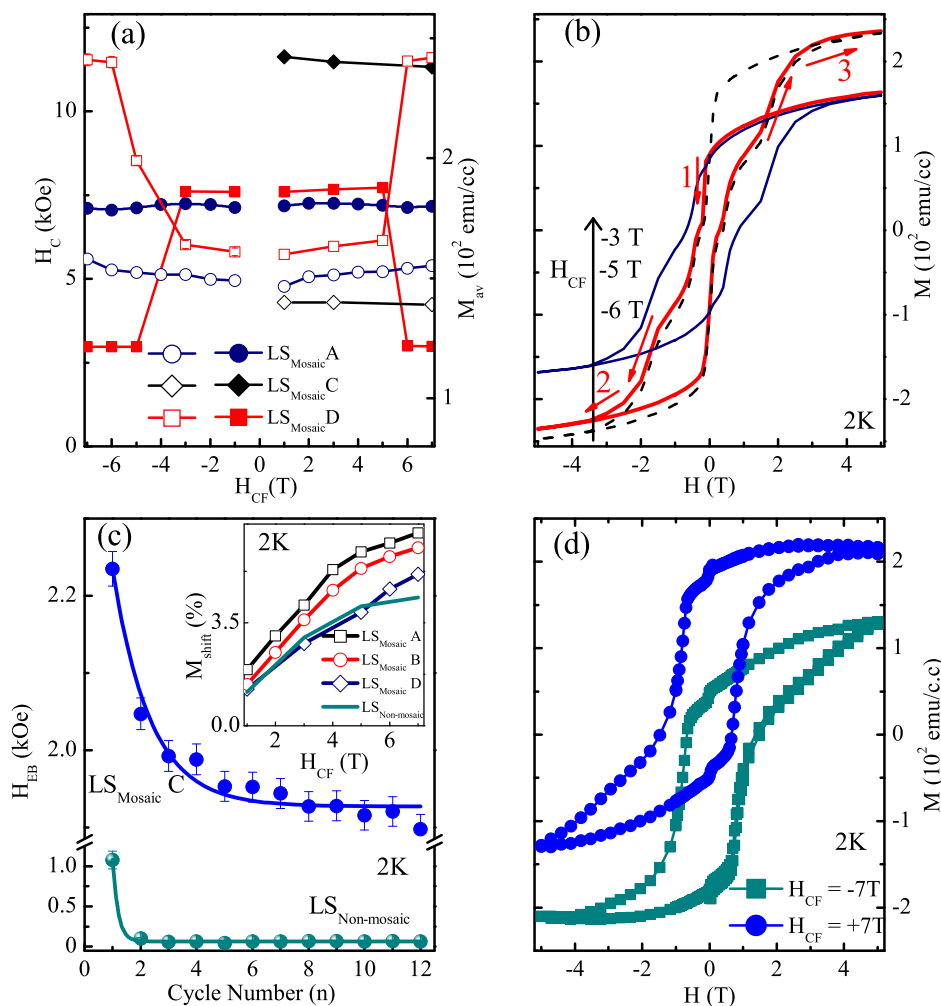

**Figure 4** | (a) Coercivity ( $H_C$ ) (closed symbols) and average saturation magnetization ( $M_{av}$ ) (open symbols) versus cooling field ( $H_{CF}$ ) at a temperature of 2 K, (b) Magnetization ( $M$ ) versus magnetic field ( $H$ ) loops at different  $H_{CF}$  for LS<sub>Mosaic</sub>D, (c) Exchange bias ( $H_{EB}$ ) with number of cycles ( $n$ ) [solid line is the fit as per equation. 1] for LS<sub>Mosaic</sub>C and LS<sub>Non-mosaic</sub>, inset shows vertical shift ( $M_{shift}$ ) versus  $H_{CF}$  for LS<sub>Mosaic</sub> (LS<sub>Mosaic</sub>A  $\rightarrow$  LS<sub>Mosaic</sub>D) and LS<sub>Non-mosaic</sub> samples, and (d) shows the maximum  $M_{shift}$  ( $\sim 35\%$ ) for the optimized bilayer [LSFO (110 nm)/SRO(10 nm)].

figure 3(a). It may be seen that the M-H loops for LS<sub>Mosaic</sub> exhibits dissimilar manifestation of the  $H_{EB}$  with  $H_{CF}$ . On one hand, we observe PEB for LS<sub>Mosaic</sub> at low cooling field ( $H_{CF}$ )  $\sim 1$  T [ $>H_C$ ] while, on the other hand, a  $H_{CF}$  of  $\sim 7$  T dramatically supplants this PEB to a NEB regime [figure 3(a)]. This, in essence, is displayed in figure 3(b), where an unusual crossover from PEB to NEB  $\sim 5$  T is observed. In contrast to this the LS<sub>Non-mosaic</sub> sample exhibits only NEB at various  $H_{CF}$  which saturates in a field of  $\sim 5$  T [figure 3(b)]. Overall, the EB properties of LS<sub>Mosaic</sub> are novel and unusual, whereas, the EB for LS<sub>Non-mosaic</sub> is rather conventional and is commonly observed for FM-AFM systems.

In the LS<sub>Mosaic</sub> sample the mosaicity of the substrate induces topographic modulations which results in randomly oriented AFM easy axis of AFM grains in LSFO layer with a FM SRO layer coupled on to it. These sporadic distributions of magnetic inhomogeneities, having imperfections and defects at the interface result in various spin frustrated ensembles with a mixture of FM, AFM and spin flop coupling regimes<sup>22,23</sup>. The resultant of these microscopic FM-AFM exchange interactions at the interface and at the grain boundaries is understood to govern the dynamics of the system. The  $H_{CF}$  drives the LS<sub>Mosaic</sub> in two ways, namely, i) at low  $H_{CF}$  [ $H_C < H_{CF} < 5$  T], the microscopic AFM superexchange (AFM-SE) interactions dominate the FM double exchange at the interface and result in the PEB [figure 2(a)] and ii) as the  $H_{CF}$  is increased above 5 T, FM double

exchange gets strengthened and dominates the microscopic AFM exchange at the interface giving NEB. Thus, a PEB  $\rightarrow$  NEB crossover can be tuned via subtle interplay of surface AFM spin correlations with  $H_{CF}$ .

To gain deeper insight of AFM spin correlations, we performed a multistage training cycles on the LS<sub>Mosaic</sub> and the LS<sub>Non-mosaic</sub> sample<sup>24–26</sup>. This was experimentally realized in the following sequence; LS<sub>Mosaic</sub>A (initial cycle)  $\rightarrow$  LS<sub>Mosaic</sub>B (after 15 cycles)  $\rightarrow$  LS<sub>Mosaic</sub>C (after 15 cycles)  $\rightarrow$  LS<sub>Mosaic</sub>D (after 12 cycles), while for nonmosaic LS<sub>Non-mosaic</sub> (12 cycles) [1 cycle is the loop recorded at 2 K with  $H_{CF} = +7$  T]. Training from LS<sub>Mosaic</sub>A to LS<sub>Mosaic</sub>B, causes a marginal increase in the PEB with a slight decrease in  $H_C$  [inset figure 3(b)]. Further, training results in vanishing of the PEB with a complete emergence of NEB regime for LS<sub>Mosaic</sub>C [figure 4(c)]. This NEB for the LS<sub>Mosaic</sub>C is associated with an increased  $H_C$  and a decreased  $M_{av}$  [ $= (M_{sat}^{+5T} + M_{sat}^{-5T})/2$ ] compared to that for LS<sub>Mosaic</sub>A [figure 4(a)] suggesting enhanced spin-flop coupling for LS<sub>Mosaic</sub>C<sup>16</sup>. The subsequent training cycle yields to LS<sub>Mosaic</sub>D, which shows a transition in shape of the hysteresis loop as a function of  $H_{CF}$  at 2 K [figure 4(b)]. It may be seen for LS<sub>Mosaic</sub>D the  $H_{CF}$  of  $-3$  T yields a NEB loop [figure 4(b)]. As this  $H_{CF}$  is increased to  $-5$  T the loop manifests with a lesser  $H_C$  [step 1 to 2] with a marked increase in overall  $M$  [step 2–3]. Another loop recorded with  $H_{CF}$  of  $-6$  T displays an entirely different shape as switching field ( $H_C$ ) decreases, as





compared to the loop recorded with  $H_{CF}$  of  $-3$  T [figure 4(b)]. This indicates that the pinning defects in the AFM layer are undergoing changes not only with training runs but have  $H_{CF}$  sensitivity as well.


The disorder induced in the  $LS_{Mosaic}$  is quite intriguing, as training causes  $H_{EB}$  to traverse from PEB ( $LS_{Mosaic}A-B$ ) to NEB ( $LS_{Mosaic}C-D$ ) regime, whereas its counterpart  $LS_{Non-mosaic}$  exhibits NEB regime only. The TE is essential signature and can unveil the microstructural spin rearrangements along with the possible mechanisms driving the  $H_{EB}$ . To understand the underlying intricacies, we compared the influence of training in the NEB regime of  $LS_{Mosaic}C$  with that of the  $LS_{Non-mosaic}$ . The training leads to irreversible changes in the interfacial domain configurations, which causes the magnetization of the LSFO pinning layer to be nonconserved<sup>26</sup>. Such relaxation effects in the nonconserved order parameters can be addressed using Landau-Khalatnikov expression which was successfully employed to describe the TE in LSMO/SRO heterostructures<sup>26</sup>. The phenomenological expression used to model the cycle dependence ( $n$ ) with  $H_{EB}$  is,

$$H_{EB}(n) = (K+1)^{n-1} \left\{ H_{EB}(1) - KH_{EB}^e \left[ \frac{(K+1)^{n+1} - 1}{K(K+1)^{n-1}} - (K+2) \right] \right\} \quad (1)$$

where,  $K$  and  $H_{EB}^e = H_{EB}(n \rightarrow \infty)$  are the crucial fitting parameters,  $H_{EB}(1)$  is the first loop  $H_{EB}$  value. The equation (1) can also be written as  $H_{EB}(n+1) = (K+1)H_{EB}(n) - KH_{EB}^e$ <sup>26</sup>. The value of  $K$  usually lies in the range  $-1 \leq K \leq 0$ <sup>26</sup>. When  $K = 0$ , it yields  $H_{EB}(n+1) = H_{EB}(n)$  implying no training, whereas for  $K = -1$ , it is  $H_{EB}(n+1) = H_{EB}^e$  which yields a step like change in  $H_{EB}$  between the first two data points with no TE for  $n > 2$ <sup>26</sup>. Equation (1) was successfully fitted to both  $LS_{Mosaic}C$  and  $LS_{Non-mosaic}$  with the values of  $K$  as  $-0.52$  and  $-0.97$ , respectively. For  $n \geq 2$ , the  $H_{EB}$  for  $LS_{Mosaic}C$  keeps on decreasing with  $n$ , whereas, the  $H_{EB}$  for  $LS_{Non-mosaic}$  exhibits a negligible change.

The contrasting training behaviour for  $LS_{Mosaic}C$  and  $LS_{Non-mosaic}$ , plausibly indicates different training mechanisms governing both the samples. We attribute the initial large decrease in  $H_{EB}$  for both the samples to a ‘Hoffmann’ like behaviour, where the major changes after the first reversal can be ascribed to a transformation from an initial noncollinear arrangement of the AFM spins to a more relaxed collinear arrangement<sup>27</sup>. Furthermore, as per Hoffmann’s model, the TE should cease for  $n \geq 2$ <sup>27</sup>. This is displayed by  $LS_{Non-mosaic}$ , whereas,  $LS_{Mosaic}C$  shows a continuous decrease in  $H_{EB}$  even beyond  $n \geq 2$ . This decrease in  $H_{EB}$  ( $n \geq 2$ ) for  $LS_{Mosaic}$ , typically indicates that along with the Hoffmann’s component (which largely trains out after the first cycle), a second contribution to training may be present. This seems to arise from the thermally activated depinning of the uncompensated AFM spins<sup>28,29</sup>. Thus, the  $LS_{Mosaic}$  and the  $LS_{Non-mosaic}$  can explicitly be distinguished via field training, as the former exhibits a combination of a Hoffman and thermally activated depinning mechanism, whereas, the later trains out via ‘Hoffman’ mechanism<sup>27,28</sup>.

We also observed a positive vertical magnetization shift in the hysteresis loop along the same sign as of the  $H_{CF}$  for both the samples  $LS_{Mosaic}$  and  $LS_{Non-mosaic}$  [inset figure 4(c)]. Interestingly, vertical shift also displays the TE as it decreases from  $LS_{Mosaic}A \rightarrow LS_{Mosaic}D$  [inset figure 4(c)]. Vertical shift can be calculated using,  $M_{shift} = M_{Sat}^+ + M_{Sat}^-/2$ , where,  $M_{Sat}^+$  and  $M_{Sat}^-$  are positive and negative saturation values of the hysteresis loop. Observation of vertical shift is rare and usually points towards the uncompensated spins at the FM-AFM interface or that are in the bulk AFM<sup>14,15,30–32</sup>. Further, this rare and intriguing observation of vertical shift present in our bilayer system on STO (111) was found to vary with the thickness of AFM LSFO layer [unpublished data]. Thickness variation in AFM or FM phase of a FM/AFM bilayer system is an essential component to control the  $H_{EB}$ ,  $H_C$  and can also be used to tune the vertical shift<sup>33–35</sup>. We noted a maximum vertical shift of 35% for our optimized bilayer

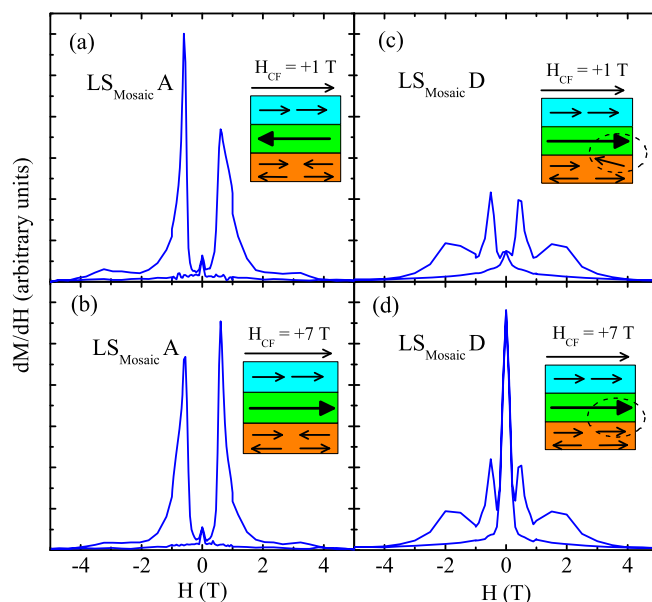


**Figure 5 | Asymmetry in hysteresis loop ( $dM/dH$ ) versus magnetic field ( $H$ ) for  $LS_{Mosaic}A$  and  $LS_{Mosaic}D$  at different cooling field ( $H_{CF}$ ). Inset boxes with orange, green and blue colour depicts the spin configurations at  $La_{0.3}Sr_{0.7}FeO_3$ /Interface/ $SrRuO_3$ , respectively.**

sample with LSFO(110 nm)/SRO(10 nm) on non-mosaic STO(111) [figure 4(d)].

For further analysis of the sign reversal of the EB of  $LS_{Mosaic}$ , the loop asymmetries ( $dM/dH$ ) were derived from the hysteresis data and are shown in figure 5<sup>9</sup>. It may be seen that for low positive  $H_{CF}$  (1 T) the first loop reversal is sharper than the second reversal of the loop [figure 5(a)] and yields PEB. As the  $H_{CF}$  is increased to +7 T the peak height is reversed and yields a transformation to a NEB regime for the  $LS_{Mosaic}A$  [figure 5(b)]. This shows the sensitivity of the AFM spin structure to the  $H_{CF}$  and points towards a change in the microscopic AFM to FM exchange interaction at the interface [see schematic in figure 5(a) (AFM interface coupling)  $\rightarrow$  5 (b) (FM interface coupling)]. The shape of the subsequent hysteresis loops after training is more symmetric and rounded for  $LS_{Mosaic}C$  [not shown and is similar to figure 5(c)]. Furthermore, a peak in the vicinity of  $H = 0$  T for  $LS_{Mosaic}D$  [figure 5(d)] shows that the FM spins have now softened and are very sensitive to any reversal of the direction of sweeping field. This scenario is in good congruence with that discussed earlier for figure 4 (b) in which we observed an enhanced saturation  $M$  with a decreased  $H_C$ . The loop asymmetries as described above portrays the significant deviations in the pinning AFM layer with the  $H_{CF}$  and training runs resulting in PEB  $\rightarrow$  NEB transition [Inset figure 5(a–d)].

Figure 6(a) illustrates the temperature dependence of the  $H_{EB}$  for the  $LS_{Mosaic}$  sample after various training runs. The blocking temperature for  $LS_{Mosaic}$  and  $LS_{Non-mosaic}$  is nearly the same 130 K [Supplementary figure S2]. We find that for  $LS_{Mosaic}A$  exhibiting PEB, the  $H_{EB}$  increases slightly for a temperature upto 50 K and then it shows a decrease with increasing temperature [Figure 6(a)]. In the NEB regime for  $LS_{Mosaic}C$  and  $LS_{Mosaic}D$  the  $H_{EB}$  exhibits an exponential type of decrease with increasing temperature. This usually signifies the frustrated spin state at the interface<sup>36,37</sup>. To substantiate this the  $H_{EB}$  data of  $LS_{Mosaic}C$  and  $LS_{Mosaic}D$  were fitted to the equation  $H_{EB}(T) = H_{EB}^0 \exp(-T/T_A)$ , where  $H_{EB}^0$  is the extrapolation of  $H_{EB}$  at absolute zero and  $T_A$  is a constant [figure 6 (a)]<sup>36,37</sup>. We obtained convincing fits with,  $H_{EB}^0 = -0.17$  T and  $-0.063$  T with  $T_A = 30$  K and 21 K for  $LS_{Mosaic}C$  and  $LS_{Mosaic}D$ , respectively. Further, inset figure 6(a) depicts the temperature variation in the

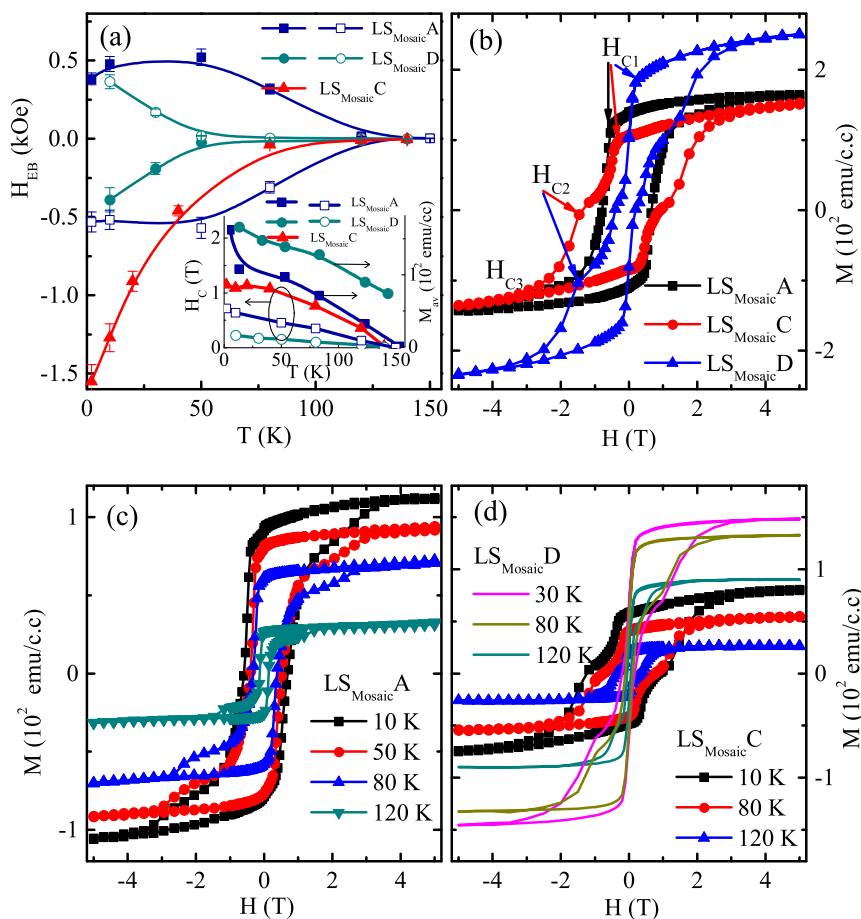

**Figure 6** | (a) Exchange Bias ( $H_{EB}$ ) versus temperature ( $T$ ) for  $LS_{Mosaic}$  at a cooling field of +3 T (solid symbols) and -3 T (hollow symbols), dashed line is fit as per equation  $H_{EB}(T) = H_{EB}^0 \exp(-T/T_A)$ , while the solid line is guide to the eye. Inset depicts temperature variation of  $H_C$  and  $M_{av}$  for  $LS_{Mosaic}$  sample, (b), (c) & (d) shows the temperature variation of hysteresis loop shapes for  $LS_{Mosaic}A$ ,  $LS_{Mosaic}C$  and  $LS_{Mosaic}D$ .

$H_C$  and  $M_{av}$  for  $LS_{Mosaic}$  sample. We observed an enhanced overall  $M_{av}$  for  $LS_{Mosaic}D$ , as compared to that of  $LS_{Mosaic}(A-C)$  in the entire temperature range [figure 6(b,c and d)]. This suggests that the training causes a temperature independent retention of the irrecoverable permanent spin rearrangements in the AFM layer for the  $LS_{Mosaic}D$ .

## Discussions

In this section we will discuss the key observations of the  $LS_{Mosaic}$  sample, in the following sequence, i) competing exchange interactions at the LSFO/SRO interface and the possible EB model for the observed PEB, ii) dynamics of the training induced dissimilar hysteresis loop shape transitions, and iii) the vertical magnetization shift.

The subtle interplay of FM-SE and AFM-SE interactions at the LSFO/SRO interface drives the PEB  $\rightarrow$  NEB transition in the  $LS_{Mosaic}$  sample. The transition may be attributed to a potential crossover from AFM to FM exchange coupling [figure 3(b)]. This occurs as the mosaicity induces a disorder at the  $LS_{Mosaic}$  interface, thus, inducing the competition between FM-AFM exchange interactions. On one hand, LSFO grain boundaries exhibit FM-SE interaction in  $Fe^{5+}-O-Fe^{3+}$  and AFM-SE interaction in  $Fe^{3+}-O-Fe^{3+}$  in the [001] plane<sup>20</sup>. On the other hand, across the FM-AFM interface  $Ru^{4+}-O-Fe^{3+}$  and  $Ru^{4+}-O-Fe^{5+}$  exhibits a FM double exchange interaction. The increasing  $H_{CF}$  overcomes the localized AFM-SE interaction and strengthens the FM double exchange resulting in a crossover from PEB to NEB regime. Several models were proposed to explain the EB effect<sup>22,23,38-45</sup>. The EB in mosaic  $LS_{Mosaic}$  sample is suggestive of a scenario in which the interface domain wall (IDW) develops as a result of competition between AFM coupling and the Zeeman

energy<sup>44,45</sup>. Presently, IDW can manifest between different crystallite ensembles, consisting of independent AFM grain boundaries with a coupled FM layer on to it. The IDW can provide AFM coupling at the interface which will yield PEB for  $LS_{Mosaic}A$ . Also, IDW shows training and  $H_{CF}$  sensitivity. Thus, as the  $H_{CF}$  is increased thickness of IDW may decrease due to domain wall compression, yielding a complete NEB regime for  $LS_{Mosaic}C-D$ <sup>44,45</sup>.

At this point, it is imperative to discuss the possibility of charge transfer at the LSFO-SRO interface. Charge transfer was found to be associated with the observed unidirectional anisotropy in LSMO/YBCO<sup>46,47</sup>. In contrast, for the  $La_2CuO_4/LSMO$  bilayers, it was demonstrated that charge transfer is not a key factor, as the  $H_C$  was found to exhibit a AFM thickness dependence [keeping FM thickness constant]. In the present case too, the  $H_C$  was found to vary with the LSFO thickness for the LSFO/SRO bilayers on non-mosaic STO substrate [unpublished data]. This further bolsters the dominant role of SE interaction at the LSFO/SRO spin-glass like interface.

The TE introduces irreversible changes in the LSFO layer and at the LSFO/SRO interface, which manifests in the form of a magnetic reorientation from a square loop [ $LS_{Mosaic}A-B$ ] to a stepped hysteresis loop [ $LS_{Mosaic}C-D$ ] [figure 6 (b)]<sup>48</sup>. Interestingly, this loop shape variation may be associated with an enhancement in spin-flop coupling strength ( $J_{ex}$ ). For the  $LS_{Mosaic}$  sample, the strength of spin-flop coupling at the interface can be estimated using,  $J_{ex} = H_{EB} t_{FM} M_S$ , (where,  $t_{FM}$  is thickness of FM SRO layer, and  $M_S$  is saturation magnetization)<sup>48</sup>. The deduced value of  $J_{ex}$  (2 K) for  $LS_{Mosaic}(A-B) \rightarrow LS_{Mosaic}C \rightarrow LS_{Mosaic}D$  varies as  $0.2 \rightarrow 0.66 \rightarrow 0.57$  erg/cm<sup>2</sup>.



Apparently higher value of  $J_{ex}$  substantiates the enhanced spin-flop coupling in  $LS_{Mosaic}C-D$  which yields a stepped hysteresis loop, whereas a low  $J_{ex}$  favours a square loop in  $LS_{Mosaic}A-B$ .

Now, we further discuss the implications of the multistage training runs and switching of the hysteresis loops in the  $LS_{Mosaic}$  sample [figure 6 (b)]<sup>49–51</sup>. The  $LS_{Mosaic}A$  sample exhibits a coherent reversal of the hysteresis loop in the whole temperature range [figure 6(c)]. On the other hand, this coherent reversal of the SRO spins is hindered at  $H_{C2}$  for the  $LS_{Mosaic}C-D$  and the loop closes at  $H_{C3}$ . This emergence of  $H_{C2}$  can be associated with the domain wall depinning processes which may be training or thermally assisted<sup>128,29,50,51</sup>. Further the TE largely alters the pinned spin concentration from  $LS_{Mosaic}A$  to  $LS_{Mosaic}D$ . This is evident as the relative changes in  $H_{C1}$  with temperature are quite pronounced for  $LS_{Mosaic}A$  and  $LS_{Mosaic}C$ . In contrast, the  $LS_{Mosaic}D$  exhibits a negligible change in  $H_{C1}$ . This indicates that the pinning defects concentration have been drastically reduced for  $LS_{Mosaic}D$  with subsequent training runs. Furthermore, the  $H_{C1}$  was found to decrease from  $-0.4$  T ( $LS_{Mosaic}C$ ) to  $+0.1$  T ( $LS_{Mosaic}D$ ). This points towards a sharp reversal of the SRO spins even before  $H = 0$ . Remarkably, this was also evident in the loop asymmetries, as a sharp peak was observed near  $H = 0$  [figure 5(d)]. The nearly temperature independent trend of  $H_{C1}$  for  $LS_{Mosaic}D$  suggests that the LSFO interfacial spins have now been depinned and have started reversing with the FM SRO spins. This causes drastic reduction in  $H_C$  for  $LS_{Mosaic}D$ , which is also accompanied with a huge increase (64%) in  $M_{av}$  of the loops [figure 3(b)]. This excess M in  $LS_{Mosaic}D$  may have contributions from, i) the interfacial AFM ions  $Fe^{5+}$  ( $\sim 1.5 \mu_B$ ) and  $Fe^{3+}$  ( $\sim 3.5 \mu_B$ ) which have started rotating coherently with the FM layer<sup>20</sup>, ii) the, FM SRO might break into mixture of different regions (hard and soft), for large  $H_C$  hard regions out number their softer counterparts and vice versa<sup>52</sup>.

Finally, we comment on another important observation, which is the vertical magnetization shift [inset figures 4(c) and 4(d)]. The observation of vertical shift along the same sign as of the  $H_{CF}$  usually indicates FM coupling at the interface<sup>5,6</sup>. We observed a positive vertical shift for  $LS_{Mosaic}A$  and  $LS_{Non-mosaic}$  which suggests FM coupling at interface. But, interestingly,  $LS_{Mosaic}A$  also exhibits a PEB, which point towards the AFM coupling at the interface. Nevertheless, similar contrasting scenario was well addressed by Fritzzimmons *et al.*, as they showed that a microscopic AFM coupling at the interface is likely possible and can manifest along with a positive vertical shift<sup>30</sup>. This is seen for  $LS_{Mosaic}A$  sample. Moreover, a giant vertical shift of about 35% for our optimized sample suggests that a large number of uncompensated AFM spins exists when the bilayer is grown along (111) orientation of STO [figure 4(d)]. This may occur as LSFO is known to exhibit an intriguing quasi-2D charge ordering on STO (111) rather than a perfect 3D charge ordered regime with a charge-disproportionate  $Fe^{3+}$  and  $Fe^{5+}$  ions along (111)<sup>19</sup>. The latent defects and imperfections in the film may give rise to uncompensated spins in the bulk along with the surface AFM spins resulting in massive EB.

To summarize, we report a novel method of mosaicity induced disorder to obtain a rare phenomenon of PEB, magnetic annealing and  $H_{CF}$  induce PEB  $\rightarrow$  NEB transition and accompanying loop shape transitions. While the mosaic-disorder induces AFM exchange coupling at the interface which causes PEB, the uncompensated spins arising from the intrinsic nature of the magnetic order of LSFO yield the huge vertical shift. These studies open up new avenues for obtaining the otherwise elusive PEB for FM/AFM systems and an innovative way to tune giant vertical shift in magnetic oxides.

## Methods

The bilayers of LSFO as bottom layer and SRO as top layer were fabricated on STO (111) single crystal substrates by pulsed laser deposition (PLD) technique using a 248 nm KrF excimer laser. Deposition was carried out at a repetition rate of 4 Hz with laser energy of  $1.7$  J/cm<sup>2</sup> at the target with a substrate temperature of  $700^\circ\text{C}$ ,

oxygen partial pressure of 25 Pa and a post-deposition annealing for 5 minutes in 1.5 kPa of O<sub>2</sub>. Thickness of the bilayers with LSFO (37 nm) and SRO (20 nm) for  $LS_{Mosaic}$  and  $LS_{Non-mosaic}$  were measured using a surface profiler. The X-ray diffraction (XRD) measurements were carried out using PANalytical Empyrean. Magnetization measurements were performed on a SQUID magnetometer (Quantum design, USA).

- Meiklejohn, W. H. & Bean, C. P. New magnetic anisotropy. *Phys. Rev.* **102**, 1413 (1956).
- Bibes, M., Villegas, J. E. & Barthelemy, A. Ultrathin oxide films and interfaces for electronics and spintronics. *Adv. Phys.* **60**, 5 (2011).
- Dieny, B. *et al.* Giant magnetoresistive in soft ferromagnetic multilayers. *Phys. Rev. B* **43**, 1297 (1991).
- Nogués, J. *et al.* Exchange bias in nanostructures. *Phys. Rep.* **422**, 65 (2005).
- Nogués, J., Lederman, D., Moran, T. J. & Schuller, I. K. Positive exchange bias in FeF<sub>2</sub>-Fe bilayers. *Phys. Rev. Lett.* **76**, 4624 (1996).
- Nogués, J., Morellon, L., Leighton, C., Ibarra, M. R. & Schuller, I. K. Antiferromagnetic spin flop and exchange bias. *Phys. Rev. B* **61**, R6455 (2000).
- Ke, X., Rzchowski, M. S., Belenky, L. J. & Eom, C. B. Positive exchange bias in ferromagnetic La<sub>0.67</sub>Sr<sub>0.33</sub>MnO<sub>3</sub>/SrRuO<sub>3</sub> bilayers. *Appl. Phys. Lett.* **84**, 5458 (2004).
- Ali, M. *et al.* Exchange bias using a spin glass. *Nature Mater.* **6**, 70–75 (2007).
- Mishra, S. K., Radu, F., Dürr, H. A. & Eberhardt, W. Training-induced positive exchange bias in NiFe/IrMn bilayers. *Phys. Rev. Lett.* **102**, 177208 (2009).
- Malozemoff, A. P. Mechanisms of exchange anisotropy (invited). *J. Appl. Phys.* **63**, 3874 (1988).
- Leighton, C., Nogués, J., Jönsson-Åkerman, B. J. & Schuller, I. K. Coercivity Enhancement in exchange biased systems driven by interfacial magnetic frustration. *Phys. Rev. Lett.* **84**, 3466 (2000).
- Gibert, M., Zuboko, P., Scherwitzl, R., Ñíguez, J. & Triscone, J. M. Exchange bias in LaNiO<sub>3</sub>-LaMnO<sub>3</sub> superlattices. *Nature Mater.* **11**, 195–198 (2012).
- He, C. *et al.* Interfacial ferromagnetism and exchange bias in CaRuO<sub>3</sub>/CaMnO<sub>3</sub> Superlattices. *Phys. Rev. Lett.* **109**, 197202 (2012).
- Padhan, P. & Prellier, W. Coercivity enhancement in the SrRuO<sub>3</sub>/SrMnO<sub>3</sub> superlattices. *Appl. Phys. Lett.* **88**, 263114 (2006).
- Choi, Y. *et al.* Ferromagnetic Mn moments at SrRuO<sub>3</sub>/SrMnO<sub>3</sub> interface. *Appl. Phys. Lett.* **91**, 022503 (2007).
- Tian, Y. F. *et al.* Anomalous exchange bias at collinear/noncollinear spin interface. *Sci. Rep.* **3**, 1094 (2013).
- Cui, B. *et al.* Strain engineering induced interfacial self-assembly and intrinsic exchange bias in a manganite perovskite film. *Sci. Rep.* **3**, 2542 (2013).
- Li, J. Q., Matsui, Y., Park, S. K. & Tokura, Y. Charge ordered states in La<sub>1-x</sub>Sr<sub>x</sub>FeO<sub>3</sub>. *Phys. Rev. Lett.* **79**, 297 (1997).
- Okamoto, J. *et al.* Quasi-two-dimensional d-spin and p-hole ordering in the three-dimensional perovskite La<sub>1/3</sub>Sr<sub>2/3</sub>FeO<sub>3</sub>. *Phys. Rev. B* **82**, 132402 (2010).
- Sabyasachi, S. *et al.* Glassy magnetic phase driven by short-range charge and magnetic ordering in nanocrystalline La<sub>1/3</sub>Sr<sub>2/3</sub>FeO<sub>3</sub> -  $\delta$  Magnetization, Mössbauer, and polarized neutron studies. *Phys. Rev. B* **86**, 104416 (2012).
- Koster, G. *et al.* Structure, physical properties, and applications of SrRuO<sub>3</sub> thin films. *Rev. Mod. Phys.* **84**, 253 (2012).
- Koon, N. C. Calculation of exchange bias in thin-films with ferromagnetic/antiferromagnetic interfaces. *Phys. Rev. Lett.* **78**, 4865 (1997).
- Schulthess, T. C. & Butler, W. H. Consequences of spin-flop coupling in exchange biased films. *Phys. Rev. Lett.* **81**, 4516 (1998).
- Binek, C. Training of the exchange-bias effect: A simple analytic approach. *Phys. Rev. B* **70**, 014421 (2004).
- Binek, Ch., Polisetty, S., He, Xi. & Berger, A. Exchange bias training effect in coupled all ferromagnetic bilayer structures. *Phys. Rev. Lett.* **96**, 067201 (2006).
- Polisetty, S., Sahoo, S., Berger, A. & Binek, C. H. Temperature dependence of the training effect in exchange coupled ferromagnetic bilayers. *Phys. Rev. B* **78**, 184426 (2008).
- Hoffmann, A. Symmetry driven irreversibilities at ferromagnetic-antiferromagnetic interfaces. *Phys. Rev. Lett.* **93**, 097203 (2004).
- Chan, M. K., Parker, J. S., Crowell, P. A. & Leighton, C. Identification and separation of two distinct contributions to the training effect in polycrystalline CoO/FeMn bilayers. *Phys. Rev. B* **77**, 014420 (2008).
- Stiles, M. D. & McMichael, R. D. Temperature dependence of exchange bias in polycrystalline ferromagnet-antiferromagnet bilayers. *Phys. Rev. B* **60**, 12950 (1999).
- Fitzsimmons, M. R. *et al.* Pinned magnetization in the antiferromagnet and ferromagnet of an exchange bias system. *Phys. Rev. B* **75**, 214412 (2007).
- Gruyters, M. & Schmitz, D. Microscopic nature of ferro and antiferromagnetic interface coupling of uncompensated magnetic moments in Exchange Bias Systems. *Phys. Rev. Lett.* **100**, 077205 (2008).
- Ohldag, H. *et al.* Correlation between exchange bias and pinned interfacial spins. *Phys. Rev. Lett.* **91**, 017203 (2003).
- Kobriniskii, A. L., Goldman, A. M., Varela, M. & Pennycook, S. J. Thickness dependence of the exchange bias in epitaxial manganite bilayers. *Phys. Rev. B* **79**, 094405 (2009).
- Binek, Ch., Hochstrat, A. & Kleemann, W. Exchange bias in a generalized Meiklejohn-Bean approach. *J. Magn. Magn. Mater.* **234**, 353 (2001).



35. Ding, J. F., Tian, Y. F., Hu, W. J., Lin, W. N. & Wu, T. Exchange coupling and coercivity enhancement in cuprate/manganite bilayers. *Appl. Phys. Lett.* **102**, 032401 (2013).
36. Moutis, N., Christides, C., Panagiotopoulos, I. & Niarchos, D. Exchange-coupling properties of  $\text{La}_{1-x}\text{Ca}_x\text{MnO}_3$  ferromagnetic/antiferromagnetic multilayers. *Phys. Rev. B* **64**, 094429 (2001).
37. Ding, J. F. *et al.* Interfacial spin glass state and exchange bias in manganite bilayers with competing magnetic orders. *Phys. Rev. B* **87**, 054428 (2013).
38. Mauri, D., Siegmann, H. C., Bagus, P. S. & Kay, E. Simple model for thin ferromagnetic films exchange coupled to an antiferromagnetic substrate. *J. Appl. Phys.* **62**, 3047 (1987).
39. Kiwi, M., López, J. M., Portugal, R. D. & Ramírez, R. Positive exchange bias model: Fe/FeF<sub>2</sub> and Fe/MnF<sub>2</sub> bilayers. *Solid State Comm.* **116**, 315 (2000).
40. Stiles, M. D. & McMichael, R. D. Model for exchange bias in polycrystalline ferromagnet-antiferromagnet bilayers. *Phys. Rev. B* **59**, 3722 (1999).
41. Nowak, U. *et al.* Domain state model for exchange bias. I. Theory. *Phys. Rev. B* **66**, 014430 (2002).
42. Keller, J. *et al.* Domain state model for exchange bias. II. Experiments. *Phys. Rev. B* **66**, 014431 (2002).
43. Dong, S. *et al.* Exchange bias driven by the Dzyaloshinskii-Moriya interaction and ferroelectric polarization at G-type antiferromagnetic perovskite interfaces. *Phys. Rev. Lett.* **103**, 127201 (2009).
44. Hauet, T., Borchers, J. A., Mangin, Ph., Henry, Y. & Mangin, S. Training effect in an exchange bias system: the role of interfacial domain walls. *Phys. Rev. Lett.* **96**, 067207 (2006).
45. Henry, Y., Mangin, S., Hauet, T. & Montaigne, F. Positive exchange-bias induced by interface domain wall quenching in GdFe/TbFe films. *Phys. Rev. B* **73**, 134420 (2006).
46. Przyslupski, P. *et al.* Magnetic properties of  $\text{La}_{0.67}\text{Sr}_{0.33}\text{MnO}_3/\text{YBa}_2\text{Cu}_3\text{O}_7$  superlattices. *Phys. Rev. B* **69**, 134428 (2004).
47. Holden, T. *et al.* Proximity induced metal-insulator transition in  $\text{YBa}_2\text{Cu}_3\text{O}_7/\text{La}_{2/3}\text{Ca}_{1/3}\text{MnO}_3$  superlattices. *Phys. Rev. B* **69**, 064505 (2004).
48. Zhan, Q. & Krishnan, K. M. In-plane reorientation of magnetization in epitaxial exchange biased Fe/MnPd bilayers. *Appl. Phys. Lett.* **96**, 112506 (2010).
49. Rothman, J. *et al.* Observation of a bi-domain state and nucleation free switching in mesoscopic ring magnets. *Phys. Rev. Lett.* **86**, 1098 (2001).
50. Kläui, M. *et al.* Direct observation of spin configurations and classification of switching processes in mesoscopic ferromagnetic rings. *Phys. Rev. B* **68**, 134426 (2003).
51. Kläui, M. *et al.* Switching processes and switching reproducibility in ferromagnetic ring structures. *Appl. Phys. Lett.* **84**, 951 (2004).
52. Fullerton, E. E., Jiang, J. S., Grimsditch, M., Sowers, C. H. & Bader, S. D. Exchange-spring behavior in epitaxial hard/soft magnetic bilayers. *Phys. Rev. B* **58**, 12193 (1998).

## Acknowledgments

This work is supported by the Department of Science and Technology, New Delhi under the research project SR/S2/LOP-13/2010.

## Author contributions

R.R. and D.S.R. conceived and designed the experiments. R.R. and P.P. carried out the experiments. R.R. and D.S.R. wrote the paper. R.R., P.P., R.P.S. and D.S.R. discussed the results and commented on the manuscript.

## Additional information

Supplementary information accompanies this paper at <http://www.nature.com/scientificreports>

**Competing financial interests:** The authors declare no competing financial interests.

**How to cite this article:** Rana, R., Pandey, P., Singh, R.P. & Rana, D.S. Positive exchange-bias and giant vertical hysteretic shift in  $\text{La}_{0.3}\text{Sr}_{0.7}\text{FeO}_3/\text{SrRuO}_3$  bilayers. *Sci. Rep.* **4**, 4138; DOI:10.1038/srep04138 (2014).



This work is licensed under a Creative Commons Attribution 3.0 Unported license. To view a copy of this license, visit <http://creativecommons.org/licenses/by/3.0>