



OPEN

Dynamics and mechanism of oxygen annealing in $\text{Fe}_{1+y}\text{Te}_{0.6}\text{Se}_{0.4}$ single crystal

SUBJECT AREAS:

SUPERCONDUCTING
PROPERTIES AND
MATERIALSMAGNETIC PROPERTIES AND
MATERIALSYue Sun^{1,2}, Yuji Tsuchiya¹, Toshihiro Taen¹, Tatsuhiro Yamada¹, Sunseong Pyon¹, Akira Sugimoto³, Toshikazu Ekino³, Zhixiang Shi² & Tsuyoshi Tamegai¹Received
16 January 2014Accepted
19 March 2014Published
3 April 2014Correspondence and
requests for materials
should be addressed to
Z.X.S. (zxs@seu.edu.
cn) or T.T. (tamegai@
ap.t.u-tokyo.ac.jp)

¹Department of Applied Physics, The University of Tokyo, 7-3-1 Hongo, Bunkyo-ku, Tokyo 113-8656, Japan, ²Department of Physics and Key Laboratory of MEMS of the Ministry of Education, Southeast University, Nanjing 211189, People's Republic of China, ³Graduate School of Integrated Arts and Sciences, Hiroshima University, Higashi-Hiroshima 739-8521, Japan.

Iron chalcogenide $\text{Fe}(\text{Te},\text{Se})$ attracted much attention due to its simple structure, which is favorable for probing the superconducting mechanism. Its less toxic nature compared with iron arsenides is also advantageous for applications of iron-based superconductors. By intercalating spacer layers, superconducting transition temperature has been raised over 40 K. On the other hand, the presence of excess Fe is almost unavoidable in $\text{Fe}(\text{Te},\text{Se})$ single crystals, which hinders the appearance of bulk superconductivity and causes strong controversies over its fundamental properties. Here we report a systematic study of O_2 -annealing dynamics in $\text{Fe}_{1+y}\text{Te}_{1-x}\text{Se}_x$ by controlling the amount of O_2 , annealing temperature, and time. Bulk superconductivity can be gradually induced by increasing the amount of O_2 and annealing time at suitable temperatures. The optimally annealed crystals can be easily obtained by annealing with $\sim 1.5\%$ molar ratio of oxygen at 400°C for more than 1 hour. Superconductivity was witnessed to evolve mainly from the edge of the crystal to the central part. After the optimal annealing, the complete removal of excess Fe was demonstrated via STM measurements. Some fundamental properties were recharacterized and compared with those of as-grown crystals to discuss the influence of excess Fe.

Superconductivity discovered in iron chalcogenides has stimulated great interests since it is a possible candidate to break the superconducting transition temperature record ($T_c \sim 55$ K) in the iron-based superconductors. Although the initial T_c in FeSe is just 8 K, it increased up to 14 K^{1,2} with appropriate Te substitution and 37 K^{3,4} under high pressure. Furthermore, by intercalating spacer layers between adjacent FeSe layers, T_c has reached ~ 32 K⁵ in $\text{A}_x\text{Fe}_{2-y}\text{Se}_2$ ($A = \text{K}, \text{Cs}, \text{Rb}$ and Tl) and 43 K⁶ in $\text{Li}_x(\text{NH}_2)_y(\text{NH}_3)_{1-y}\text{Fe}_2\text{Se}_2$ ($x \sim 0.6; y \sim 0.2$). By applying pressure to $\text{A}_x\text{Fe}_{2-y}\text{Se}_2$, T_c can even reach ~ 48 K⁷. Recent angle-resolved photoemission spectroscopy (ARPES) revealed unexpected large superconducting gap ~ 19 meV in a single-layer FeSe , which suggests a T_c as high as 65 K⁸. Among iron chalcogenides, $\text{Fe}_{1+y}\text{Te}_{1-x}\text{Se}_x$ are unique in their structural simplicity, composing of only iron-chalcogenide layers, which is favorable for probing the mechanism of superconductivity. Band structure calculation^{9,10} and ARPES¹¹⁻¹³ results show that Fermi surface of $\text{FeTe}_{1-x}\text{Se}_x$ is characterized by hole bands around Γ point and electron bands around M point, which is similar to iron pnictides. Moreover, the competition between magnetism and superconductivity, similar to iron pnictides, is also observed in iron chalcogenides¹⁴. The parent compound Fe_{1+y}Te is not superconducting, but exhibits a spin-density wave (SDW) ground state. With Se doping, superconductivity emerges and T_c goes up to 14 K accompanied by the suppression of SDW. Iron chalcogenides also manifest some differences compared with iron pnictides. In particular, $\text{Fe}_{1+y}\text{Te}_{1-x}\text{Se}_x$ exhibits a bi-collinear antiferromagnetic ordering and it can be either commensurate or incommensurate depending on the Fe content^{15,16}, different from the common collinear commensurate antiferromagnetic ordering observed in all iron pnictides.

Although much attention has been paid to this compound, some crucially fundamental physical properties are still controversial. In optimally-doped $\text{Fe}_{1+y}\text{Te}_{1-x}\text{Se}_x$, ARPES¹³ shows an isotropic superconducting gap, while anisotropic or two-gap features were suggested by angle-resolved specific heat measurement¹⁷, muon spin rotation measurements^{18,19}, and optical conductivity measurements^{19,20}. Recently, London penetration depth measurement down to 50 mK indicates a possible nodal gap²¹. On the other hand, although Liu *et al.*¹⁴ reported that bulk superconductivity resides only in the region of Se level higher than 29%, it was observed in the Se doping level between 10 and 50% by Noji *et al.*^{22,23}. As for the Hall coefficient, conflicting low-temperature behaviors have



been observed in crystals with nominally the same amount of Se^{24-26} . Even in the case of resistivity, both the metallic and nonmetallic behaviors were reported, and the absolute value just above T_c has a spread from 200 to 1500 $\mu\Omega \text{ cm}^{1,2,23-26}$. These controversies are believed to come from the sample-dependent Fe nonstoichiometries^{15,27}, which originate from the partial occupation of the second Fe site (excess Fe site) in the Te/Se layer. The excess Fe with valence near Fe^+ will provide electron doping into the 11 system. The excess Fe is also strongly magnetic, which provides local moments that interact with the adjacent Fe layers²⁸. The magnetic moment from excess Fe will act as a pair breaker and also localize the charge carriers²⁴. Thus the existence of excess Fe complicates the study of iron chalcogenides from the mechanism of superconductivity to normal state properties. Unfortunately, the excess Fe is easily formed in the standard growth technique employing slow cooling²⁹. Specifically, crystals with higher Te content usually contain more excess Fe, and the magnitude of excess Fe decreases with the increase in Se doping²⁹. The excess Fe may be also responsible for the unexpected lagged application research despite its simpler structure, less toxic nature, and easier synthesis technology compared with iron-based 122 compounds^{30,31}. Thus, eliminating the influence of excess Fe is essential to clarify the intrinsic mechanism of superconductivity as well as to implement applications of iron chalcogenides.

Some previous studies indicated that annealing in O_2 ³²⁻³⁴, I_2 ³⁵ and chalcogen^{36,37} atmosphere is effective to induce superconductivity in the as-grown $\text{Fe}_{1+y}\text{Te}_{1-x}\text{Se}_x$ single crystal. In particular, our previous studies³⁴ have demonstrated that proper O_2 -annealing is very effective in inducing bulk superconductivity in $\text{Fe}_{1+y}\text{Te}_{0.6}\text{Se}_{0.4}$ single crystal. In this report, we have systematically studied the optimum condition and dynamics of O_2 -annealing to induce bulk superconductivity. O_2 -annealing is proved to be effective to remove the excess Fe, and a pure crystal without excess Fe was obtained. In addition to the evolution of superconductivity under O_2 -annealing, changes in some fundamental properties after removing the excess Fe were also studied and presented in the paper.

Results

Optimum condition and dynamics of O_2 -annealing in $\text{Fe}_{1+y}\text{Te}_{0.6}\text{Se}_{0.4}$. To study the optimum condition and dynamics of O_2 -annealing, we firstly fixed the annealing temperature at 400°C, and annealed the crystals by successively increasing amount of O_2 for 20 hours (enough time for the crystals to absorb the O_2 totally). Shown in Figure 1a is the temperature dependence of zero-field-cooled (ZFC) and field-cooled (FC) magnetization at 5 Oe for $\text{Fe}_{1+y}\text{Te}_{0.6}\text{Se}_{0.4}$ single crystal annealed with increasing the amount of O_2 . The as-grown crystal usually shows no superconductivity or very weak diamagnetic signal below ~ 3 K. After annealing, superconductivity emerges and T_c is gradually enhanced with increasing the cumulative amount of O_2 . The diamagnetic signal also increases with increasing the amount of O_2 even faster than the increase of T_c . Its magnitude at low temperatures reaches the maximum value when the onset T_c reaches ~ 7 K. However, it is well known that even the sample is mostly non-superconducting, the diamagnetic signal becomes significant when the non-superconducting region is covered by superconducting region. Thus, to prove the bulk superconductivity induced by O_2 -annealing, we need to refer to other quantities. Although specific heat is ideal for this purpose, limited size of the crystal optimized for uniform annealing does not allow reliable evaluation of the volume fraction of superconductivity. As an excellent alternative to probe bulk superconductivity, we propose to use the critical current density J_c . The method used for the calculation of J_c can be seen in the supplement. Self-field J_c at 2 K vs. the amount of O_2 are summarized in Figure 1b together with the change in T_c . It is obvious that both T_c and J_c are gradually enhanced by annealing with increasing amount of O_2 , and reach the optimal values of T_c higher than 14 K and J_c

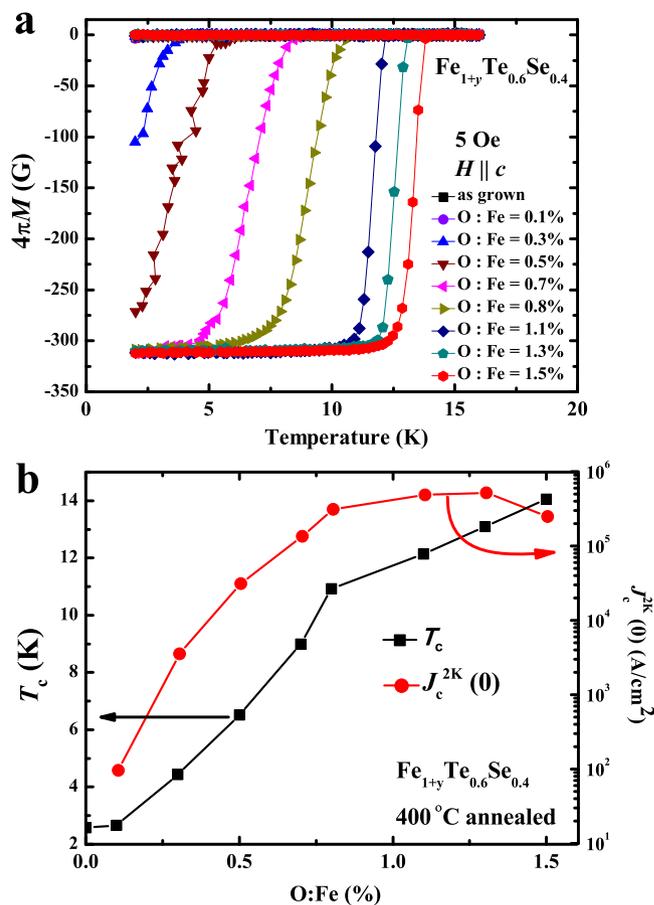


Figure 1 | (a) Temperature dependence of zero-field-cooled (ZFC) and field-cooled (FC) magnetization at 5 Oe for $\text{Fe}_{1+y}\text{Te}_{0.6}\text{Se}_{0.4}$ single crystal annealed at 400°C with increasing amount of O_2 (molar ratio of the oxygen to the nominal Fe ranging from 0.1% to 1.5%). (b) Changes in T_c and self-field $J_c(2 \text{ K})$ for $\text{Fe}_{1+y}\text{Te}_{0.6}\text{Se}_{0.4}$ annealed at 400°C with increasing amount of O_2 .

larger than $1 \times 10^5 \text{ A/cm}^2$ when the ratio of oxygen to the total Fe is $\sim 1.3\%$ to 1.5%. Bulk superconductivity with high T_c and large J_c is induced by the removal of excess Fe as we will show later. Here we should point out that when the ratio of oxygen is higher than 1.3%, the value of J_c slightly decreases, which may come from the reaction of Fe in Fe layers with O_2 . Actually, we found the crystal will be decomposed into oxides such as Fe_2O_3 , TeO_2 and SeO_2 after annealing with too much O_2 , as shown in the X-ray diffraction (XRD) pattern of Figure S1.

Next we study the effect of annealing temperature and time. In this experiment, the crystals were annealed with the optimal amount of O_2 (ratio of oxygen to the nominal Fe is 1.5%) at different temperatures with increasing time. It should be noted that the total amount of O_2 reacted with the crystal is larger than 1.5% since we fix the amount of O_2 in all the annealing processes. Shown in Figure 2a is the typical result of annealing at 200°C. With increasing annealing time, T_c gradually shifts to higher temperatures together with the sharpening of the transition width. J_c is also measured to probe the evolution of bulk superconductivity, which is shown in Figure 2b together with the change in T_c . Both T_c and J_c are increased with increasing annealing time, and reach the optimal values after 10 and 100 hours, respectively. To know the influence of temperature, the crystals were also annealed at 250, 300 and 400°C with increasing time, and one more typical results of a crystal annealed at 400°C are shown in Figure 2c. At all these annealing temperatures, both T_c and J_c are gradually increased with annealing time similar to the case of 200°C.

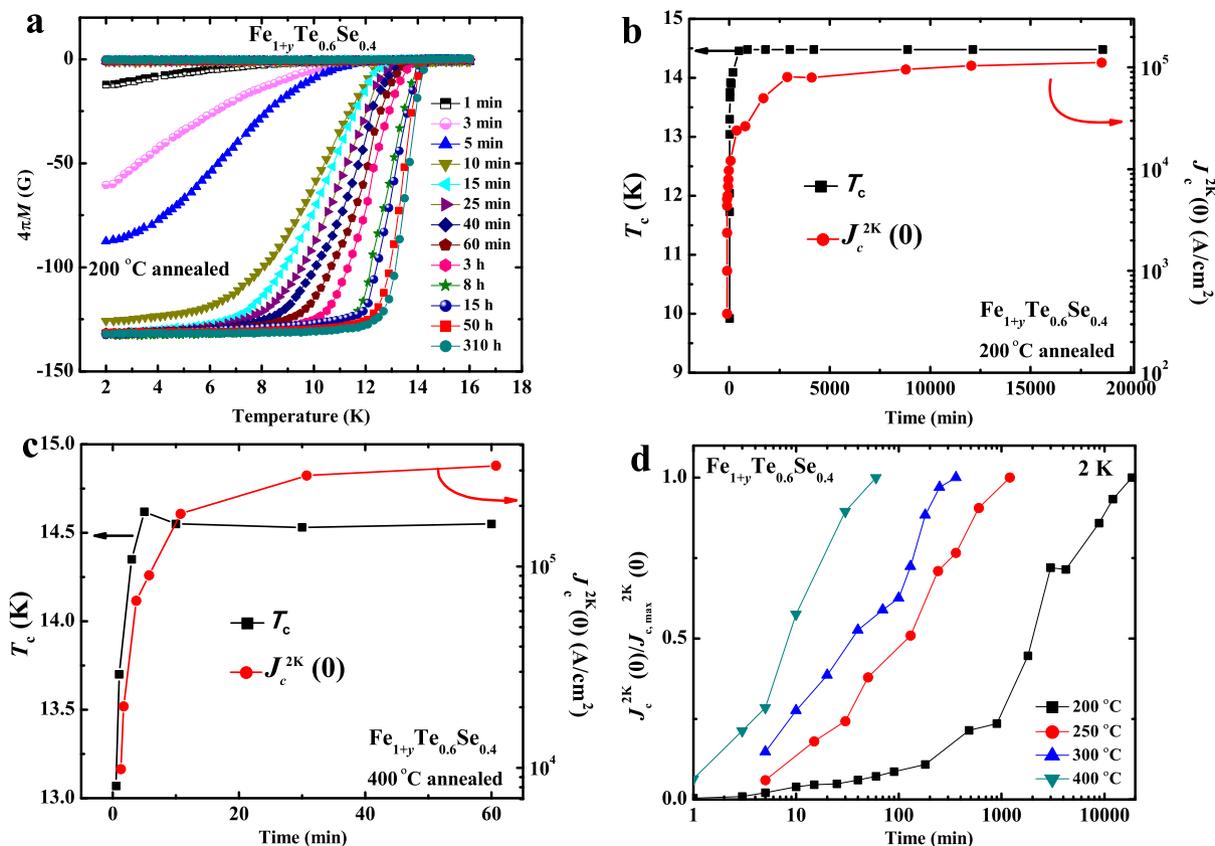


Figure 2 | (a) Temperature dependence of magnetization at 5 Oe for $\text{Fe}_{1+y}\text{Te}_{0.6}\text{Se}_{0.4}$ single crystal annealed at 200°C with increasing time. Changes in T_c and self-field $J_c(2\text{ K})$ with increasing annealing time at (b) 200°C, (c) 400°C. (d) Changes in $J_c^{2K}(0)/J_{c,\max}^{2K}(0)$ with increasing the annealing time at temperature from 200°C to 400°C.

Changes in J_c with annealing time at different temperatures were further scaled by $J_c/J_{c,\max}$, and plotted in Figure 2d, which manifests that the rate of inducing superconductivity is accelerated at higher annealing temperatures. It also proves that O_2 -annealing is very effective to induce bulk superconductivity in $\text{Fe}_{1+y}\text{Te}_{0.6}\text{Se}_{0.4}$. In particular, in the case of 400°C, T_c and J_c reach the optimal values only after 5 and 60 min annealing, respectively. We also tried to anneal the crystal at higher temperatures, like 500°C. In this case, the crystal is damaged during the annealing and superconductivity is not induced.

Spatial evolution of superconductivity during annealing. The above results manifest that O_2 -annealing can gradually induce bulk superconductivity in $\text{Fe}_{1+y}\text{Te}_{0.6}\text{Se}_{0.4}$, while the spatial evolution of superconductivity during the annealing and distribution of J_c are still unknown, which is crucial to the understand of the mechanism of O_2 -annealing. In order to reveal these unresolved issues, we employ the magneto-optical (MO) imaging for a crystal annealed for different periods of time, which allows direct observations of the spatial evolution of superconductivity and J_c . Figure 3a and b show the MO images of flux expulsion under 5 Oe at 10 K for the crystal annealed at 400°C for 1 and 3 min, respectively. When the sample is annealed for 1 min, only the edge part shows Meissner state, while the central part still remains non-superconducting. When the annealing time is increased to 3 min, all parts of the sample turn into Meissner state. It indicates that the superconductivity mainly evolves from edges of the crystal to the center.

As we know from Figure 2c, J_c of the crystal annealed at 400°C for 3 min is still lower than the optimal value, which means if the superconducting state evolves from the edge to the center, the edge of the crystal should maintain larger J_c than the central region. To examine

this assumption, we also took MO images on the crystal annealed for 3 min in the remanent state at temperatures ranging from 5 to 14 K, which are shown in Figure S2 in the supplement. Figure 3c shows profiles of the magnetic induction at different temperatures along the dashed line shown in Figure S2a. Both the MO images and profiles show that the magnetic field cannot totally penetrate the sample at 5 K. At higher temperature, the field penetrates deeper into the center. At 8 K, the sample is totally penetrated, and the MO image manifests a typical roof-top pattern up to 10 K. After that, from 11 to 14 K, the edge of the crystal traps higher magnetic field than the center, which indicates J_c in the edge of the crystal is larger. To directly observe the distribution of J_c in the crystal, we converted the MO images into the current distribution with a thin-sheet approximation and by using the fast Fourier transform calculation method³⁸. A typical image of the distribution of the modulus of J_c at 10 K is shown in Figure 3d, which manifests that the edge of the crystal maintains a larger current, and the J_c decays from the edge to the center. All these results testify that superconductivity mainly evolves from the edge of the crystal to the center. It should be noted, however, that we can observe a total expulsion of magnetic flux at 5 K even in the sample annealed for only 1 min (not shown). This fact means that weak superconductivity also evolves from the top and bottom surfaces.

Discussion

The above results on the O_2 -annealing dynamics prove that it is effective to induce bulk superconductivity in $\text{Fe}_{1+y}\text{Te}_{0.6}\text{Se}_{0.4}$ single crystal, and the superconductivity evolves mainly from the edge of the sample to the central part. Now we turn to the discussion of the mechanism of O_2 -annealing. Single crystal XRD measurements show that lattice constant c keeps almost constant value during the

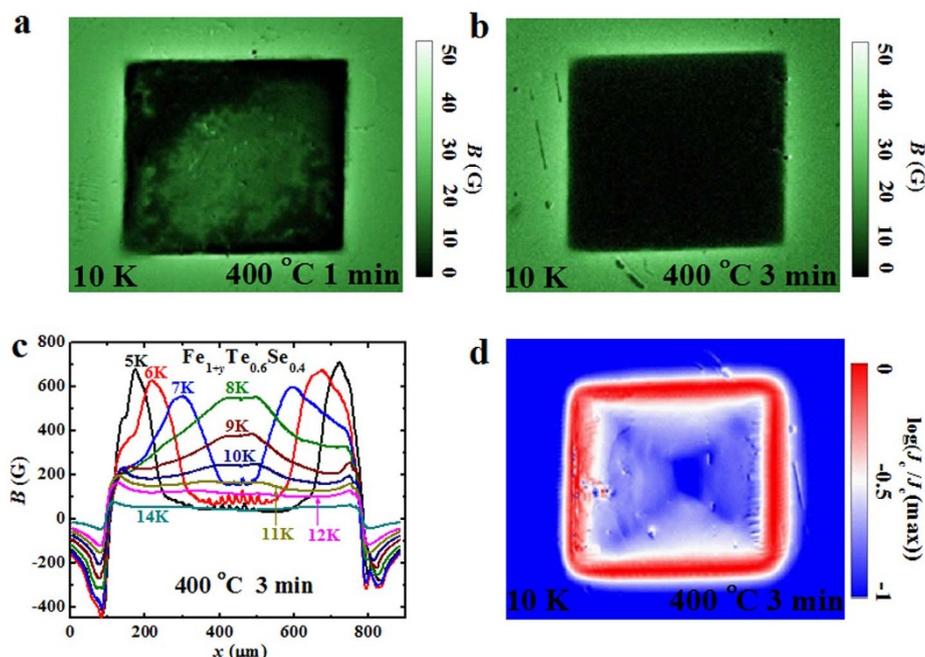


Figure 3 | Meissner state magneto-optical (MO) images under 5 Oe at 10 K for $\text{Fe}_{1+y}\text{Te}_{0.6}\text{Se}_{0.4}$ annealed at 400°C for (a) 1 and (b) 3 min, respectively. (c) Local magnetic induction profiles at temperatures from 5 K to 14 K taken along the dashed lines in Figure S2a. (d) Spatial distribution of $J_c/J_c(\text{max})$ at 10 K for sample annealed at 400°C for 3 min.

annealing process as shown in Figure S3a. On the other hand, the lattice constant a increases from $3.802 \pm 0.002 \text{ \AA}$ for the as-grown crystal to $3.812 \pm 0.002 \text{ \AA}$ for the annealed one. Such an increase in the in-plane lattice constant after removing excess Fe is similar to previous reports on structure refinement of crystals containing different amount of excess Fe^{35,39}. However, it is different from the structure change of $\text{FeTe}_{0.8}\text{S}_{0.2}$ annealed in O_2 ⁴⁰. Actually, in $\text{FeTe}_{0.8}\text{S}_{0.2}$, the superconductivity induced by O_2 -annealing is reported to be removed by further vacuum annealing⁴⁰. We also annealed our O_2 -annealed crystal again in vacuum at 400°C for more than two weeks. The magnetization results for a crystal before and after vacuum annealing were compared in Figure S3b, which shows that the superconductivity induced by O_2 -annealing is stable under further vacuum annealing. This result together with the unchanged lattice constant c all indicates that the oxygen is not simply doped into the sample.

As is well known, the presence of excess Fe is unavoidable in the growth of $\text{Fe}_{1+y}\text{Te}_{1-x}\text{Se}_x$ single crystals, which suppresses the superconductivity and causes magnetic correlations²⁷. In our as-grown single crystals, the amount of excess Fe is $\sim 14\%$ as analyzed by Inductively-coupled plasma (ICP) atomic emission spectroscopy. The O_2 -annealing may induce superconductivity by removing excess Fe from the as-grown crystal. Although the excess Fe may be removed after O_2 -annealing, it should still remain in the crystal, mainly on the surface, in some form of oxides. Thus, traditional compositional analysis methods like ICP, energy dispersive X-ray spectroscopy (EDX) and electron probe microanalyzer (EPMA) can hardly detect the change of excess Fe. Actually our ICP analyses on the O_2 -annealed crystal just show a slight change in the Fe content compared with the as-grown one. One important information is the fact that the color of the surface layer of the crystal gradually changes during the O_2 -annealing and turns into blue after annealing with sufficient O_2 as shown in the Figure S4, which is similar to the previous report on the crystal annealed in air⁴¹. EDX results show that the blue surface contains more Fe, which is interpreted as a signature that removed excess Fe forms oxide on the surface after annealing. To precisely determine the change in the number of excess Fe, we employ the scanning tunneling microscopy (STM)

measurement, which has atomic resolution. The excess Fe occupies the interstitial site in the Te/Se layer⁴², and the previous report proved that the cleaved $\text{Fe}_{1+y}\text{Te}_{1-x}\text{Se}_x$ single crystal possesses only the termination layer of Te/Se⁴³, which guarantee the STM can directly observe the excess Fe in Te/Se layer without the influence of neighboring Fe layers. Shown in Figure 4a is the STM image for the as-grown $\text{Fe}_{1+y}\text{Te}_{0.6}\text{Se}_{0.4}$ single crystal. There are several bright spots in the image, which represent the excess Fe according to the previous STM analysis^{43–47}. After optimally annealing in O_2 , the bright spots, i.e. the excess Fe, disappeared in STM images as shown in Figure 4b and a larger region in Figure 4c. Actually, we searched several different regions, and almost no bright spots can be found, which

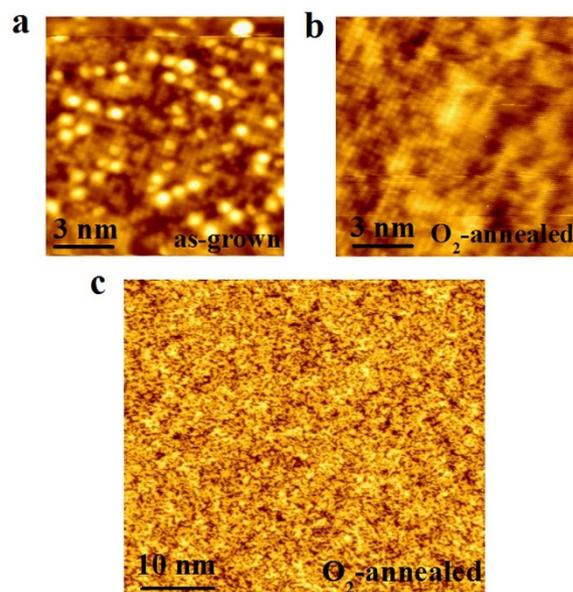


Figure 4 | STM images for (a) as-grown, (b) – (c) O_2 -annealed $\text{Fe}_{1+y}\text{Te}_{0.6}\text{Se}_{0.4}$ single crystal. The bright spots in (a) correspond to the excess Fe, which disappear in the optimally-annealed crystal.



directly proves that the excess Fe is almost totally removed by O₂-annealing. It may be also the reason why our O₂-annealed Fe_{1+y}Te_{0.6}Se_{0.4} single crystal is of high quality.

Figure 5a shows the temperature dependence of in-plane resistivity for the as-grown and O₂-annealed Fe_{1+y}Te_{0.6}Se_{0.4} single crystals. For both as-grown and O₂-annealed crystals, resistivity maintains a nearly constant value above ~150 K. On the other hand, from 150 K down to the superconducting transition, the as-grown crystal shows a nonmetallic behavior ($d\rho/dT < 0$), which is replaced by a metallic behavior ($d\rho/dT > 0$) after removing the excess Fe by O₂-annealing. Similar results are also reported in Fe_{1+y}Te_{1-x}Se_x with different amounts of excess Fe^{24,48}. To probe the influence of excess Fe to the superconductivity, specific heat is carefully measured in both the as-grown and O₂-annealed Fe_{1+y}Te_{0.6}Se_{0.4} single crystals. Specific heat divided by temperature C/T as a function of T for both crystals are shown in Figure 5b. Obviously, no specific heat jump can be observed in the as-grown crystal, which proves that the superconducting transition observed in the resistivity measurement comes from the filamentary superconductivity. After O₂-annealing, a clear specific heat jump can be observed, indicating the bulk nature of the superconductivity in O₂-annealed Fe_{1+y}Te_{0.6}Se_{0.4}. Specific heat jump $\Delta C/T_c$ was obtained as ~66.3 mJ/molK² with $T_c = 14.5$ K determined by entropy balance consideration. The normalized specific heat jump at T_c , $\Delta C/\gamma_n T_c$, is ~3.0 by using the fitted Sommerfeld coefficient of $\gamma_n = 22$ mJ/molK². (Details about the fitting of the specific heat data and more discussions can be seen in the supplement.) The value is larger than those of 2.1 ~ 2.8 in previous reports^{22,49}, and is much larger than BCS weak-coupling value of 1.43 indicating that superconductivity in O₂-annealed Fe_{1+y}Te_{0.6}Se_{0.4} is strong coupling in nature. To further reveal the influence of excess Fe on the electronic behavior, Hall coefficient R_H of the as-grown and well-annealed samples were measured and shown in Figure 5c. R_H is almost

temperature independent above 150 K, and keeps a constant value $\sim 1 \times 10^{-9}$ m³/C for both the as-grown and O₂-annealed samples. When temperature decreases below 150 K, an obvious divergence in R_H is observed. For the as-grown crystal, R_H gradually increases with decreasing temperature. On the other hand, for the O₂-annealed crystal, R_H keeps nearly temperature independence above 50 K, followed by a sudden decrease, and finally changes sign from positive to negative before approaching T_c . The sign reversal in Hall coefficient can be attributed to the multiband structure¹², indicating the dominance of electron in the charge carriers before the occurrence of superconductivity. We should point out that the sign reversal in R_H is also observed in high-quality polycrystal and thin films^{26,50}, usually absent in single crystals with more excess Fe²⁴, which may be the intrinsic nature of FeTe_{0.6}Se_{0.4}. Figure 5d shows the comparison of high-temperature magnetic susceptibility, χ , for Fe_{1+y}Te_{0.6}Se_{0.4} single crystals before and after the O₂-annealing. At high temperatures, susceptibilities for both crystals maintain almost constant values, and the value of χ in the O₂-annealed crystal is appreciably larger than that of the as-grown crystal, distinct from the previous report⁵¹, which may come from the contribution of iron oxide on the surface. When the temperature approaches T_c , χ slightly decreases in the annealed crystal, while it dramatically increases in the as-grown sample. The differences in resistivity, specific heat, Hall effect, and magnetic susceptibility in Fe_{1+y}Te_{0.6}Se_{0.4} before and after the O₂-annealing can be attributed to the delocalization of excess Fe by the O₂-annealing. Density functional study shows that the excess Fe in the interstitial sites is magnetic and interacts with magnetism of Fe in Fe planes²⁸. The magnetic moment from excess Fe will act as a pair breaker, so that the specific heat jump associated with the superconducting transition is suppressed in the as-grown crystal and recurs after removing the excess Fe by O₂-annealing. On the other hand, the magnetic moment will also localize the charge

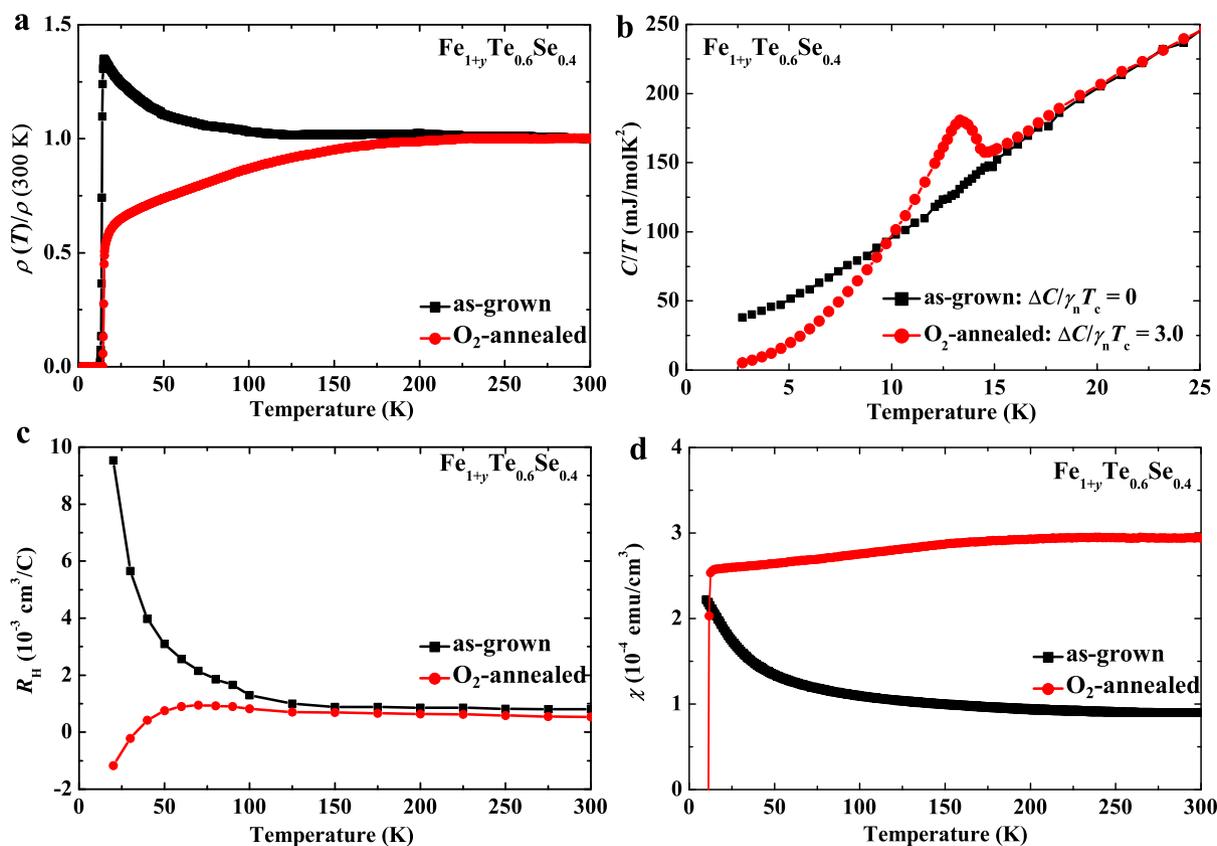


Figure 5 | Temperature dependence of (a) in-plane resistivity scaled by the value at 300 K, (b) specific heat plotted as C/T vs T , (c) Hall coefficient, and (d) magnetization under 50 kOe with field parallel to c -axis in the as-grown and O₂-annealed Fe_{1+y}Te_{0.6}Se_{0.4} single crystals.



carriers, which causes the nonmetallic resistive behavior and the increase of R_{H} at low temperatures. Moreover, neutron scattering measurements revealed that the coupling between the excess Fe and adjacent Fe layers will tune the AFM order from commensurate to incommensurate^{15,16}. Furthermore, the resistivity, Hall coefficient, and magnetic susceptibility for the as-grown crystal all undergo a steep increase below 50 K, which is consistent with the neutron scattering result that the short-range magnetic order in a crystal with rich excess Fe enhances noticeably below 40 K^{15,52}. On the other hand, the divergence of transport properties between the as-grown and O₂-annealed samples occurs below 150 K, which may come from the increasing correlation below that temperature⁵³.

In summary, we have systematically studied the optimal condition and dynamics of O₂-annealing in Fe_{1+y}Te_{0.6}Se_{0.4} single crystal. Bulk superconductivity was gradually induced by annealing with increasing amount of O₂ and annealing time at temperatures from 200 ~ 400 °C. MO images show that superconductivity mainly evolves from the edge of the crystal to the center. STM observations directly demonstrate that the excess Fe is removed after the optimal annealing. Transport, heat capacity, and magnetization measurements on the sample before and after the O₂-annealing manifest that the O₂-annealing induces bulk superconductivity and delocalize the charge carriers by removing the excess Fe. The controllable way of obtaining high-quality Fe(Te,Se) crystals without excess Fe is hopeful to solve the controversies in iron chalcogenides, and to pave the way to overcome the obstacles for applications.

Methods

Sample growth and O₂-annealing. Single crystals with a composition Fe_{1+y}Te_{0.6}Se_{0.4} were grown by using the self-flux method as described in detail elsewhere³⁴. The obtained crystals were then cut and cleaved into thin slices with dimensions about 2.0 × 1.0 × 0.05 mm³, weighed and loaded into a quartz tube with $d \sim 10$ mm ϕ for further annealing. The quartz tube was carefully baked and tested not to emit any gas under the same condition as the sample annealing. The quartz tube was carefully evacuated by a diffusion pump, and the pressure was measured by a diaphragm-type manometer with an accuracy better than 1 mTorr. After totally pumping out the gas, we filled Ar/O₂(1%) mixed gas into the quartz tube and sealed it into the length of 100 mm. During the sealing process, the manometer monitored the pressure in the system in real-time to prevent gas leakage and controlled the O₂ pressure in the quartz tube. Because of the fixed volume, the amount of O₂ filled into the quartz tube can be evaluated by the pressure. Then the crystals were annealed at selected temperatures (ranging from 200 °C to 400 °C) for different periods of time, followed by water quenching. We also confirmed that almost all O₂ in the quartz tube were consumed by the crystal by breaking the quartz tube in a larger quartz tube while monitoring its pressure. In this case, we used pure O₂ gas. Furthermore, we confirmed that the increase in the crystal weight after the annealing is equal to the mass of O₂ filled into the quartz tube. Our careful experiments described above guarantee that the O₂ was totally absorbed by the crystal.

Measurements and verifications. Magnetization measurements were performed to check the superconducting transition temperature T_c and critical current density J_c by using a commercial superconducting quantum interference device (SQUID). Measurements on sample annealed at certain temperature with increasing amount of O₂, or increasing annealing time were performed on a given crystal piece to avoid piece-dependent influence. Longitudinal and transverse (Hall) resistivity measurements were performed by the six-lead method. Specific heat was measured with a Quantum Design physical property measurement system (PPMS). Magneto-optical images were taken by using the local-field-dependent Faraday effect in the in-plane magnetized garnet indicator film employing a differential method. Details of the lattice constant change during the annealing was characterized by means of X-ray diffraction (MAC Science M18XHF) with Cu-K α radiation. Inductively-coupled plasma (ICP) atomic emission spectroscopy and energy dispersive X-ray spectroscopy (EDX) were used for chemical analyses. Scanning tunneling microscopy (STM) images were obtained by a modified Omicron LT-UHV-STM system⁵⁴. The sample was cleaved in situ at 4 K in an ultra-high vacuum chamber of $\sim 10^{-8}$ Pa to obtain fresh and unaffected crystal surface.

- Sales, B. C. *et al.* Bulk superconductivity at 14 K in single crystals of Fe_{1+y}Te_xSe_{1-x}. *Phys. Rev. B* **79**, 094521 (2009).
- Taen, T., Tsuchiya, Y., Nakajima, Y. & Tamegai, T. Superconductivity at $T_c \sim 14$ K in single-crystalline FeTe_{0.61}Se_{0.39}. *Phys. Rev. B* **80**, 092502 (2009).
- Margadonna, S. *et al.* Pressure evolution of the low-temperature crystal structure and bonding of the superconductor FeSe ($T_c = 37$ K). *Phys. Rev. B* **80**, 064506 (2009).

- Medvedev, S. *et al.* Electronic and magnetic phase diagram of β -Fe_{1.01}Se with superconductivity at 36.7 K under pressure. *Nat. Mater.* **8**, 630–633 (2009).
- Guo, J. *et al.* Superconductivity in the iron selenide K_xFe₂Se₂ ($0 \leq x \leq 1.0$). *Phys. Rev. B* **82**, 180520 (2010).
- Burrard-Lucas, M. *et al.* Enhancement of the superconducting transition temperature of FeSe by intercalation of a molecular spacer layer. *Nat. Mater.* **12**, 15–19 (2013).
- Sun, L. *et al.* Re-emerging superconductivity at 48 kelvin in iron chalcogenides. *Nature* **483**, 67–69 (2012).
- He, S. *et al.* Phase diagram and electronic indication of high-temperature superconductivity at 65 K in single-layer FeSe films. *Nat. Mater.* **12**, 605–610 (2013).
- Raghu, S., Qi, X. L., Liu, C. X., Scalapino, D. J. & Zhang, S. C. Minimal two-band model of the superconducting iron oxypnictides. *Phys. Rev. B* **77**, 220503 (2008).
- Subedi, A., Zhang, L., Singh, D. J. & Du, M. H. Density functional study of FeS, FeSe, and FeTe: Electronic structure, magnetism, phonons, and superconductivity. *Phys. Rev. B* **78**, 134514 (2008).
- Xia, Y. *et al.* Fermi Surface Topology and Low-Lying Quasiparticle Dynamics of Parent Fe_{1+x}Te/Se Superconductor. *Phys. Rev. Lett.* **103**, 037002 (2009).
- Chen, F. *et al.* Electronic structure of Fe_{1.04}Te_{0.66}Se_{0.34}. *Phys. Rev. B* **81**, 014526 (2010).
- Miao, H. *et al.* Isotropic superconducting gaps with enhanced pairing on electron Fermi surfaces in FeTe_{0.55}Se_{0.45}. *Phys. Rev. B* **85**, 094506 (2012).
- Liu, T. J. *et al.* From (π ,0) magnetic order to superconductivity with (π , π) magnetic resonance in Fe_{1.02}Te_{1-x}Se_x. *Nat. Mater.* **9**, 718–720 (2010).
- Bao, W. *et al.* Tunable ($\delta\pi$, $\delta\pi$)-Type Antiferromagnetic Order in α -Fe(Te,Se) Superconductors. *Phys. Rev. Lett.* **102**, 247001 (2009).
- Li, S. L. *et al.* First-order magnetic and structural phase transitions in Fe_{1+y}Se_xTe_{1-x}. *Phys. Rev. B* **79**, 054503 (2009).
- Zeng, B. *et al.* Anisotropic structure of the order parameter in FeSe_{0.45}Te_{0.55} revealed by angle-resolved specific heat. *Nat. Commun.* **1**, 112 (2010).
- Bendele, M. *et al.* Anisotropic superconducting properties of single-crystalline FeSe_{0.5}Te_{0.5}. *Phys. Rev. B* **81**, 224520 (2010).
- Biswas, P. K. *et al.* Muon-spin-spectroscopy study of the penetration depth of FeTe_{0.5}Se_{0.5}. *Phys. Rev. B* **81**, 092510 (2010).
- Pimenov, A. *et al.* Terahertz conductivity in FeSe_{0.5}Te_{0.5} superconducting films. *New J. Phys.* **15**, 013032 (2013).
- Diaconu, A. *et al.* Possible nodal superconducting gap in Fe_{1+y}Te_{1-x}Se_x single crystals from ultralow temperature penetration depth measurements. *Phys. Rev. B* **88**, 104502 (2013).
- Noji, T. *et al.* Specific-Heat Study of Superconducting and Normal States in FeSe_{1-x}Te_x ($0.6 \leq x \leq 1$) Single Crystals: Strong-Coupling Superconductivity, Strong Electron-Correlation, and Inhomogeneity. *J. Phys. Soc. Jpn.* **81**, 054708 (2012).
- Noji, T. *et al.* Growth, Annealing Effects on Superconducting and Magnetic Properties, and Anisotropy of FeSe_{1-x}Te_x ($0.5 \leq x \leq 1$) Single Crystals. *J. Phys. Soc. Jpn.* **79**, 084711 (2010).
- Liu, T. J. *et al.* Charge-carrier localization induced by excess Fe in the superconductor Fe_{1+y}Te_{1-x}Se_x. *Phys. Rev. B* **80**, 174509 (2009).
- Liu, Y., Kremer, R. K. & Lin, C. T. Doping evolution of the magnetic susceptibility and transport properties of Fe_{1+y}Te_{1-x}Se_x single crystals. *Supercond. Sci. Technol.* **24**, 035012 (2011).
- Tsukada, I. *et al.* Hall effect in superconducting Fe(Se_{0.5}Te_{0.5}) thin films. *Phys. Rev. B* **81**, 054515 (2010).
- Bendele, M. *et al.* Tuning the superconducting and magnetic properties of Fe_{0.25}Te_{0.75} by varying the iron content. *Phys. Rev. B* **82**, 212504 (2010).
- Zhang, L., Singh, D. J. & Du, M. H. Density functional study of excess Fe in Fe_{1+x}Te: Magnetism and doping. *Phys. Rev. B* **79**, 012506 (2009).
- Wen, J., Xu, G., Gu, G., Tranquada, J. M. & Birgeneau, R. J. Interplay between magnetism and superconductivity in iron-chalcogenide superconductors: crystal growth and characterizations. *Rep. Prog. Phys.* **74**, 124503 (2011).
- Weiss, J. D. *et al.* High intergrain critical current density in fine-grain (Ba_{0.6}K_{0.4})Fe₂As₂ wires and bulks. *Nat. Mater.* **11**, 682–685 (2012).
- Ding, Q. P. *et al.* Low-temperature synthesis of FeTe_{0.5}Se_{0.5} polycrystals with a high transport critical current density. *Supercond. Sci. Technol.* **24**, 075025 (2011).
- Hu, H. *et al.* Structure of the oxygen-annealed chalcogenide superconductor Fe_{1.08}Te_{0.55}Se_{0.45}O_x. *Phys. Rev. B* **85**, 064504 (2012).
- Kawasaki, Y. *et al.* Phase diagram and oxygen annealing effect of FeTe_{1-x}Se_x iron-based superconductor. *Solid State Commun.* **152**, 1135–1138 (2012).
- Sun, Y., Taen, T., Tsuchiya, Y., Shi, Z. X. & Tamegai, T. Effects of annealing, acid and alcoholic beverages on Fe_{1+y}Te_{0.6}Se_{0.4}. *Supercond. Sci. Technol.* **26**, 015015 (2013).
- Rodriguez, E. E. *et al.* Chemical control of interstitial iron leading to superconductivity in Fe_{1+x}Te_{0.7}Se_{0.3}. *Chem. Sci.* **2**, 1782–1787 (2011).
- Sun, Y. *et al.* Evolution of Superconductivity in Fe_{1+y}Te_{1-x}Se_x Annealed in Te Vapor. *J. Phys. Soc. Jpn.* **82**, 093705 (2013).
- Sun, Y. *et al.* Bulk Superconductivity in Fe_{1+y}Te_{1-x}Se_x Induced by Annealing in Se and S Vapor. *J. Phys. Soc. Jpn.* **82**, 115002 (2013).
- Roth, B. J., Sepulveda, N. G. & Wikswo, J. P. Using a magnetometer to image a two-dimensional current distribution. *J. Appl. Phys.* **65**, 361–372 (1989).



39. Viennois, R., Giannini, E., van der Marel, D. & Černý, R. Effect of Fe excess on structural, magnetic and superconducting properties of single-crystalline $\text{Fe}_{1+x}\text{Te}_{1-y}\text{Se}_y$. *J Solid State Chem.* **183**, 769–775 (2010).
40. Mizuguchi, Y., Deguchi, K., Tsuda, S., Yamaguchi, T. & Takano, Y. Evolution of superconductivity by oxygen annealing in $\text{FeTe}_{0.8}\text{S}_{0.2}$. *Europhys. Lett.* **90**, 57002 (2010).
41. Dong, C. *et al.* Revised phase diagram for the $\text{FeTe}_{1-x}\text{Se}_x$ system with fewer excess Fe atoms. *Phys. Rev. B* **84**, 224506 (2011).
42. Singh, D. J. Superconductivity and magnetism in 11-structure iron chalcogenides in relation to the iron pnictides. *Sci. Technol. Adv. Mat.* **13**, 054304 (2012).
43. Masee, F. *et al.* Cleavage surfaces of the $\text{BaFe}_{2-x}\text{Co}_x\text{As}_2$ and $\text{Fe}_y\text{Se}_{1-x}\text{Te}_x$ superconductors: A combined STM plus LEED study. *Phys. Rev. B* **80**, 140507 (2009).
44. Hanaguri, T., Niitaka, S., Kuroki, K. & Takagi, H. Unconventional s-Wave Superconductivity in $\text{Fe}(\text{Se},\text{Te})$. *Science* **328**, 474–476 (2010).
45. Kato, T. *et al.* Local density of states and superconducting gap in the iron chalcogenide superconductor $\text{Fe}_{1+\delta}\text{Se}_{1-x}\text{Te}_x$ observed by scanning tunneling spectroscopy. *Phys. Rev. B* **80**, 180507 (2009).
46. Ukita, R., Sugimoto, A. & Ekino, T. Scanning tunneling microscopy on iron-chalcogenide superconductor $\text{Fe}(\text{Se},\text{Te})$ single crystal. *Physica C* **471**, 622–624 (2011).
47. Ukita, R., Sugimoto, A. & Ekino, T. Scanning-tunneling microscopy and break-junction spectroscopy on the superconducting $\text{Fe}(\text{Se},\text{Te})$ single crystal. *Physica C* **484**, 22–26 (2013).
48. Rößler, S. *et al.* Disorder-driven electronic localization and phase separation in superconducting $\text{Fe}_{1+y}\text{Te}_{0.5}\text{Se}_{0.5}$ single crystals. *Phys. Rev. B* **82**, 144523 (2010).
49. Hu, J. *et al.* Calorimetric evidence of strong-coupling multiband superconductivity in $\text{Fe}(\text{Te}_{0.57}\text{Se}_{0.43})$ single crystal. *Phys. Rev. B* **83**, 134521 (2011).
50. Tropeano, M. *et al.* Transport and superconducting properties of Fe-based superconductors: a comparison between $\text{SmFeAsO}_{1-x}\text{F}_x$ and $\text{Fe}_{1+y}\text{Te}_{1-x}\text{Se}_x$. *Supercond. Sci. Technol.* **23**, 054001 (2010).
51. Komiya, S., Hanawa, M., Tsukada, I. & Maeda, A. Effect of Vacuum Annealing on Superconductivity in $\text{Fe}(\text{Se},\text{Te})$ Single Crystals. *J. Phys. Soc. Jpn.* **82**, 064710 (2013).
52. Wen, J. *et al.* Short-range incommensurate magnetic order near the superconducting phase boundary in $\text{Fe}_{1+\delta}\text{Te}_{1-x}\text{Se}_x$. *Phys. Rev. B* **80**, 104506 (2009).
53. Homes, C. C. *et al.* Electronic correlations and unusual superconducting response in the optical properties of the iron chalcogenide $\text{FeTe}_{0.55}\text{Se}_{0.45}$. *Phys. Rev. B* **81**, 180508 (2010).
54. Sugimoto, A., Ekino, T. & Eisaki, H. Nanoscale modulation of local barrier height on Bi-based cuprate superconductors observed by scanning tunneling microscopy/spectroscopy. *J. Phys. Soc. Jpn.* **77**, 043705 (2008).

Acknowledgments

This work is partly supported by the Natural Science Foundation of China, the Ministry of Science and Technology of China (973 project: No. 2011CBA00105), and Japan-China Bilateral Joint Research Project by the Japan Society for the Promotion of Science. ICP analyses were performed at Chemical Analysis Section in Materials Analysis Station of NIMS.

Author contributions

Y.S. performed most of the experiments and analyzed the data. Y.T. contributed to the MO images. T. Taen contributed to the growth of single crystal. T.Y. and S.P. contributed to the specific heat measurement. A.S. and T.E. performed the STM measurement. Y.S., Z.S. and T. Tamegai designed the research. Most of the text of the paper was written jointly by Y.S. and T. Tamegai. All the authors contributed to discussion on the results for the manuscript.

Additional information

Supplementary information accompanies this paper at <http://www.nature.com/scientificreports>

Competing financial interests: The authors declare no competing financial interests.

How to cite this article: Sun, Y. *et al.* Dynamics and mechanism of oxygen annealing in $\text{Fe}_{1+y}\text{Te}_{0.6}\text{Se}_{0.4}$ single crystal. *Sci. Rep.* **4**, 4585; DOI:10.1038/srep04585 (2014).



This work is licensed under a Creative Commons Attribution-NonCommercial-ShareAlike 3.0 Unported License. The images in this article are included in the article's Creative Commons license, unless indicated otherwise in the image credit; if the image is not included under the Creative Commons license, users will need to obtain permission from the license holder in order to reproduce the image. To view a copy of this license, visit <http://creativecommons.org/licenses/by-nc-sa/3.0/>