



OPEN

SUBJECT AREAS:
COLLOIDS
NANOPARTICLESReceived
2 September 2014Accepted
19 January 2015Published
17 February 2015Correspondence and
requests for materials
should be addressed to
L.T.C. (lt.cai@siat.ac.
cn)* These authors
contributed equally to
this work.

Large-Scale Synthesis of Palladium Concave Nanocubes with High-Index Facets for Sustainable Enhanced Catalytic Performance

Xiaobin Xie^{1,2*}, Guanhui Gao^{1*}, Zhengyin Pan¹, Tingjun Wang², Xiaoqing Meng^{1,2} & Lintao Cai¹

¹Guangdong Key Laboratory of Nanomedicine, CAS Key Laboratory of Health Informatics, Institute of Biomedicine and Biotechnology, Shenzhen Institutes of Advanced Technology, Chinese Academy of Sciences, Shenzhen, 518055, P. R. China, ²Nano Science and Technology Institute, University of Science & Technology of China, Suzhou, 215123, P. R. China.

The catalytic activity of palladium (Pd) nanostructures highly relies on their size and morphology, especially enclosed with high-index facets, which provide more active sites so as to enhance their catalytic performance comparing with their low-index facet counterparts. Herein, Pd concave nanocubes enclosed with {730} facets by a one-pot scalable liquid method, with various high-index facets are synthesized via tuning reduction kinetics. Due to their high-index facets, the Pd concave nanocubes exhibit much higher electrocatalytic activity and stability for methanol oxidation than the Pd nanocubes enclosed by {100} facets and commercial Pd/C. Furthermore, we scale up synthesis of Pd concave nanocubes by expanding the volume of all species to fifty times with high-yield production.

Palladium (Pd) nanostructures with a variety of size and shape have been actively received great attention for years, due to their excellent performance as catalysts used in chemical industry, environmental technology and energy field^{1–6}. Recent studies proposed that the catalytic activity was highly dependent on the size and morphology of Pd nanostructures, especially, the morphology played a significant role in determining the selectivity and active sites^{7–10}. Very recently, Pd nanocrystals have been prepared with various morphologies including cube, octahedron, decahedron, icosahedrons and plate^{11–15}. Most of them were enclosed by low-index facets such as {100}, {110} and {111}^{12–17}. However, Pd nanostructures with high-index facets have generally exhibited much higher catalytic performance comparing with their low-index facet counterparts^{10,18–21}. Moreover, synthesis of Pd nanocrystals enclosed by high-index facets has been challenged in engineering both size and morphology. Xia and his co-workers reported seed-mediated method for synthesis of Pd concave nanocubes (PdCNs) covered by high-index {730} facets using poly (vinylpyrrolidone) (PVP) and KBr as capping agents²². Zhang et al demonstrated a liquid approach, which reduced Na₂PdCl₄ by L-ascorbic acid (AA) and capped by cetyltrimethyl-ammonium bromide (CTAB) and cetyltrimethylammonium chloride (CTAC), towards preparation of Pd concave nanocubes enclosed by various high-index facets such as {730} and {310} facets²³. It was reported that a Cu (II)-assisted seed-mediated protocol triggering Pd concave nanocubes²⁴. Nonetheless, these synthesis processes of PdCNs were multi-stepped and impure products, which made it difficult to achieve large scalable yield²⁵. Therefore, it is a great challenge to explore a robust and simple technique approaching a large yield with high-index enclosed facets.

Herein, we develop a scalable strategy to synthesize PdCNs with high-index facets via tuning reduction kinetics. It achieves the insights into high-volume production and controllable morphologies by manipulating the reaction temperature and the concentration of CTAB and AA. Generally, elevating the reaction temperature is beneficial to the formation of thermodynamic favored production—Pd nanocubes. While, the high-index facets PdCNs could be obtained by increasing concentration of AA but reducing the reaction temperature. Hence, the evolution of controllable Pd morphologies from nanocubes structures to various concave nanocubes is conducted by a series of optimization routine. Furthermore, we scale up synthesis of Pd concave nanocubes by approaching the volume of all species to fifty times as shown in scheme S1 (Experimental section details in supporting information), which is in high-yield production of PdCNs. As expected, these PdCNs with high-index facets exhibit a highly enhanced catalytic property toward methanol oxidation comparing with the normal Pd nanocubes enclosed by low-index



Increasing Concentration of AA

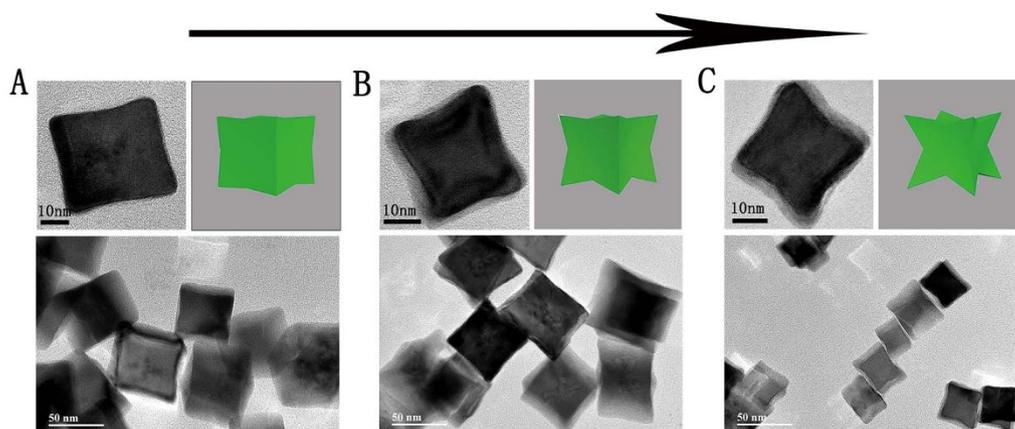


Figure 2 | Morphology evolution of PdCNs via tuning the concentration of AA. The variation in concentration for AA listed below: (A) 3 mM; (B) 15 mM; (C) 60 mM.

cathodic peak which is associated with the oxidation/reduction of Pd nanostructures, appears near 0.4 V versus saturated calomel electrode (SCE) for PdCNs and Pd nanocubes. Furthermore, the electrochemically active surface area (ECSA) of PdCNs, Pd nanocubes and commercial Pd/C is evaluated respectively by investigating the electric charges of oxygen desorption based on the CV curves recorded in the 0.5 M H_2SO_4 (Figure S7 A). There is a clear desorption peak for all samples near 0.4 V corresponding to the terrace on Pd surface. The calculated ECSA of PdCNs with 30 nm length is $18.472 \text{ m}^2/\text{g}$, which is about 1.5 times and 1.9 times of that of Pd nanocubes ($12.354 \text{ m}^2/\text{g}$) and commercial Pd/C ($9.651 \text{ m}^2/\text{g}$), respectively (Figure S7 B). Notably, the ECSA of PdCNs with 43 nm length is $7.912 \text{ m}^2/\text{g}$ only, due to their smaller specific surface area comparably.

The higher oxidation/reduction activity of the PdCNs indicates their superior performance for the electrooxidation of methanol. Methanol oxidation measurements are further carried out in a solution containing 1M KOH and 1M methanol. As demonstrated in Figure 4B & C, the forward anodic peak current density for Pd catalyst increases in the order of Pd/C < Pd nanocubes < PdCNs, what is worth mentioning, the current density of that commercial Pd/C is about $0.374 \text{ mA}/\text{cm}^2$, illustrating its weak catalytic property. And the catalytic current of PdCNs is greatly improved 2.8 times and 50 times compared to that of Pd nanocubes and Pd/C, respectively

(Figure 4C). It manifests that the catalytic activity of PdCNs for methanol oxidation is significantly higher than Pd nanocubes and Pd/C. In addition, it is considered that the reverse-scan peaks are related to the tolerance of catalyst to the accumulation of intermediate carbonaceous species. Moreover, The PdCNs with more highly concave structure depression emerge enhanced catalytic activity (Figure S8), caused by abundant terraces and steps on surface. Furthermore, the accelerated CV measurements are performed to evaluate the catalytic stability. The peak current density of PdCNs still remain 66.62% after 1500 cycles as shown in Figure 4D, which is much higher than the Pd nanocubes and Pd/C comparably. Additionally, TEM characterization confirms that most of PdCNs maintain their concave structures after 1500 cycles measurement (Figure S9 A–D), evidencing their long-term durability.

In summary, we develop a one-pot strategy with large-scale yield to synthesize of PdCNs enclosed by high-index 24 {730} facets. The conditions of low temperature and high concentration of AA are both favored to induce to well-defined concave structure. The PdCNs have plenty steps, corners and edge-sites triggering more active sites, which sustainably enhance higher catalytic performance and durability for methanol oxidation than Pd nanocubes and commercial Pd/C. More importantly, this facile approach provides a bright prospect for achieving large-scale preparation of noble metal nanostructures with their morphologies controlling simultaneously.

Elevating Reaction Temperature

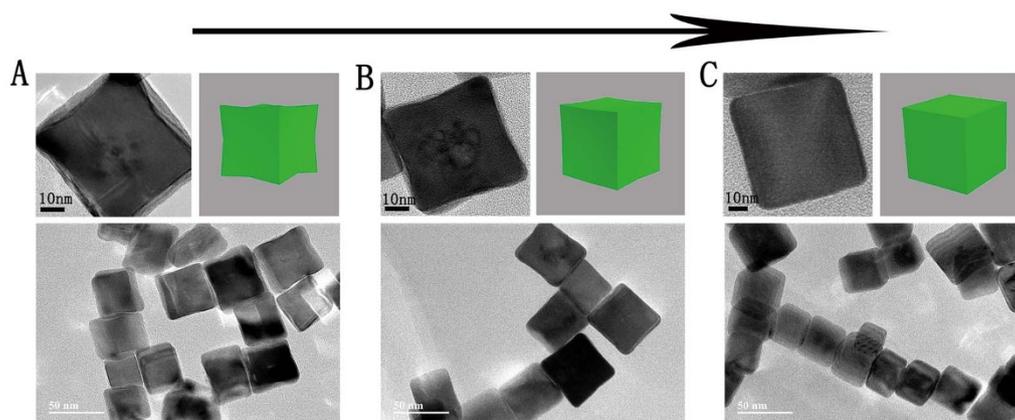


Figure 3 | Morphology evolution of Pd nanostructures by elevating temperature, the temperature is controlled as follow: (A) 35 ~ 40 °C; (B) 55 ~ 60 °C; (C) 75 ~ 80 °C.

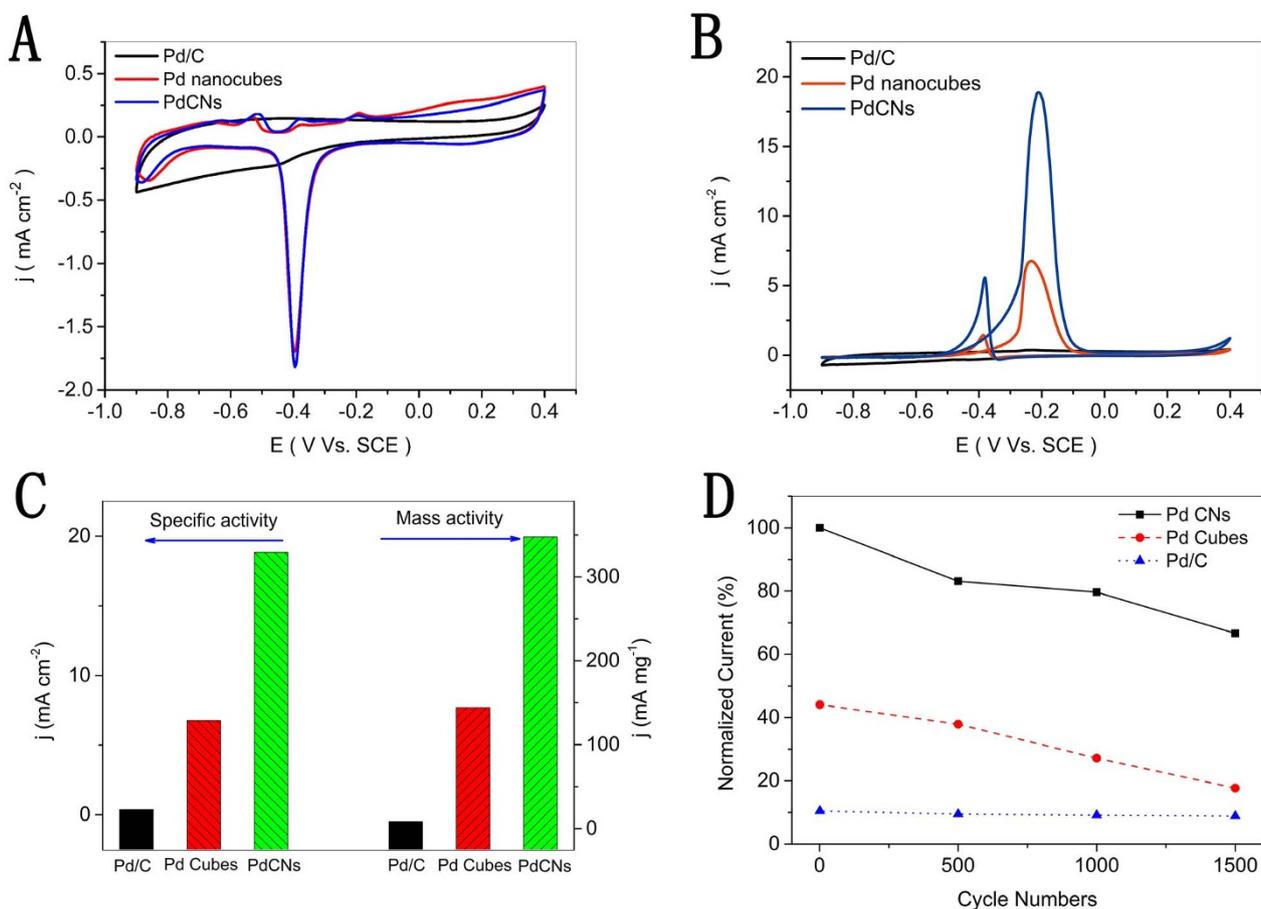


Figure 4 | Cyclic Voltammograms of the PdCNs, Pd nanocubes and commercial Pd/C, which are recorded at room temperature with the scan rate of 50 mV/s in (A) 1M KOH solution; (B) 1M KOH contained 1M CH₃OH; (C) The mass and specific activities (at -0.2 Vs. SCE); (D) Normalized current of 1500 cycles.

Methods

Preparation of Pd concave nanocubes. Typically, mixture of 0.1 mL of 0.1 M CTAB, 4.4 mL of deionized water and 0.5 mL of 10 mM K₂PdCl₄ in a 10 mL bottle, then added 0.15 mL of 0.1 M AA into above mixture with magnetic stirring. The bottle was shifted in 35–40°C water bath under magnetic stirring. The black product was collected by centrifugation at 12000 rpm for 10 min, washed by deionized water for several times to removal excess CTAB. (Details and conditions change show as Table S1 to Table S4)

Large-scale preparation of Pd concave nanocubes. The protocol was similar to the typical synthesis, except that expand the amount of all species to fifty times (Details show as Table S5.).

Electrochemical Measurement. The electrochemical activities of Pd nanocatalysts were performed at room temperature using a three-electrode system consisting a glassy carbon electrode (GCE, 5 mm diameter, geometric area of 0.196 cm²), a Pt plate (1 × 1 cm²) counter electrode, and a saturated calomel electrode (SCE) at an electrochemical station (CHI660E). Representatively, 0.6 mg of Pd nano-catalyst and 150 μL of Nafion solution (0.1 wt%) were dispersed in 300 μL of water-ethanol solution with volume ratio of 3 : 1 followed by ultra-sonication for 0.5 h to form a homogeneous ink. Then 15 μL of the dispersion (containing 20 μg of catalyst) was loaded onto the GCE (loading catalyst 0.102 mg cm⁻²). Prior to test, the solution of 1.0 M KOH and 1.0 M CH₃OH was purged with pure Ar gas for 1 h. Methanol oxidation measurements were conducted in a solution containing 1.0 M KOH and 1.0 M CH₃OH using GCE at a sweep rate of 50 mV/s. The stability test was performed at a sweep rate of 0.5 V/s in a 1.0 M KOH and 1.0 M CH₃OH solution for 1500 cycles.

Characterizations. Transmission electron microscopy (TEM), high resolution bright-field TEM, and selected area electron diffraction (SAED) measurements were carried out with the field emission FEI-F20, operated at 200 kV.

1. Huang, X. *et al.* Palladium-based nanostructures with highly porous features and perpendicular pore channels as enhanced organic catalysts. *Angew. Chem. Int. Edit.* **52**, 2520–2524 (2013).

- Ji, X. *et al.* Nanocrystalline intermetallics on mesoporous carbon for direct formic acid fuel cell anodes. *Nat. Chem.* **2**, 286–293 (2010).
- Kesavan, L. *et al.* Solvent-free oxidation of primary carbon-hydrogen bonds in toluene using Au-Pd alloy nanoparticles. *Science* **331**, 195–199 (2011).
- Tedsree, K. *et al.* Hydrogen production from formic acid decomposition at room temperature using a Ag-Pd core-shell nanocatalyst. *Nat. Nanotechnol.* **6**, 302–307 (2011).
- Xu, C. W., Wang, H., Shen, P. K. & Jiang, S. P. Highly ordered Pd nanowire arrays as effective electrocatalysts for ethanol oxidation in direct alcohol fuel cells. *Adv. Mater.* **19**, 4256–4259 (2007).
- Antolini, E. Palladium in fuel cell catalysis. *Energy Environ. Sci.* **2**, 915 (2009).
- Zhou, W. P. *et al.* Size effects in electronic and catalytic properties of unsupported palladium nanoparticles. *J. Phys. Chem. B* **10**, 13393–13398 (2006).
- Zhou, Z. Y., Tian, N., Li, J. T., Broadwell, I. & Sun, S. G. Nanomaterials of high surface energy with exceptional properties in catalysis and energy storage. *Chem. Soc. Rev.* **40**, 4167–4185 (2011).
- Yang, C. W. *et al.* Fabrication of Au-Pd core-shell heterostructures with systematic shape evolution using octahedral nanocrystal cores and their catalytic activity. *J. Am. Chem. Soc.* **133**, 19993–20000 (2011).
- Zhang, H., Jin, M. & Xia, Y. Noble-metal nanocrystals with concave surfaces: synthesis and applications. *Angew. Chem. Int. Edit.* **51**, 7656–7673 (2012).
- Xiong, Y. & Xia, Y. Shape-controlled synthesis of metal nanostructures: the case of palladium. *Adv. Mater.* **19**, 3385–3391 (2007).
- Xia, Y., Xiong, Y., Lim, B. & Skrabalak, S. E. Shape-controlled synthesis of metal nanocrystals: simple chemistry meets complex physics? *Angew. Chem. Int. Edit.* **48**, 60–103 (2009).
- Chen, Y. H., Hung, H. H. & Huang, M. H. Seed-mediated synthesis of palladium nanorods and branched nanocrystals and their use as recyclable suzuki coupling reaction catalysts. *J. Am. Chem. Soc.* **131**, 9114–9121 (2009).
- Mazumder, V. & Sun, S. Oleyamine-mediated synthesis of Pd nanoparticles for catalytic formic acid oxidation. *J. Am. Chem. Soc.* **131**, 4588–4589 (2009).
- Xiong, Y. *et al.* Synthesis and mechanistic study of palladium nanobars and nanorods. *J. Am. Chem. Soc.* **129**, 3665–3675 (2007).
- Xia, X. *et al.* Facile synthesis of palladium right bipyramids and their use as seeds for overgrowth and as catalysts for formic acid oxidation. *J. Am. Chem. Soc.* **135**, 15706–15709 (2013).



17. Zhang, J. *et al.* Shape-controlled synthesis of palladium single-crystalline nanoparticles: the effect of HCl oxidative etching and facet-dependent catalytic properties. *Chem. Mater.* **26**, 1213–1218 (2014).
18. Feldheim, D. L. Chemistry, the new face of catalysis. *Science* **316**, 699–700 (2007).
19. Tian, N., Zhou, Z. Y., Yu, N. F., Wang, L. Y. & Sun, S. G. Direct electrodeposition of tetrahedral Pd nanocrystals with high-index facets and high catalytic activity for ethanol electrooxidation. *J. Am. Chem. Soc.* **132**, 7580–7581 (2010).
20. Xia, B. Y., Wu, H. B., Wang, X. & Lou, X. W. Highly concave platinum nanoframes with high-index facets and enhanced electrocatalytic properties. *Angew. Chem. Int. Edit.* **52**, 12337–12340 (2013).
21. Zhang, L., Niu, W. & Xu, G. Synthesis and applications of noble metal nanocrystals with high-energy facets. *Nano Today* **7**, 586–605 (2012).
22. Jin, M., Zhang, H., Xie, Z. & Xia, Y. Palladium concave nanocubes with high-index facets and their enhanced catalytic properties. *Angew. Chem. Int. Edit.* **50**, 7850–7854 (2011).
23. Zhang, J. *et al.* Synthesis of concave palladium nanocubes with high-index surfaces and high electrocatalytic activities. *Chem. Eur. J.* **17**, 9915–9919 (2011).
24. Niu, W., Zhang, W., Firdoz, S. & Lu, X. Controlled synthesis of palladium concave nanocubes with sub-10-nanometer edges and corners for tunable plasmonic property. *Chem. Mater.* **26**, 2180–2186 (2014).
25. Zhang, H., Jin, M., Xiong, Y., Lim, B. & Xia, Y. Shape-controlled synthesis of Pd nanocrystals and their catalytic applications. *Acc. Chem. Res.* **46**, 1783–1794 (2013).
26. Tian, N., Zhou, Z. Y., Sun, S. G., Ding, Y. & Wang, Z. L. Synthesis of tetrahedral platinum nanocrystals with high-index facets and high electro-oxidation activity. *Science* **316**, 732–735 (2007).
27. Tian, N., Zhou, Z. Y. & Sun, S. G. Platinum metal catalysts of high-index surfaces from single-crystal planes to electrochemically shape-controlled nanoparticles. *J. Phys. Chem. C* **112**, 19801–19817 (2008).
28. Lim, B. *et al.* Shape-controlled synthesis of Pd nanocrystals in aqueous solutions. *Adv. Funct. Mater.* **19**, 189–200 (2009).
29. Tao, A. R., Habas, S. & Yang, P. Shape control of colloidal metal nanocrystals. *Small* **4**, 310–325 (2008).
30. Liu, M., Zheng, Y., Zhang, L., Guo, L. & Xia, Y. Transformation of Pd nanocubes into octahedra with controlled sizes by maneuvering the rates of etching and regrowth. *J. Am. Chem. Soc.* **135**, 11752–11755 (2013).
31. Peng, H. C., Xie, S., Park, J., Xia, X. & Xia, Y. Quantitative analysis of the coverage density of Br⁻ ions on Pd{100} facets and its role in controlling the shape of Pd nanocrystals. *J. Am. Chem. Soc.* **135**, 3780–3783 (2013).
32. Xiong, Y. *et al.* Kinetically controlled synthesis of triangular and hexagonal nanoplates of palladium and their SPRSERS properties. *J. Am. Chem. Soc.* **127**, 17118–17127 (2005).

Acknowledgments

The presented research was financially supported by the National Basic Research Program of China (973 Program No. 2011CB933600), the Natural Science Foundation of China (21401211), the Science and Technology Innovation Fund of Shenzhen (JCYJ20130401170306832, JC201104220242A, ZYC201105170279A), SIAT Innovation Program for Excellent Young Researchers (201309), and Guangdong Innovation Research Team of Low-cost Healthcare.

Author contributions

X.X., G.G. and L.C. conceived and designed the study, prepared all figures, and they all wrote the manuscript. X.X. performed the experiments mainly, and Z.P., T.W. and X.M. helped to do the measurements. L.C. is the corresponding author. All authors reviewed the manuscript.

Additional information

Supplementary information accompanies this paper at <http://www.nature.com/scientificreports>

Competing financial interests: The authors declare no competing financial interests.

How to cite this article: Xie, X. *et al.* Large-Scale Synthesis of Palladium Concave Nanocubes with High-Index Facets for Sustainable Enhanced Catalytic Performance. *Sci. Rep.* **5**, 8515; DOI:10.1038/srep08515 (2015).



This work is licensed under a Creative Commons Attribution 4.0 International License. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in the credit line; if the material is not included under the Creative Commons license, users will need to obtain permission from the license holder in order to reproduce the material. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>