

# SCIENTIFIC REPORTS



OPEN

## Enhanced photoelectric conversion efficiency of dye-sensitized solar cells by the incorporation of flower-like $\text{Bi}_2\text{S}_3:\text{Eu}^{3+}$ sub-microspheres

Bingyu Xu, Guofeng Wang &amp; Honggang Fu

Received: 07 January 2016


Accepted: 01 March 2016

Published: 21 March 2016


In this paper,  $\text{TiO}_2\text{-Bi}_2\text{S}_3$  and  $\text{TiO}_2\text{-Bi}_2\text{S}_3:\text{Eu}^{3+}$  composite photoanodes were successfully designed, which can not only fully absorb visible light but also transfer the electron from  $\text{Bi}_2\text{S}_3$  to  $\text{TiO}_2$  conduction band due to the narrow band gap and high conduction band of  $\text{Bi}_2\text{S}_3$ . Compared to pure  $\text{TiO}_2$  cell, the photoelectric conversion efficiencies of  $\text{TiO}_2\text{-Bi}_2\text{S}_3$  and  $\text{TiO}_2\text{-Bi}_2\text{S}_3:\text{Eu}^{3+}$  composite cells were increased significantly. In addition, the efficiency of  $\text{TiO}_2\text{-Bi}_2\text{S}_3:\text{Eu}^{3+}$  composite cells were higher than that of  $\text{TiO}_2\text{-Bi}_2\text{S}_3$  cell which could be attributed to the larger BET surface area of  $\text{Bi}_2\text{S}_3:\text{Eu}^{3+}$ . The electron transport and interfacial recombination kinetics were investigated by the electrochemical impedance spectroscopy and intensity-modulated photocurrent/photovoltage spectroscopy. The results indicated that the interfacial resistance of the  $\text{TiO}_2\text{-dye}|\text{I}_3^-/\text{I}^-$  electrolyte interface of  $\text{TiO}_2\text{-Bi}_2\text{S}_3:\text{Eu}^{3+}$  composite cell was much bigger than that of pure  $\text{TiO}_2$  cell. In addition, the  $\text{TiO}_2\text{-Bi}_2\text{S}_3:\text{Eu}^{3+}$  cell has longer electron recombination time and longer electron transport time than pure  $\text{TiO}_2$  cell. The charge collection efficiency of  $\text{TiO}_2\text{-Bi}_2\text{S}_3:\text{Eu}^{3+}$  composite cell was higher than that of pure  $\text{TiO}_2$  cell.

In the past decade, dye-sensitized solar cells (DSSCs) have attracted extensive attention due to their easy fabrication, lowcost and relatively high conversion efficiency<sup>1,2</sup>. A typical DSSC consists of a dye-sensitized semiconductor photoanode, an electrolyte with the dissolved iodide/triiodide ( $\text{I}_3^-/\text{I}^-$ ) redox couple between the electrodes and a catalytic counter electrode<sup>3–6</sup>. Especially, an advanced photoelectrode is one of the most important prerequisites for highly efficient DSSCs. A variety of materials have been used as photoelectrodes and show good electrocatalytic activity. In general,  $\text{TiO}_2$  has been widely used as for DSSCs owing to their large surface area for loading more dye molecules, the sensitizer of the DSSC is mainly N719 dye, and the DSSC consists of  $\text{TiO}_2$  film sensitized by a dye for absorbing incident light. Recently, extensive studies on the individual components of DSSCs have been performed to further reduce production costs and to achieve better cell performance<sup>7–9</sup>. Many attempts have been made to enhance the performances of DSSCs by controlling the size, shape and morphologies of the semiconductors, utilizing low band gap organic materials, introducing buffer layers, and so on. Among them, one facile and efficient approach is to introduce foreign ions into organic semiconductors<sup>10,11</sup>. Some metal oxides<sup>12,13</sup>, nitrides<sup>14</sup>, carbides<sup>15</sup> and sulfides<sup>16–19</sup> have also been investigated as CEs due to their preferentially electrocatalytic activity. However, the application of sulfides as photoanode has been seldom reported. Metal sulfides gained more attention due to their facile preparation conditions and relatively low toxicity. As a well-known semiconductor, bismuth sulfide ( $\text{Bi}_2\text{S}_3$ ) has the potential to improve the photocatalytic activity due to its narrow bandgap ( $\sim 1.4\text{ eV}$ )<sup>20,21</sup>. It could has been used as a photoanode materials in DSSC due to its ability to absorb a large part of visible light up to 800 nm and transfer the electron from  $\text{Bi}_2\text{S}_3$  to  $\text{TiO}_2$  conduction band. So far, there are many classic preparation methods for  $\text{Bi}_2\text{S}_3$ , such as hydrothermal method, solvothermal method, electrochemical deposition, microwave refluxing, organometallic complex decomposition and chemical vapor deposition<sup>22–28</sup>.

Key Laboratory of Functional Inorganic Material Chemistry, Ministry of Education, School of Chemistry and Materials Science, Heilongjiang University, Harbin, 150080, China. Correspondence and requests for materials should be addressed to G.W. (email: wanggf\_w@163.com) or H.F. (email: fuhg@vip.sina.com)

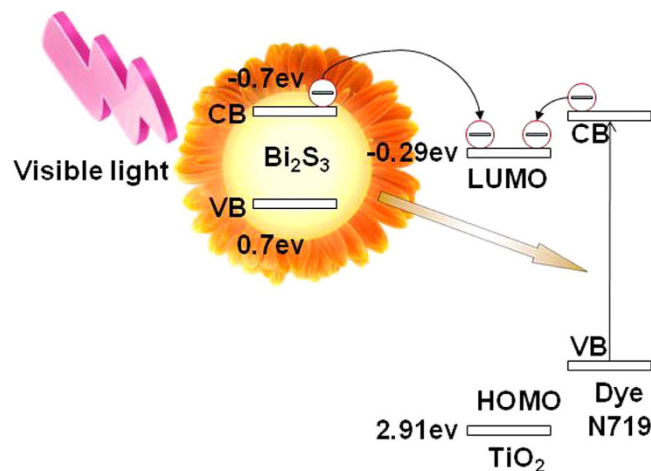

**Figure 1.** Mechanism of visible light harvesting in  $\text{TiO}_2\text{-Bi}_2\text{S}_3\text{:Eu}^{3+}$  cells.

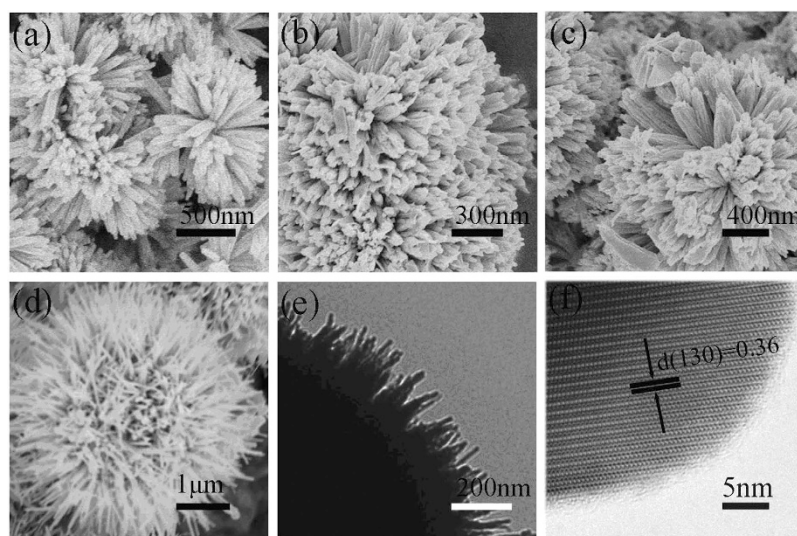


**Figure 2.** SEM (a–d), TEM and HRTEM (e,f) images of  $\text{Bi}_2\text{S}_3\text{:Eu}^{3+}$  nanocrystals prepared at  $180^\circ\text{C}$  for 12h after annealing at  $400^\circ\text{C}$  with different  $\text{Eu}^{3+}$  concentrations: (a) 5%, (b) 10%, (c) 15%, and (d–f) 20%.

As a result, if one can design down-conversion luminescent  $\text{TiO}_2\text{-Bi}_2\text{S}_3\text{:Eu}^{3+}$  composite photoanodes, not only the utilization of visible light can be improved but also the electron can transfer from  $\text{Bi}_2\text{S}_3$  to  $\text{TiO}_2$  conduction band (see Fig. 1). And thus, the efficiency of the solar cells can be enhanced. In addition, metal ions doping semiconductor is also an effective strategy to improve the photocatalytic performance. Based on the consideration above, we report the synthesis of flower-like  $\text{Bi}_2\text{S}_3\text{:Eu}^{3+}$  through a hydrothermal route, and introduce  $\text{Bi}_2\text{S}_3\text{:Eu}^{3+}$  to the dye-sensitized solar photoanodes. The BET surface areas increased with increasing  $\text{Eu}^{3+}$  concentration. The photoelectric conversion efficiencies of  $\text{TiO}_2\text{-Bi}_2\text{S}_3$  and  $\text{TiO}_2\text{-Bi}_2\text{S}_3\text{:Eu}^{3+}$  composite cells were significantly increased compared to pure  $\text{TiO}_2$  cell. The electron transport and interfacial recombination kinetics of cells were investigated in detail.


## Discussion

Figure 2(a–d) represent the typical SEM images of the  $\text{Bi}_2\text{S}_3$  products with different  $\text{Eu}^{3+}$  concentrations, which show that the products are composed of flower-like nanostructures. The average diameter of these superstructures is about 500 nm. The TEM and HRTEM images are presented in Fig. 2(e,f). The HRTEM image reveals that the interplanar spacing of 0.36 nm corresponds to the (130) plane of  $\text{Bi}_2\text{S}_3$ .


Figure 3 shows the XRD patterns of  $\text{Bi}_2\text{S}_3$  nanocrystals (without annealing) with different reaction time, which are in good agreement with the standard data of orthorhombic phase  $\text{Bi}_2\text{S}_3$  (JCPDS 17-0320). No other impurity peaks were detected. Figure 4 shows the XRD patterns of  $\text{Bi}_2\text{S}_3$  nanocrystals after annealing at different temperatures. It can be seen crystalline size increases with increasing the annealing temperature. The peaks in Fig. 4 marked by asterisk (\*) arise from cubic phase Bi particles (JCPDS 44-1256). The other diffraction peaks can be indexed to the orthorhombic phase  $\text{Bi}_2\text{S}_3$ . Figure 5 shows the XRD pattern of  $\text{Bi}_2\text{S}_3\text{:Eu}^{3+}$  nanocrystals (without

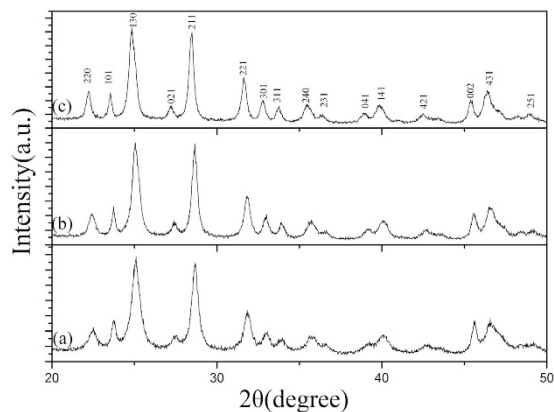

**Figure 3.** XRD patterns of  $\text{Bi}_2\text{S}_3:\text{Eu}^{3+}$  nanocrystals prepared at  $180^\circ\text{C}$  for different reaction time: (a) 6 h, (b) 9 h, and (c) 12 h.

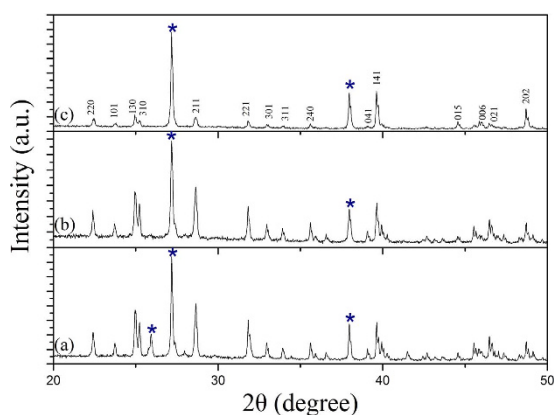


**Figure 4.** XRD patterns of  $\text{Bi}_2\text{S}_3:\text{Eu}^{3+}$  nanocrystals prepared at  $180^\circ\text{C}$  for 12h with annealing at different temperatures for 2h: (a)  $400^\circ\text{C}$ , (b)  $600^\circ\text{C}$ , and (c)  $800^\circ\text{C}$ .

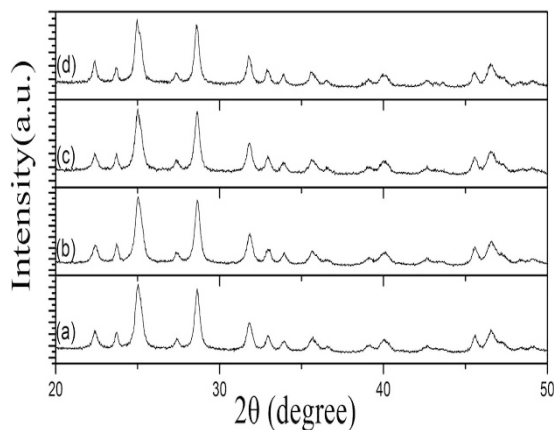


**Figure 5.** XRD patterns of  $\text{Bi}_2\text{S}_3:\text{Eu}^{3+}$  nanocrystals prepared at  $180^\circ\text{C}$  for 12h with different  $\text{Eu}^{3+}$  concentrations: (a) 5%, (b) 10%, (c) 15%, and (d) 20%.

annealing) with different  $\text{Eu}^{3+}$  concentrations. Obviously, no other impurity peaks were detected with increasing  $\text{Eu}^{3+}$  concentration.

Figure 6 shows the Raman spectra of  $\text{Bi}_2\text{S}_3:\text{Eu}^{3+}$  with different  $\text{Eu}^{3+}$  concentrations. The typical features in Raman spectra were located at  $129\text{ cm}^{-1}$ ,  $610\text{ cm}^{-1}$  and  $965\text{ cm}^{-1}$ . The 610 and  $965\text{ cm}^{-1}$  bands are assigned to the Bi-S stretching vibrations. The  $129\text{ cm}^{-1}$  is attributed to the surface of the optical phonon modes<sup>29</sup>.

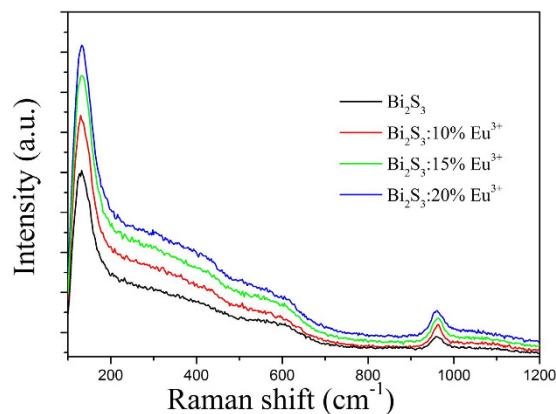


**Figure 6.** Raman spectra of  $\text{Bi}_2\text{S}_3:\text{Eu}^{3+}$  nanocrystals prepared at  $180^\circ\text{C}$  for 12h with different  $\text{Eu}^{3+}$  concentrations.

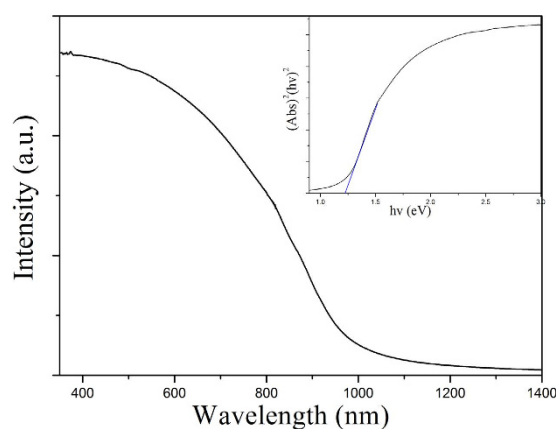

**Figure 7.** UV-Vis diffuse reflectance spectrum of  $\text{Bi}_2\text{S}_3$  nanocrystals prepared at  $180^\circ\text{C}$  for 12h.

Figure 7 shows the UV-vis diffuse reflectance spectrum of  $\text{Bi}_2\text{S}_3$  nanocrystals. The inset displays the plot of the transformed Kubelka-Munk function versus energy of light. The Kubelka-Munk function,  $F(R)$ , allows the optical absorbance of a sample to be approximated from its reflectance:  $F(R) = (1 - R)^2/2R$ . For a semiconductor sample this allows the construction of a Tauc Plot- $(F(R) \cdot h\nu)^n$  vs  $h\nu$ . For a direct band gap semiconductor the plot  $n = 1/2$  will show a linear Tauc Region just above the optical absorption edge. Extrapolation of this line to the photon energy axis yields the semiconductor band gap. The calculated value of the band gap is about 1.22 eV for  $\text{Bi}_2\text{S}_3$  nanocrystals.


In order to investigate the effects of  $\text{TiO}_2\text{-Bi}_2\text{S}_3:\text{Eu}^{3+}$  on the photoelectric properties of DSSCs, the DSSC prototype devices were fabricated by using N719-sensitised  $\text{TiO}_2\text{-Bi}_2\text{S}_3:\text{Eu}^{3+}$  composite electrodes. Figure 8(a) shows the photocurrent-voltage ( $I$ - $V$ ) curves of pure  $\text{TiO}_2$  cell,  $\text{TiO}_2\text{-Bi}_2\text{S}_3$  composite cell, and  $\text{TiO}_2\text{-Bi}_2\text{S}_3:\text{Eu}^{3+}$  cells. The mass concentrations of  $\text{Bi}_2\text{S}_3:\text{Eu}^{3+}$  in the  $\text{TiO}_2\text{-Bi}_2\text{S}_3:\text{Eu}^{3+}$  cells are 1%, 3%, and 5%, respectively. The corresponding values of the open-circuit voltage ( $V_{oc}$ ), short-circuit current ( $J_{sc}$ ), fillfactor (FF), and overall conversion efficiency ( $\eta$ ), obtained from the curves of solar cells, are shown in Table 1. The result indicated that the photoelectric conversion efficiencies of the  $\text{TiO}_2\text{-Bi}_2\text{S}_3$  and  $\text{TiO}_2\text{-Bi}_2\text{S}_3:\text{Eu}^{3+}$  composite cells were higher than that of pure  $\text{TiO}_2$  cell. The best photoelectric conversion performance was observed when the mass concentration of  $\text{Bi}_2\text{S}_3:\text{Eu}^{3+}$  was 3%. The high  $V_{oc}$  of the  $\text{TiO}_2\text{-Bi}_2\text{S}_3$  could be attributed to heavy doping effects. Heavy impurity doping makes the conduction and valence bands shift, and brings about the so-called Band Gap Narrowing that resulting in the decrease of open circuit voltage. Figure 8(b) shows the incident photon to current (IPCE) spectra of pure  $\text{TiO}_2$ ,  $\text{TiO}_2\text{-Bi}_2\text{S}_3$ , and  $\text{TiO}_2\text{-Bi}_2\text{S}_3:\text{Eu}^{3+}$  composite cells. The results indicated that the photon-to-current conversion efficiency obviously increases by the incorporation of  $\text{Bi}_2\text{S}_3:\text{Eu}^{3+}$ . With the increase of the proportion of  $\text{Bi}_2\text{S}_3:\text{Eu}^{3+}$  in  $\text{TiO}_2\text{-Bi}_2\text{S}_3:\text{Eu}^{3+}$  cell, the efficiency increases first, and then decreases. At low concentrations of  $\text{Bi}_2\text{S}_3:\text{Eu}^{3+}$ , the increase of the efficiency with the proportion of  $\text{Bi}_2\text{S}_3:\text{Eu}^{3+}$  could be attributed to the narrow band-gap and higher conduction band of  $\text{Bi}_2\text{S}_3$ , which not only improve the utilization of visible light but also transfer the electron from  $\text{Bi}_2\text{S}_3$  to the conduction band of  $\text{TiO}_2$ . However, the incorporation of  $\text{Bi}_2\text{S}_3:\text{Eu}^{3+}$  can influence the electrical conductivity of  $\text{TiO}_2$  and lead to a decrease in photocurrent. In addition, the effects of pure  $\text{Bi}_2\text{S}_3$  on the photoelectric properties of DSSC were also studied. The results indicated that the photoelectric conversion efficiency of  $\text{TiO}_2\text{-Bi}_2\text{S}_3$  cell was lower than that of  $\text{TiO}_2\text{-Bi}_2\text{S}_3:\text{Eu}^{3+}$  cell.

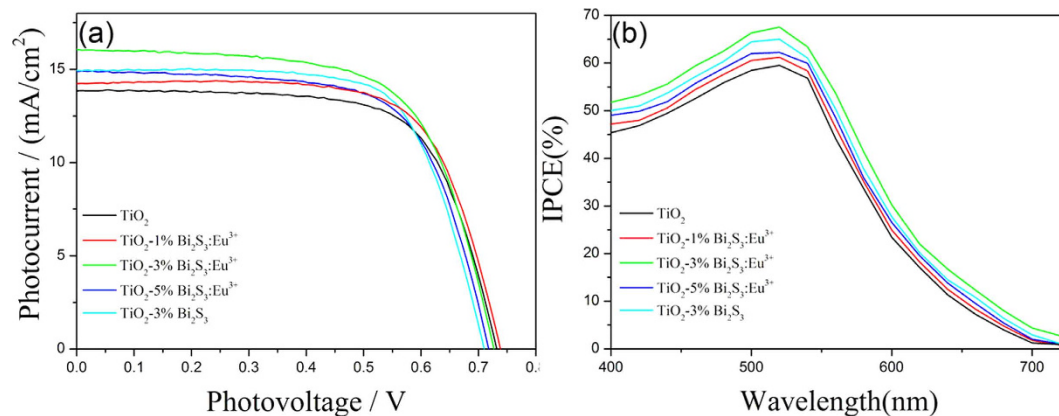

**Figure 8.** Photocurrent-voltage (I–V) curves (a) and IPCE (b) of TiO<sub>2</sub>, TiO<sub>2</sub>-Bi<sub>2</sub>S<sub>3</sub>, and TiO<sub>2</sub>-Bi<sub>2</sub>S<sub>3</sub>:Eu<sup>3+</sup> cells with different concentration of Bi<sub>2</sub>S<sub>3</sub>:Eu<sup>3+</sup>.

Samples	I <sub>sc</sub> (mA cm <sup>-2</sup> )	V <sub>oc</sub> (V)	FF	η (%)
Pure TiO <sub>2</sub>	13.0056	0.743	0.68	6.95
TiO <sub>2</sub> -1%Bi <sub>2</sub> S <sub>3</sub> :Eu <sup>3+</sup>	14.2333	0.739	0.69	7.29
TiO <sub>2</sub> -3%Bi <sub>2</sub> S <sub>3</sub> :Eu <sup>3+</sup>	16.0667	0.727	0.65	7.47
TiO <sub>2</sub> -5%Bi <sub>2</sub> S <sub>3</sub> :Eu <sup>3+</sup>	14.8667	0.718	0.67	7.10
TiO <sub>2</sub> -3%Bi <sub>2</sub> S <sub>3</sub>	14.9333	0.711	0.69	7.33

**Table 1.** Solar cell parameters of TiO<sub>2</sub>, TiO<sub>2</sub>-Bi<sub>2</sub>S<sub>3</sub>, and TiO<sub>2</sub>-Bi<sub>2</sub>S<sub>3</sub>:Eu<sup>3+</sup> cells with different contents of Bi<sub>2</sub>S<sub>3</sub>:Eu<sup>3+</sup>.

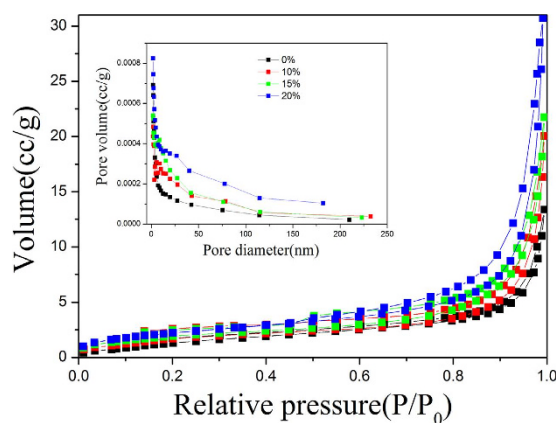


**Figure 9.** N<sub>2</sub> adsorption-desorption isotherm curves and pore size distribution (inset) of Bi<sub>2</sub>S<sub>3</sub>:Eu<sup>3+</sup> nanocrystals prepared at 180 °C for 12 h with different Eu<sup>3+</sup> concentrations.

It is well known that the photoelectric performance was closely related to the ratios of the surface areas of samples. N<sub>2</sub> adsorption-desorption isotherms and the corresponding BJH pore size distribution plots of the as-obtained Bi<sub>2</sub>S<sub>3</sub>:Eu<sup>3+</sup> with different Eu<sup>3+</sup> concentrations were performed to determine the surface area of the samples, as shown in Fig. 9. The BET surface areas are 4.8435, 5.4181, 6.6296, and 7.1739 m<sup>2</sup>/g for 0%, 10%, 15%, and 20% Eu<sup>3+</sup>, respectively.

EIS is a powerful method to investigate internal resistances for the charge-transfer process of DSSCs. The wide frequency range of EIS means that it can measure wide-scale internal resistances of each electrochemical step at the same time<sup>30,31</sup>. DSSCs are complex systems which are composed of several interfaces. A high level of electron accumulation must occur because photogenerated electrons are not extracted immediately at the electrode contact under illumination. Generally, the impedance at low frequency (0.05–1 Hz) refers to the Nernst diffusion of I<sub>3</sub><sup>-</sup>/I<sup>-</sup> within the electrolyte. The impedance at high frequency (1–100 kHz) corresponds to the capacitance and charge-transfer resistance at the Pt/I<sub>3</sub><sup>-</sup>/I<sup>-</sup> electrolyte interface. The medium-frequency response at 1 Hz–100 Hz is related to the photoelectrode–dye/I<sub>3</sub><sup>-</sup>/I<sup>-</sup> electrolyte interface, where the accumulation of photoelectrons and redox shuttles is expected<sup>32,33</sup>. Figure 10 shows the EIS of pure TiO<sub>2</sub> cell and TiO<sub>2</sub>-Bi<sub>2</sub>S<sub>3</sub>:Eu<sup>3+</sup> cell. It can be seen



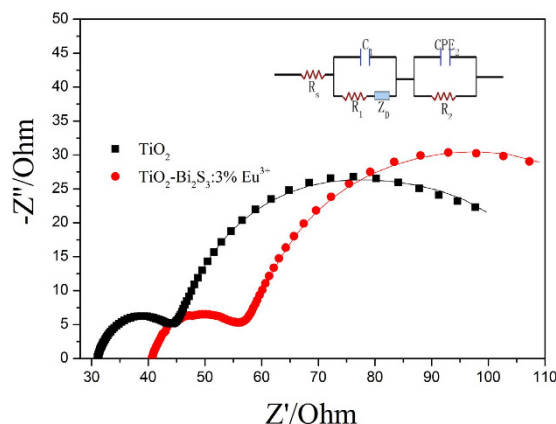

**Figure 10.** Nyquist plots of DSSCs comprised of pure  $\text{TiO}_2$  cell and  $\text{TiO}_2\text{-3\%Bi}_2\text{S}_3\text{:Eu}^{3+}$  cell. Inset is the equivalent circuit used to represent interfaces in composite solar cells composed of  $\text{FTO}|\text{TiO}_2\text{-dye}|I_3^-/I_3^-||\text{Pt}|\text{FTO}$ .

DSSCs	$R_s/\Omega$	$C_1/\text{F}$	$R_1/\Omega$	$Y_{oi}/\text{S}$	$B/s^{1/2}$	$R_2/\Omega$	CPE
Pure $\text{TiO}_2$	31.53	$9.378 \times 10^{-6}$	12.00	0.01077	0.387	30.31	0.0005914
$\text{TiO}_2\text{-Bi}_2\text{S}_3\text{:3\%Eu}^{3+}$	41.26	$7.789 \times 10^{-6}$	12.30	0.00641	0.252	41.30	0.00217

**Table 2.** Parameters obtained by fitting the impedance spectra of composite solar cells using the equivalent circuit in the inset of Fig. 9.

that the interfacial resistance of the  $\text{TiO}_2\text{-dye}|I_3^-/I_3^-$  electrolyte interface of  $\text{TiO}_2\text{-Bi}_2\text{S}_3\text{:Eu}^{3+}$  cell is much bigger than that of pure  $\text{TiO}_2$  cell.


The inset in Fig. 10 shows the equivalent circuit fitting of the impedance spectra,  $R_s[C_1(R_1O_1)](R_2\text{CPE})$ , which was used for all the DSSCs.  $R_s$  is the series resistance, corresponding to the sheet resistance of the FTO glass, the contact resistance and the wire resistance.  $R_2$  represents the charge transfer resistance between the photoelectrode-dye $|I_3^-/I_3^-$  electrolyte interface.  $Z_{\text{Dif}}$  represents the finite-length Warburg impedance. The impedance of the finite-length Warburg diffusion is expressed as  $Z_{\text{Dif}} = R_{\text{Dif}} \frac{\tanh(j\omega\tau)^{1/2}}{(j\omega\tau)^{1/2}}$  where  $R_{\text{Dif}} = B/Y_0$ , and  $\tau = B^2$ .  $B$  is a constant phase element.

According to the equivalent circuit, the EIS data obtained by fitting the impedance spectra of composite DSSCs are listed in Table 2. It can be seen that  $R_2$ , representing the interfacial resistance of the  $\text{TiO}_2\text{-dye}|I_3^-/I_3^-$  electrolyte interface, is 30.31  $\Omega$  for pure  $\text{TiO}_2$  cell and 41.30  $\Omega$  for  $\text{TiO}_2\text{-Bi}_2\text{S}_3\text{:Eu}^{3+}$  composite cell. It is noted that the lower interfacial resistance can result in higher interfacial electron transfer, which is a beneficial factor for enhanced photoelectric conversion efficiency. In addition, the series resistance ( $R_s$ ) for pure  $\text{TiO}_2$  cell and  $\text{TiO}_2\text{-Bi}_2\text{S}_3\text{:Eu}^{3+}$  cell are separately 31.53  $\Omega$  and 41.26  $\Omega$ , indicating that the incorporation of  $\text{Bi}_2\text{S}_3\text{:Eu}^{3+}$  is not beneficial for the interfacial electron transfer of  $\text{FTO}|\text{TiO}_2$ .


In DSSCs, the electron recombination time ( $\tau_n$ ), the electron transport time ( $\tau_d$ ), and the charge collection efficiency ( $\eta_{\text{cc}}$ ) are important factors for the performance of DSSCs. Time-resolved photoluminescence spectrum can be used as an effective method to characterize the interface electron transport and electron recombination of the solar cell<sup>34,35</sup>. But restricted by the conditions, we can not test Time-resolved photoluminescence spectrum. However, the IMVS and IMPS are also a kind of effective characterization methods, which can be used to characterize the transmission life, charge separation and recombination of interface electrons. The IMPS response plots and IMVS response plots of pure  $\text{TiO}_2$  cell and  $\text{TiO}_2\text{-Bi}_2\text{S}_3\text{:Eu}^{3+}$  composite cell are shown in Fig. 11. Compared with pure  $\text{TiO}_2$  cell, the  $\text{TiO}_2\text{-Bi}_2\text{S}_3\text{:Eu}^{3+}$  composite cell has longer electron recombination time and longer electron transport time. It noted that longer transport time can result in poorer photoelectric properties, while longer recombination time is beneficial for enhancing photoelectric properties.

The charge collection efficiencies ( $\eta_{\text{cc}}$ ) of DSSCs are determined by the relation:  $\eta_{\text{cc}} = 1 - \tau_d/\tau_n$ . Where,  $\tau_d$  is a charge transport time and  $\tau_n$  is a charge recombination lifetime. Figure 12 shows the charge collection efficiencies of pure  $\text{TiO}_2$  cell and  $\text{TiO}_2\text{-Bi}_2\text{S}_3\text{:Eu}^{3+}$  cell.  $\text{TiO}_2\text{-Bi}_2\text{S}_3\text{:Eu}^{3+}$  composite cell has a higher charge collection efficiency than pure  $\text{TiO}_2$  cell. All these results indicated that the performance of the solar cells can be improved by adding  $\text{Bi}_2\text{S}_3\text{:Eu}^{3+}$ .

In summary, flower-like  $\text{Bi}_2\text{S}_3\text{:Eu}^{3+}$  was successfully prepared by a facial solvothermal method. The obtained  $\text{Bi}_2\text{S}_3\text{:Eu}^{3+}$  was chosen to design  $\text{TiO}_2\text{-Bi}_2\text{S}_3\text{:Eu}^{3+}$  composite photoanodes. The result indicated that the photoelectric conversion efficiency were enhanced greatly by the incorporation of  $\text{Bi}_2\text{S}_3\text{:Eu}^{3+}$ . The best photoelectric conversion performance was observed when the mass concentration of  $\text{Bi}_2\text{S}_3\text{:Eu}^{3+}$  was 3 wt%. The result of EIS analysis revealed that the interfacial resistance of the  $\text{TiO}_2\text{-dye}|I_3^-/I_3^-$  electrolyte interface of  $\text{TiO}_2\text{-Bi}_2\text{S}_3\text{:Eu}^{3+}$  composite cell was much bigger than that of pure  $\text{TiO}_2$  cell. In addition, the  $\text{TiO}_2\text{-Bi}_2\text{S}_3\text{:Eu}^{3+}$  composite cell exhibited longer electron recombination time, longer electron transport time, and higher charge collection efficiency than

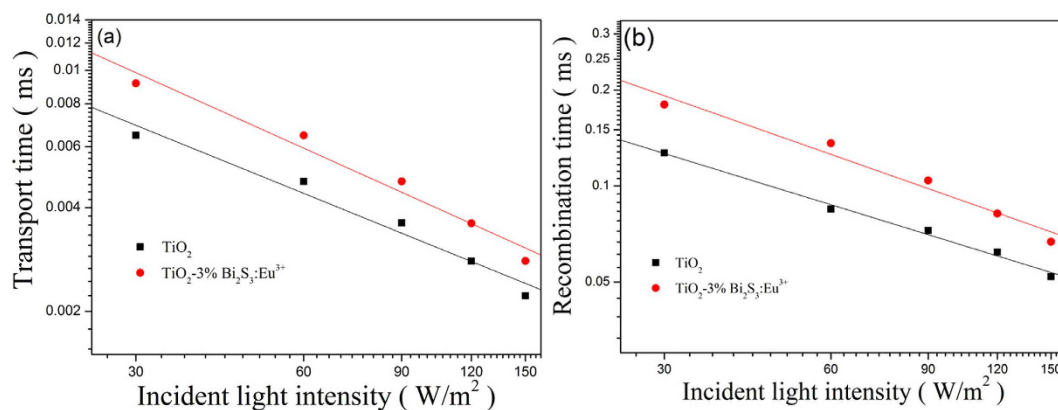

**Figure 11.** Comparison of (a) transport time constant and (b) recombination time constant for DSSCs comprised of pure TiO<sub>2</sub> cell and TiO<sub>2</sub>-3%Bi<sub>2</sub>S<sub>3</sub>:Eu<sup>3+</sup> cell.

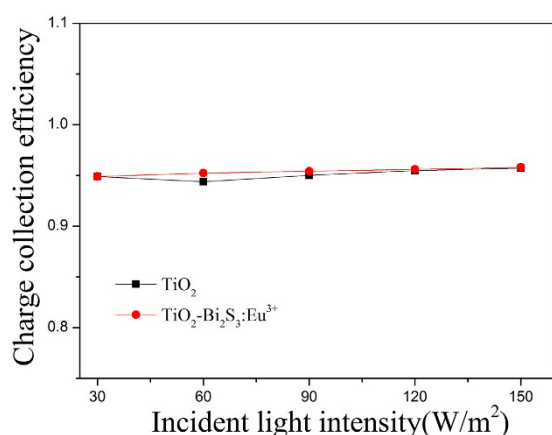

**Figure 12.** Comparison of charge collection efficiency for DSSCs comprised of pure TiO<sub>2</sub> cell and TiO<sub>2</sub>-Bi<sub>2</sub>S<sub>3</sub>:Eu<sup>3+</sup> cell.

those of pure TiO<sub>2</sub> cell. Of course, the enhancement of the efficiency of the TiO<sub>2</sub>-Bi<sub>2</sub>S<sub>3</sub>:Eu<sup>3+</sup> composite cells was also related to the larger BET surface areas of Bi<sub>2</sub>S<sub>3</sub>:Eu<sup>3+</sup>.

## Methods

**Synthesis of flower-like Bi<sub>2</sub>S<sub>3</sub> nanocrystals.** In a typical experiment, Bi(NO<sub>3</sub>)<sub>3</sub>, CH<sub>4</sub>N<sub>2</sub>S and Eu(NO<sub>3</sub>)<sub>3</sub> were separated add to ethylene glycol (10 ml), and the solution was thoroughly stirred. Subsequently, the solution was transferred to a 50 ml Teflon-lined autoclave for 12 h at 180 °C. After cooling to room temperature, the final products were collected by means of centrifugation, washed with ethanol, dried at 80 °C in air and then annealed at different temperature.

**Fabrication of photoelectrodes.** Fabrication of photoelectrode and the assembly of DSSCs: several pastes, from homogeneously mixing Bi<sub>2</sub>S<sub>3</sub>:Eu<sup>3+</sup> and TiO<sub>2</sub> (Degussa P25) into 3 mL of TiO<sub>2</sub> colloid, were prepared with different mass concentrations of Bi<sub>2</sub>S<sub>3</sub>:Eu<sup>3+</sup>. The TiO<sub>2</sub> colloid was prepared following the previously published synthesis procedure<sup>36</sup>. A screen-printed double layer of TiO<sub>2</sub>-Bi<sub>2</sub>S<sub>3</sub>:Eu<sup>3+</sup> was used as the photoanode. The first layer of TiO<sub>2</sub>-Bi<sub>2</sub>S<sub>3</sub>:Eu<sup>3+</sup> was prepared by a doctor-blade method on the FTO substrate and then sintered at 450 °C for 1 h. Subsequently, the second layer of TiO<sub>2</sub>-Bi<sub>2</sub>S<sub>3</sub>:Eu<sup>3+</sup> was covered on the first TiO<sub>2</sub>-Bi<sub>2</sub>S<sub>3</sub>:Eu<sup>3+</sup> film and then sintered at 450 °C for 30 min again. The sensitization of the photoelectrodes was achieved by immersing them into 0.5 mM ((C<sub>4</sub>H<sub>9</sub>)<sub>4</sub>N)<sub>2</sub>[Ru(4-carboxy-4'-carboxylate-2,2' bipyridine)2(NCS)<sub>2</sub>] dye (N719, Solaronix SA, Switzerland) in acetonitrile and tertbutanol (volume ratio, 1:1) for 48 h at room temperature. The Pt counter electrodes were prepared following the previous literature<sup>37</sup>. The dye-sensitized photoanode was assembled with a Pt counter electrode into a sandwich-type cell. The sandwich-type cell was further fixed together with epoxy resin. The space between the electrodes was filled with the electrolyte, which comprised 0.6 M 1-propyl-2,3-dimethyl-imidazolium iodide, 0.05 M I<sub>2</sub>, 0.1 M LiI, and 0.5 M tert-butylpyridine (TBP) in 3-methoxypropionitrile (3-MPN), by capillary action.

**Materials Characterizations.** The composition of the materials was determined by a Rigaku (Japan) D/MAX-rA X-ray diffraction meter (XRD) equipped with graphite monochromatized Cu K $\alpha$  radiation

( $\gamma = 1.541874 \text{ \AA}$ ), keeping the operating voltage and current at 40 kV and 40 mA. The size and morphology of the final products were investigated by scanning electron microscopy (SEM, Hitachi, S-4800) and transmission electron microscopy (TEM, JEOL, JEM-3010). UV-Vis absorption spectrum were determined by a UV-Vis spectrophotometer (Shimadzu UV-2550, Tokyo, Japan). The Raman spectra were measured by a HORIBA JOBIN YVON LabRam-HR 800 micro-Raman spectrometer.

**Photovoltaic properties study.** Photovoltaic measurements were carried out with a solar simulator (Oriel, USA) equipped with an AM 1.5G radiation (1 sun conditions,  $100 \text{ mW cm}^{-2}$ ) filter was used as the light source. Current-voltage (J–V) curves were measured with a BAS100B electrochemical analyzer (Zahner Elektrik, Germany). The area of DSSCs is  $1.5 \text{ cm}^2$  and the irradiation area is  $0.09 \text{ cm}^2$  with a light intensity meter. The photoanode of  $\text{Bi}_2\text{S}_3:\text{Eu}^{3+}$  films were fabricated in the same condition. To make the data strictly and scientifically, all the cells was test for at least 5 times then obtained an average value. The EIS were performed with a computer-controlled IM6e impedance measurement unit (Zahner Elektrik, Germany) and carried out by applying sinusoidal perturbations of 10 mV with a bias of  $-0.8 \text{ V}$  at a frequency ranges from 10 mHz to 1 MHz. The obtained spectra were fitted with ZsimpWin software in terms of appropriate equivalent circuits. The electron transport and recombination properties were measured by intensity-modulated photocurrent spectroscopy (IMPS) and intensity-modulated photovoltage spectroscopy (IMVS) (Zahner Elektrik, Germany). The DSSCs were probed through the photoanode side by a frequency response analyzer using a white lightemitting diode (wlr-01) as the light source. The frequency range was 0.1–1000 Hz. The irradiated intensity was varied from 30 to  $150 \text{ mW cm}^{-2}$ .

## References

- O'Regan, B. & Grätzel, M. A low-cost, high-efficiency solar cell based on dye-sensitized colloidal  $\text{TiO}_2$  films. *Nature* **353**, 737–740 (1991).
- Kung, C. W. *et al.* CoS acicular nanorod arrays for the counter electrode of an efficient dye-sensitized solar cell. *ACS Nano* **6**, 7016–7025 (2012).
- Miao, X. H. *et al.* Well-dispersed CoS nanoparticles on a functionalized graphene nanosheet surface: A counter electrode of dye-sensitized solar cells. *Chem. - Eur. J.* **20**, 474–482 (2014).
- Choi, H. *et al.* High molar extinction coefficient organic sensitizers for efficient dye-sensitized solar cells. *Chem.-Eur. J.* **16**, 1193–1201 (2010).
- Luo, Y., Li, D. & Meng, Q. Towards optimization of materials for dye-sensitized solar cells. *Adv. Mater.* **21**, 4647–4651 (2009).
- Song, J. G., Song, X., Ling, T., Du, X. W. & Qiao, S. Z. Enhancing the conversion efficiency of semiconductor sensitized solar cells via the co-sensitization of dual-sized quantum dots. *Ind. Eng. Chem. Res.* **51**, 10074–10078 (2012).
- Du, J., Qi, J., Wang, D. & Tang, Z. Y. Facile synthesis of  $\text{Au}@\text{TiO}_2$  core-shell hollow spheres for dye-sensitized solar cells with remarkably improved efficiency. *Energy Environ. Sci.* **5**, 6914–6918 (2012).
- Choi, H. *et al.* An efficient dye-sensitized solar cell with an organic sensitizer encapsulated in a cyclodextrin cavity. *Angew. Chem.-Int. Edit.* **48**, 5938–5941 (2009).
- Choi, H. *et al.* Highly efficient and thermally stable organic sensitizers for solvent-free dye-sensitized solar cells. *Angew. Chem.-Int. Edit.* **47**, 327–330 (2008).
- Li, Q. H. *et al.* Reducing the excess energy offset in organic/inorganic hybrid solar cells: Toward faster electron transfer. *Appl. Catal. B-Environ.* **162**, 524–531 (2015).
- Jin, X. *et al.* Exciton generation/dissociation/charge-transfer enhancement in inorganic/organic hybrid solar cells by robust single nanocrystalline  $\text{LnP}_x\text{O}_y$  ( $\text{Ln} = \text{Eu}, \text{Y}$ ) Doping. *ACS Appl. Mater. Inter.* **6**, 8771–8781 (2014).
- Chen, X. X. *et al.* Platinum-free binary Co-Ni alloy counter electrodes for efficient dye-sensitized solar cells. *Angew. Chem.-Int. Edit.* **53**, 10799–10803 (2014).
- Duan, Y. Y. *et al.* Transparent metal selenide alloy counter electrodes for high-efficiency bifacial dye-sensitized solar cells. *Angew. Chem.-Int. Edit.* **53**, 14569–14574 (2014).
- Wang, Z. B. *et al.* Recent advances in alloy counter electrodes for dye-sensitized solar cells. A critical review. *Electrochim. Acta* **178**, 886–899 (2015).
- Tang, Q. W. *et al.* Dissolution engineering of platinum alloy counter electrodes in dye-sensitized solar cells. *Angew. Chem.-Int. Edit.* **54**, 11448–11452 (2015).
- Liao, Y. P. *et al.* Facile synthesis of high-crystallinity graphitic carbon/ $\text{Fe}_3\text{C}$  nanocomposites as counter electrodes for high-efficiency dye-sensitized solar cells. *ACS Appl. Mater. Inter.* **5**, 3663–3670 (2013).
- Huang, X. Y., Han, S. Y., Huang, W. & Liu, X. G. Enhancing solar cell efficiency: the search for luminescent materials as spectral converters. *Chem. Soc. Rev.* **42**, 173–201 (2013).
- Wang, Q., Gao, R. & Li, J. H. Porous, self-supported  $\text{Ni}_3\text{S}_2/\text{Ni}$  nanoarchitected electrode operating through efficient lithium-driven conversion reactions. *Appl. Phys. Lett.* **90**, 143107 (2007).
- Hardin, B. E. *et al.* Increased light harvesting in dye-sensitized solar cells with energy relay dyes. *Nat. Photonics* **3**, 406–411 (2009).
- Brahimi, R., Bessekhoud, Y., Bouguelia, A. & Trari, M. Visible light induced hydrogen evolution over the heterosystem  $\text{Bi}_2\text{S}_3/\text{TiO}_2$ . *Catal. Today* **122**, 62–65 (2007).
- Liao, H. C. *et al.* Synthesis, optical and photovoltaic properties of bismuth sulfide nanorods. *CrystEngComm* **14**, 3645–3652 (2012).
- Grigas, J., Talik, E. & Lazauskas, V. X-ray photoelectron spectra and electron structure of  $\text{Bi}_2\text{S}_3$  crystals. *Phys. Status Solidi.* **232**, 220–230 (2002).
- Phuruangrat, A., Thongtem, S. & Thongtem, T. Controlling morphologies of  $\text{Bi}_2\text{S}_3$  nanostructures synthesized by glycothermal method. *Mater. Lett.* **72**, 104–106 (2012).
- Dong, Z. *et al.* Accurate control of multishelled ZnO hollow microspheres for dye-sensitized solar cells with high efficiency. *Adv. Mater.* **24**, 1046–1049 (2012).
- Gao, C., Shen, H. L., Sun, L. & Shen, Z. Chemical bath deposition of  $\text{Bi}_2\text{S}_3$  films by a novel deposition system. *Appl. Sur. Sci.* **257**, 7529–7533 (2011).
- Wang, S. Y. & Du, Y. W. Preparation of nanocrystalline bismuth sulfide thin films by asynchronous-pulse ultrasonic spray pyrolysis technique. *J. Cryst. Growth* **236**, 627–634 (2002).
- Wu, J. L., Qin, F. & Cheng, G. Large-scale synthesis of bismuth sulfide nanorods by microwave irradiation. *J. Alloy. Compd.* **509**, 2116–2126 (2011).
- Zhang, H., Huang, J., Zhou, X. G. & Zhong, X. H. Single-crystal  $\text{Bi}_2\text{S}_3$  nanosheets growing via attachment-recrystallization of nanorods. *Inorg. Chem.* **50**, 7729–7734 (2011).
- Yang, X., Wang, X. & Zhang, Z. Facile solvothermal synthesis of single-crystalline  $\text{Bi}_2\text{S}_3$  nanorods on a large scale. *Mater. Chem. Phys.* **95**, 154–157 (2006).



30. Lan, J. L. *et al.* Effects of iodine content in the electrolyte on the charge transfer and power conversion efficiency of dye-sensitized solar cells under low light intensities. *J. Phys. Chem. C* **116**, 25727–25733 (2012).
31. Qian, J. *et al.* TiO<sub>2</sub>-coated multilayered SnO<sub>2</sub> hollow microspheres for dye-sensitized solar cells. *Adv. Mater.* **21**, 3663–3667 (2009).
32. Longo, C., Nogueira, A. F., De Paoli, M. A. & Cachet, H. Solid-state and flexible dye-sensitized TiO<sub>2</sub> solar cells: a study by electrochemical impedance spectroscopy. *J. Phys. Chem. B* **106**, 5925–5930 (2002).
33. Zhang, J. Y. *et al.* Ligand-assisted assembly approach to synthesize large-pore ordered mesoporous titania with thermally stable and crystalline framework. *Adv. Energy Mater.* **1**, 241–248 (2011).
34. Li, Q. H. *et al.* Nd<sub>2</sub>(S, Se, Te)<sub>3</sub> colloidal quantum dots: synthesis, energy level alignment, charge transfer dynamics, and their applications to solar cells. *Adv. Funct. Mater.* **26**, 254–266 (2016).
35. Jin, X. *et al.* Energy gradient architected praseodymium chalcogenide quantum dot solar cells: towards unidirectionally funneling energy transfer. *J. Mater. Chem. A*, **3**, 23876–23887 (2015).
36. Yang, J. *et al.* High catalytic activity and stability of nickel sulfide and cobalt sulfide hierarchical nanospheres on the counter electrodes for dye-sensitized solar cells. *Chem. Commun.* **50**, 4824–4826 (2014).
37. Li, Y. B. *et al.* A {0001} faceted single crystal NiS nanosheet electrocatalyst for dye-sensitized solar cells: sulfur-vacancy induced electrocatalytic activity. *Chem. Commun.* **50**, 5569–5571 (2014).

## Acknowledgements

We gratefully acknowledge the support of this research by the National Natural Science Foundation of China (21471050), Program for Innovative Research Team in University (IRT-1237), Innovation Team of Education Bureau of Heilongjiang Province (2013TD002), and Heilongjiang Province Natural Science Foundation of Key Projects (ZD201301).

## Author Contributions

B.Y.X. performed synthesis experiments, G.F.W. and H.G.F. designed the experiment. G.F.W. carried out photoelectrochemical evaluation and discussion. B.Y.X. and G.F.W. wrote the manuscript.

## Additional Information

**Competing financial interests:** The authors declare no competing financial interests.

**How to cite this article:** Xu, B. *et al.* 23327 Enhanced photoelectric conversion efficiency of dye-sensitized solar cells by the incorporation of flower-like Bi<sub>2</sub>S<sub>3</sub>:Eu<sup>3+</sup> sub-microspheres. *Sci. Rep.* **6**, 23395; doi: 10.1038/srep23395 (2016).



This work is licensed under a Creative Commons Attribution 4.0 International License. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in the credit line; if the material is not included under the Creative Commons license, users will need to obtain permission from the license holder to reproduce the material. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>