

SCIENTIFIC REPORTS

OPEN

Magnetization and magneto-transport staircaselike behavior in layered perovskite Sr_2CoO_4 at low temperature

Received: 09 March 2016

Accepted: 24 May 2016

Published: 13 June 2016

Qiuhan Li¹, Xueping Yuan², Lei Xing¹ & Mingxiang Xu¹

Polycrystalline layered perovskite Sr_2CoO_4 sample was synthesized by high temperature and high pressure method. The staircaselike behavior has been observed in the magnetization and resistivity versus field curves of Sr_2CoO_4 at low temperature. The main features of the steps can be obtained from the measured results: (i) the positions of the external magnetic field at which steps occur are varying in different measurement runs, (ii) the steps only appear at low temperature and disappear with a slight increase of the temperature, (iii) the steps are dependent on the temperature and field sweep rate. Based on the features of the magnetization and magneto-transport staircaselike behavior in Sr_2CoO_4 , the unusual phenomenon can be ascribed to an avalanche of flipping domains in terms of the random field theory.

In recent years, two dimensional compounds with K_2NiF_4 -type structure (a type of tetragonal structures) have generated great interest after the discovery of superconductivity, magnetoresistance (MR), spin/charge stripes in nickelates and manganites^{1–13}. Two-dimensional layer structured perovskite compound Sr_2CoO_4 is one of K_2NiF_4 -type structured materials with space group $I4/mmm$ ¹. The structure of Sr_2CoO_4 consists of corner sharing CoO_6 octahedra with two-dimension CoO_2 planes separated by insulating rock-salt layers of SrO. In the past reports, both Sr_2CoO_4 single-crystalline thin films and polycrystalline bulks were reported as a metallic ferromagnets with a fairly high Curie temperature (T_C) of 255 K^{1–3}. The susceptibility data above T_C of Sr_2CoO_4 can be well fitted to the Curie-Weiss law $\chi = C/(T + \Theta)$. The observed value of the effective magnetic moment per Co ion μ_{eff} (μ_B/Co) is 4.11, which can approximately coincide with that expected for spin only moment of the intermediate-spin (IS) state ($t_{2g}^4 e_g^1$, $S = 3/2$) Co^{4+} ($3.87 \mu_B/\text{Co}$) and be quite different from the values of the low-spin (LS) state ($t_{2g}^5 e_g^0$, $S = 1/2$) Co^{4+} ($1.73 \mu_B/\text{Co}$) and high-spin (HS) state ($t_{2g}^3 e_g^2$, $S = 5/2$) Co^{4+} ($5.92 \mu_B/\text{Co}$)^{1,4}. Below T_C , a cluster-glass state exists in Sr_2CoO_4 system⁵. It has been observed that Sr_2CoO_4 reveals large magnetic anisotropy where the c -axis is the magnetic easy axis⁶. The coercivity (H_C) of Sr_2CoO_4 is approximately 2.2~2.5 T at 5 K from polycrystalline sample¹ and single-crystalline film². It suggests great potential of Sr_2CoO_4 for high quality memory applications⁷. The half-metallicity of Sr_2CoO_4 has been predicted⁶. Different relationships of the electrical resistivity (ρ) versus temperature were observed in polycrystalline Sr_2CoO_4 and single-crystalline Sr_2CoO_4 film^{2,4}. The temperature dependence of ρ in polycrystalline Sr_2CoO_4 exhibits semiconducting characteristics¹. The ρ above T_C for the polycrystalline Sr_2CoO_4 can be well fitted by the variable range hopping (VRH) model $\rho = \rho_0 \exp(T_0/T)^{1/4}$. By comparison, in single-crystalline Sr_2CoO_4 film, the inter- CoO_2 -plane ρ of c -axis shows a sharp peak at T_C , with a metallic behavior below T_C and a semiconducting behavior above T_C ². In contrast, the intra- CoO_2 -plane ρ of b -axis shows metallic characteristics². At low temperature, large negative MR was observed in Sr_2CoO_4 ¹. The MR reaches a maximum at H_C . Therefore, the magnetic and electrical properties of Sr_2CoO_4 at low temperature, especially below 5 K, will be rather significant to study. Moreover, certain exceptional and unusual physical phenomena were observed frequently at low temperature, such as superconductivity, magnetic jump and quantum tunneling^{14–20}.

An interesting phenomenon, a staircaselike behavior which is analogous to resonant quantum tunneling of magnetization, was indeed observed in our Sr_2CoO_4 polycrystalline sample below 2.8 K. So far, to our knowledge, this is the first time that the staircaselike behavior was observed in Sr_2CoO_4 . It may suggest the new application

¹Department of Physics and Key Laboratory of MEMS of the Ministry of Education, Southeast University, Nanjing 210096, China. ²Department of Fundamental Courses, Nantong Polytechnic College, Nantong 226002, China. Correspondence and requests for materials should be addressed to M.X. (email: mxu@seu.edu.cn)

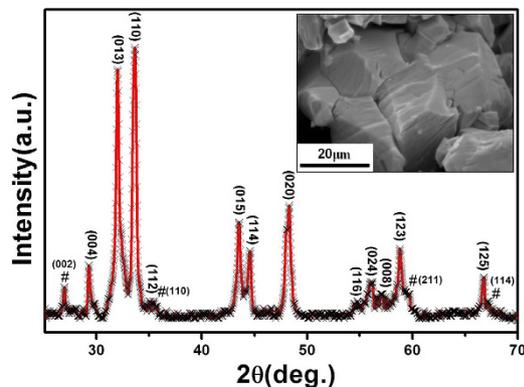


Figure 1. The XRD pattern of polycrystalline Sr_2CoO_4 sample. The inset shows the SEM image of polycrystalline Sr_2CoO_4 sample.

potentials of Sr_2CoO_4 in magnetic materials and devices. Thus, systematical experiments are urgently needed to study the exceptional phenomenon of Sr_2CoO_4 at low temperature and explore the possibility of the staircaselike behavior for various practical applications. In this work, the magnetic and electrical properties of polycrystalline Sr_2CoO_4 were studied below 5 K. The staircaselike behavior was observed in a series of magnetic and electrical curves, such as magnetization versus field (M - H) and resistivity versus field (ρ - H) curves. Based on the reported researches and explanations on the staircaselike behaviors observed in other materials, the mechanism of the staircaselike behavior in Sr_2CoO_4 was discussed in detail.

Results

Figure 1 shows the powder X-ray diffraction (XRD) pattern of polycrystalline Sr_2CoO_4 measured at room temperature. The main diffraction peaks of the sample can be fitted well with the XRD profile of Sr_2CoO_4 and indexed using the lattice parameters for a tetragonal structure with $a = 3.8372 \text{ \AA}$ and $c = 12.1935 \text{ \AA}$. A few additional peaks (marked by #) corresponding to nonmagnetic impurity SrO_2 can be observed in the pattern. However, this SrO_2 impurity phase is present in a small amount from the weak intensity of the peaks and has no effect on the magnetic properties of our sample. The inset of Fig. 1 shows the scanning electron microscope (SEM) photograph of Sr_2CoO_4 . The grains of the sample, with the average size approximately $20 \mu\text{m}$, are dense and distribute uniformly.

The M - H curve of Sr_2CoO_4 measured at 1.8 K with a field sweep rate of 25 Oe/s is displayed in Fig. 2(a). The saturation magnetization is $1.02 \mu_B/\text{Co}$, and the H_C is approximately 1.9 T. The large H_C is caused by high anisotropy in Sr_2CoO_4 ⁸. Most interestingly, unlike the general hysteresis loops, a staircaselike behavior can be observed from the M - H loop in Fig. 2(a). The steps on both sides of the hysteresis loop are central symmetry. The span (ΔM) of the four stairs on one side of the loop decreases with the increasing of the applied field (see Fig. 2(a)). The dM/dH versus field curve (Fig. 2(b)) clearly shows that the four jumps on one side occur at -1.84 T (1), -2.56 T (2), -3.20 T (3), -3.70 T (4), respectively. Moreover, two almost invisible jumps are reflected (see the # in Fig. 2(b)). The inset of Fig. 2(a) shows the three measurement runs from the same piece of sample measured at 1.8 K with a field sweep rate of 25 Oe/s . It can be seen that the steps on these curves of the same piece of sample are obviously misaligned for different measurement runs under the same measurement condition. This result suggests the randomness of the staircaselike behavior in different measurement runs.

Figure 3 shows the M - H curves of Sr_2CoO_4 measured at different temperatures. It can be observed that with increasing of the temperature, the quantity of the steps decreases and the positions of the corresponding steps move towards the direction of high field. At 2.8 K, the staircaselike behavior disappears completely. These results suggest that the staircaselike behavior is sensitive excessively to the slight temperature variation. The inset of Fig. 3 shows the M - H curves of Sr_2CoO_4 measured at 2 K with different magnetic field sweep rates. With the increasing of the sweep rate, the quantity of the steps increases gradually and the positions of the corresponding steps move towards the low field (see the arrow in the inset of Fig. 3). It can be deemed that the staircaselike behavior in Sr_2CoO_4 is dependent on the magnetic field sweep rate.

Figure 4 shows the ρ - H curve of Sr_2CoO_4 measured at 2 K. The resistivity reaches a maximum at H_C , which is consistent with the previous reports^{1,2}. This phenomenon can be considered as tunneling MR at domain boundaries. It is attributed to the field suppression of the spin-dependent scattering at domain boundaries⁸. The staircaselike behavior can be also observed from the ρ - H curve. The insets (a) and (b) of Fig. 4 show the ρ - H curves of Sr_2CoO_4 measured at different temperatures and magnetic field sweep rates, respectively. The steps in the inset (a) disappear gradually with the increasing of the temperature. The three ρ - H curves in the inset (b) of Fig. 4 are misaligned for different field sweep rates. The positions of the corresponding steps on the ρ - H curves also move towards the low field with the increasing of the field sweep rate (see the arrow in the inset (b) of Fig. 4). The steps on the ρ - H curves of the same piece of sample are also misaligned for different measurement runs under the same measurement condition (figure not shown). These phenomena are consistent with the above magnetic results of Sr_2CoO_4 (see the M - H curves of Fig. 3).

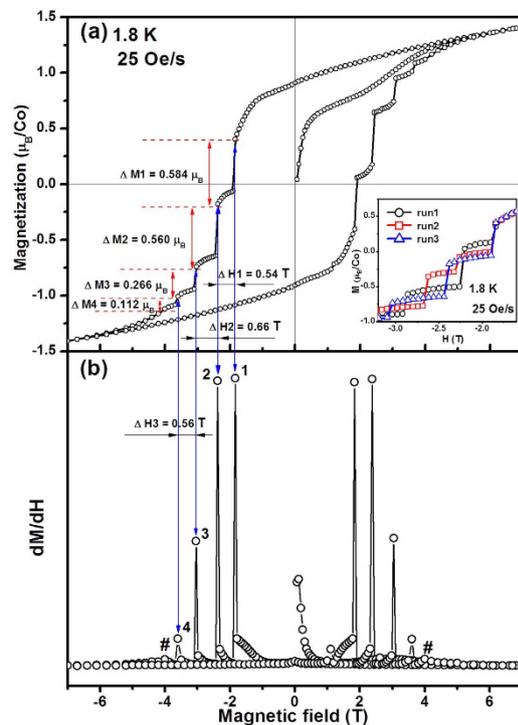


Figure 2. (a) Magnetization versus field (M - H) curve at 1.8 K with a field sweep rate of 25 Oe/s for the Sr_2CoO_4 . (b) dM/dH - H curve at 1.8 K for the Sr_2CoO_4 . The inset of (a) shows the three measurement runs of the same piece of sample obtained under the same measurement condition.

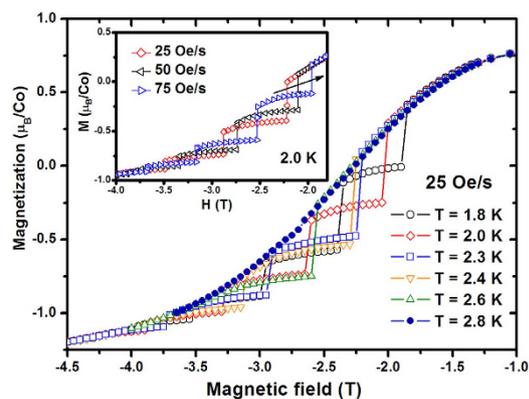


Figure 3. Magnetization versus field (M - H) curves for the Sr_2CoO_4 sample at different temperatures with the same field sweep rate of 25 Oe/s. The inset shows M - H curves for the Sr_2CoO_4 at 2 K with different magnetic field sweep rates.

Discussion

Three main characteristics of the staircaselike behavior in Sr_2CoO_4 are concluded from the measured results: (i) the positions of the steps are varying in different measurement runs, (ii) the steps only appear at low temperature ($T < 2.8$ K) and disappear with a slight increase of the temperature, (iii) the steps are dependent on the temperature and field sweep rate. The possible mechanism of the staircaselike behavior will be systematically discussed below.

The similar staircaselike behaviors in hysteresis loops have been also reported in many types of materials, such as $\text{Ca}_3\text{Co}_2\text{O}_6$ ^{14,15}, $[\text{Mn}_4]_2$ dimer¹⁶, $\text{Fe}_x\text{Mg}_{1-x}\text{Cl}_2$ ²¹, PrVO_3 ²², UGe_2 ^{23,24}, and amorphous Dy-Cu²⁵. Simultaneously, different theories have been presented to explain the staircaselike behaviors. The main three theories are resonant quantum tunneling^{14–20}, random field^{21–35}, and intrinsic pinning of magnetic domain walls^{36–38}.

Resonant quantum tunneling has been applied to systems involving a large number of identical high-spin materials^{14–20}, as in the case of $\text{Ca}_3\text{Co}_2\text{O}_6$ ^{14,15}, and Mn_{12} acetate²⁰. $\text{Ca}_3\text{Co}_2\text{O}_6$ is a type of perovskite material with K_4CdCl_6 -type structure (an infinite chain-type structure). The analogous steps can be observed from the M - H curves of $\text{Ca}_3\text{Co}_2\text{O}_6$ at low temperature^{14,15}. The steps are resulted from the transformation and change of the

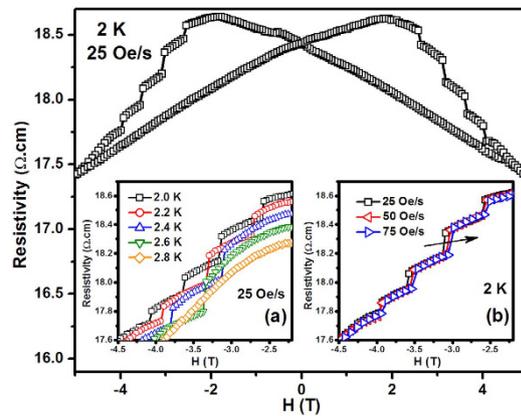


Figure 4. Resistivity versus field (ρ - H) curve for the Sr_2CoO_4 at 2 K with a field sweep rate of 25 Oe/s. The inset (a) shows ρ - H curves for the Sr_2CoO_4 sample at different temperatures with the same field sweep rate of 25 Oe/s. The inset (b) shows ρ - H curves for the Sr_2CoO_4 sample at 2 K with different magnetic field sweep rates.

percentage of different magnetism in the materials caused by the applied field at different temperatures¹⁴. The chain-type structure is the key factor to the staircaselike behavior. The intrachain coupling is ferromagnetic and the interchain coupling is antiferromagnetic. However, Sr_2CoO_4 is one type of two-dimensional layer structured compound. Obviously, no chain-type structure exists in Sr_2CoO_4 . On the other hand, the most important characteristic of the staircaselike behavior in quantum-effect system is that the positions of the steps are temperature-independent below a critical temperature^{17,18}. The results from the Fig. 3 of Sr_2CoO_4 show that the steps in the six M - H curves exhibit no similar characteristic of temperature independence. This result indicates that the staircaselike behavior in Sr_2CoO_4 is incompatible with resonant quantum tunneling.

The presence of random fields is another explanation that can lead to staircaselike behavior. Under this mechanism, a given domain is flipped by an external field, thus reversing the magnetization of the neighboring domains and finally resulting in an avalanche of flipping domains^{21–29} considering the random field Ising model (RFIM)^{31–34}. Each jump in one curve corresponds to an avalanche process where the spins (of one or more clusters in the polycrystalline Sr_2CoO_4) align with the applied magnetic field²⁶. The noteworthy characteristic of the steps in this theory is the randomness. The positions of the steps are varying in different measurement runs. Meanwhile, the steps can be only observed at low temperature. The ferromagnetic clusters in Sr_2CoO_4 sample play a crucial role for this phenomenon^{13,26–28}. Below the critical temperature at which the steps are vanished, the ferromagnetic cluster-sizes in the sample increase, and the cluster percolation process yields an increase in the ferromagnetic correlation length with lowering the temperature²⁶. The larger cluster-size can result in the bigger avalanche, which gives rise to the distinct jumps. Above the critical temperature, the thermal activation is dominating²⁶, and the cluster-size is so small, which can only cause small avalanche. As a consequence, the jumps become sightless, and the hysteresis loop becomes smooth. This type of staircaselike behaviors is dependent on temperature, but independent on field sweep rate. Such an explanation has been proposed in site-diluted metamagnet $\text{Fe}_x\text{Mg}_{1-x}\text{Cl}_2$ ²¹, single crystal antiferromagnet PrVO_3 ²², single crystalline UGe_2 ^{23,24}, disordered systems such as the amorphous Dy-Cu ²⁵, polycrystalline $\text{CeNi}_{1-x}\text{Cu}_x$ ^{26–29}, and liquid quenched R_3Co alloys³⁰. All the features of the steps in Sr_2CoO_4 are similar to the characteristics of staircaselike behaviors in PrVO_3 ²², UGe_2 ^{23,24}, and $\text{CeNi}_{1-x}\text{Cu}_x$ ^{26–29}. The other features of the steps, except the dependence of magnetic field sweep rate, can be well explained by the random field theory. The dependence of magnetic field sweep rate may result from the magnetocaloric effect^{22,35}. The positions of the corresponding steps move to higher field with the decreasing of the sweep rate. It suggests the existence of adiabaticity in Sr_2CoO_4 . In the adiabatic state, the energy released in the spin reversal process dissipates tardily³⁵. With the increasing of the sweep rate, the energy accumulates rapidly and facilitates the reversal of neighboring spins. It results in the sweep rate dependence of the steps. From this point of view, the fundamental reason of the staircaselike behavior in Sr_2CoO_4 may be ascribed to an avalanche of flipping domains in terms of the random field theory.

The intrinsic pinning of magnetic domain walls is compatible with the magnetization jumps observed in alloy samples^{36–38}. The domain walls motioning inside the ferromagnetic domains depend on the pinning effect introduced by foreign elements and the local crystal fields. The pinning effect can result in the creation of energetic barriers, which influence the magnetization process at low temperature³⁶. In the case of $\text{EuBaCo}_{1.92}\text{M}_{0.08}\text{O}_{5.5-8}$ ($M = \text{Zn}, \text{Cu}$)³⁷, Zn^{2+} and Cu^{2+} are the origin of the pinning of the narrow domain walls. When the magnetic field becomes high enough to overcome the pinning effect, the domain walls tend to disappear and the spins of the ferromagnetic domains are all aligned. This type of the staircaselike behaviors strongly depends on the external magnetic field sweep rate. When the magnetic field changes slowly enough, the M - H curve becomes normal with no jump³⁸. This phenomenon was similar to the result from the inset of Fig. 3 in Sr_2CoO_4 . In the perfect Sr_2CoO_4 crystals, no substituted defect results in the effective pinning. However, here, the saturated moment of the Sr_2CoO_4 sample ($1.02 \mu_B/\text{Co}$) is lower than the calculated value ($1.97 \mu_B/\text{Co}$)². Meanwhile, the μ_{eff} of Co ion ($4.11 \mu_B/\text{Co}$) in Sr_2CoO_4 is also different from the spin only moments of LS Co^{4+} ($1.73 \mu_B/\text{Co}$), IS Co^{4+} ($3.87 \mu_B/\text{Co}$), and HS Co^{4+} ($5.92 \mu_B/\text{Co}$)^{1,4}. These results suggest that multiple spin states may exist in our Sr_2CoO_4 sample.

The interactions between the neighboring IS or HS Co ions (Co(IS or HS)-O-Co(IS or HS)) are antiferromagnetic^{39,40}, though the ground state of Sr₂CoO₄ is ferromagnetic⁶. It means that antiferromagnetism and ferromagnetism are coexistent in Sr₂CoO₄, which can lead to multiple magnetic phases. The multiple magnetic phases may result in the intrinsic pinning of magnetic domain walls^{36,41,42}, and further contribute to the magnetization and magneto-transport staircaselike behavior in the Sr₂CoO₄.

In summary, layered perovskite compound Sr₂CoO₄ polycrystalline sample was synthesized by high temperature and high pressure method. The magnetic and magneto-transport properties of Sr₂CoO₄ were studied at low temperature. A staircaselike behavior on *M-H* and $\rho-H$ curves was observed in polycrystalline Sr₂CoO₄ below 2.8 K. The steps appear with a certain degree of randomness in different measurement runs. The staircaselike behavior is dependent on the temperature and the magnetic field sweep rate. The fundamental reason of the staircaselike behavior can be considered as the presence of random fields, leading to an avalanche of flipping domains. The multiple magnetic phases which can result in the intrinsic pinning of magnetic domain walls, may contribute to the magnetization and magneto-transport staircaselike behavior in the Sr₂CoO₄.

Methods

Polycrystalline sample of composition Sr₂CoO₄ was synthesized under high pressure at high temperature. Starting materials of SrO₂ and Co were well mixed in a molar ratio of SrO₂ : Co = 2 : 1. The mixture was sealed into a gold capsule. The capsule was first compressed at 6 GPa in a high pressure apparatus (flat-belt-type-high-pressure apparatus, 1500 ton), then heated to 1200 °C for 30 minutes and finally quenched to room temperature followed by releasing of pressure. The crystal structure of the polycrystalline sample was identified by the powder X-ray diffraction (XRD, Rigaku Smartlab3), using Cu-K α radiation ($\lambda = 1.54184 \text{ \AA}$). The morphology of the sample was observed using a scanning electron microscope (SEM). The dc magnetic measurements were investigated using a vibrating sample magnetometer (VSM) integrated in a physical property measurement system (PPMS-9, Quantum Design). The electrical resistivity of the sample was measured with a Quantum Design PPMS-9 system using the standard four-probe ac method.

References

- Wang, X. L. & Takayama-Muromachi, E. Magnetic and transport properties of the layered perovskite system Sr_{2-y}Y_yCoO₄ ($0 \leq y \leq 1$). *Phys. Rev. B* **72**, 064401 (2005).
- Matsuno, J. *et al.* Metallic ferromagnet with square-lattice CoO₂ sheets. *Phys. Rev. Lett.* **93**, 167202 (2004).
- Wang, X. L., Takayama-Muromachi, E., Dou, S. X. & Cheng, Z. X. Band structures, magnetic properties, and enhanced magnetoresistance in the high pressure phase of Gd and Y doped two-dimensional perovskite Sr₂CoO₄ compounds. *Appl. Phys. Lett.* **91**, 062501 (2007).
- Xu, M., Balamurugan, S. & Takayama-Muromachi, E. Magnetic and transport properties and spin states of layered cobalt oxides Sr_{2-x}Ho_xCoO₄ ($0 \leq x \leq 1.0$). *Prog. Theor. Phys. Supp.* **159**, 349 (2005).
- Pandey, P. K., Choudhary, R. J. & Phase, D. M. Magnetic behavior of layered perovskite Sr₂CoO₄ thin film. *Appl. Phys. Lett.* **103**, 132413 (2013).
- Pandey, S. K. Correlation induced half-metallicity in a ferromagnetic single-layered compound: Sr₂CoO₄. *Phys. Rev. B* **81**, 035114 (2010).
- Pandey, P. K., Choudhary, R. J., Mishra, D. K., Sathe, V. G. & Phase, D. M. Signature of spin-phonon coupling in Sr₂CoO₄ thin film: a Raman spectroscopic study. *Appl. Phys. Lett.* **102**, 142401 (2013).
- Wang, X. L., Sakurai, H. & Takayama-Muromachi, E. Synthesis, structures, and magnetic properties of novel Roddlesden-Popper homologous series Sr_{n+1}Co_nO_{3n+1} ($n = 1, 2, 3, 4$, and ∞). *J. Appl. Phys.* **97**, 10M519 (2005).
- Lee, K.-W. & Pickett, W. E. Correlation effects in the high formal oxidation-state compound Sr₂CoO₄. *Phys. Rev. B* **73**, 174428 (2006).
- Wu, H. Metal-insulator transition in Sr_{2-x}La_xCoO₄ driven by spin-state transition. *Phys. Rev. B* **86**, 075120 (2012).
- Yao, Q. W. *et al.* Band structures, and magnetic and transport properties of La doped two dimensional Sr₂CoO₄. *J. Appl. Phys.* **101**, 09N515 (2007).
- Yao, Q. *et al.* Density of states, magnetic and transport properties of Nd doped two dimensional perovskite compound Sr₂CoO₄. *J. Appl. Phys.* **111**, 07D708 (2012).
- Pandey, P. K., Choudhary, R. J. & Phase, D. M. Anomalous temperature dependence in valence band spectra: a resonant photoemission study of layered perovskite Sr₂CoO₄. *Appl. Phys. Lett.* **104**, 182409 (2014).
- Maignan, A., Michel, C., Masset, A. C., Martin, C. & Raveau, B. Single crystal study of the one dimensional Ca₃Co₂O₆ compound: five stable configurations for the Ising triangular lattice. *Eur. Phys. J. B* **15**, 657 (2000).
- Maignan, A. *et al.* Quantum tunneling of the magnetization in the Ising chain compound Ca₃Co₂O₆. *J. Mater. Chem.* **14**, 1231 (2004).
- Tiron, R., Wernsdorfer, W., Foguet-Albiol, D., Aliaga-Alcalde, N. & Christou, G. Spin quantum tunneling via entangled states in a dimer of exchange-coupled single-molecule magnets. *Phys. Rev. Lett.* **91**, 227203 (2003).
- Wernsdorfer, W., Bhaduri, S., Boskovic, C., Christou, G. & Hendrickson, D. N. Spin-parity dependent tunneling of magnetization in single-molecule magnets. *Phys. Rev. B* **65**, 180403(R) (2002).
- Wernsdorfer, W., Aliaga-Alcalde, N., Hendrickson, D. N. & Christou, G. Exchange-biased quantum tunnelling in a supramolecular dimer of single-molecule magnets. *Nature* **416**, 406 (2002).
- Wernsdorfer, W., Bhaduri, S., Tiron, R., Hendrickson, D. N. & Christou, G. Spin-spin cross relaxation in single-molecule magnets. *Phys. Rev. Lett.* **89**, 197201 (2002).
- Wernsdorfer, W., Sessoli, R. & Gatteschi, D. Nuclear-spin-driven resonant tunnelling of magnetisation in Mn₁₂ acetate. *Europhys. Lett.* **47**, 254 (1999).
- Kushauer, J., van Bentum, R., Kleemann, W. & Bertrand, D. Athermal magnetization avalanches and domain states in the site-diluted metamagnet Fe₂Mg_{1-x}Cl₂. *Phys. Rev. B* **53**, 11647 (1996).
- Tung, L. D. PrVO₃: an inhomogeneous antiferromagnetic material with random fields. *Phys. Rev. B* **72**, 054414 (2005).
- Nishioka, T., Motoyama, G., Nakamura, S., Kadoya, H. & Sato, N. K. Unusual nature of ferromagnetism coexisting with superconductivity in UGe₂. *Phys. Rev. Lett.* **88**, 237203 (2002).
- Lhotel, E., Paulsen, C. & Huxley, A. D. Comment on "Unusual nature of ferromagnetism coexisting with superconductivity in UGe₂". *Phys. Rev. Lett.* **91**, 209701 (2003).
- Coe, J. M. D., McGuire, T. R. & Tissier, B. Amorphous Dy-Cu: random spin freezing in the presence of strong local anisotropy. *Phys. Rev. B* **24**, 1261 (1981).

26. Iglesias, J. R., Espeso, J. I., Marcano, N. & Gómez Sal, J. C. Cluster model with random anisotropy for hysteresis jumps in CeNi_{1-x}Cu_x alloys. *Phys. Rev. B* **79**, 195128 (2009).
27. Marcano, N., Gómez Sal, J. C., Espeso, J. I., Fernández Barquín, L. & Paulsen, C. Cluster-glass percolative scenario in CeNi_{1-x}Cu_x studied by very low-temperature ac susceptibility and dc magnetization. *Phys. Rev. B* **76**, 224419 (2007).
28. Kawasaki, I. *et al.* Magnetic properties around quantum critical point of CePt_{1-x}Rh_x. *Physica B* **404**, 2908 (2009).
29. Marcano, N. *et al.* Mesoscopic magnetic states in metallic alloys with strong electronic correlations: a percolative scenario for CeNi_{1-x}Cu_x. *Phys. Rev. Lett.* **98**, 166406 (2007).
30. Baranov, N. V., Pushkarski, V. I., Sviderski, A. E. & Sassik, H. Magnetic properties of liquid quenched R₃Co alloys. *J. Magn. Magn. Mater.* **157**, 635 (1996).
31. Sethna, J. P. *et al.* Hysteresis and hierarchies: dynamics of disorder-driven first-order phase transformations. *Phys. Rev. Lett.* **70**, 3347 (1993).
32. Dahmen, K. & Sethna, J. P. Hysteresis loop critical exponents in 6-e dimensions. *Phys. Rev. Lett.* **71**, 3222 (1993).
33. Perkovic, O., Dahmen, K. & Sethna, J. P. Avalanches, barkhausen noise, and plain old criticality. *Phys. Rev. Lett.* **75**, 4528 (1995).
34. Dahmen, K. & Sethna, J. P. Hysteresis, avalanches, and disorder-induced critical scaling: a renormalization-group approach. *Phys. Rev. B* **53**, 14872 (1996).
35. Ferre, R. & Barbara, B. Magnetisation studies of disordered systems: importance of adiabaticity in non-equilibrium processes. *J. Magn. Magn. Mater.* **140**, 1861 (1995).
36. Zhong, W., Lan, J., Liu, Z. & Li, G. Intrinsic pinning of domain walls in Dy(Fe_{1-x}M_x)₂ (M = Ga, Al; x ≤ 0.2). *J. Magn. Magn. Mater.* **74**, 39 (1988).
37. Raveau, B., Simon, C., Pralong, V., Caignaert, V. & Lefevre, F.-X. Ferromagnetism, phase separation and ultrasharp magnetization multisteps below 40 K in the ordered “112” cobaltites EuBaCo_{1.92}M_{0.08}O_{5.5-δ} (M = Zn, Cu). *Solid State Commun.* **139**, 301 (2006).
38. Mushnikov, N. V., Zajkov, N. K. & Korolyov, A. V. On the nature of magnetization jumps in Dy(Fe,M)₂ (M = Al, Si). *J. Magn. Magn. Mater.* **163**, 322 (1996).
39. Yamaguchi, S., Okimoto, Y. & Tokura, Y. Local lattice distortion during the spin-state transition in LaCoO₃. *Phys. Rev. B* **55**, R8666 (1997).
40. Imada, M., Fujimori, A. & Tokura, Y. Metal-insulator transitions. *Rev. Mod. Phys.* **70**, 1039 (1998).
41. Alejandro, G. *et al.* Barkhausen-like steps and magnetic frustration in doped La_{0.67-x}A_xCa_{0.33}MnO₃ (A = Ce, Y). *Phys. Rev. B* **73**, 054427 (2006).
42. Jammalamadaka, S. N., Mohapatra, N., Das, S. D., Iyer, K. K. & Sampathkumaran, E. V. Magnetic anomalies in Gd₆Co_{1.67}Si₃ and Tb₆Co_{1.67}Si₃. *J. Phys.: Condens. Matter* **20**, 425204 (2008).

Acknowledgements

The authors gratefully thank Professor Eiji Takayama-Muromachi of National Institute for Materials Science (NIMS), Japan to provide the flat-belt-type-high-pressure apparatus for the sample synthesis. This work is partially supported by Natural Science Foundation of Jiangsu Province of China (Grant No. BK20141337), National Basic Research Program of China (973 Program) (Grant No. 2014CB932103), the Fundamental Research Funds for the Central Universities (Grant No. KYLX_0085), the Scientific Research Foundation of Graduate School of Southeast University (Grant No. YBJJ1562) and Large Equipment Grants of Southeast University, China.

Author Contributions

Q.L. performed most of the experiments and analyzed the data. L.X. contributed to the basic characterization of the sample. X.Y. contributed to the analysis of magnetization and magnetoresistance. M.X. designed and directed the research. Q.L. and X.Y. wrote the manuscript.

Additional Information

Competing financial interests: The authors declare no competing financial interests.

How to cite this article: Li, Q. *et al.* Magnetization and magneto-transport staircaselike behavior in layered perovskite Sr₂CoO₄ at low temperature. *Sci. Rep.* **6**, 27712; doi: 10.1038/srep27712 (2016).



This work is licensed under a Creative Commons Attribution 4.0 International License. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in the credit line; if the material is not included under the Creative Commons license, users will need to obtain permission from the license holder to reproduce the material. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>