

SCIENTIFIC REPORTS



OPEN

High saturation magnetization of γ -Fe₂O₃ nano-particles by a facile one-step synthesis approach

Derang Cao¹, Hao Li², Lining Pan¹, Jianan Li¹, Xicheng Wang², Panpan Jing¹, Xiaohong Cheng¹, Wenjie Wang³, Jianbo Wang^{1,2} & Qingfang Liu¹

Received: 22 January 2016

Accepted: 05 August 2016

Published: 01 September 2016

We have demonstrated the synthesis of γ -Fe₂O₃ nano-particles through a facile and novel calcination process in the air. There is no pH regulation, gas atmosphere, additive, centrifugation or other complicated procedures during the preparing process. A detailed formation process of the nano-particles is proposed, and DMF as a polar solvent may slower the reaction process of calcination. The structures, morphologies, and magnetic properties of γ -Fe₂O₃ nano-particles were investigated systematically, and the pure γ -Fe₂O₃ nano-particles obtained at 200 °C display uniform morphology good magnetic property. The saturation magnetization of obtained pure γ -Fe₂O₃ is about 74 emu/g, which is comparable with bulk material (76 emu/g) and larger than other results. In addition, the photocatalytic activity for degradation of methylene blue is also studied, which shows proper photocatalytic activity.

Magnetic nanomaterials have attracted much interest gradually, since these materials have many potential applications such as information storage, color imaging, magnetic refrigeration, gas sensors, ferrofluids, and photocatalysis etc.^{1–7} Recently, researches of magnetic nanomaterials are fascinating due to its powerful usefulness for a variety of biomedical^{8,9} and chemical engineering applications¹⁰. Among the magnetic nanomaterials, maghemite (γ -Fe₂O₃) is considered as one of the most desirable materials for various applications due to its inherent biocompatible nature and stability of oxidation as well as its good magnetic properties^{11–13}. γ -Fe₂O₃ also exhibits modest photocatalytic activity and separability^{7,14}. It can be used associated with ZnO or TiO₂ to enhance the visible light adsorption and increase the electron/hole separation^{15,16}. High magnetization of γ -Fe₂O₃ has potential applications for cleaning polluted water with the help of magnetic separation. As a result, magnetic properties, as an important symbolic characteristic of γ -Fe₂O₃ nano-particles, are noticeable for study.

Therefore, new approaches for the synthesis of γ -Fe₂O₃ particles as well as the investigation on their properties are of fundamental importance for the development of science and technology. The basic and conventional route of these methods or processes for the synthesis of γ -Fe₂O₃ nano-particles are controlling the oxidation of Fe₃O₄^{17–20}, and the total preparation process is shown as follows:



Various methods have been reported for the synthesis of γ -Fe₂O₃ nano-particles, such as coprecipitation^{12,21}, hydrothermal²², microemulsions^{4,23}, thermal decomposition^{24,25}, aerosol pyrolysis²⁶, sole-gel²⁷, hydrosol chemical reaction²⁰, combustion synthesis⁷, Massart method^{2,28}, solvothermal method^{29,30}, wet chemical method^{31,32}, sonochemical route³³, ultrasonic decomposition³⁴, high-temperature solution reaction¹, chemical reaction⁶, and other chemical process^{35–39}. These synthesis processes or methods are the important routes for the synthesis of γ -Fe₂O₃ nano-particles and its composite materials. However, suitable pH value, long reaction time, and definite additives or surfactants are indispensable for obtaining pure γ -Fe₂O₃ nano-particles with controllable morphology during those synthesis processes. Furthermore, centrifugation and purification are the vital factor for nano-particles with single products and good dispersity. Those preparation processes were totally complicated and cumbersome.

¹Key Laboratory for Magnetism and Magnetic Materials of the Ministry of Education, Lanzhou University, Lanzhou 730000, People's Republic of China. ²Key Laboratory of Special Function Materials and Structure Design, Ministry of Education, Lanzhou University, Lanzhou 730000, People's Republic of China. ³Key Laboratory of nonferrous metals chemistry and resources utilization, Lanzhou University, Lanzhou 730000, People's Republic of China. Correspondence and requests for materials should be addressed to Q.L. (email: liuqf@lzu.edu.cn)

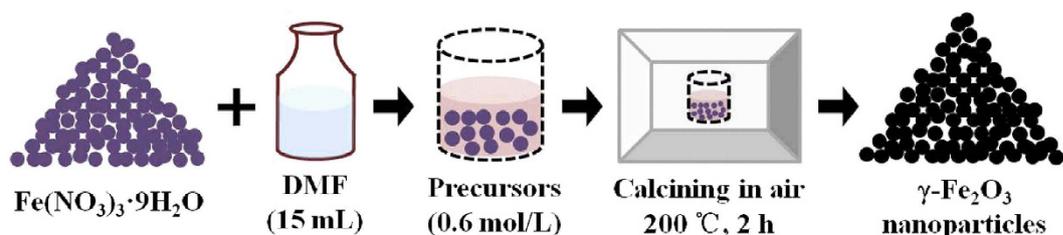


Figure 1. The schematic diagram of experimentation.

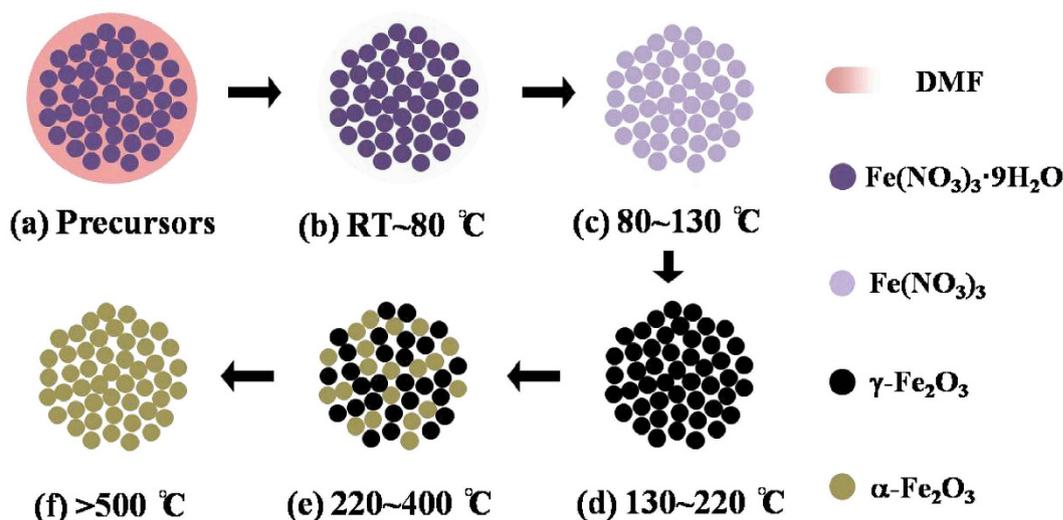


Figure 2. The formation mechanism of γ - Fe_2O_3 nano-particles.

Significantly, the saturation magnetization of γ - Fe_2O_3 nano-particles of the most methods mentioned above is still dissatisfied.

Herein, we report a unified approach for the synthesis of γ - Fe_2O_3 nano-particles in the air via a facile and novel calcination process. The method is different from the earlier approaches, and there is no pH regulation, gas atmosphere, centrifugation and other supplementary reagents during the preparing process. Various characterizations were measured to perform the obtained pure γ - Fe_2O_3 nano-particles, and γ - Fe_2O_3 nano-particles show a high saturation magnetization. In addition, the photocatalytic activity of γ - Fe_2O_3 nano-particles was also studied.


Methods

A unified method was provided using a simple and convenient route to assemble γ - Fe_2O_3 nano-particles. Ferric nitrate was dissolved in Dimethyl Formamide (DMF), the precursor was 0.6 mol/L, and calcined at different temperature (100 °C~400 °C, the interval is 50 °C) for 2 hours in the air. The heating rate was 1 °C/min. The schematic diagram of experiment is shown in Fig. 1.

The crystal structure of samples were measured by X-ray diffraction (XRD, PANalytical X'Pert) equipped with Cu-K α radiation ($\lambda = 1.5406 \text{ \AA}$). The morphology of all samples was observed by using field emission scanning electron microscopy (FESEM, Hitachi S-4800) and transmission electron microscopy (TEM, TecnaiTM G² F30, FEI) equipped with an energy-dispersive spectrometer (EDS). The X-ray photoelectron spectroscopy (XPS, PHI-5702, Physical Electronics) were performed using a monochromatic Al-K α irradiation and a charge neutralizer. All binding energies were referred to the C1s peak at 284.6 eV of the surface adventitious carbon. The magnetic properties of the samples were measured by a vibrating sample magnetometer (VSM, Lakeshore 7304). The measurement process of surface areas and photocatalytic activity of the sample were shown in the Supporting Information (SI).

Results and Discussion

On the basis of the below experiments and results, a formation mechanism of the nano-particles in this work is proposed, which is outlined in Fig. 2. It is suggested that the following reactions occur during the calcination process:



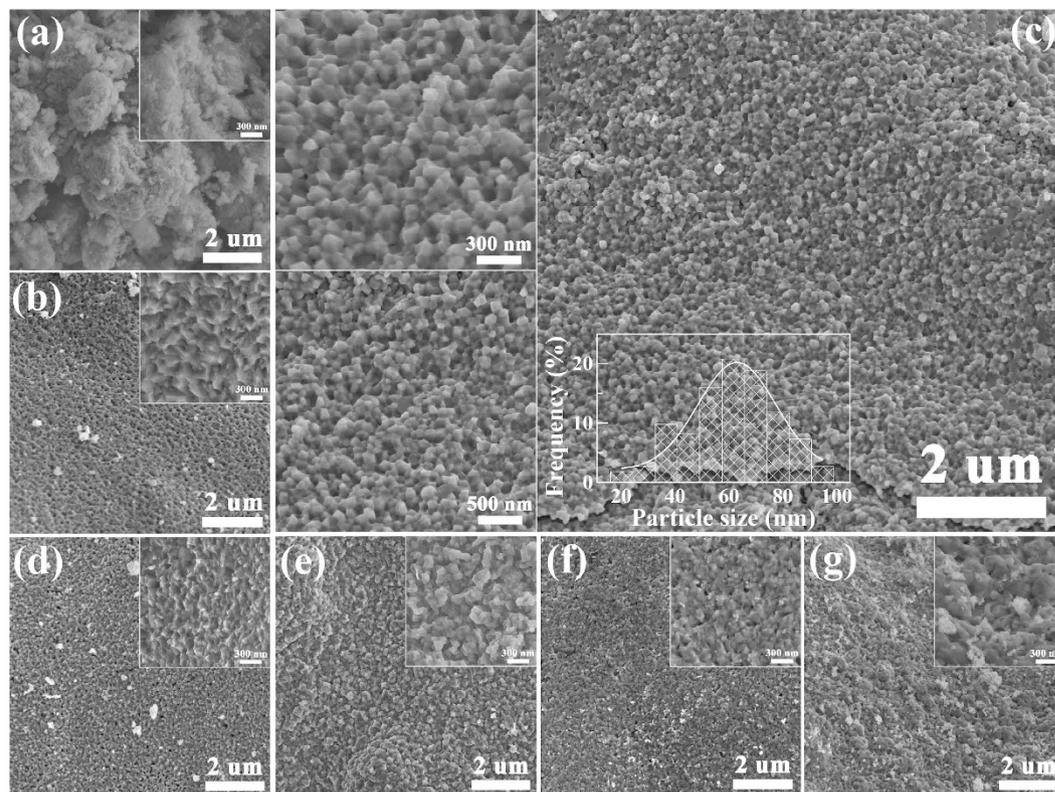


Figure 3. SEM images of nano-particles of different calcinations temperature (a) 100 °C, (b) 150 °C, (c) 200 °C, (d) 250 °C, (e) 300 °C, (f) 350 °C, and (g) 400 °C, respectively. The inset of (c) is the size distributions of nano-particles at 200 °C.

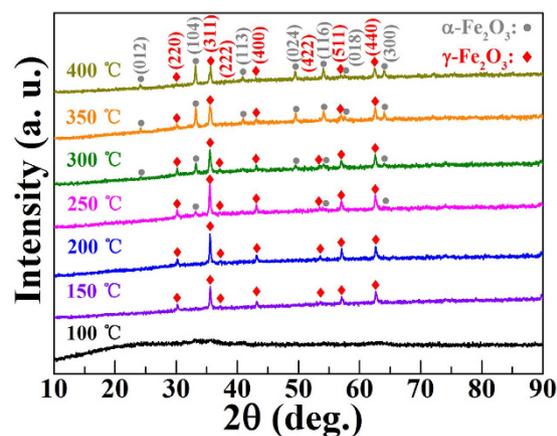


Figure 4. XRD patterns of γ - Fe_2O_3 nano-particles at different calcinations temperature.



As shown in Fig. 2(a), the precursor is composed of DMF and iron nitrate. The solvents begin to volatilize at the beginning of the heating process (Fig. 2b). DMF in precursors plays a role of solvent, which helps the diffusion and contact of the reactant molecules in the course of volatilization. When calcination temperature (CT) is increased (Fig. 2c), DMF is exhausted gradually, and the iron nitrite nonahydrate ($\text{Fe}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$) loses its water of hydration. The processes of Fig. 2(a–c) reveal that the surface morphology of sample seems not to be changed

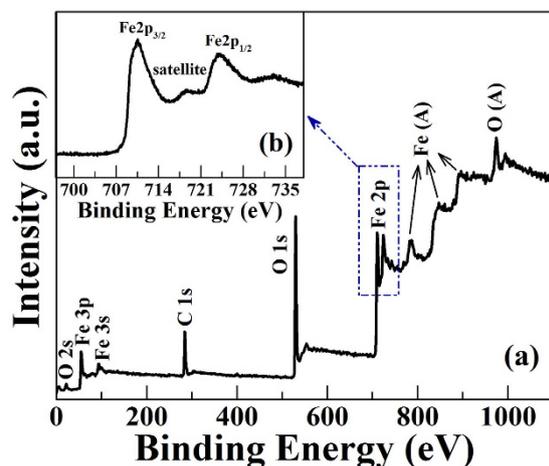


Figure 5. XPS patterns of γ - Fe_2O_3 nano-particles under 200 °C. (a) Full scanned XPS spectra, (b) XPS spectra of Fe 2p core-level.

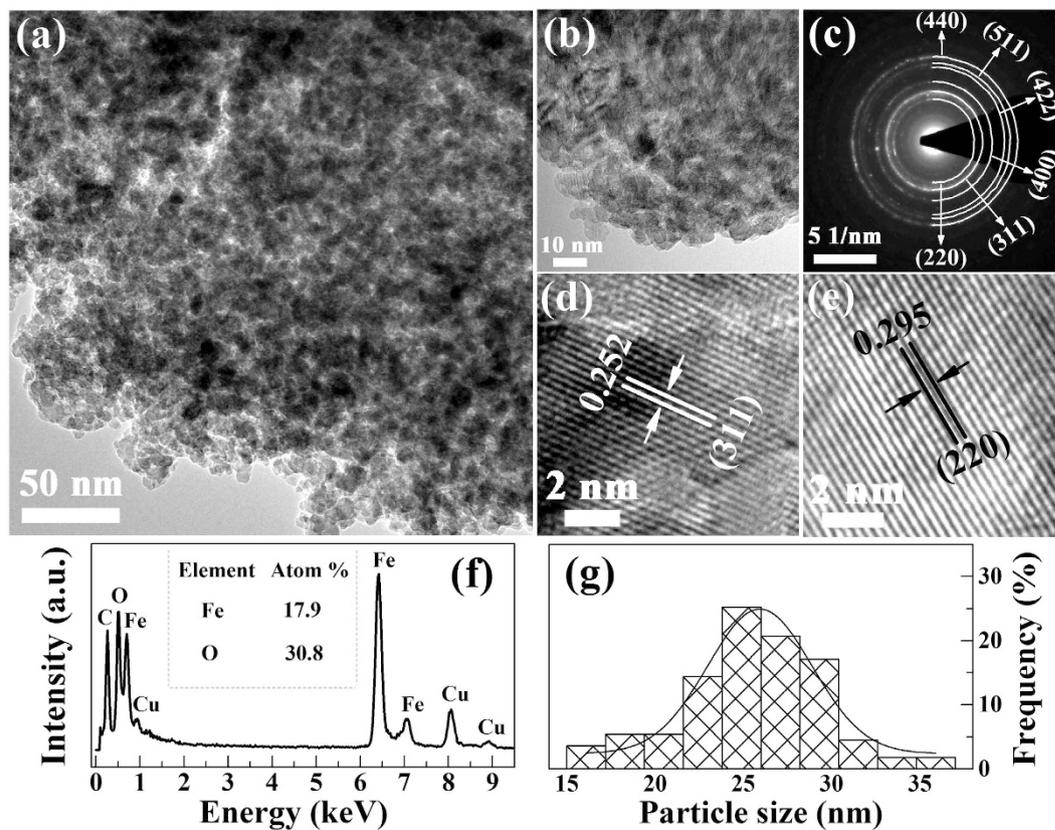


Figure 6. Typical TEM images (a,b), SAED (c), HRTEM image (d,e), EDX (f), and grain size distributions of γ - Fe_2O_3 nano-particles of 200 °C.

from their nature. The corresponding SEM picture and XRD pattern at 100 °C show bulk grains, suggesting an amorphous structure. The non-magnetic results (VSM loop) also confirm the amorphous structure. When the specimen is calcined at a moderate temperature (Fig. 2d), $\text{Fe}(\text{NO}_3)_3$ decomposes into γ - Fe_2O_3 , and the nucleation process is observed (See SEM image and XRD spectrum at 150 °C). When CT then increases, a large area of γ - Fe_2O_3 nucleation is crystallized to the uniform nano-particles, which can be demonstrated by SEM image and XRD spectrum of 200 °C. Thereafter, when CT is about 220–400 °C (Fig. 2e), γ - Fe_2O_3 nano-particles begin to engulf its surrounded crystals, and various sizes of α - Fe_2O_3 particles are formed. This can be supported by

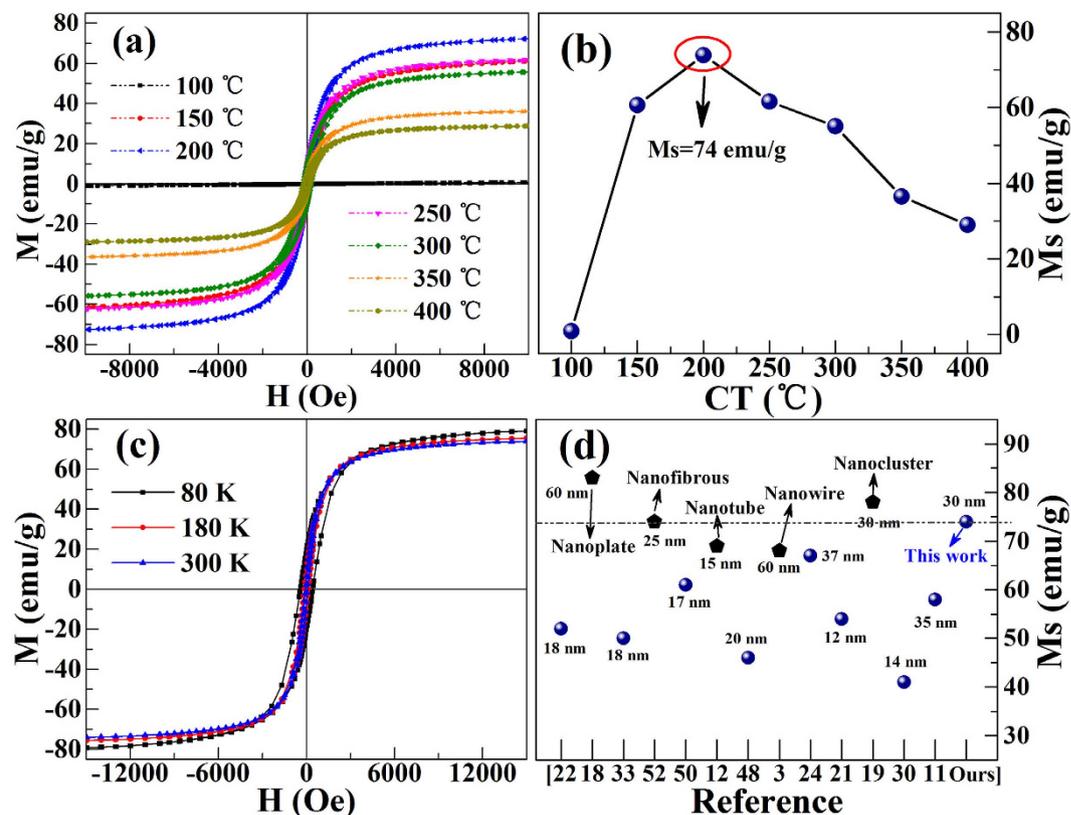


Figure 7. (a,b) Room temperature M - H loops for γ - Fe_2O_3 nano-particles and its corresponding M_s of different CT; (c) Temperature dependence of hysteresis loops measured at 80 K, 180 K, and 300 K of the pure γ - Fe_2O_3 nano-particles of 200 °C. (d) Comparisons of our work and other typical results of the particles size and M_s of γ - Fe_2O_3 nano-particles. The samples have been marked with circle (nano-particles) and pentagon (others), the values of the size represents the diameter of the samples.

SEM images and XRD spectra of 250~300 °C. As CT is further improved, more γ - Fe_2O_3 particles are transformed to α - Fe_2O_3 , and the morphologies and structures of samples are mainly composed of α - Fe_2O_3 particles (see SEM images and XRD spectra of 350~400 °C). Finally, when CT exceeds 500 °C, all γ - Fe_2O_3 is disappeared, and plenty of α - Fe_2O_3 nano-particles are achieved. The result can be confirmed by the previous phase transformation studies^{2,38,40}.

To sum up, combining all results of γ - Fe_2O_3 nano-granules, the detailed formation processes are discussed below. DMF is a commendable solvent when compared with water, and DMF is associated well with the cation^{41,42}. As a solvent, DMF could disperse the ions, and coats each ion during the calcination process. As shown in Figure S1–S2 of SI, α - Fe_2O_3 particles are produced in the water but it cannot generate in DMF under the same experiment condition (1 °C/min, 200 °C). This indicates DMF may slower the reaction process of calcination, which restrains the transformation process of γ - Fe_2O_3 to α - Fe_2O_3 . When CT or heating rates is increased, this restraint will be weakened.

Figure 3 shows SEM images of the samples of different CT. It can be seen that the morphologies change obviously with the increased CT. The sample of 100 °C (Fig. 3a) presents a number of disorderly bulk particles, and the shape of particles changes to compact and well-regulated nano-particles at 150 °C (Fig. 3b). Especially when CT is 200 °C (Fig. 3c), a large quantity of uniform nano-particles with the size about 60 nm are achieved. However, when CT is further improved (250~400 °C of Fig. 3d–g), the particles display an increased grain growth (Fig. 3d,e). The particle size becomes nonuniform, and strong piece of reunited particles are observed with the improvement of CT (Fig. 3f,g). These results are detailedly studied by the following techniques.

XRD data were used to determine the structural parameters of all the samples. Figure 4 shows XRD patterns of all the samples at different CT. It can be observed that when CT is 100 °C, the sample is not crystallized due to the slow evaporation of DMF. Thus, there are no peaks could be seen in XRD pattern. Afterwards, the diffraction spectra reveal the good single γ - Fe_2O_3 phases (150 °C and 200 °C) with the cubic crystal system (JCPDS#39-1346), and all the diffraction peaks can be well indexed. It can be confirmed that the particles are γ - Fe_2O_3 rather than α - Fe_2O_3 , due to the different XRD pattern of α - Fe_2O_3 (JCPDS#80-2377) and γ - Fe_2O_3 ^{17,19}. The average crystalline size estimated from Scherrer analysis is about 36 nm (150 °C) and 32 nm (200 °C) for γ - Fe_2O_3 . In addition, the peak intensity of γ - Fe_2O_3 calcined at 200 °C is stronger than that of 150 °C, which indicates that the nano-particles present higher crystallization at 200 °C. However, the samples display α - Fe_2O_3 phases when CT exceeds to 250 °C. The emergence of additional impurity phase, i.e., α - Fe_2O_3 , is more obvious with the enhanced temperature (300~400 °C). These XRD results indicate that the oxide of iron cannot be formed when CT is 100 °C.

| Method or process | Solvent or Additive or surfactant | pH | Main reaction conditions | Centrifugation or wash | Others | Particle size (nm) | M_n (emu/g) |
|---|---|-------|--|------------------------|--|--------------------|---------------|
| solvothermal ³⁰ | water, H ₂ O ₂ , D-(+)-C ₆ H ₁₂ O ₆ , C ₆ H ₁₂ O ₆ , oleic acid | / | 400 °C, 0.5 h | ethanol | Need ultrasound, dried using H ₂ O ₂ | ~12 | 26–42 |
| wet chemical method ³² | HCl, water, TEOS ethanol, ammonia aqueous solution, | 9.7 | 2 h, 30 min, 60 min | DMF, ethanol, water | using water and ethanol dried at 70 °C | 17–29 | / |
| high-temperature solution reaction ¹ | diphenylether, 1,2-hexadecanediol, oleic acid, oleylamine | / | Ar flow all time, 200 °C 30 min, 265 °C 30 min | ethanol | Need Ar | 6.4 | / |
| sole-gel ²⁷ | PVP, vinyl alcohol, saturated metal nitrate | / | 150 °C, 2 h, 400 °C, 4 h | / | thermal degradation | 30–50 | / |
| microemulsions ²³ | octyl ether, oleic acid, (CH ₃) ₃ NO, ethanol | / | 100 °C, 1 h, 130 °C, 2 h, reflux 1 h | ethanol | Need Ar | 4–16 | / |
| Massart's method ²⁸ | NaOH, HNO ₃ , FeNO ₃ | / | 450–1200 °C, 30 min | acetone | / | 4 | / |
| thermal decomposition ²⁴ | Ethanol, CTAB, CON ₂ H ₄ | / | 2.5 h, 200 °C 1 h | ethanol | Dried at 45 °C | 28–37 | 8–67 |
| wet chemical method ³² | HCl, water, TEOS ethanol, ammonia aqueous solution, | 9.7 | 2 h, 30 min, 60 min | DMF, ethanol, water | Dried at 70 °C using water and ethanol | 17–29 | / |
| coprecipitation ¹² | Water, ammonium hydroxide, urea, CTAB | 10–11 | 2–3 h, 70 °C | water | Need vacuum, 120 °C | 10 | 69.8 |
| aerosol pyrolysis ²⁶ | Water, oxalic acid, ammonia aqueous solution, KIO ₃ | / | ~300 °C, ~500 °C | water | Need nitrogen | 50–120 | / |
| combustion method ⁷ | glycine, ammonium nitrate, starch, polyethylene glycol | / | 400 °C 2 h | / | Complex collection process | 45–55 | / |
| chemical reaction ⁶ | ethanol, water, hexane, 1-octadecene, oleic acid, sodium oleate | / | 70 °C, 4 h | water, ethanol | Dried 320 °C, 0.5 h | 5–22 | / |
| sonochemical route ³³ | Decahydronaphthalene, pentane | / | 300 °C, 400 °C, 450 °C, 3 h | Yes | Ultrasonic 2 h, need vacuum | / | 50 |
| ultrasonic decomposition ³⁴ | anhydrous decane, pentane | / | room temperature, sonicate for 3 h | / | Dried under vacuum 300 °C, 3 h | 25 | 38–55 |
| hydrothermal ²² | Water, MOE, acetylacetone, | Yes | 140 °C, 4 h | acetone | Dried overnight under N ₂ | 12–26 | 53–73 |
| hydrosol chemical reaction ²⁰ | Water, HCl, NaOH | 11–12 | Papered Fe ₃ O ₄ then Fe ₃ O ₄ was oxidated for 30 min at about 100 °C | water, HCl | Complex reaction process | 20–50 | / |
| This work | DMF | No | 200 °C, 2 h | No | No | ~30 | 74 |

Table 1. Compare the typical methods or processes with ours. These methods or processes are not confined to the literatures we list.

When CT is increased to 150–200 °C, γ -Fe₂O₃ nano-particles can be achieved, and α -form is observed as CT exceeds 250 °C. It is well-known that γ -Fe₂O₃ can be further transformed into α -Fe₂O₃ at higher temperature^{33,40}, and the phase transformation temperature in our research (250 °C) is similar to the previous literature^{2,40,43}.

In order to distinguish the chemical composition of γ -Fe₂O₃ as opposed to Fe₃O₄, XPS measurement of pure γ -Fe₂O₃ nano-particles is further performed, which is displayed in Fig. 5. The full scanned XPS spectra of γ -Fe₂O₃ sample of 200 °C in the range of 0–1200 eV were shown in Fig. 5(a). Except for Fe 2p, O 1s, and C 1s peaks in the spectra, no redundant peaks appear together in γ -Fe₂O₃ nano-particles, and C element belongs to the carbon contaminants adsorbed on the surface of the tested samples. In particular, Fe 2p_{3/2} spectra (Fig. 5b) exhibit two peaks at 710.6 and 724.1 eV, which are the characteristic peaks of the 3+ ion of γ -Fe₂O₃^{3,19}, and there is no signal or shoulder at smaller binding energies as would be expected for the presence of the Fe²⁺ ion (~708 eV)^{44,45}. Furthermore, an additional peak at about 718.7 eV is the shakeup satellite peak, which also indicates the absence of the Fe²⁺ ion^{3,44}. XPS results are consistent with the judgment of XRD spectra.

As a representative, the morphology and structure of the pure γ -Fe₂O₃ nano-particles (200 °C) are further characterized by TEM. As shown in the Fig. 6(a,b), the results indicate large and black areas of near-spherical γ -Fe₂O₃ nano-particles, and the granules present a low dispersity, which may be due to the reuniting of the nano-particles. HRTEM characterizations show the lattice fringes of the obtained ferrites, and the interfringe distance shown in Fig. 6(d,e) are 0.252 nm and 0.295 nm, which are correspond well to {311} and {220} planar spaces of γ -Fe₂O₃ nano-particles, respectively. Both the lattice fringes and SAED (Fig. 6c) clearly presents a group of atomic planes within each particle, revealing the highly crystalline nature of these nano-particles. Meanwhile, Fig. 6(f) gives EDX data of γ -Fe₂O₃ nano-particles, and the appearance of Cu peaks results from copper net used in the experiment. The element ratio of Fe:O is calculated to be 17.9:30.8, which is very close to the stoichiometry of γ -Fe₂O₃, which further confirms that the composition and structure are coincident with the chemical formulation of γ -Fe₂O₃. The particle size distributions, obtained from TEM micrographs, are shown in Fig. 6(g), and the histograms show that the samples display uniform particle distributions. The mean particle sizes obtained from the Gaussian fit of the histograms are 27 ± 2 nm, which is comparable with XRD line width results. However, size distributions obtained from SEM are larger than that of TEM, which may be due to the superimposed crystal or the compact arrangement of particles, and the shadow or astigmatism of the nano-particles could also cause the measurement error⁴⁶. Some reports⁴⁷ also show a relatively large particle size distribution.

On the base of good understanding of the microstructure and chemical phase of nano-particles, the room temperature magnetic performance of products is discussed below. As shown in Fig. 7(a), the non-crystalline sample (100 °C) has no magnetism. When CT is 150 °C, i.e. γ -Fe₂O₃ appears, the nano-particles emerge strong magnetism immediately, and the saturation magnetization (M_s) is about 61 emu/g. Particularly, when CT reaches to 200 °C, M_s increases to 74 emu/g, which is comparable with bulk γ -Fe₂O₃ sample ($M_s = 76$ emu/g)^{34,48,49} but larger than other γ -Fe₂O₃ nanoparticles^{11,30,33,50}. The higher values of M_s are due to the better crystals of the nano-particles, consistent with both the XRD and HRTEM data. A recent work also shows that the higher crystallinity is benefited to enhanced M_s of the sample⁵¹. Typical comparative results of variable quantity of M_s are shown in Fig. 7(d). It can be seen M_s of this work is higher than other nanoparticles, but less when compared with nanoplate and nanocluster. However, when CT exceeds 250 °C, M_s is decreased monotonously. That is because that the presence of non-magnetic α -Fe₂O₃ leads to the relative reduction of magnetic γ -Fe₂O₃, and the magnetic moments total quality drop. When CT is further increased to 250–400 °C, the impurity α -Fe₂O₃ appears more obviously (which can be confirmed by XRD results), and M_s is reduced gradually. Furthermore, low temperature hysteresis loops of γ -Fe₂O₃ (200 °C) have also been carried out at 80 K, 180 K, and 300 K, which are shown in Fig. 7(c). The low temperature is realized by the liquid nitrogen. As expected, M_s and coercivity are also enhanced at low temperature. It is well-known that the coercivity and M_s will increase when the temperature decreases^{34,50}.

The degradation of methylene blue (MB) was performed as a model reaction to investigate the photocatalytic activity of the sample, which was shown in Figure S3. The results reveal that γ -Fe₂O₃ has a little adsorption ability of MB with proper photocatalytic activity, which can degrade 16% MB dye in 60 min under UV irradiation. The photocatalytic activity of this work is comparable with the previous report⁵². As a result, the results provide the fabrication of Fe-based nanocomposites as proper performance photocatalysts, and high magnetization of γ -Fe₂O₃ also has potential in addressing environmental protection issues. The Brunauer-Emmett-Teller (BET) surface areas of γ -Fe₂O₃ nano-particles were measured to be 24.8 m²/g, which is smaller than the mesoporous nano-particles^{24,29,30}. This suggests that the content of mesopores in the sample is considerably low. BJH average pore diameters calculated from the adsorption branch of the isotherms is 4.7 nm for the γ -Fe₂O₃ nano-particles, and the corresponding total pore volume is 0.04 cm³/g.

Various above investigations have demonstrated that a number of uniform and smooth γ -Fe₂O₃ nano-particles are obtained using calcination process in the air. Significantly, some typical methods or processes as the comparative results are discussed, and the comparative data are presented in Table 1. Except for the iron source of the preparing process, Table 1 detailedly shows the experiment parameters of solvent, additive or surfactant, pH, reaction time, centrifugation, and other parts of various methods. These methods or processes are not limited to the literatures we provided. As a result, although the dispersity and size of nano-particles in our research are not good with some of the previous reports, this technique only needs one solvent during the preparing process, and other additional processes are omitted. The method realizes a simple, rapid and convenient route for assembling γ -Fe₂O₃ nano-particles when compared with others.

Conclusions

We reported a unified approach for the synthesis of γ -Fe₂O₃ nano-particles via a facile and novel calcination process in the air. The process is no pH regulation, gas atmosphere, additive, centrifugation or other procedure during the experiment. The obtained pure γ -Fe₂O₃ nano-particles at 200 °C display good uniformity, and α -Fe₂O₃ will be observed when CT exceeds 250 °C. As a result, DMF is a commendable solvent when compared with water, which could well disperse the ions, and coats each ion during the calcination process. DMF may slower the reaction process of calcination, which restrains the transformation process of γ -Fe₂O₃ to α -Fe₂O₃. The saturation magnetization pure γ -Fe₂O₃ is about 74 emu/g, which is comparable with bulk material. In addition, the photocatalytic activity of the obtained nano-particles for the degradation of methylene blue shows proper photocatalytic properties.

References

- Capone, S. *et al.* Fe₃O₄/ γ -Fe₂O₃ Nanoparticle Multilayers Deposited by the Langmuir-Blodgett Technique for Gas Sensors Application. *Langmuir* **30**, 1190–1197 (2014).
- Vichery, C., Maurin, I., Bonville, P., Boilot, J.-P. & Gacoin, T. Influence of Protected Annealing on the Magnetic Properties of γ -Fe₂O₃ Nanoparticles. *J. Phys. Chem. C* **116**, 16311–16318 (2012).
- Rao, P. M. & Zheng, X. Unique Magnetic Properties of Single Crystal γ -Fe₂O₃ Nanowires Synthesized by Flame Vapor Deposition. *Nano Lett.* **11**, 2390–2395 (2011).
- Zhu, H.-Y., Jiang, R., Xiao, L. & Li, W. A novel magnetically separable gamma-Fe₂O₃/crosslinked chitosan adsorbent: Preparation, characterization and adsorption application for removal of hazardous azo dye. *J. Hazard. Mater.* **179**, 251–257 (2010).
- Kostiainen, M. A. *et al.* Hierarchical Self-Assembly and Optical Disassembly for Controlled Switching of Magnetoferritin Nanoparticle Magnetism. *ACS Nano* **5**, 6394–6402 (2011).
- Park, J. *et al.* Ultra-large-scale syntheses of monodisperse nanocrystals. *Nat. Mater.* **3**, 891–895 (2004).
- Apte, S., Naik, S., Sonawane, R., Kale, B. & Baeg, J. Synthesis of Nanosize-Necked Structure α - and γ -Fe₂O₃ and its Photocatalytic Activity. *J. Am. Ceram. Soc.* **90**, 412–414 (2007).
- Nemati, Z., Alonso, J., Khurshid, H., Phan, M. H. & Srikanth, H. Core/shell iron/iron oxide nanoparticles: are they promising for magnetic hyperthermia? *RSC Adv.* **6**, 38697–38702 (2016).
- Tseng, P., Judy, J. W. & Di Carlo, D. Magnetic nanoparticle-mediated massively parallel mechanical modulation of single-cell behavior. *Nat. Meth.* **9**, 1113–1119 (2012).
- Zywietz, U., Evlyukhin, A. B., Reinhardt, C. & Chichkov, B. N. Laser printing of silicon nanoparticles with resonant optical electric and magnetic responses. *Nat. Commun.* **5**, 1–7 (2014).
- Lu, J., Jiao, X., Chen, D. & Li, W. Solvothermal Synthesis and Characterization of Fe₃O₄ and γ -Fe₂O₃ Nanoplates. *J. Phys. Chem. C* **113**, 4012–4017 (2009).
- Singh, K., Ohlan, A., Kotnala, R. K., Bakhshi, A. K. & Dhawan, S. K. Dielectric and magnetic properties of conducting ferromagnetic composite of polyaniline with gamma-Fe₂O₃ nanoparticles. *Mater. Chem. Phys.* **112**, 651–658 (2008).

13. Hu, J. S., Zhong, L. S., Song, W. G. & Wan, L. J. Synthesis of hierarchically structured metal oxides and their application in heavy metal ion removal. *Adv. Mater.* **20**, 2977–2982 (2008).
14. Wang, C. *et al.* Magnetic (γ -Fe₂O₃@SiO₂)_n/TiO₂ Functional Hybrid Nanoparticles with Activated Photocatalytic Ability. *J. Phys. Chem. C* **113**, 4008–4011 (2009).
15. Zhou, W. *et al.* Mesoporous TiO₂/ α -Fe₂O₃: Bifunctional Composites for Effective Elimination of Arsenite Contamination through Simultaneous Photocatalytic Oxidation and Adsorption. *J. Phys. Chem. C* **112**, 19584–19589 (2008).
16. Achouri, F. *et al.* Aqueous synthesis and enhanced photocatalytic activity of ZnO/Fe₂O₃ heterostructures. *J. Phys. Chem. Solids* **75**, 1081–1087 (2014).
17. Zhong, L. S. *et al.* Self-Assembled 3D flowerlike iron oxide nanostructures and their application in water treatment. *Adv. Mater.* **18**, 2426–2431 (2006).
18. Ni, Y., Ge, X., Zhang, Z. & Ye, Q. Fabrication and Characterization of the Plate-Shaped γ -Fe₂O₃ Nanocrystals. *Chem. Mater.* **14**, 1048–1052 (2002).
19. Zhang, Y. *et al.* Two-in-One Strategy for Effective Enrichment of Phosphopeptides Using Magnetic Mesoporous γ -Fe₂O₃ Nanocrystal Clusters. *ACS Appl. Mater. Interfaces* **5**, 614–621 (2013).
20. Kang, Y. S., Risbud, S., Rabolt, J. F. & Stroeve, P. Synthesis and characterization of nanometer-size Fe₃O₄ and gamma-Fe₂O₃ particles. *Chem. Mater.* **8**, 2209–2211 (1996).
21. Lin, S., Lu, D. & Liu, Z. Removal of arsenic contaminants with magnetic γ -Fe₂O₃ nanoparticles. *Chem. Eng. J* **211–212**, 46–52 (2012).
22. Chen, D. & Xu, R. Hydrothermal Synthesis and Characterization of Nanocrystalline γ -Fe₂O₃ Particles. *J. Solid State Chem.* **137**, 185–190 (1998).
23. Hyeon, T., Lee, S. S., Park, J., Chung, Y. & Na, H. B. Synthesis of highly crystalline and monodisperse maghemite nanocrystallites without a size-selection process. *J. Am. Chem. Soc.* **123**, 12798–12801 (2001).
24. Asuha, S., Zhao, Y. M., Zhao, S. & Deligeer, W. Synthesis of mesoporous maghemite with high surface area and its adsorptive properties. *Solid State Sci.* **14**, 833–839 (2012).
25. Asuha, S., Zhao, S., Wu, H. Y., Song, L. & Tegus, O. One step synthesis of maghemite nanoparticles by direct thermal decomposition of Fe-urea complex and their properties. *J. Alloys Compd.* **472**, L23–L25 (2009).
26. Basak, S., Rane, K. S. & Biswas, P. Hydrazine-Assisted, Low-Temperature Aerosol Pyrolysis Method to Synthesize γ -Fe₂O₃. *Chem. Mater.* **20**, 4906–4914 (2008).
27. Silva, M. F. *et al.* Optimization of maghemite-loaded PLGA nanospheres for biomedical applications. *Eur. J. Pharm. Sci.* **49**, 343–351 (2013).
28. El Mendili, Y., Bardeau, J.-F., Randrianantoandro, N., Grasset, F. & Greneche, J.-M. Insights into the Mechanism Related to the Phase Transition from gamma-Fe₂O₃ to alpha-Fe₂O₃ Nanoparticles Induced by Thermal Treatment and Laser Irradiation. *J. Phys. Chem. C* **116**, 23785–23792 (2012).
29. Xu, J.-S. & Zhu, Y.-J. Monodisperse Fe₃O₄ and γ -Fe₂O₃ magnetic mesoporous microspheres as anode materials for lithium-ion batteries. *ACS Appl. Mater. Interfaces* **4**, 4752–4757 (2012).
30. Ianos, R., Taculescu, E.-A., Pacurariu, C. & Niznansky, D. gamma-Fe₂O₃ nanoparticles prepared by combustion synthesis, followed by chemical oxidation of residual carbon with H₂O₂. *Mater. Chem. Phys.* **148**, 705–711 (2014).
31. Pour, Z. S. & Ghaemy, M. Fabrication and characterization of superparamagnetic nanocomposites based on epoxy resin and surface-modified gamma-Fe₂O₃ by epoxide functionalization. *J. Mater. Sci.* **49**, 4191–4201 (2014).
32. Darezreshki, E., Ranjbar, M. & Bakhtiari, F. One-step synthesis of maghemite (γ -Fe₂O₃) nano-particles by wet chemical method. *J. Alloys Compd.* **502**, 257–260 (2010).
33. Lai, J. *et al.* Doping γ -Fe₂O₃ Nanoparticles with Mn(III) Suppresses the Transition to the α -Fe₂O₃ Structure. *J. Am. Chem. Soc.* **125**, 11470–11471 (2003).
34. Shafi, K. V. P. M. *et al.* Magnetic Enhancement of γ -Fe₂O₃ Nanoparticles by Sonochemical Coating. *Chem. Mater.* **14**, 1778–1787 (2002).
35. Boal, A. K., Das, K., Gray, M. & Rotello, V. M. Monolayer Exchange Chemistry of γ -Fe₂O₃ Nanoparticles. *Chem. Mater.* **14**, 2628–2636 (2002).
36. Andersen, H. L., Jensen, K. M., Tyrsted, C., Bøjesen, E. D. & Christensen, M. Size and Size Distribution Control of γ -Fe₂O₃ Nanocrystallites: An *in situ* Study. *Cryst. Growth Des.* **14**, 1307–1313 (2014).
37. Sakurai, S., Namai, A., Hashimoto, K. & Ohkoshi, S.-i. First Observation of Phase Transformation of All Four Fe₂O₃ Phases (gamma \rightarrow epsilon \rightarrow beta \rightarrow alpha-Phase). *J. Am. Chem. Soc.* **131**, 18299–18303 (2009).
38. Laurent, S. *et al.* Magnetic iron oxide nanoparticles: synthesis, stabilization, vectorization, physicochemical characterizations, and biological applications. *Chem. Rev.* **108**, 2064–2110 (2008).
39. Synek, P. *et al.* Plasmachemical synthesis of maghemite nanoparticles in atmospheric pressure microwave torch. *Mater. Lett.* **65**, 982–984 (2011).
40. Yen, F. S., Chen, W. C., Yang, J. M. & Hong, C. T. Crystallite Size Variations of Nanosized Fe₂O₃ Powders during γ - to α -Phase Transformation. *Nano Lett.* **2**, 245–252 (2002).
41. Pastoriza-Santos, I. & Liz-Marzán, L. M. N,N-Dimethylformamide as a Reaction Medium for Metal Nanoparticle Synthesis. *Adv. Funct. Mater.* **19**, 679–688 (2009).
42. Muzart, J. N. N-Dimethylformamide: much more than a solvent. *Tetrahedron* **65**, 8313–8323 (2009).
43. Gallagher, K. Mechanism of oxidation of magnetite to gamma-Fe₂O₃. *Nature* **217**, 1118–1121 (1968).
44. Fujii, T. *et al.* *In situ* XPS analysis of various iron oxide films grown by NO₂-assisted molecular-beam epitaxy. *Phys. Rev. B* **59**, 3195–3202 (2001).
45. Gao, Y. & Chambers, S. A. Heteroepitaxial growth of alpha-Fe₂O₃, gamma-Fe₂O₃ and Fe₃O₄ thin films by oxygen-plasma-assisted molecular beam epitaxy. *J. Cryst. Growth* **174**, 446–454 (1997).
46. Sadhu, A. & Bhattacharyya, S. Enhanced Low-Field Magnetoresistance in La_{0.7}ISr_{0.29}MnO₃ Nanoparticles Synthesized by the Nonaqueous Sol-Gel Route. *Chem. Mater.* **26**, 1702–1710 (2014).
47. Guo, P. *et al.* Facile Synthesis of ZnFe₂O₄ Nanoparticles with Tunable Magnetic and Sensing Properties. *Langmuir* **29**, 8997–9003 (2013).
48. Wang, J., Ma, Y. & Watanabe, K. Magnetic-Field-Induced Synthesis of Magnetic γ -Fe₂O₃ Nanotubes. *Chem. Mater.* **20**, 20–22 (2008).
49. Berkowitz, A. E., Schuele, W. J. & Flanders, P. J. Influence of Crystallite Size on the Magnetic Properties of Acicular γ -Fe₂O₃ Particles. *J. Appl. Phys.* **39**, 1261–1263 (1968).
50. Park, K. *et al.* Structural and Magnetic Properties of Gold and Silica Doubly Coated γ -Fe₂O₃ Nanoparticles. *J. Phys. Chem. C* **111**, 18512–18519 (2007).
51. Das, R. *et al.* Tunable High Aspect Ratio Iron Oxide Nanorods for Enhanced Hyperthermia. *J. Phys. Chem. C* **120**, 10086–10093 (2016).
52. Chen, F. & Zhao, J. Preparation and photocatalytic properties of a novel kind of loaded photocatalyst of TiO₂/SiO₂/ γ -Fe₂O₃. *Catal. Lett.* **58**, 246–247 (1999).

Acknowledgements

This work is supported by National Basic Research Program of China (Grant No. 2012CB933101), National Science Fund of China (11574121, 51371092), PCSIRT (Grant No. IRT1251).

Author Contributions

The manuscript was written through contributions of all authors. D.C. prepared the samples and wrote the main manuscript text; D.C., H.L., L.P., P.J., J.L., X.W. and X.C. processed data; D.C., H.L., J.W. and Q.L. discussed the synthesis mechanism and magnetic properties of samples. All authors reviewed the manuscript.

Additional Information

Supplementary information accompanies this paper at <http://www.nature.com/srep>

Competing financial interests: The authors declare no competing financial interests.

How to cite this article: Cao, D. *et al.* High saturation magnetization of γ -Fe₂O₃ nano-particles by a facile one-step synthesis approach. *Sci. Rep.* **6**, 32360; doi: 10.1038/srep32360 (2016).



This work is licensed under a Creative Commons Attribution 4.0 International License. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in the credit line; if the material is not included under the Creative Commons license, users will need to obtain permission from the license holder to reproduce the material. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>

© The Author(s) 2016