

# SCIENTIFIC REPORTS



OPEN

## Facile Synthesis of Layer Structured GeP<sub>3</sub>/C with Stable Chemical Bonding for Enhanced Lithium-Ion Storage

Wen Qi<sup>1</sup>, Haihua Zhao<sup>1,2</sup>, Ying Wu<sup>1</sup>, Hong Zeng<sup>1</sup>, Tao Tao<sup>3</sup>, Chao Chen<sup>3</sup>, Chunjiang Kuang<sup>1</sup>, Shaoxiong Zhou<sup>1</sup> & Yunhui Huang<sup>2</sup>

Received: 27 October 2016

Accepted: 24 January 2017


Published: 27 February 2017

Recently, metal phosphides have been investigated as potential anode materials because of higher specific capacity compared with those of carbonaceous materials. However, the rapid capacity fade upon cycling leads to poor durability and short cycle life, which cannot meet the need of lithium-ion batteries with high energy density. Herein, we report a layer-structured GeP<sub>3</sub>/C nanocomposite anode material with high performance prepared by a facial and large-scale ball milling method *via in-situ* mechanical reaction. The P-O-C bonds are formed in the composite, leading to close contact between GeP<sub>3</sub> and carbon. As a result, the GeP<sub>3</sub>/C anode displays excellent lithium storage performance with a high reversible capacity up to 1109 mA h g<sup>-1</sup> after 130 cycles at a current density of 0.1 A g<sup>-1</sup>. Even at high current densities of 2 and 5 A g<sup>-1</sup>, the reversible capacities are still as high as 590 and 425 mA h g<sup>-1</sup>, respectively. This suggests that the GeP<sub>3</sub>/C composite is promising to achieve high-energy lithium-ion batteries and the mechanical milling is an efficient method to fabricate such composite electrode materials especially for large-scale application.

Li-ion batteries (LIBs) have been extensively used to power portable electronics and electric vehicles because of high energy density and long cycle life. In order to meet the need for LIBs with high energy and low cost, it is essential to develop large-capacity electrodes made from nontoxic, low cost, and abundant materials<sup>1–9</sup>. Group IVA elements (Si, Ge, Sn etc.) based alloys with high theoretical capacities have been reported as potential anode materials. Recently, Ge has attracted more and more attention due to large gravimetric capacity (1624 mA h g<sup>-1</sup>), good lithium diffusion, high electrical conductivity and great oxidation resistance<sup>10–18</sup>. However, Ge suffers dramatic volumetric change (270%) during Li alloying/de-alloying process, which leads to the pulverization of particles, destabilization of solid electrolyte interphase (SEI) films and hence poor cyclability<sup>19–21</sup>.

To overcome the fast capacity fade of Ge, various Ge-based alloys have been designed. For example, inactive metal was used as host matrix to accommodate the large volumetric change<sup>12,22,23</sup>. In addition, nanocrystallization is an effective strategy for Ge-based alloys to avoid the pulverization during cycling, such as fabricating tailored morphology<sup>10,18,19</sup>, hollow structure<sup>14,15,17</sup>, nanoparticles<sup>24</sup> and carbon-based composites<sup>25</sup>. Several recent studies have illustrated that phosphorus could serve as volume buffer material in metal phosphides and exhibit improved lithium ion storage and sodium ion storage during alloy process<sup>26–34</sup>. Cui's<sup>35</sup> and Wang's groups<sup>36,37</sup> found stable P-C and P-O-C bonding in the phosphorus-based composites and obtained high capacity and excellent rate capability even after extended cycles. Manthiram *et al.* embedded CuP<sub>2</sub> nanoparticles into the carbon matrix to get improved electrochemical performance<sup>30</sup>. It is suggested that the formed stable P-O-C can increase the contact between active materials, accommodate large volume change and preserve mechanical integrity during cycling. Zhou *et al.* reported that GeP<sub>5</sub>/C exhibited a specific capacity as high as 2300 mA h g<sup>-1</sup> that could be maintained to 40 cycles<sup>38</sup>. However, the long-term cycling stability caused by the huge volume expansion and

<sup>1</sup>Beijing Key Laboratory of Energy Nanomaterials, Advanced Technology & Materials Co., Ltd, China Iron & steel Research Institute Group, Beijing 100081, P.R. China. <sup>2</sup>State Key Laboratory of Material Processing and Die & Mould Technology, School of Materials Science and Engineering, Huazhong University of Science and Technology, Wuhan, Hubei 430074, P.R. China. <sup>3</sup>School of Materials and Energy, Guangdong University of Technology, Guangzhou, 510006, P.R. China. Correspondence and requests for materials should be addressed to S.X.Z. (email: sxzhou@atmcn.com) or Y.H.H. (email: huangyh@mail.hust.edu.cn)

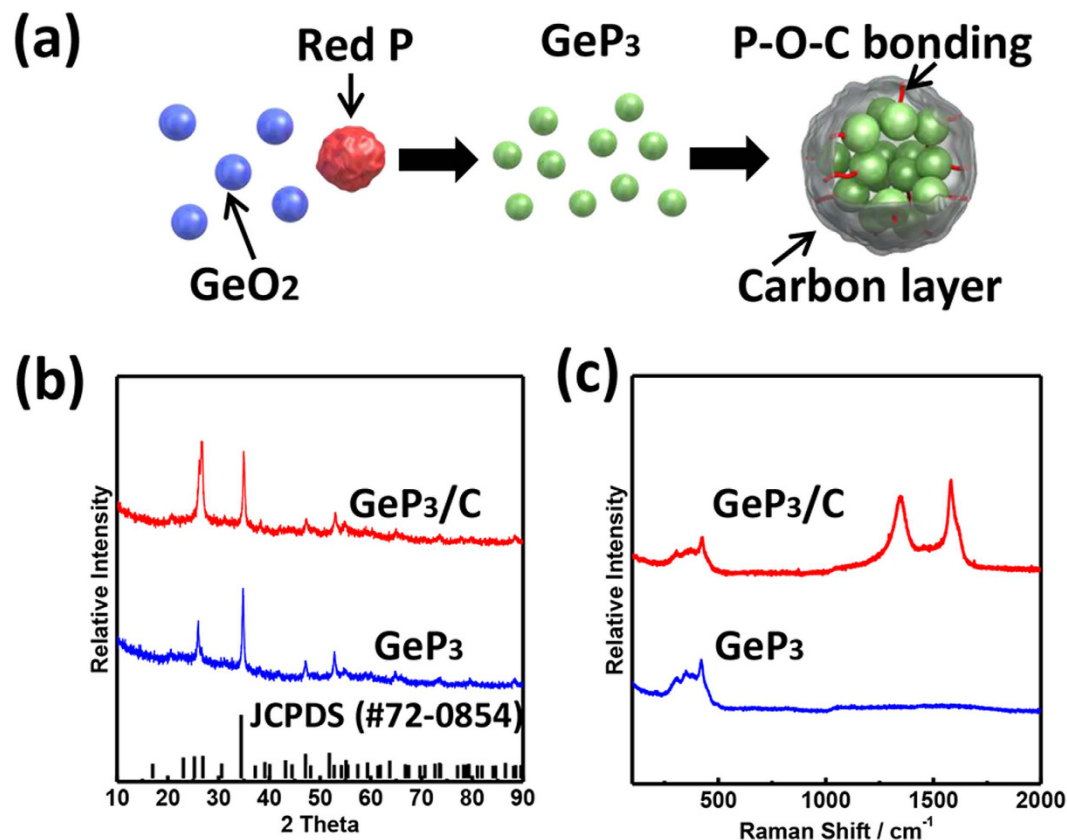

**Figure 1.** Synthesis and characterization of  $\text{GeP}_3/\text{C}$ : (a) schematic illustration of ball milling process from red P,  $\text{GeO}_2$  and carbon; (b) XRD patterns of  $\text{GeP}_3$  and  $\text{GeP}_3/\text{C}$ ; (c) Raman spectra of  $\text{GeP}_3$  and  $\text{GeP}_3/\text{C}$ .

poor interaction during cycling is still a challenge for practical application. Although the nanostructured materials have been investigated to significantly improve electrochemical performances for high capacity anode, it is still limited for commercial applications due to the complex synthesis procedures<sup>9</sup>. The facile synthesis of nanomaterials is needed to reduce the cost for large-scale application.

Here, we develop a simple and large scale method to prepare nanostructured  $\text{GeP}_3/\text{C}$  composite in which layer structured  $\text{GeP}_3$  nanoparticles are *in-situ* formed and embedded by carbon layer. The carbon not only works as conducting matrix but also facilitates to form stable P-O-C bonding with  $\text{GeP}_3$  to accommodate the volume change. The as-obtained  $\text{GeP}_3/\text{C}$  composite exhibits a high reversible capacity of  $1109 \text{ mA h g}^{-1}$ , good cyclability with 86% retention over 130 cycles, and excellent rate capability, which could be promising as anode material for LIBs with high energy density.


## Results

The  $\text{GeP}_3/\text{C}$  composite was synthesized *via* HEMM method with  $\text{GeO}_2$  powder, red P and carbon as starting materials. The HEMM can not only provide enough energy to make the phase change *via* mechanical reaction, but also peel apart the layered materials by shear force. With HEMM, the red P reacts with  $\text{GeO}_2$  to form  $\text{GeP}_3$  phase, and the  $\text{GeP}_3$  particles are further turned to small ones. Meanwhile, carbon is coated onto  $\text{GeP}_3$  particles *via* ball milling to enhance the conductivity. Thus the nanostructured  $\text{GeP}_3/\text{C}$  composite is attained, as illustrated in Fig. 1a. The reaction can be expressed as below in which the extra oxygen is absorbed on the surface of  $\text{GeP}_3$ :



The phase purity and structure of  $\text{GeP}_3$  and  $\text{GeP}_3/\text{C}$  were checked by XRD and Raman spectra. After first-step ball milling, the diffractions are well indexed to pure  $\text{GeP}_3$  phase (JCPDS No. 72-0854) with rhombohedral crystal structure, which is similar to layer structured  $\text{GeP}_3$  with good conductivity<sup>38,39</sup>. After second-step ball milling together with carbon, the peak intensity at  $34^\circ$  corresponding to (202) plane for  $\text{GeP}_3$  decreases, indicative of further refinement of particles. For comparison, if we directly ball mill red P,  $\text{GeO}_2$  and carbon at same condition, only  $\text{GeO}_2$  diffraction peaks appear (see Supplementary Fig. S1), demonstrating that  $\text{GeP}_3$  phase cannot be formed by such one-step ball milling process. This is because carbon prevents  $\text{GeP}_3$  from reacting with  $\text{GeO}_2$ .

The structure of the composite was further detected by Raman spectra (Fig. 1c). The broad peak in the region of  $300\text{--}500 \text{ cm}^{-1}$  can be defined to  $\text{GeP}_3$ . After carbon coating, the typical D and G band are observed to indicate the disorder carbon caused by mechanical impact and shear force during the ball-milling process. Our previous studies<sup>40,41</sup> on the ball milled graphitic materials show that the higher intensity of D band (corresponding to the disordered C-C bond) would benefit the lithium storage. In this work, we prolonged ball milling time and

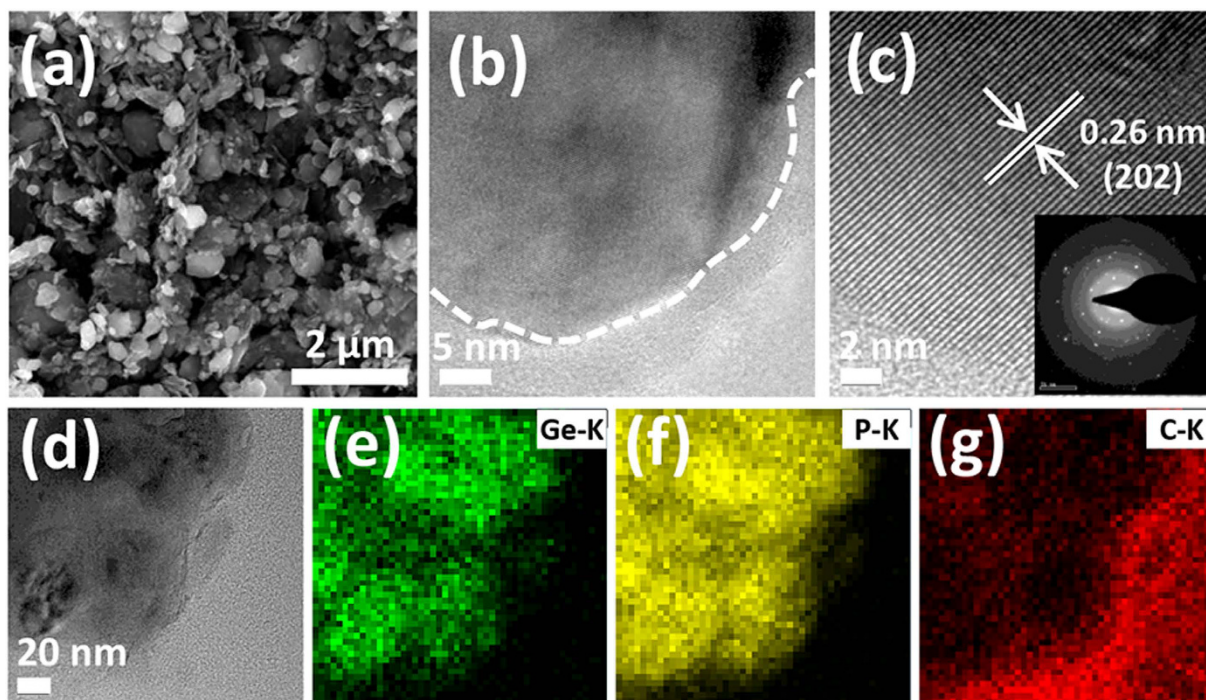


**Figure 2.** (a) SEM image of  $\text{GeP}_3/\text{C}$ ; (b) typical TEM image of  $\text{GeP}_3/\text{C}$ ; (c) HRTEM image of  $\text{GeP}_3/\text{C}$ , the inset is the selected area electron diffraction (SAED); (d–g) TEM image and corresponding elemental mappings of Ge, P and C.

obtained increased intensity of D band ( $I_D/I_G = 0.84$ ) in the  $\text{GeP}_3/\text{C}$  composite, demonstrating that the average size of the  $\text{sp}^2$  domains decreases because of the mechanical shear exfoliation of carbon in the HEMM.

Figure 2 shows the morphology of  $\text{GeP}_3/\text{C}$  composite. The average particle size is 200–300 nm (Fig. 2a), much smaller than those of starting red P,  $\text{GeO}_2$  and  $\text{GeP}_3$  particles (see Supplementary Figs S2–S4). To further confirm the actual composition of  $\text{GeP}_3$ , the EDS spectrum as well as results are presented in Fig. S4b. The molar ratio of Ge/P is 1:3.05, close to the designed composition. The HRTEM image and the selected area electron diffraction (SAED) (Fig. 2b,c) clearly show that  $\text{GeP}_3$  nanoparticles surrounded by carbon layers have a basal distance of 0.26 nm, which is consistent with the (202) lattice spacing of  $\text{GeP}_3$  phase (JCPDS 72-0854). The SAED in the inset of Fig. 2c reveals the well crystallized  $\text{GeP}_3$ . From the elemental mappings of  $\text{GeP}_3/\text{C}$  in Fig. 2d–f, we can see the overlapped Ge signal and P signal, which further confirms the formation of  $\text{GeP}_3$  phase. The carbon layer coated on the  $\text{GeP}_3$  surface can be clearly observed. We can also see that  $\text{GeP}_3$  nanoparticles are well dispersed in the carbon matrix, which can facilitate the transfer of electrons and ions. The carbon layer acts not only as conductive network to enhance the conductivity, but also as mechanical buffer to accommodate large volume change during cycling. In addition, the surface area of  $\text{GeP}_3$  is  $5.3 \text{ m}^2 \text{ g}^{-1}$ , while that of  $\text{GeP}_3/\text{C}$  is  $25.1 \text{ m}^2 \text{ g}^{-1}$  (see Supplementary Fig. S5), indicating that the surface area is greatly enhanced due to the carbon coating.



The interaction between carbon and  $\text{GeP}_3$  particles was further investigated by FT-IR and XPS. The ball milled red P can be transferred to black P<sup>37,42</sup>, which makes it easy to absorb oxygen to form P–O and P=O bond signalled by the IR peak at around  $1080$  and  $1200 \text{ cm}^{-1}$ , respectively. In the  $\text{GeP}_3/\text{C}$  composite, the P–O and P=O peaks almost disappear but the additional P–O–C peak located at  $1008 \text{ cm}^{-1}$  is detected, which may be due to the residual oxygen formed by reduction reaction between  $\text{GeO}_2$  and red phosphorus during the HEMM process (Fig. 3a)<sup>30,36,43</sup>. The high-resolution P 2p XPS spectrum in Fig. 3b can be used to examine the surface electronic state and the formation of P–O–C bond. The peaks at  $130.2$  and  $131.1 \text{ eV}$  are ascribed to  $2\text{P}_{3/2}$  and  $2\text{P}_{1/2}$ , respectively. The peak at  $134 \text{ eV}$  can be fitted into two peaks at  $133.6$  and  $134.6 \text{ eV}$ , corresponding to P–O–C and P–O bond<sup>30,44</sup>, agreeing well with the FT-IR observation. The P–O–C bond is expected to enable the carbon matrix to get strong chemical binding with the  $\text{GeP}_3$  particles, and hence to improve electrochemical reversibility and cycling stability for the  $\text{GeP}_3/\text{C}$  composite electrode.

The electrochemical performances of  $\text{GeP}_3/\text{C}$  composite are shown in Fig. 4. From the CV curves of  $\text{GeP}_3/\text{C}$  in Fig. 4a, we can see two clear sharp cathodic peaks at  $0.48$  and  $0.7 \text{ V}$  during the first lithiation step, corresponding to the formation of  $\text{Li}_x\text{P}$ <sup>35,36,38</sup>. The cathodic peak at  $\sim 0.2 \text{ V}$  is believed to indicate the further alloying of  $\text{Li}^+$  with Ge to form  $\text{Li}_x\text{Ge}$ . Two anodic peaks observed at  $0.4$  and  $1.1 \text{ V}$  are ascribed to the reversible reaction of  $\text{Li}_x\text{Ge}$  and  $\text{Li}_x\text{P}$ , respectively. For comparison, the CV curves of black P/C and  $\text{GeO}_2/\text{C}$  confirm the above reactions (see Supplementary Figs S6 and S7). The cathodic and anodic peaks below  $0.1 \text{ V}$  are correlated with the insertion and desorption of  $\text{Li}^+$  ions into the carbon layer<sup>41</sup>. In the second cycle, the two main cathodic peaks slightly shift to  $0.5$  and  $0.76 \text{ V}$  due to polarization and the structural change of  $\text{GeP}_3$  after the Li-ion insertion in the first cycle. In the subsequent cycles, both the peak current and the integral area are almost overlapped, demonstrating the high capacity reversibility and good stability of  $\text{GeP}_3/\text{C}$ .

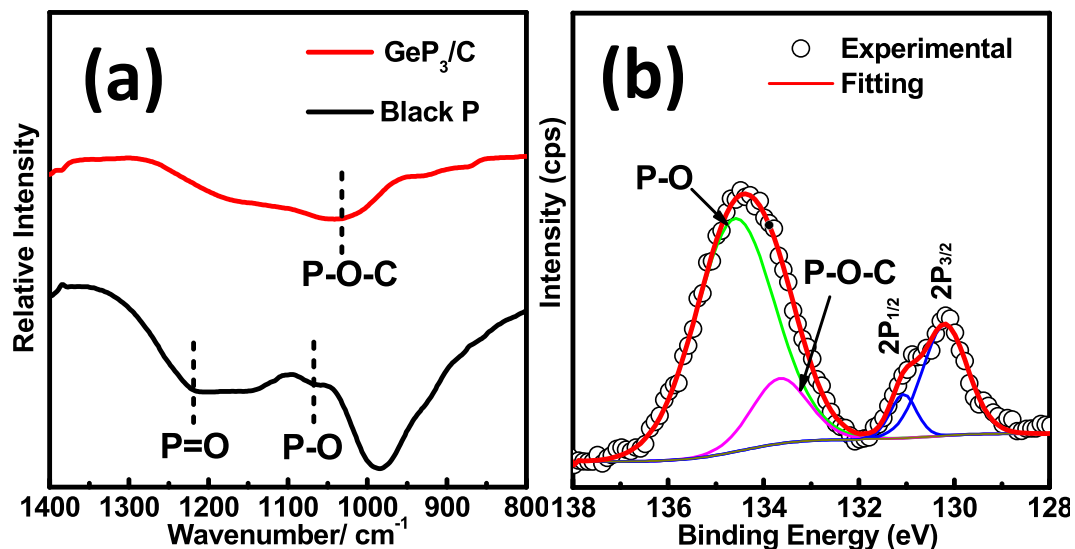

**Figure 3.** (a) FT-IR spectra of black P and  $\text{GeP}_3/\text{C}$ ; (b) high-resolution XPS P2p spectrum of  $\text{GeP}_3/\text{C}$ .

To further investigate the lithium storage mechanism of the  $\text{GeP}_3$  composite, the *ex-situ* XRD was performed after first discharge to the voltage of 0.01 V (Fig. 4b). The peaks can be well assigned to  $\text{Li}_3\text{P}$  and  $\text{Li}_{4.4}\text{Ge}^{38,45}$ . Combined with the CV curves and *ex-situ* XRD patterns, the lithium storage mechanism of  $\text{GeP}_3$  can be described as follows:




The calculated theoretical capacity of  $\text{GeP}_3$  is  $1581 \text{ mA h g}^{-1}$ , in which P atoms contribute  $1062 \text{ mA h g}^{-1}$  and Ge atoms contribute another  $519 \text{ mA h g}^{-1}$ . According to the TG curves (Fig. S8), the calculated carbon content in the composite is 25.4 wt.%, less than the designed one (30 wt.% carbon in the mixture), which can be ascribed to the partial carbonization during TG test. Therefore, the theoretical capacity of the  $\text{GeP}_3/\text{C}$  composite should be  $1218.3 \text{ mA h g}^{-1}$ , in which the contributions from  $\text{GeP}_3$  and carbon are 1106.7 and  $111.6 \text{ mA h g}^{-1}$ , respectively.

The charge/discharge profiles of the half cell with  $\text{GeP}_3/\text{C}$  composite as cathode from 1<sup>st</sup> cycle to 130<sup>th</sup> cycle are shown in Fig. 4c. The initial discharge and charge capacities are 1283 and  $948 \text{ mA h g}^{-1}$ , respectively. The initial coulombic efficiency is 73.8%, which is mainly ascribed to the formation of an SEI layer on the electrode surface. Fig. 4d,e show the cyclability and rate capability for  $\text{GeP}_3$  and  $\text{GeP}_3/\text{C}$ . For pure  $\text{GeP}_3$ , the capacity fades rapidly within several cycles, which is due to the large volume change that causes pulverization of the active material. Interestingly, the HEMM-derived  $\text{GeP}_3/\text{C}$  composite shows much better electrochemical performances. At a current density of  $0.1 \text{ A g}^{-1}$ , a reversible capacity as high as  $1109 \text{ mA h g}^{-1}$  is attained, and the capacity retention is about 86% over 130 cycles, which can be attributed to the nanostructured electrodes for the improved Li-ion accessibility upon cycling process<sup>41</sup>. Even at high current densities of 2 and  $5 \text{ A g}^{-1}$ , the  $\text{GeP}_3/\text{C}$  still exhibits specific capacities of 590 and  $425 \text{ mA h g}^{-1}$ , respectively. After running for 30 cycles at various current densities, the capacity of  $\text{GeP}_3/\text{C}$  can be recovered to  $900 \text{ mA h g}^{-1}$  and maintained well during another 70 cycles when the current is tuned back to  $0.1 \text{ A g}^{-1}$ , indicative of excellent rate capability and cyclability. The long-term cycling performance of  $\text{GeP}_3/\text{C}$  at high current density of  $1 \text{ A g}^{-1}$  was also tested. As seen in Fig. S9, it still delivers stable specific capacity of  $312 \text{ mA h g}^{-1}$  after 1000 cycles.

To verify the improved performance of  $\text{GeP}_3/\text{C}$  composite, EIS was used to compare  $\text{GeP}_3$  and  $\text{GeP}_3/\text{C}$ . The Nyquist plots of both samples before cycling measured within a frequency range of 1000 kHz to 0.001 Hz are shown in Fig. 4f. The SEI resistance ( $R_{\text{SEI}}$ ) and the charge transfer resistance ( $R_{\text{ct}}$ ) are simulated by EC-Lab software with an equivalent circuit model (see the inset of Fig. 4f) that is fitted well with experimental data. The diameter of the semicircle is a measure of the  $R_{\text{ct}}$ , which is related to the electrochemical reaction between the particles or between the electrode and the electrolyte. The diameter of the semi-circle for  $\text{GeP}_3/\text{C}$  is smaller than that of  $\text{GeP}_3$ , indicative of lower charge transfer resistance. In the low frequency region, the  $\text{GeP}_3/\text{C}$  electrode exhibits a shortened and more inclined line with a higher slope compared with  $\text{GeP}_3$  electrode, demonstrating that  $\text{GeP}_3/\text{C}$  exhibits faster  $\text{Li}^+$  diffusion. The results suggest that carbon coating *via* HEMM benefits the electron transformation between the electrode and the electrolyte.

Therefore, the excellent electrochemical performances of  $\text{GeP}_3/\text{C}$  can be explained by at least two reasons. On one hand, the carbon layer can provide good electron transportation and hence enhance the electronic contact between the active particles. On the other hand, the stable P-O-C bonding between active materials and carbon



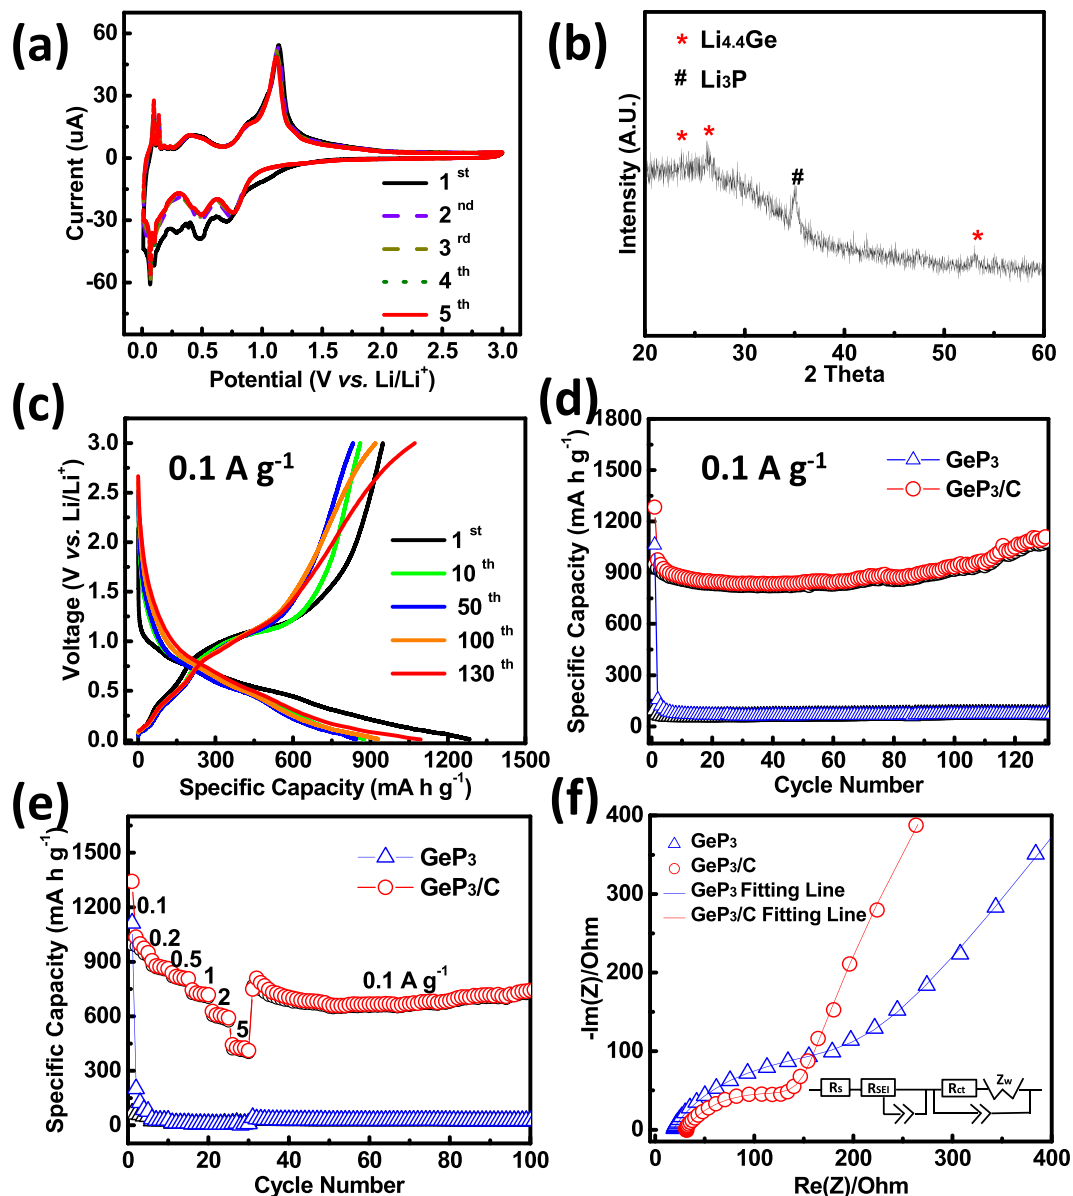

**Figure 4.** (a) CV curves of  $\text{GeP}_3/\text{C}$  obtained at a scan rate of  $0.01 \text{ mV s}^{-1}$ ; (b) *ex-situ* XRD pattern of  $\text{GeP}_3$  after 1<sup>st</sup> discharge at a current density of  $0.01 \text{ A g}^{-1}$ ; (c) selected charge/discharge curves of  $\text{GeP}_3/\text{C}$  at  $0.1 \text{ A g}^{-1}$ ; (d) cycling performance and (e) rate capability of  $\text{GeP}_3$  and  $\text{GeP}_3/\text{C}$  (the specific capacity is calculated based on the whole electrode); (f) EIS curves of  $\text{GeP}_3$  and  $\text{GeP}_3/\text{C}$  before cycling. The inset is the equivalent circuit model for the simulation.

matrix can alleviate the huge volumetric change upon  $\text{Li}^+$  interaction/extraction in  $\text{GeP}_3$ . The *ex-situ* SEM images of  $\text{GeP}_3/\text{C}$  electrode after 30 cycles at  $0.1 \text{ A g}^{-1}$  in Fig. S10 (see Supplementary) further confirm the stable microstructure of active materials during cycling. The top and cross sections of SEM images show smooth surface after cycling, suggesting the improved mechanical integrity of active materials. The TEM image along with elemental mappings after 30 cycles (see Supplementary Fig. S11) also indicate the structure stability over continuous expansion/contraction during cycling, in which P, Ge and C elements are uniformly distributed. This maintained morphology demonstrates the good conductive network and stable chemical bonding in  $\text{GeP}_3/\text{C}$ , which is responsible from another point of view for the excellent electrochemical performance.

In summary, nanostructured  $\text{GeP}_3/\text{C}$  composite has been designed and synthesized *via* a developed simple high-energy ball mill method with red phosphorus,  $\text{GeO}_2$  and graphite as starting materials. With conductive carbon as layer to form stable P-O-C chemical bonding, the  $\text{GeP}_3/\text{C}$  composite exhibits a reversible capacity as high as  $1109 \text{ mA h g}^{-1}$  at  $0.1 \text{ A g}^{-1}$  with nearly 86% capacity retention over 130 cycles. Moreover, high rate capacity and stable cycling performance are also achieved. We believe that the current HEMM method is suitable for facile and large scale synthetic strategy to prepare nanostructured alloy anode materials, and that the HEMM-derived  $\text{GeP}_3/\text{C}$  composite is promising as anode material for the next-generation lithium-ion batteries with high energy density.

## Methods

**Experimental.** The GeP<sub>3</sub>/C composite was synthesized by two-step high energy mechanical milling (HEMM) method. Commercial red phosphorus (98%, Alfa Aesar), GeO<sub>2</sub> (99%, Alfa Aesar) were mixed with a molar ratio of 3:1 in a stainless steel vial (250 mL) and sealed in an argon-filled glove box, followed by HEMM at 400 rpm for 40 h on P5 ball milling machine (Pritsch, Germany). The weight ratio of ball to powder was 20:1. The obtained powder (GeP<sub>3</sub>) was further mixed with carbon (99%, Alfa Aesar) in a weight ratio of 7:3 for another 50 h ball milling at 150 rpm to get the final product of GeP<sub>3</sub>/C nanocomposite. The sample for comparison was prepared by mixing red phosphorus, GeO<sub>2</sub> and carbon with the same condition *via* one-step HEMM. The black phosphorus was prepared from red phosphorus by HEMM at 400 rpm for 40 h. The P/C was made by mixing black phosphorus and carbon in a weight ratio of 7:3 at 150 rpm for 50 h ball milling. The GeO<sub>2</sub>/C was also made with the same condition by mixing GeO<sub>2</sub> and carbon.

**Characterization.** The phase purity and crystal structure of the samples were examined by X-ray diffraction (XRD, Bruker D8, Germany) with Cu K $\alpha$  radiation at 40 kV and 40 mA from 10° to 90°. Raman measurement was carried out on a HORIBA JOBIN YVON S.A.S. system (LabRAM HR800, Japan) at 532 nm. The X-ray photoelectron spectrometer (XPS) data were collected with an ESCALab220i-XL electron spectrometer from VG Scientific using 300 W Al K radiations. The binding energies obtained in the XPS analysis were corrected with reference to C1s (284.8 eV). Fourier transform infrared spectrometry (FTIR) was performed on Nicolet-6700 (Thermo Scientific, United State). The morphology, microstructure and corresponding energy-dispersive X-ray spectrometry (EDS) of samples were characterized by field-emission scanning electron microscope (SEM, FEI NANO 450, United State). High-resolution transmission electron microscopy (HRTEM), selected-area electron diffraction (SAED) and EDS mapping were carried out by a Tecnai G2 F20 operating at 200 kV. Thermogravimetry (TG) analysis was performed with a NETZSCH STA 449 C in the temperature range of 50–1200 °C at a heating rate of 10 °C min<sup>-1</sup> in air. Nitrogen sorption isotherms were obtained using a Quantachrome Autosorb automated gas sorption system at -196 °C. Specific surface areas were calculated using the Brunauer-Emmett-Teller (BET) theory.

**Electrochemical Measurement.** The 2025-type coin cells were used for electrochemical test. The working electrode was made by a coating technique. The active material, carbon black and polyvinylidene fluoride (70:10:20 by weight ratio) were completely mixed in N-methyl-2-pyrrolidone to achieve a slurry. The slurry was then coated onto copper foil. The electrodes were dried in a vacuum oven for 24 h before cell assembly. The loading mass of active material was about 1.3 mg cm<sup>-2</sup>. The coin cells were assembled in an argon filled glove box (Braun, Germany). Li metal foil was used as a counter electrode, and Celgard 2400 as the separator. The electrolyte was 1 mol L<sup>-1</sup> LiPF<sub>6</sub> in a mixed solvent of ethylene carbonate (EC), diethyl carbonate (DMC) and fluoroethylene carbonate (EMC) (1:1:1 by volume). Galvanostatic charge/discharge tests were carried out on a battery test system (Land BT2001A, Wuhan, China) between 0.01 and 3.0 V *versus* Li/Li<sup>+</sup>. Cyclic voltammetry (CV) was performed at a scan rate of 0.01 mV s<sup>-1</sup> within the range of 0.01–3.0 V on an electrochemical workstation (VMP3, Bio-Logic SA, France). Electrochemical impedance spectroscopy (EIS) was measured by applying a sine wave with amplitude of 5 mV in the frequency range from 1000 kHz to 1 Hz.

## References

1. Tarascon, J. M. & Armand, M. Issues and challenges facing rechargeable lithium batteries. *Nature* **414**, 359–367 (2001).
2. Aricò, A. S., Bruce, P., Scrosati, B., Tarascon, J. M. & Van Schalkwijk, W. Nanostructured Materials for Advanced Energy Conversion and Storage Devices. *Nat. Mater.* **4**, 366–377 (2005).
3. Goodenough, J. B. & Kim, Y. Challenges for Rechargeable Li Batteries. *Chem. Mater.* **22**, 587–603 (2010).
4. Liu, C., Li, F., Ma, L.-P. & Cheng, H.-M. Advanced Materials for Energy Storage. *Adv. Mater.* **22**, E28–E62 (2010).
5. Lee, S. W. *et al.* High-power lithium batteries from functionalized carbon-nanotube electrodes. *Nat. Nano.* **5**, 531–537 (2010).
6. Dunn, B., Kamath, H. & Tarascon, J.-M. Electrical Energy Storage for the Grid: A Battery of Choices. *Science* **334**, 928–935 (2011).
7. Wu, H. & Cui, Y. Designing nanostructured Si anodes for high energy lithium ion batteries. *Nano Today* **7**, 414–429 (2012).
8. Goodenough, J. B. Electrochemical energy storage in a sustainable modern society. *Energy Environ. Sci.* **7**, 14–18 (2014).
9. Sun, Y., Liu, N. & Cui, Y. Promises and challenges of nanomaterials for lithium-based rechargeable batteries. *Nature Energy* **1**, 16071 (2016).
10. Chan, C. K., Zhang, X. F. & Cui, Y. High capacity Li ion battery anodes using Ge nanowires. *Nano Lett.* **8**, 307–309 (2008).
11. Ngo, D. T. *et al.* Carbon-Interconnected Ge nanocrystals as an anode with ultra-long-term cyclability for lithium ion batteries. *Adv. Funct. Mater.* **24**, 5291–5298 (2014).
12. Song, T. *et al.* Electrochemical properties of Si-Ge heterostructures as an anode material for lithium ion batteries. *Adv. Funct. Mater.* **24**, 1458–1464 (2014).
13. Klavetter, K. C. *et al.* A high-rate germanium-particle slurry cast Li-ion anode with high Coulombic efficiency and long cycle life. *J. Power Sources* **238**, 123–136 (2013).
14. Ngo, D. T. *et al.* Mass-scalable synthesis of 3D porous germanium-carbon composite particles as an ultra-high rate anode for lithium ion batteries. *Energy Environ. Sci.* **8**, 3577–3588 (2015).
15. Li, D., Feng, C., Liu, H. K. & Guo, Z. Hollow carbon spheres with encapsulated germanium as an anode material for lithium ion batteries. *J. Mater. Chem.* **3**, 978–981 (2015).
16. Liu, Y., Vishniakou, S., Yoo, J. & Dayeh, S. A. Engineering Heteromaterials to Control Lithium Ion Transport Pathways. *Sci. Rep.* **5**, 18482 (2015).
17. Zhang, W. *et al.* Rational synthesis of carbon-coated hollow Ge nanocrystals with enhanced lithium-storage properties. *Nanoscale* **8**, 12215–12220 (2016).
18. Lee, G.-H. *et al.* Germanium microflower-on-nanostem as a high-performance lithium ion battery electrode. *Sci. Rep.* **4**, 6883 (2014).
19. Liu, J. *et al.* Ge/C nanowires as high-capacity and long-life anode materials for Li-ion batteries. *ACS nano* **8**, 7051–7059 (2014).
20. Hwang, I.-S. *et al.* A binder-free Ge-nanoparticle anode assembled on multiwalled carbon nanotube networks for Li-ion batteries. *Chem. Commun.* **48**, 7061–7063 (2012).
21. Gao, X. *et al.* Novel Germanium/Polypyrrole Composite for High Power Lithium-ion Batteries. *Sci. Rep.* **4**, 6095 (2014).

22. Klavetter, K. C., Pedro de Souza, J., Heller, A. & Mullins, C. B. High tap density microparticles of selenium-doped germanium as a high efficiency, stable cycling lithium-ion battery anode material. *J. Mater. Chem.* **3**, 5829–5834 (2015).
23. Lin, N. *et al.* Chemical synthesis of porous hierarchical Ge-Sn binary composites using metathesis reaction for rechargeable Li-ion batteries. *Chem. Commun.* **51**, 17156–17159 (2015).
24. Lee, H. *et al.* Surface-Stabilized Amorphous Germanium Nanoparticles for Lithium-Storage Material. *J. Phys. Chem. B* **109** (2005).
25. Seng, K. H., Park, M.-H., Guo, Z. P., Liu, H. K. & Cho, J. Self-Assembled Germanium/Carbon Nanostructures as High-Power Anode Material for the Lithium-Ion Battery. *Angew. Chem. Int. Ed.* **51**, 5657–5661 (2012).
26. Xiang, J., Wang, X., Zhong, J., Zhang, D. & Tu, J. Enhanced rate capability of multi-layered ordered porous nickel phosphide film as anode for lithium ion batteries. *J. Power Sources* **196**, 379–385 (2011).
27. Lu, Y. *et al.* Controllable Synthesis of a Monophase Nickel Phosphide/Carbon (Ni<sub>3</sub>P<sub>4</sub>/C) Composite Electrode via Wet-Chemistry and a Solid-State Reaction for the Anode in Lithium Secondary Batteries. *Adv. Funct. Mater.* **22**, 3927–3935 (2012).
28. Wang, X. *et al.* A three-dimensional porous MoP@C hybrid as a high-capacity, long-cycle life anode material for lithium-ion batteries. *Nanoscale* **8**, 10330–10338 (2016).
29. Li, W. *et al.* Self-supported Zn<sub>3</sub>P<sub>2</sub> nanowire arrays grafted on carbon fabrics as an advanced integrated anode for flexible lithium ion batteries. *Nanoscale* **8**, 8666–8672 (2016).
30. Kim, S.-O. & Manthiram, A. The facile synthesis and enhanced sodium-storage performance of a chemically bonded CuP<sub>2</sub>/C hybrid anode. *Chem. Commun.* **52**, 4337–4340 (2016).
31. Jiang, J., Wang, C., Li, W. & Yang, Q. One-pot synthesis of carbon-coated Ni<sub>5</sub>P<sub>4</sub> nanoparticles and CoP nanorods for high-rate and high-stability lithium-ion batteries. *J. Mater. Chem.* **3**, 23345–23351 (2015).
32. Richards, W. D. *et al.* Design and synthesis of the superionic conductor Na<sub>10</sub>SnP<sub>2</sub>S<sub>12</sub>. *Nat. Commun.* **7**, 11009 (2016).
33. Shin, H. S. *et al.* Tin phosphide-based anodes for sodium-ion batteries: synthesis via solvothermal transformation of Sn metal and phase-dependent Na storage performance. *Sci. Rep.* **6** (2016).
34. Fan, X. *et al.* Superior Stable Self-Healing SnP<sub>3</sub> Anode for Sodium-Ion Batteries. *Adv. Energy Mater.* **5**, 2314–2316 (2015).
35. Sun, J. *et al.* Formation of stable phosphorus-carbon bond for enhanced performance in black phosphorus nanoparticle-graphite composite battery anodes. *Nano Lett.* **14**, 4573–4580 (2014).
36. Song, J. *et al.* Chemically bonded phosphorus/graphene hybrid as a high performance anode for sodium-ion batteries. *Nano Lett.* **14**, 6329–6335 (2014).
37. Song, J. *et al.* Advanced Sodium Ion Battery Anode Constructed via Chemical Bonding between Phosphorus, Carbon Nanotube, and Cross-Linked Polymer Binder. *ACS nano* **9**, 11933–11941 (2015).
38. Li, W. *et al.* Layered phosphorus-like GeP<sub>5</sub>: a promising anode candidate with high initial coulombic efficiency and large capacity for lithium ion batteries. *Energy Environ. Sci.* **8**, 3629–3636 (2015).
39. Donohue, P. C. & Young, H. S. Synthesis, structure, and superconductivity of new high pressure phases in the systems GeP and GeAs. *J. Solid State Chem.* **1**, 143–149 (1970).
40. Xing, T. *et al.* Lithium storage in disordered graphitic materials: a semi-quantitative study of the relationship between structure disordering and capacity. *Phys. Chem. Chem. Phys.* **17**, 5084–5089 (2015).
41. Zhao, H. *et al.* SnSb/TiO<sub>2</sub>/C nanocomposite fabricated by high energy ball milling for high-performance lithium-ion batteries. *RSC Adv.* **6**, 32462–32466 (2016).
42. Puziy, A. M., Poddubnaya, O. I., Martínez-Alonso, A., Suárez-García, F. & Tascón, J. M. D. Surface chemistry of phosphorus-containing carbons of lignocellulosic origin. *Carbon* **43**, 2857–2868 (2005).
43. Shi, Y., Belosinschi, D., Brouillette, F., Belfkira, A. & Chabot, B. Phosphorylation of Kraft fibers with phosphate esters. *Carbohydr. Polym.* **106**, 121–127 (2014).
44. Watanabe, J. *et al.* Cytocompatible biointerface on poly(lactic acid) by enrichment with phosphorylcholine groups for cell engineering. *Mater. Sci. Eng. C* **27**, 227–231 (2007).
45. Cloud, J. E., Wang, Y., Yoder, T. S., Taylor, L. W. & Yang, Y. Colloidal Nanocrystals of Lithiated Group 14 Elements †. *Angew. Chem. Int. Ed.* **126**, 14527–14532 (2014).

## Acknowledgements

The authors would like to acknowledge financial supports from the National High Technology Research and Development Program (863 Program) (Grant Nos 2013AA032002 and 2015AA034601), Science and Technology Program of Guangzhou (201607010110).

## Author Contributions

W.Q. designed and performed the experiments, and analyzed the experimental data. H.H.Z., Y.W., H.Z., T.T., C.C. and K.C.J. assisted with some of the experiments. Y.H.H. and S.X.Z. guided the work and analysis. W.Q. and Y.H.H. wrote the paper.

## Additional Information

**Supplementary information** accompanies this paper at <http://www.nature.com/srep>

**Competing financial interests:** The authors declare no competing financial interests.

**How to cite this article:** Qi, W. *et al.* Facile Synthesis of Layer Structured GeP<sub>3</sub>/C with Stable Chemical Bonding for Enhanced Lithium-Ion Storage. *Sci. Rep.* **7**, 43582; doi: 10.1038/srep43582 (2017).

**Publisher's note:** Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.



This work is licensed under a Creative Commons Attribution 4.0 International License. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in the credit line; if the material is not included under the Creative Commons license, users will need to obtain permission from the license holder to reproduce the material. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>

© The Author(s) 2017