

SCIENTIFIC REPORTS



OPEN

Glycol Derived Carbon-TiO₂ as Low Cost and High Performance Anode Material for Sodium-Ion Batteries

Hongwei Tao*, Min Zhou*, Kangli Wang, Shijie Cheng & Kai Jiang

Received: 28 November 2016

Accepted: 30 January 2017

Published: 03 March 2017

Carbon coated TiO₂ (TiO₂@C) is fabricated by a convenient and green one-pot solvothermal method, in which ethylene glycol serve as both the reaction medium and carbon source without the addition of any other carbon additives. During the solvothermal process, ethylene glycol polymerize and coordinate with Ti⁴⁺ to form the polymeric ligand precursor, then the polymer brushes carbonize and convert to homogeneous carbon layer firmly anchored on the TiO₂ nanoparticles (~1 nm thickness). The polymerization and carbonization process of the ethylene glycol is confirmed by FT-IR, Raman, TG and TEM characterizations. Benefiting from the well-dispersed nanoparticles and uniform carbon coating, the as-prepared TiO₂@C demonstrate a high reversible capacity of 317 mAh g⁻¹ (94.6% of theoretical value), remarkable rate capability of 125 mAh g⁻¹ at 3.2 A g⁻¹ and superior cycling stability over 500 cycles, possibly being one of the highest capacities reported for TiO₂.

The development of advanced energy storage technology is of great importance to address the increasingly global concerns of energy shortage and environmental issues^{1,2}. To date, Li-ion batteries (LIBs) represent the state-of-the-art technology due to their high energy density and have dominated the energy storage market of portable electronic devices. However, the limited lithium resources and high price of lithium-based compounds remains an obstacle for their expanded application in large-scale energy storage^{3,4}. In contrast to lithium, sodium is widely distributed around the world and has a suitable redox potential ($E_{\text{Na}/\text{Na}^+}^0 = -2.71 \text{ V vs SHE}$), only 0.3 V above that of lithium. Sodium ion batteries (SIBs) with low cost and high efficiency seem to be the ideal alternative to LIBs, especially for grid-scale energy storage applications⁵⁻⁷.

Unfortunately, the large radius of sodium ions make it difficult to find appropriate Na-storage electrode materials with high capacity and rapid kinetics. With respect to the anode side, various types of hard carbon have been revealed to deliver considerable reversible capacity, but their low potential and large polarization raise safety issues for the practical battery applications⁸⁻¹⁰. Metallic anodes, such as Sn and Sb-based materials, have attracted significant attention due to their high Na-storage capacity¹¹⁻¹³. However, the unavoidable volume change of these materials during the repeated sodiation/desodiation hinders their further applications. As a result, exploiting better anode materials with low cost and cycling stability is still necessary for the development of practically viable SIBs.

Titanium-based materials, a cost effective, structurally stable and sustainable material, is considered to be promising Na-storage anode^{14,15}. Among various polymorphs of Ti-based anode materials, anatase TiO₂ exhibit much better electrochemical performances owing to the three dimensional open structure, which is favorable for the Na⁺ transport and storage¹⁶. Nevertheless, the intrinsic low conductivity of pure TiO₂ leads to low realizable capacity and poor rate performance. Considering that the electrochemical performances of TiO₂ electrode is strongly depend on the morphology and pore size of the particles, varieties of TiO₂ nanostructures have been designed and investigated as Na-storage materials with enhanced reversible Na-storage capacity, such as nanoparticles, nanotubes, nanorods, nanospheres, nanofibers¹⁷⁻²³. However, the side reactions and structure instability of nanoparticles lead to low initial coulombic efficiency and poor cycling performances. Another effective strategy to increase the capacity utilization of TiO₂ is heteratomic doping²⁴⁻²⁷. Doping elements with low charge states can create structure defects in the bulk TiO₂ and thus enhance the electrical and ionic conductivities. Of significance,

State Key Laboratory of Advanced Electromagnetic Engineering and Technology, School of Electrical and Electronic Engineering AND State Key Laboratory of Materials Processing, and Die & Mould Technology, School of Materials Science and Engineering, Huazhong University of Science and Technology, Wuhan 430074, P. R. China. *These authors contributed equally to this work. Correspondence and requests for materials should be addressed to K.W. (email: klwang@hust.edu.cn) or K.J. (email: kjjiang@hust.edu.cn)

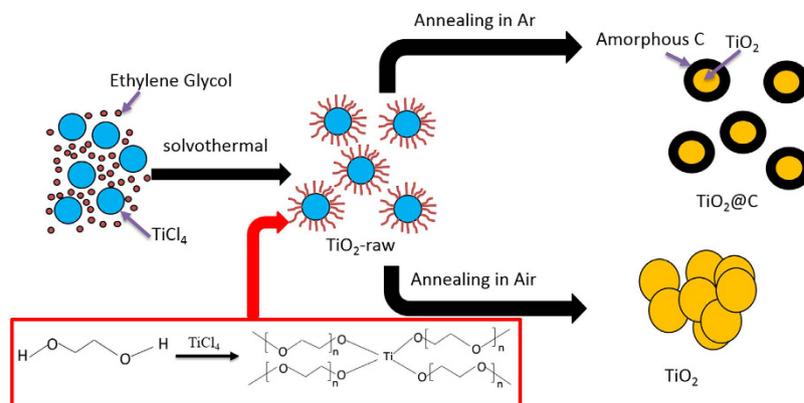




Figure 1. Schematic illustration of the synthesis of TiO₂@C nanoparticles.

Pan *et al.*²⁶ prepared Ni²⁺ doped TiO₂ nanotubes with a maximum capacity of 286 mAh g⁻¹ after 100 cycles at a current density of 50 mA g⁻¹. However, the initial coulombic efficiency (CE), which are critical for practical SIBs, still need to be upgraded considerably. In attempt to further improve the electrochemical performances of TiO₂, efforts have been devoted to combine the nanosized TiO₂ with conductive carbon^{28–32}. Carbon coating can provide conducting network and stabilize the SEI formation by restraining sodium ions, thus resulting in improved capacity utilization as well as initial coulombic efficiency and rate performances. Recently, Yang *et al.* reported a graphene supported TiO₂ nanospheres with a superior Na storage capacity of 300 mAh g⁻¹ at 20 mA g⁻¹ and a high rate capability of 123.1 mAh g⁻¹ at a high rate of 4.0 A g⁻¹. Nevertheless, the long-term cycling stability of this material still need to be improved. Moreover, the high cost, low initial coulombic efficiency and complex synthesis route of graphene create a barrier for the large-scale applications of TiO₂ anode.

Glycol is the common used reaction medium for the preparation of TiO₂ with the advantages of effectively controlling the morphology and particle size^{33–36}. In this work, we present a simple and green one-pot solvothermal method to fabricate carbon-coated TiO₂ nanoparticles (TiO₂@C), in which ethylene glycol serve as both the reaction medium and carbon source without the addition of any other carbon additives. During the solvothermal process, ethylene glycol polymerize and coordinate with Ti⁴⁺ to produce polymeric ligand precursor. Then in the subsequent annealing process, the polymer brushes pyrolyze and convert to a uniform and homogenous carbon layer firmly anchored on the surface of TiO₂ nanoparticles. As expected, the as-prepared TiO₂@C demonstrate a high reversible capacity of 317 mAh g⁻¹ at 0.05 A g⁻¹, strong rate capability of 125 mAh g⁻¹ at 3.2 A g⁻¹ and superior cycling stability over 500 cycles, offering a low cost and high performance anode material for SIBs.

Results and Discussion

Figure 1 presents the typical synthesis route of the TiO₂@C (TiO₂) nanoparticles. The solvent (ethylene glycol) polymerized during the first solvothermal process (equation 1). As polyethyleneglycol is rich in –OH and –C–O–C– groups, it can easily coordinate with Ti⁴⁺ to firmly anchor the precursor molecules on their surfaces (equation 2). The FT-IR spectrum of the TiO₂-raw material reflects all the characteristic absorptions of the typical precursor, confirming the polymerization and coordination reaction mechanism stated above (Fig. S1). In the final annealing process, the polymer brushes carbonize and convert to uniform and homogeneous carbon coating on the TiO₂ nanoparticles (equation 3). It is worth noted that the ethylene glycol cannot polymerize in the same condition without the presence of TiCl₄, indicating that the Ti⁴⁺ play a catalysis role in the polymerization of ethylene glycol.



The crystalline structure of the TiO₂@C and TiO₂ are examined by X-ray diffraction spectrometry (XRD). As shown in Fig. 2a, all the diffraction peaks of TiO₂@C and TiO₂ can be well indexed to the anatase phase TiO₂ (JCPDS: 21-1272) with the tetragonal crystal structure belonging to *I4₁/amd* space group, *a* = 3.784 ± 0.002 Å, and *c* = 9.514 ± 0.004 Å. The peak intensity of TiO₂@C is weaker than that of TiO₂, indicating the TiO₂ nanoparticles embedded in amorphous carbon matrix. Based on the Debye Scherrer equation, the crystal sizes of TiO₂@C

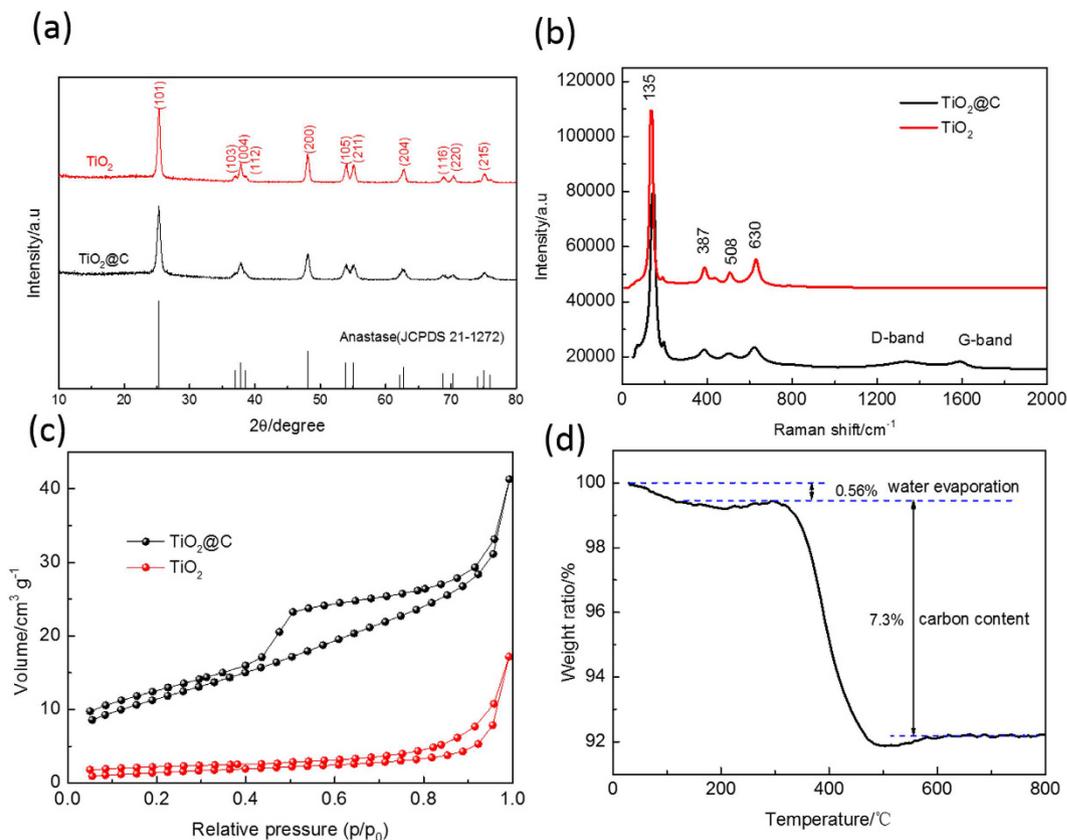


Figure 2. Physical characterizations of the $\text{TiO}_2@\text{C}$ and TiO_2 : (a) XRD pattern, (b) Raman spectra and (c) N_2 adsorption–desorption isotherm of $\text{TiO}_2@\text{C}$ and TiO_2 ; (d) TGA curve of $\text{TiO}_2@\text{C}$.

and TiO_2 are calculated to be ~ 24 nm and 27 nm, respectively. The X-ray photoelectron spectroscopy (XPS) spectra are recorded to analyze the chemical state of the $\text{TiO}_2@\text{C}$. As shown in Fig. S2, there are two peaks of binding energies at 459 and 465 eV ascribed to $\text{Ti}^{4+} 2p_{3/2}$ and $\text{Ti}^{4+} 2p_{1/2}$ in the spectrum of the $\text{TiO}_2@\text{C}$, suggesting the formation of TiO_2 . Raman spectra are recorded to investigate their surface composition and structures (Fig. 2b). The vibrational peaks at 135, 387, 508 and 630 cm^{-1} are observed in the Raman spectra of both $\text{TiO}_2@\text{C}$ and TiO_2 , well consistent with that of previously reported^{37,38}. Besides, compared with TiO_2 , two extra characteristic peaks located at 1337 and 1587 cm^{-1} are detected in the Raman spectra of $\text{TiO}_2@\text{C}$, corresponding to disorder carbon (D-band) and graphite carbon (G-band) attributed by the amorphous carbon coating layer³⁹. The Brunauer–Emmett–Teller (BET) measurement is carried out to investigate the surface and porous structures of TiO_2 . As shown in Fig. 2c, N_2 adsorption–desorption isotherms of $\text{TiO}_2@\text{C}$ and TiO_2 can be identified as type IV isotherm (IUPAC), suggesting the mesoporous structure. According to the BET analysis, the specific surface areas of the TiO_2 and $\text{TiO}_2@\text{C}$ are measured to be 5.5 and $41.3\text{ m}^2\text{ g}^{-1}$, respectively. The large surface area and porous structure can not only increase the electrolyte/electrode contact areas, but also facilitate the kinetics of Na^+ insertion/extraction and diffusion. Figure 2d presents the thermogravimetry analyses (TGA) curves of $\text{TiO}_2@\text{C}$, the carbon contents in the $\text{TiO}_2@\text{C}$ is evaluated to be $\sim 7.3\text{ wt}\%$.

The as-prepared $\text{TiO}_2@\text{C}$ is in the form of black powders, while the color of the pure TiO_2 is white (Fig. S3). The morphologies of the TiO_2 and $\text{TiO}_2@\text{C}$ are presented in Fig. 3. As shown in Fig. 3a, the as-prepared TiO_2 appeared as uneven particles with the average particle size of ~ 200 nm, which consist of aggregated primary crystallites with the crystal size of ~ 25 nm (Fig. S4). In contrast, the $\text{TiO}_2@\text{C}$ emerges as well-dispersed nanoparticles with much smaller size ranging from 30 to 50 nm (Fig. 3b,c), indicating the carbon coating can prevent the TiO_2 nanoparticles from aggregating. The high-resolution TEM image of $\text{TiO}_2@\text{C}$ (Fig. 3d) reveals clear lattices with spacing of 0.35 nm, corresponding to the $[101]$ planes of anatase TiO_2 , in accordance with the XRD result. Besides, it is clearly visualized that the amorphous carbon shell with the thickness of ~ 1 nm are well decorated on the surface of the TiO_2 nanoparticles, ensuring the high conductivity and stable structure of the $\text{TiO}_2@\text{C}$ composites.

The electrochemical reactivity of the $\text{TiO}_2@\text{C}$ sample is investigated by cyclic voltammetry (CV) and galvanostatic charge–discharge cycling in 1 M NaPF_6 in a mixed solvent of ethylene carbonate (EC) and diethyl carbonate (DEC). Figure 4a shows the CV curves of the $\text{TiO}_2@\text{C}$ electrode at the scan rate of 0.5 mV s^{-1} . During the first cathodic scan, a large and broad reduction band appears at the potential region from 1.5 to 0 V, which considerably decreases its intensity during subsequent cycles, suggesting the formation of solid electrolyte interface (SEI) by decomposition of electrolyte. In the subsequent scans, a pair of redox peaks located at 0.7 and 0.85 V, referring the Na^+ insertion/extraction reactions in the host lattice of anatase TiO_2 . It is noteworthy that the

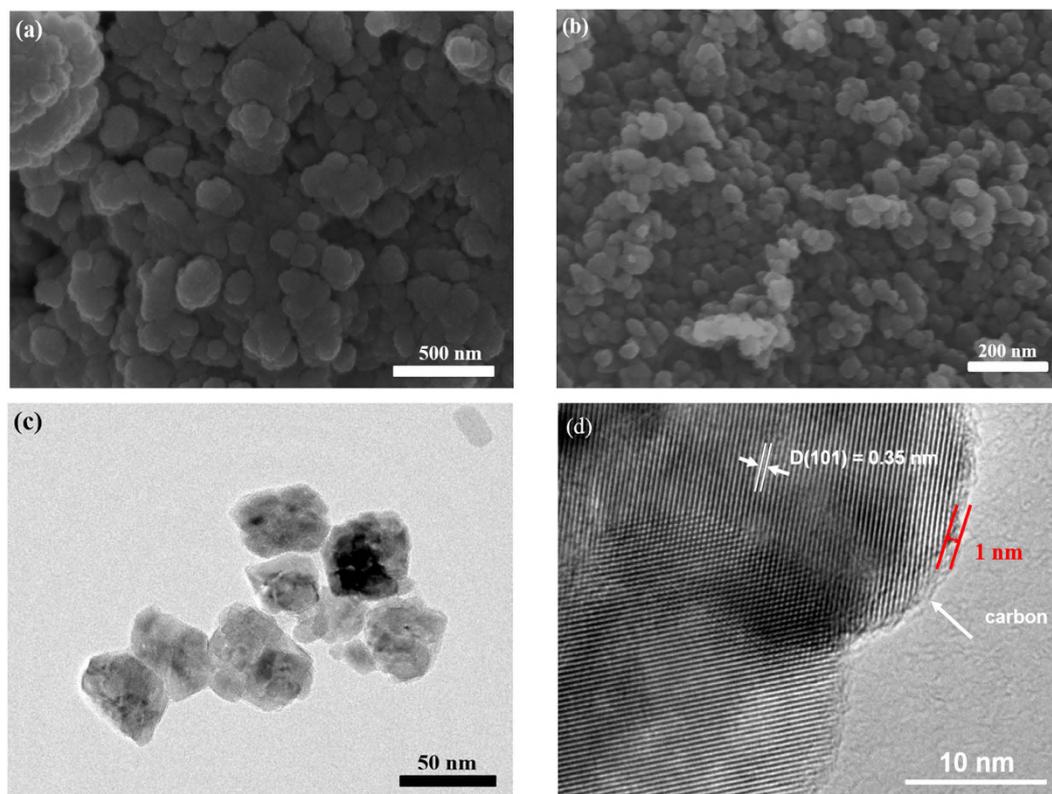


Figure 3. Morphological features of the $\text{TiO}_2@\text{C}$ and TiO_2 particles: (a) SEM image of TiO_2 ; (b) SEM image of $\text{TiO}_2@\text{C}$; (c) TEM images and (d) high resolution TEM image of $\text{TiO}_2@\text{C}$.

cathodic and anodic currents exhibit a gradual increase in the first ten cycles, possibly ascribed to an activation process of the $\text{TiO}_2@\text{C}$ electrode.

Figure 4b shows the typical charge/discharge profiles of the $\text{TiO}_2@\text{C}$ electrode at the current density of 0.05 A g^{-1} . In accordance with the CV curves, the $\text{TiO}_2@\text{C}$ electrode demonstrates sloping charge/discharge profiles in the potential range of 0.3–1.3 V (vs Na/Na⁺). The initial charge and discharge capacities of $\text{TiO}_2@\text{C}$ are 649 and 317 mAh g⁻¹ (based on the weight of $\text{TiO}_2@\text{C}$ composite), corresponding to an initial coulombic efficiency of 48.9%. The irreversible capacity during the first several cycles is due to the formation of SEI film by electrolyte decomposition and some form of irreversible trapping of Na⁺ in the TiO_2 lattice. As shown in Fig. 4c, the reversible capacities of the $\text{TiO}_2@\text{C}$ remain stably at 298 mAh g⁻¹ over 100 cycles, suggesting an outstanding cycling stability. For comparison, the TiO_2 deliver a much lower reversible capacity of less than 100 mAh g⁻¹ with an inferior initial coulombic efficiency of 28% (Fig. S5). Considering the possible capacity contribution of the carbon additives, we also measured the Na-storage capacities of the acetylene black (Fig. S6). The capacity contribution of the carbon additive is calculated to be less than 10 mAh g⁻¹, which is negligible. It is noteworthy that the reversible capacity of $\text{TiO}_2@\text{C}$ is possibly one of the highest capacities reported for the TiO_2 anodes^{23,26,28}.

In addition to the remarkable high capacity, the $\text{TiO}_2@\text{C}$ electrode also exhibits superior high rate capability and long-term cycling stability. Figure 4d compares the rate capability of the TiO_2 and $\text{TiO}_2@\text{C}$ electrodes. The $\text{TiO}_2@\text{C}$ electrode delivers a reversible capacity of 311.5, 277.8, 257, 235, 214.6, 181.8, 125.5, 91.3 mAh g⁻¹ at different current densities of 0.05, 0.1, 0.2, 0.4, 0.8, 1.6, 3.2 and 6.4 A g⁻¹, respectively. More encouragingly, after cycled at different current densities for 90 cycles, the $\text{TiO}_2@\text{C}$ electrode recovers a reversible capacity of 289 mAh g⁻¹ when the current density returns back to 0.05 A g⁻¹, about 93.2% of its initial capacity. In contrast, the TiO_2 electrode shows much poor rate performances and can only deliver a reversible capacity of less than 70 mAh g⁻¹ at the current density of 1.6 A g⁻¹, indicating a significant enhancement in rate capability of the TiO_2 after carbon coating. In order to further evaluate the long-term cycling stability of the $\text{TiO}_2@\text{C}$, cells are assembled and galvanostatically charged and discharged at 0.4 A g⁻¹ for 500 cycles. As shown in Fig. 4e, a reversible capacity of 241 mAh g⁻¹ is obtained after 500 cycles with a capacity retention of 85.2%. The coulombic efficiency rapidly rise up to 99.2% in the first few cycles, indicating stable reversibility.

The excellent electrochemical performance of $\text{TiO}_2@\text{C}$ can be ascribed to the synergistic effect of the well-dispersed TiO_2 nanoparticles and the homogeneous carbon coating. The nanostructured TiO_2 are beneficial for Na storage on account of the large surface areas, short diffusion length and fast kinetic properties. The surrounding carbon matrix, derived from the polyethyleneglycol, can not only provide abundant active sites for Na⁺ insertion/desertion, but also offers high electric conduction paths for fast electron transport, leading to a remarkable reversible capacity and strong rate capability. Moreover, the uniform carbon layer can stabilize the SEI formation by preventing the TiO_2 nanoparticles from aggregating and attacking by electrolyte, thus resulting in high initial coulombic efficiency and long cycle life.

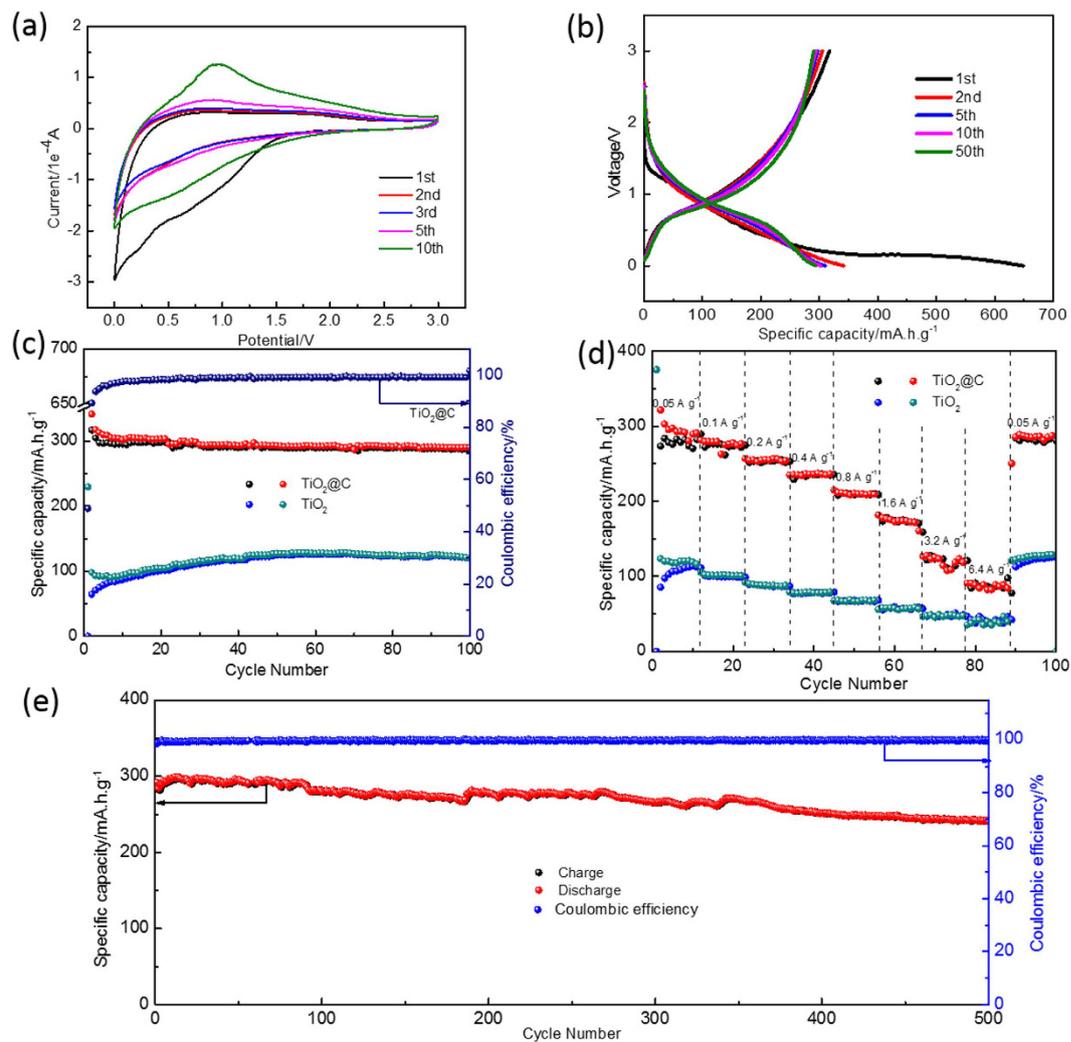


Figure 4. Electrochemical characterizations of the $\text{TiO}_2@\text{C}$ electrode: (a) CV curves obtained at a scan rate of 0.5 mV s^{-1} ; (b) charge-discharge profiles at a current rate of 0.05 A g^{-1} in the first 50 cycles; (c) cycling performance at a constant current of 0.05 A g^{-1} ; (d) rate capability at various current rates from 0.05 A g^{-1} to 6.4 A g^{-1} ; (e) long-term cycling performances at a constant current density of 400 mA g^{-1} .

To further provide a better understanding of the improved electrochemical performance by carbon coating, electrochemical impedance spectra (EIS) of the $\text{TiO}_2@\text{C}$ and TiO_2 electrodes are obtained in the frequency range from 100 KHz to 0.1 Hz. As shown in Fig. S7, the semicircles in the high-frequency region is attributed to the interface reaction of SEI film, while the medium-frequency semicircle is assigned to the real axis corresponding to the sodium-diffusion process in the bulk phase. The $\text{TiO}_2@\text{C}$ electrode exhibits much lower SEI film resistance (R_{SEI} , 13.3Ω) and charge transfer resistance (R_{ct} , 305.4Ω) than those of the TiO_2 electrode (87.2Ω and 403.9Ω) based on the equivalent circuit simulation, respectively, indicating better electronic and ionic conduction in the $\text{TiO}_2@\text{C}$ composite.

Conclusion

In summary, we present a convenient and green one-pot solvothermal method to fabricate carbon-coated TiO_2 nanoparticles ($\text{TiO}_2@\text{C}$). The ethylene glycol serve as both the reaction mediate and carbon source without adding any other carbon additives. Benefiting from the well-dispersed nanoparticles and homogeneous carbon coating, the as-prepared $\text{TiO}_2@\text{C}$ demonstrate a high reversible capacity of 317 mAh g^{-1} , strong rate capability of 125 mAh g^{-1} at 3.2 A g^{-1} and superior cycling stability over 500 cycles, offering a low cost and high performance anode material for Na-storage. Particularly, the synthesis route described in this work is simple and intrinsically green, which provide new insights for the development of better host materials for practical SIBs.

Methods

Material Synthesis. The carbon-coated TiO_2 nanoparticles were synthesized by solvothermal process as schematically illustrated in Fig. 1. Typically, 1 ml TiCl_4 were added into 80 ml ethylene glycol dropwise with continuous stirring until the solution became clear. Then 2 ml ammonium hydroxide (25%) were added into the

above solution and stirred for another 15 mins. The mixed solution was transferred into a 100 ml Teflon-lined stainless steel autoclave and treated at 180 °C for 24 h. After cooling down to room temperature, the products were collected by centrifugation and washed several times with ethanol and distilled water. Then the samples were dried at 80 °C under vacuum for 10 h to obtain the raw powders of TiO₂ (denoted as TiO₂-raw). This raw material was then calcined in Argon atmosphere at 700 °C for 2 h to obtain the carbon-coated TiO₂ nanoparticles (denoted as TiO₂@C). For comparison, TiO₂ nanoparticles were also prepared in the same way as above except for annealing in air (denoted as TiO₂).

Material characterization. The crystalline structure of the as-prepared materials were recorded on powder X-ray diffraction (XRD, PANalytical B.V., Holland) using Cu-K α radiation. Particle morphologies were characterized by scanning electron microscopy (SEM, SIRION200) and transmission electron microscopy (TEM, JEOL2100). Fourier transformed infrared (FTIR) spectra were recorded on a Bruker VERTEX 70 FTIR spectrometer. Raman spectroscopic analyses were performed with a Horiba Jobin-Yvon LabRAM HR800 Raman system using laser excitation at 532 nm from an Nd-YAG laser. The specific surface area were determined by Brunauer-Emmett-Teller (BET) nitrogen adsorption-desorption measurement on TriStar II 3020. X-ray photoelectron spectroscopic (XPS) measurement was performed on an AXIS-ULTRA DLD X-ray photoelectron spectrometer. Carbon content of the carbon-coated anatase-phase TiO₂ was confirmed by TG-DSC (Netzsch STA 449 F5) in an air atmosphere with a heating rate of 10 °C/min from room temperature to 800 °C.

Electrochemical measurements. The working electrodes were prepared by mixing the TiO₂@C (TiO₂), acetylene black and polyvinylidene difluoride (PVDF) in N-methyl-2-pyrrolidone (NMP) in a mass ratio of 80:10:10. The slurry was coated uniformly (doctor-blade) on Cu foil and vacuum-dried at 110 °C for more than 12 h. Electrochemical tests were carried out using CR2016 coin cells, which were assembled in glove box filled with highly pure argon gas (O₂ and H₂O levels <0.1 ppm). Sodium metal acted as the counter and reference electrode, Celgard 2400 membrane as the separator. The electrolyte was 1 M NaPF₆ salt in a mixture of ethylene carbonate (EC) and dimethyl carbonate (DEC) solution (EC: DEC, 1:1 in volume) with the addition of 10 wt% fluoroethylene carbonate (FEC). Cyclic voltammetry (CV) was measured on an electrochemistry workstation (CHI 660E) using a scan rate of 0.5 mV s⁻¹. Galvanostatic discharge/charge cycling was made on a LANHE battery test system (Wuhan, China) in the voltage range of 0 ~3 V (vs. Na/Na⁺). Electrochemical impedance spectroscopy (EIS) analysis was conducted using an electrochemical workstation (Autolab, PGSTAT302N) with the frequency range of 100 kHz to 0.1 Hz after operating the electrodes for 100 cycles.

References

- Dunn, B., Kamath, H. & Tarascon, J.-M. Electrical energy storage for the grid: a battery of choices. *Science* **334**, 928–935 (2011).
- Yang, Z. *et al.* Electrochemical energy storage for green grid. *Chemical reviews* **111**, 3577–3613 (2011).
- Scrosati, B., Hassoun, J. & Sun, Y.-K. Lithium-ion batteries. A look into the future. *Energy & Environmental Science* **4**, 3287–3295 (2011).
- Scrosati, B. Technology: Charging towards the superbattery. *Nature* **473**, 448–449 (2011).
- Palomares, V., Casas-Cabanas, M., Castillo-Martinez, E., Han, M. H. & Rojo, T. Update on Na-based battery materials. A growing research path. *Energy & Environmental Science* **6**, 2312–2337 (2013).
- Kim, S. W., Seo, D. H., Ma, X., Ceder, G. & Kang, K. Electrode materials for rechargeable sodium-ion batteries: potential alternatives to current lithium-ion batteries. *Advanced Energy Materials* **2**, 710–721 (2012).
- Kundu, D., Talaie, E., Duffort, V. & Nazar, L. F. The emerging chemistry of sodium ion batteries for electrochemical energy storage. *Angewandte Chemie International Edition* **54**, 3431–3448 (2015).
- Stevens, D. & Dahn, J. The mechanisms of lithium and sodium insertion in carbon materials. *Journal of The Electrochemical Society* **148**, A803–A811 (2001).
- Li, W. *et al.* A high performance sulfur-doped disordered carbon anode for sodium ion batteries. *Energy & Environmental Science* **8**, 2916–2921 (2015).
- Xiao, L. *et al.* Hard carbon nanoparticles as high-capacity, high-stability anodic materials for Na-ion batteries. *Nano Energy* **19**, 279–288 (2016).
- Li, H. *et al.* Layered SnS₂ cross-linked by carbon nanotubes as a high performance anode for sodium ion batteries. *RSC Advances* **6**, 35197–35202 (2016).
- Li, W. *et al.* Carbon-coated Sb₂Se₃ composite as anode material for sodium ion batteries. *Electrochemistry Communications* **60**, 74–77 (2015).
- Li, W. *et al.* Carbon-coated Mo₃Sb₇ composite as anode material for sodium ion batteries with long cycle life. *Journal of Power Sources* **307**, 173–180 (2016).
- Guo, S., Yi, J., Sun, Y. & Zhou, H. Recent advances in titanium-based electrode materials for stationary sodium-ion batteries. *Energy & Environmental Science* (2016).
- Ni, J. *et al.* Superior Sodium Storage in Na₂Ti₃O₇ Nanotube Arrays through Surface Engineering. *Advanced Energy Materials* **6** (2016).
- Su, D., Dou, S. & Wang, G. Anatase TiO₂: Better Anode Material Than Amorphous and Rutile Phases of TiO₂ for Na-Ion Batteries. *Chemistry of Materials* **27**, 6022–6029 (2015).
- Kim, K.-T. *et al.* Anatase titania nanorods as an intercalation anode material for rechargeable sodium batteries. *Nano letters* **14**, 416–422 (2014).
- Xiong, H., Slater, M. D., Balasubramanian, M., Johnson, C. S. & Rajh, T. Amorphous TiO₂ nanotube anode for rechargeable sodium ion batteries. *The journal of physical chemistry letters* **2**, 2560–2565 (2011).
- Xu, Y. *et al.* Nanocrystalline anatase TiO₂: a new anode material for rechargeable sodium ion batteries. *Chemical Communications* **49**, 8973–8975 (2013).
- Oh, S.-M. *et al.* High electrochemical performances of microsphere C-TiO₂ anode for sodium-ion battery. *ACS applied materials & interfaces* **6**, 11295–11301 (2014).
- Ge, Y. *et al.* High cyclability of carbon-coated TiO₂ nanoparticles as anode for sodium-ion batteries. *Electrochimica Acta* **157**, 142–148 (2015).
- Yang, X. *et al.* Anatase TiO₂ nanocubes for fast and durable sodium ion battery anodes. *Journal of Materials Chemistry A* **3**, 8800–8807 (2015).

23. Xiong, Y., Qian, J., Cao, Y., Ai, X. & Yang, H. Electrospun TiO₂/C Nanofibers As a High-Capacity and Cycle-Stable Anode for Sodium-Ion Batteries. *ACS Applied Materials & Interfaces* **8**, 16684–16689 (2016).
24. Yang, Y. *et al.* Carbon dots supported upon N-doped TiO₂ nanorods applied into sodium and lithium ion batteries. *J. Mater. Chem. A* **3**, 5648–5655, doi: 10.1039/c4ta05611f (2015).
25. Yan, D. *et al.* Sn-doped TiO₂ nanotubes as superior anode materials for sodium ion batteries. *Chemical Communications* **51**, 8261–8264 (2015).
26. Yan, D. *et al.* Improved sodium-ion storage performance of TiO₂ nanotubes by Ni²⁺ doping. *Journal of Materials Chemistry A* **4**, 11077–11085 (2016).
27. Chen, J. *et al.* Black Anatase Titania with Ultrafast Sodium-Storage Performances Stimulated by Oxygen Vacancies. *ACS applied materials & interfaces* **8**, 9142–9151 (2016).
28. Xiong, Y., Qian, J., Cao, Y., Ai, X. & Yang, H. Graphene-supported TiO₂ nanospheres as a high-capacity and long-cycle life anode for sodium ion batteries. *Journal of Materials Chemistry A* **4**, 11351–11356 (2016).
29. Lee, J., Chen, Y.-M., Zhu, Y. & Vogt, B. D. Fabrication of porous carbon/TiO₂ composites through polymerization-induced phase separation and use as an anode for Na-ion batteries. *ACS applied materials & interfaces* **6**, 21011–21018 (2014).
30. Ding, C., Nohira, T. & Hagiwara, R. A high-capacity TiO₂/C negative electrode for sodium secondary batteries with an ionic liquid electrolyte. *Journal of Materials Chemistry A* **3**, 20767–20771 (2015).
31. Zhang, Y. *et al.* Enhanced sodium storage behavior of carbon coated anatase TiO₂ hollow spheres. *Journal of Materials Chemistry A* **3**, 18944–18952 (2015).
32. Chen, C. *et al.* Na⁺ intercalation pseudocapacitance in graphene-coupled titanium oxide enabling ultra-fast sodium storage and long-term cycling. *Nature Communications* **6** (2015).
33. Wang, D. *et al.* High-performance, nano-structured LiMnPO₄ synthesized via a polyol method. *Journal of Power Sources* **189**, 624–628, doi: 10.1016/j.jpowsour.2008.09.077 (2009).
34. Chen, C. *et al.* Ionic-Liquid-Assisted Synthesis of Self-Assembled TiO₂-B Nanosheets under Microwave Irradiation and Their Enhanced Lithium Storage Properties. *European Journal of Inorganic Chemistry* **2013**, 5320–5328, doi: 10.1002/ejic.201300832 (2013).
35. Chen, C. *et al.* Controllable growth of TiO₂-B nanosheet arrays on carbon nanotubes as a high-rate anode material for lithium-ion batteries. *Carbon* **69**, 302–310, doi: 10.1016/j.carbon.2013.12.029 (2014).
36. Chen, C. *et al.* TiO₂-B nanosheets/anatase nanocrystals co-anchored on nanoporous graphene: *in situ* reduction-hydrolysis synthesis and their superior rate performance as an anode material. *Chemistry* **20**, 1383–1388, doi: 10.1002/chem.201303734 (2014).
37. Cao, F.-F. *et al.* Symbiotic coaxial nanocables: Facile synthesis and an efficient and elegant morphological solution to the lithium storage problem. *Chemistry of Materials* **22**, 1908–1914 (2010).
38. Wang, B. *et al.* Mesoporous CNT@TiO₂-C nanocable with extremely durable high rate capability for lithium-ion battery anodes. *Scientific reports* **4**, 3729 (2014).
39. Zhang, L. W., Fu, H. B. & Zhu, Y. F. Efficient TiO₂ photocatalysts from surface hybridization of TiO₂ particles with graphite-like carbon. *Advanced Functional Materials* **18**, 2180–2189 (2008).

Acknowledgements

This work was supported by the Natural Science Foundation of China (Grant 51622703), 973 Program (2015CB258400) and the National Thousand Talents Program of China. The authors thank Analytical and Testing Center of HUST for XRD, SEM and FETEM measurements.

Author Contributions

K.J. and K.L.W. proposed and designed the work. H.W.T. and M.Z. performed the experiments. H.W.T., M.Z., K.L.W., S.J.C. and K.J. drafted the manuscript.

Additional Information

Supplementary information accompanies this paper at <http://www.nature.com/srep>

Competing Interests: The authors declare no competing financial interests.

How to cite this article: Tao, H. *et al.* Glycol Derived Carbon- TiO₂ as Low Cost and High Performance Anode Material for Sodium-Ion Batteries. *Sci. Rep.* **7**, 43895; doi: 10.1038/srep43895 (2017).

Publisher's note: Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.



This work is licensed under a Creative Commons Attribution 4.0 International License. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in the credit line; if the material is not included under the Creative Commons license, users will need to obtain permission from the license holder to reproduce the material. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>

© The Author(s) 2017